REPORT NO. NADC-77149-30

DESIGN AND TEST OF A LOW COST, SURVIVABLE COMPOSITE FUSELAGE

T.E. Hess, R.J. Richey, Jr., and S.L. Huang
Air Vehicle Technology Department
NAVAL AIR DEVELOPMENT CENTER
Warminster, Pennsylvania 18974

1 AUGUST 1977

Checked no Acc

19960223 054

PLASTEC 2942

DTIC QUALITY INSPECTED 1

NOTICES

REPORT NUMBERING SYSTEM - The numbering of technical project reports issued by the Naval Air Development Center is arranged for specific identification purposes. Each number consists of the Center acronym, the calendar year in which the number was assigned, the sequence number of the report within the specific calendar year, and the official 2-digit correspondence code of the Command Office or the Functional Department responsible for the report. For example: Report No. NADC-76015-40 indicates the fifteenth Center report for the year 1976, and prepared by the Crew Systems Department. The numerical codes are as follows:

CODE	OFFICE OR DEPARTMENT
00	Commander, Naval Air Development Center
01	Technical Director, Naval Air Development Center
02	Program and Financial Management Department
07	V/STOL Program Office
09	Technology Management Office
10	Naval Air Facility, Warminster
20	Aero Electronic Technology Department
30	Air Vehicle Technology Department
40	Crew Systems Department
50	Systems Department
60	Naval Navigation Laboratory
81	Technical Support Department
85	Computer Department

PRODUCT ENDORSEMENT - The discussion or instructions concerning commercial products herein do not constitute an endorsement by the Government nor do they convey or imply the license or right to use such products.

APPROVED BY: _____   DATE: _____

P. M. STURM   1 August 1977
Commander, USN
Deputy Director, AVTD

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER NADC-77149-30	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE *(and Subtitle)* DESIGN AND TEST OF A LOW COST, SURVIVABLE COMPOSITE FUSELAGE		5. TYPE OF REPORT & PERIOD COVERED FINAL REPORT
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) T. E. HESS, R. J. RICHEY, JR., S. L. HUANG		8. CONTRACT OR GRANT NUMBER(s)
9. PERFORMING ORGANIZATION NAME AND ADDRESS AIR VEHICLE TECHNOLOGY DEPARTMENT NAVAL AIR DEVELOPMENT CENTER 35 WARMINSTER, PA. 18974		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS IED TASK NUMBER ZF61412001 WORK UNIT GC-313
11. CONTROLLING OFFICE NAME AND ADDRESS DIRECTOR, NAVAL RESEARCH LABORATORY Department of the Navy WASHINGTON, D.C. 20375		12. REPORT DATE 1 AUGUST 1977
		13. NUMBER OF PAGES 160
14. MONITORING AGENCY NAME & ADDRESS(if different from Controlling Office)		15. SECURITY CLASS. (of this report) UNCLASSIFIED
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT *(of this Report)* APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED		
17. DISTRIBUTION STATEMENT *(of the abstract entered in Block 20, if different from Report)*		
18. SUPPLEMENTARY NOTES *Appendices A,B*		

19. KEY WORDS *(Continue on reverse side if necessary and identify by block number)*

aircraft structures
hybrid composite
primary structure
crack arresters
damage tolerance

Epoxy 3501
Graphite AS
Epoxy SP250
Fiberglass S
Laminate π/4

20. ABSTRACT *(Continue on reverse side if necessary and identify by block number)*

A damage tolerant hybrid composite fuselage section has been designed, fabricated and tested. One of the key features of this structure is the integral crack arresters which have been incorporated into the design to increase its tolerance to damage, either inherent flaws or battle induced damage. The ability of the design to withstand critical flight loads has been demonstrated by both analysis and test. The effectiveness of the crack arresters, which are designed to stop a propagating crack (damage) and still allow the structure to carry limit load, was proven in a series of tests where the

DD FORM 1473 1 JAN 73   EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-LF-014-6601

initial damage was of two types, a preformed crack cut with a saw blade and that resulting from projectiles fired into the shell. The design has been completely analyzed using finite element techniques and shown to save both weight and cost over its metal counterpart. Analysis and testing of composite panels has also been done to investigate failure modes and establish design criteria for crack arrester designs.

DISCLAIMER NOTICE

S U M M A R Y

A damage tolerant hybrid composite fuselage section has been designed, fabricated and tested. One of the key features of this structure is the integral crack arresters which have been incorporated into the design to increase its tolerance to damage, either inherent flaws or battle induced damage. The ability of the design to withstand critical flight loads has been demonstrated by both analysis and test. The effectiveness of the crack arresters, which are designed to stop a propagating crack (damage) and still allow the structure to carry limit load, was proven in a series of tests where the initial damage was of two types, a preformed crack cut with a saw blade and that resulting from projectiles fired into the shell. The design has been completely analyzed using finite element techniques and shown to save both weight and cost over its metal counterpart. Analysis and testing of composite panels has also been done to investigate failure modes and establish design criteria for crack arrester designs.

TABLE OF CONTENTS

T A B L E   O F   C O N T E N T S   (Cont'd)

LIST OF TABLES

LIST OF FIGURES

LIST OF FIGURES (Cont'd)

L I S T   O F   F I G U R E S   (Cont'd)

1.0   I N T R O D U C T I O N

Existing composite technology, based upon conservative metal-replacement philosophy and applied to individual secondary and small primary structures, has demonstrated significant structural advantages and has matured sufficiently to support a broader/total system application. Maximum composite payoff is recognized to be attainable through reconfiguration in the initial conceptual design. In-depth investigations to fully explore the potential cost and performance advantages of composites must exploit the tailorability and improved formability of composites. Cost reduction, weight reduction, and high tolerance to damage require design of the structural material system concurrently with the internal structural arrangement. An RPV provides a low risk/moderate cost opportunity to seek maximum utilization of composites at each level of design and manufacture.

The objectives of this program, therefore, are to develop a composite fuselage design which is low in cost compared to conventional metal design, affords increased survivability with respect to inherent flaws and hostile action and the resulting damage, and at the same time has reduced weight. The center fuselage section of the BQM-34E Remote Piloted Vehicle, Figure 1-1, was selected as the demonstration vehicle for this design/development. Although the technology presented here is directly applicable to manned aircraft, the RPV affords a basis for comparison between an inproduction, operational, metal counterpart and the redesigned composite version, and it provides an opportunity for near-term flight demonstration in both the subsonic and supersonic regimes. This same vehicle has been used as a test bed for an all graphite epoxy wing which was designed and fabricated at the Naval Air Development Center and which is currently flying on operational vehicles as part of the Navy's service evaluation program. This center fuselage section provides a practical design model since it contains access doors, wing attachment points, external fuel tank attachment and the recovery parachute line attachment.

The center fuselage section of the BQM-34E is 1.04m (41 inches) long, from station 233.5 to 274.1 and .63m (25 inches) in diameter. The metal design is aluminum sheet with reinforcing frames, a shear web which distributes parachute loads, a keel which reacts bending and external fuel tank loads, and a strongback which reacts parachute loads, Figure 1-2.

The through-wing is attached to this section in the upper portion of the cross section and an overwing structure covers the wing and closes out the circular shape. A large access door is at the bottom and runs the entire length of the section.

The overall procedure and work flow followed in this program is shown in Figure 1-3. The loads and criteria used were those of the BQM-34E. Studies were made from which material and type of construction were selected. Preliminary design and subcomponent testing were based on material properties determined analytically from micromechanics analysis of the selected material. At the same time fabrication processes were established and material coupons were fabricated and tested to characterize the material. Detailed design of the fuselage and a cylindrical test specimen were based on material properties from this characterization.

8
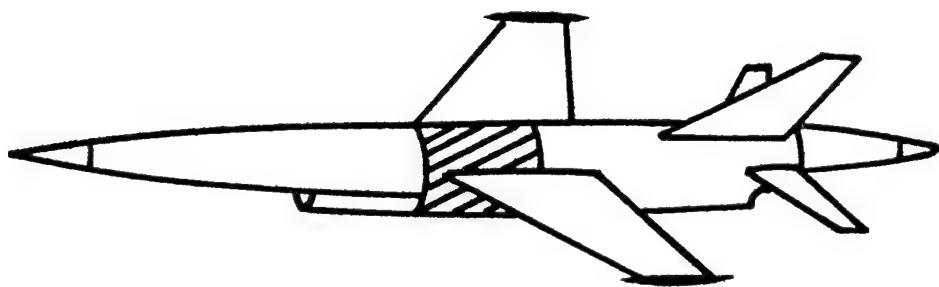
Figure 1-1. BQM-34E Point Design
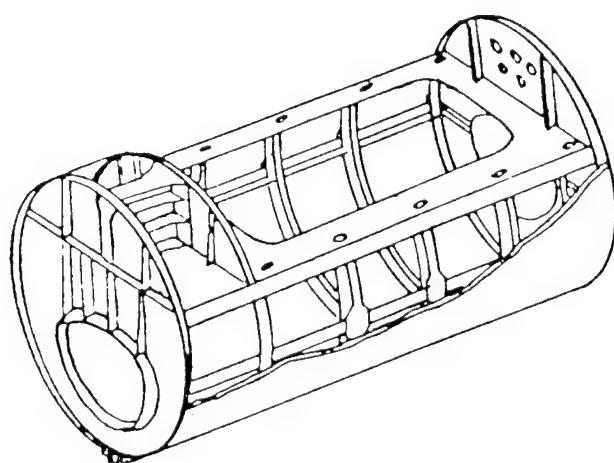
Figure 1-2. Center Fuselage - Metal Design
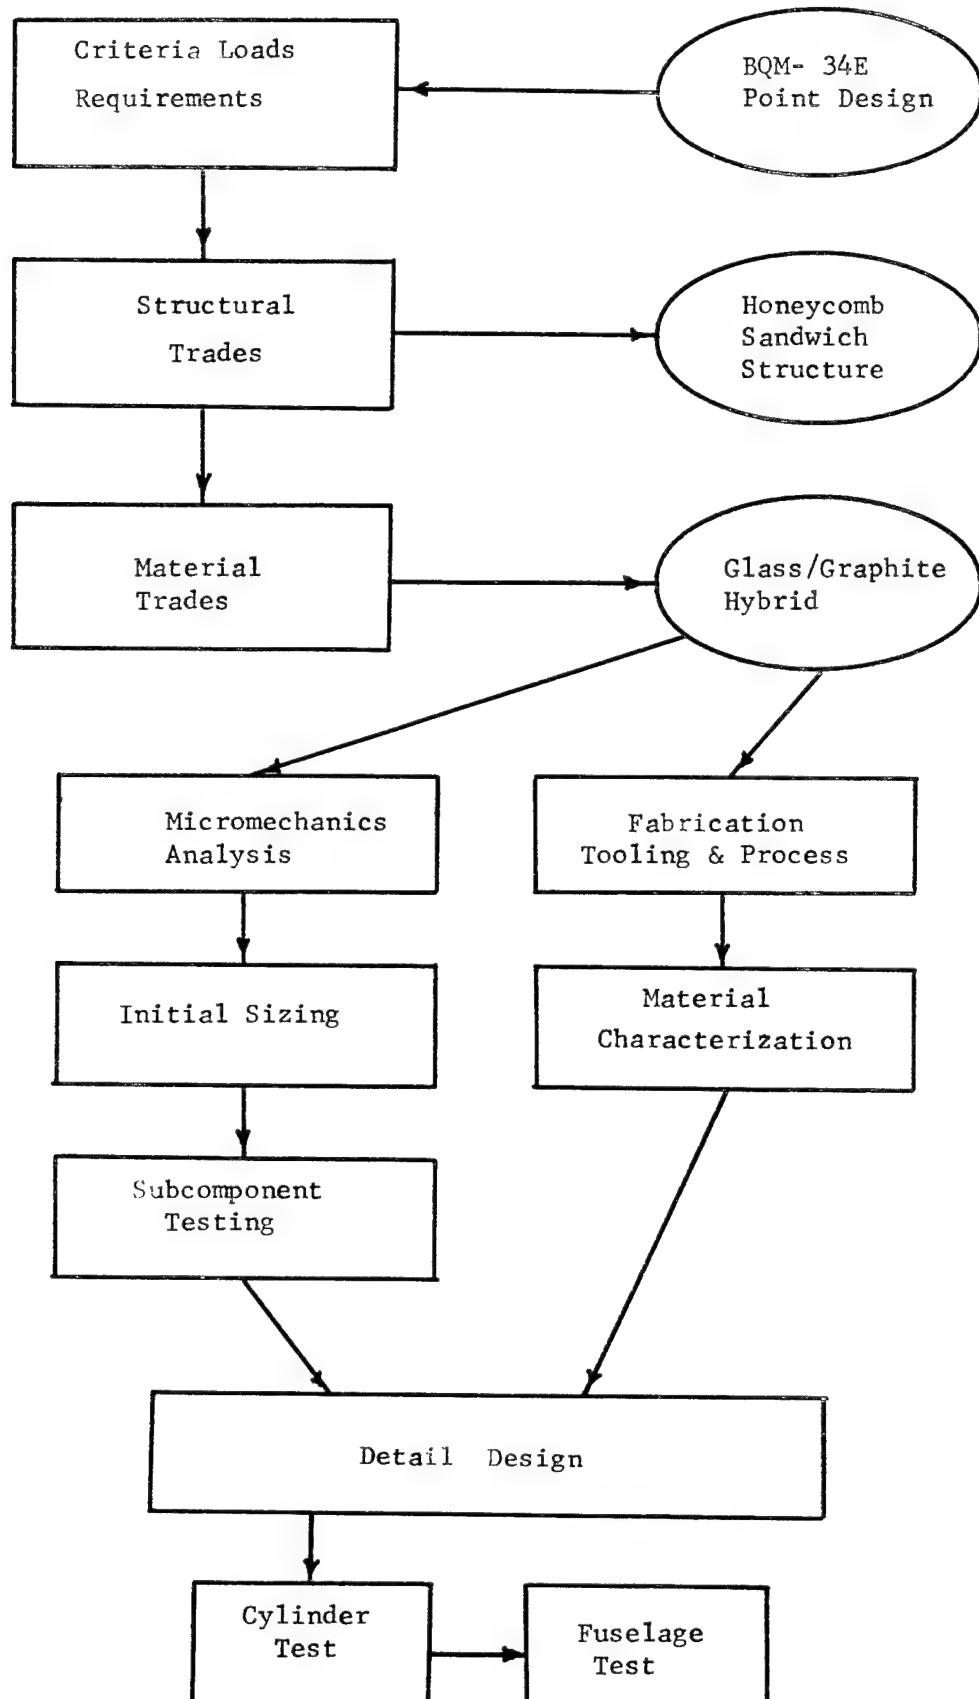
Figure 1-3. Low Cost, Survivable Composite Fuselage

2.0   D E S I G N   C O N D I T I O N S

In designing the composite fuselage section, two design conditions were considered, based on a review of the metal design. These conditions are identified in references (1) and (2) as conditions 4PX02, recovery, and 2SD02, 5g maneuver. The first, and most important, condition is a recovery condition in which 7.4g is developed by a 66720 N (15,000 lb.) load on the parachute line which is attached at the top of the fuselage near the forward end of the center section. The inertia loading of that part of the fuselage forward of the center section produces a large bending moment, which is applied to the center fuselage section. It is this condition that sizes the center fuselage shell, Figure 2-1. The 5g maneuver in free flight produces maximum wing bending combined with concentrated loads on the keel from an external fuel tank, Figure 2-2. This condition induces local load in the fuselage in the circumferential direction, and the shell must be checked for its ability to react these loads.

It should be pointed out that the loading applied at the forward end of the center fuselage section, station 233.5, is not applied around the complete periphery of the fuselage. This is due to the geometric shape of the fuselage structure in the equipment compartment which is forward of this center section. Just forward of station 233.5, this structure extends just slightly over the upper semi-circle of the center fuselage shape, with longerons at the lower extremeties, Figure 2-3. This results in some buildup of load opposite these longerons, but leaves the lower portion of the center fuselage at station 233.5 unloaded. This is important since it is at this point that maximum compressive stresses in the center fuselage occur.

3.0   S T R U C T U R E / M A T E R I A L   S E L E C T I O N

At the outset it had to be recognized that three basic goals were influencing the selection of a material and type of construction for the fuselage. These, in order of importance, were low cost, improved survivability, and decreased weight.

The achievement of low cost depends on many factors such as design costs, raw material costs, manufacturing costs and if a cost comparison is to address total life cycle costs, considerations such as maintenance, replacement, repair and the like must be included. This study considers only the first, **cost of designing and building the fuselage component.**

One of the principle approaches used to reduce costs in designing with composite materials is to reduce total parts count. The existing metal fuselage is a semi-monocoque design, with frames and longerons. The skin is critical in buckling. In order to make a reduction in parts count and at the same time maintain a high resistance to buckling, honeycomb sandwich construction was chosen for this study. Reduction in parts count would be achieved by elimination of the intermediate frames and longerons.
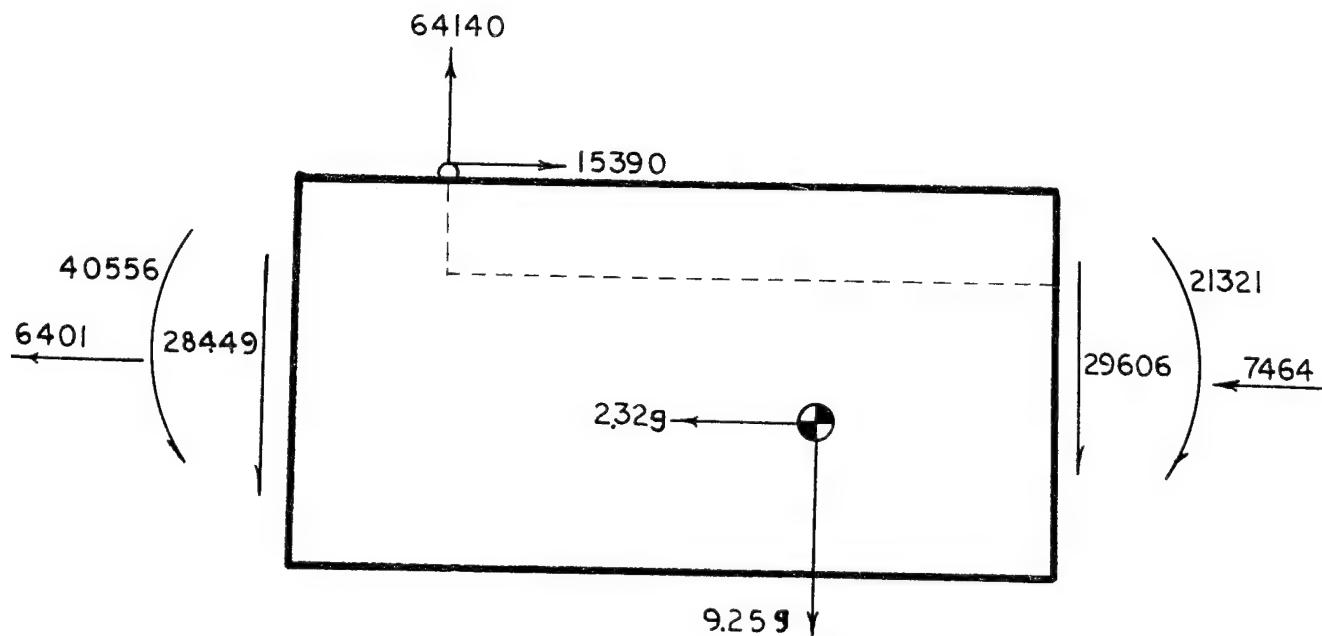
Figure 2-1. Ultimate Recovery Loads on Fuselage Section
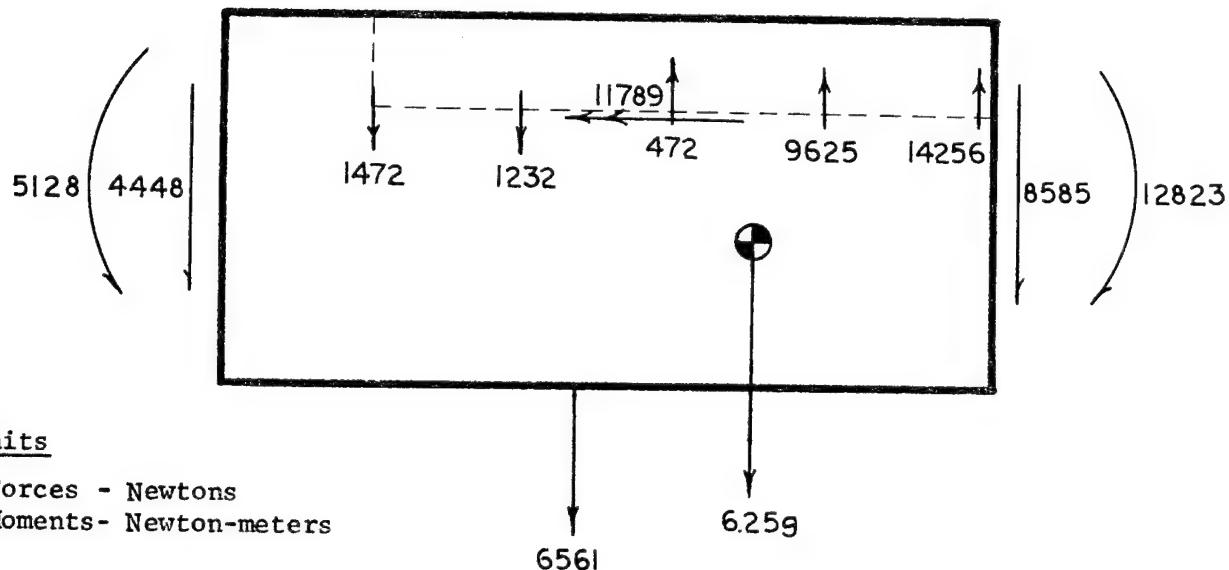
Units

Forces - Newtons
Moments- Newton-meters

Figure 2-2. Ultimate 5g Maneuver Loads on Fuselage Half Section

12
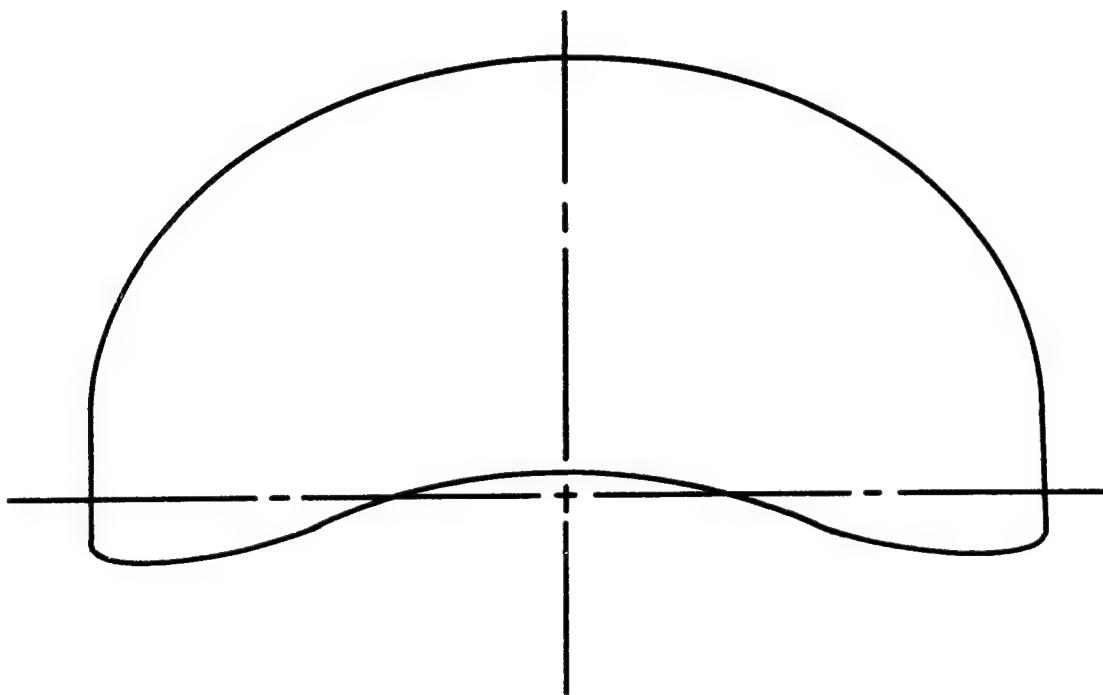
Figure 2-3. Fuselage Cross-Section Forward of Station 233.5

Candidate materials for this design were graphite-epoxy and glass-epoxy. Fuselage designs with each material in a 0°, $\pm45^{\circ}$ configuration were analyzed for the critical conditions and small sandwich specimens of both were tested. As a result of this analysis and testing the use of glass-epoxy faces for the honeycomb sandwich was ruled out for the following reasons. First, the glass design is heavier than the graphite. It also appeared that it would be marginal with respect to weak direction (circumferential) strength. Its lower stiffness makes it less effective in buckling, and also forces more load into metal components which will not be replaced with composite material.

On the other hand, glass-epoxy is a tough and compliant material for fracture, and it is a good material for softening strips used for crack arrestment. In addition, successful experiments had been performed at this time using glass crack arrester strips to stop cracks in graphite-epoxy panels. Therefore, the decision was made to use a hybrid composite for the honeycomb face sheets, combining the strength and stiffness characteristics of the graphite with the toughness of the glass. The basic design is a two ply inner face with 0° graphite, $\pm45^{\circ}$ glass fabric, and a 3-ply outer face also with 0° graphite but with two $\pm45^{\circ}$ plies of glass fabric, the second glass ply being for added protection of the outer face against damage.

4.0   M A T E R I A L   C H A R A C T E R I Z A T I O N

4.1 INTRODUCTION

Material property characterization was performed on two basic hybrid material systems, one with 50% glass, representing the inner face, and one with 2/3 glass, representing the outer face. Both configurations consisted of unidirectional graphite in the 0°, or longitudinal direction, and woven glass fabric oriented in the $\pm45^{\circ}$ direction. Information was desired for tension and compression in the longitudinal and transverse directions, interlaminar shear and in-plane shear.

The test specimens were fabricated using NARMCO 5209 unidirectional graphite prepreg and prepreged Hexcel F161 woven glass fabric. The materials were cured at $125^{\circ}C$ ($255^{\circ}F$) and 350 kPa (50 psi). For the outer face configuration, 12 plies were used, 8 glass and 4 graphite, and for the inner face configuration 8 plies were used, 4 glass and 4 graphite.

4.2 SPECIMEN CONFIGURATION

The four test specimen configurations are shown in Figure 4-1. All are basically flat laminates except for the tensile specimens which have end tabs bonded on for gripping.

4.3 RESULTS

The results of the material characterization tests are given in Tables 4-1 to 4-10. Tension and compression results in both the longitudinal and transverse directions are given, as well as in-plane and interlaminar shear, and Poisson's ratio.
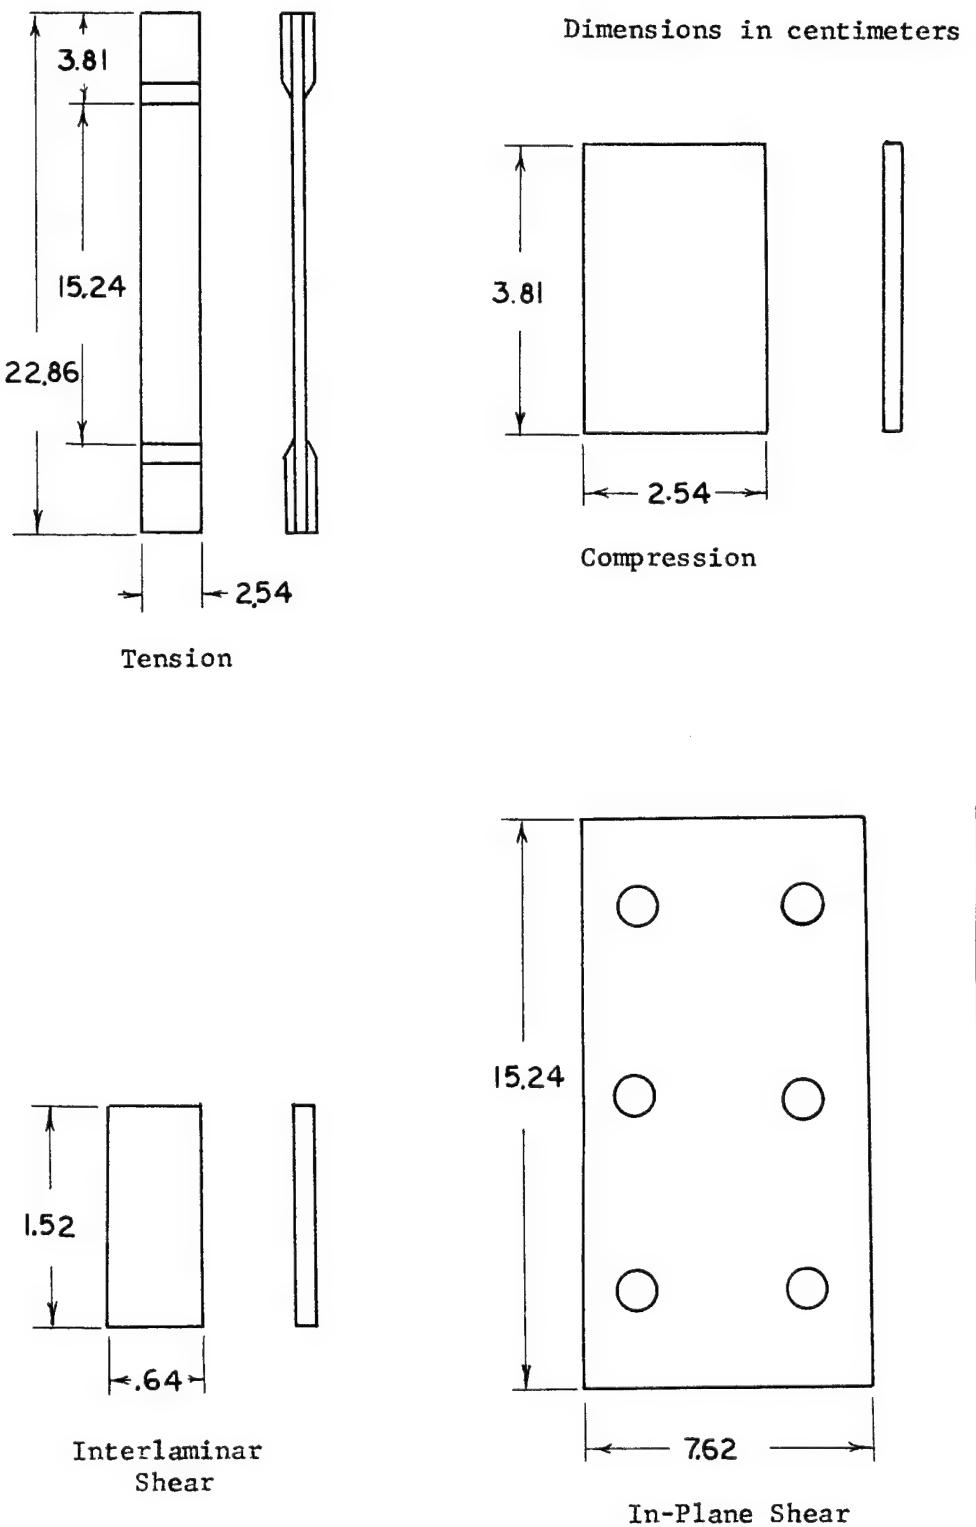
Figure 4-1. Test Specimen Configurations

TABLE 4-1

HYBRID PANEL A (INNER FACE, 50% GLASS)

LONGITUDINAL TENSION TESTS

SPECIMEN	ULTIMATE STRENGTH		MODULUS	
	MPa	KSI	GPa	MSI
1	705	102.3	72.4	10.5
2	659	95.6	69.6	10.1
3	642	93.1	-	-
4	683	99.1	69.6	10.1
5	694	100.7	-	-
6	638	92.6	-	-
Average	670	97.2	70.5	10.2
Standard Deviation	27.9	4.06	1.6	.22
Variance	779.7	16.48	2.6	.05

TABLE 4-2

HYBRID PANEL A (INNER FACE, 50% GLASS)

TRANSVERSE TENSION TESTS

SPECIMEN	ULTIMATE STRENGTH		PRIMARY MODULUS		SECANT MODULUS	
	MPa	KSI	GPa	MSI	GPa	MSI
1	148	21.4	-	-		-
2	149	21.6	14.4	2.09	8.8	1.27
3	145	21.0	14.0	2.03	9.7	1.40
4	141	20.4	12.9	1.87	9.9	1.44
5	154	22.3	-	-	-	-
6	156	22.6	-	-	-	-
Average	149	21.5	13.8	2.00	9.5	1.37
Standard Deviation	5.6	.81	.78	.114	.58	.089
Variance	31.0	.66	.60	.013	.34	.008

TABLE 4-3

HYBRID PANEL A (INNER FACE, 50% GLASS)

COMPRESSION TESTS

SPECIMEN	LONGITUDINAL ULTIMATE STRENGTH		TRANSVERSE ULTIMATE STRENGTH	
	MPa	KSI	MPa	KSI
1	524	76.0	221	32.1
2	-	-	206	29.9
3	530	76.9	207	30.0
4	-	-	234	34.0
5	543	78.7	216	31.4
6	548	79.5	226	32.8
Average	536	77.8	218	31.7
Standard Deviation	11.1	1.62	10.9	1.61
Variance	124.2	2.62	119.4	2.58

TABLE 4-4

HYBRID PANEL A (INNER FACE, 50% GLASS)

SHEAR TESTS

SPECIMEN	INTERLAMINAR STRENGTH		STRENGTH		IN-PLANE PRIMARY MODULUS		SECANT MODULUS	
	MPa	KSI	MPa	KSI	GPa	MSI	GPa	KSI
1	52	7.5	168	24.3	7.7	1.11	6.2	0.90
2	57	8.3	161	23.4	8.5	1.23	7.1	1.03
3	47	6.8	157	22.7	8.2	1.19	5.0	0.73
4	47	6.8	142	20.7	9.2	1.34	5.2	0.75
5	43	6.2	143	20.7	6.6	.96	5.6	0.81
6	52	7.6	157	22.7	8.3	1.20	5.9	0.85
7	54	7.9						
8	55	8.0						
9	55	8.0						
10	52	7.6						
11	57	8.2						
Average	52	7.5	155	22.4	8.1	1.17	8.1	0.84
Standard Deviation	4.5	.67	10.3	1.45	.88	.13	.76	.11
Variance	20.3	.45	105.1	2.09	.77	.02	.58	.01

TABLE 4-5

HYBRID PANEL A (INNER FACE, 50% GLASS)

POISSON'S RATIO

SPECIMEN	V_{12}	V_{21}
1	.615	-
2	.543	-
3	-	.09
4	.616	.09
Average	.591	.09
Standard Deviation	.042	0.0
Variance	.0018	0.0

TABLE 4-6

HYBRID PANEL B (OUTER FACE, 2/3 GLASS)
LONGITUDINAL TENSION TESTS

SPECIMEN	ULTIMATE STRENGTH		MODULUS	
	MPa	KSI	GPa	MSI
1	540	78.3	46.1	6.69
2	424	61.5	-	-
3	452	65.6	48.5	7.03
4	592	85.8	51.3	7.44
5	510	74.0	48.0	6.96
6	442	71.3	47.0	6.81
Average	502	72.8	48.2	6.99
Standard Deviation	60.5	8.75	1.97	.29
Variance	.3658	76.5	3.90	.08

TABLE 4-7

HYBRID PANEL B (OUTER FACE, 2/3 GLASS)

TRANSVERSE TENSION TESTS

SPECIMEN	ULTIMATE STRENGTH		PRIMARY MODULUS		SECANT MODULUS	
	MPa	KSI	GPa	MSI	GPa	MSI
1						
2	182	26.4	-	-	-	-
3	182	26.4	16.1	2.34	9.7	1.41
4	173	25.1	15.4	2.23	9.5	1.38
5	172	25.0	15.0	2.18	9.5	1.38
6	172	25.0	14.6	2.11	9.9	1.43
Average	176	25.6	15.3	2.22	9.7	1.40
Standard Deviation	5.3	.75	.64	.097	.19	.025
Variance	28.2	.56	.41	.009	.04	.0006

TABLE 4-8

HYBRID PANEL B (OUTER FACE, 2/3 GLASS)

COMPRESSION TESTS

SPECIMEN	LONGITUDINAL ULTIMATE STRENGTH		TRANSVERSE ULTIMATE STRENGTH	
	MPa	KSI	MPa	KSI
1	370.2	53.7	248	36.0
2	496	71.9	267	38.7
3	-	-	236	34.3
4	481	69.8	199	28.9
5	494	71.7	243	35.2
6	418	60.6	-	-
Average	472	65.5	239	34.6
Standard Deviation	36.8	8.08	24.9	3.36
Variance	1352	65.30	622.3	12.93

TABLE 4-9

HYBRID PANEL B (OUTER FACE, 2/3 GLASS)

INTERLAMINAR SHEAR TESTS

SPECIMEN	ULTIMATE STRENGTH	
	MPa	KSI
1	59	8.6
2	56	8.1
3	57	8.3
4	57	8.3
5	56	8.1
6	55	8.0
7	56	8.1
8	54	7.9
9	54	7.9
10	57	8.3
11	-	-
12	57	8.2
13	58	8.4
Average	56	8.2
Standrad Deviation	1.5	.22
Variance	2.2	.05

TABLE 4-10

HYBRID PANEL B (OUTER FACE, 2/3 GLASS)

POISSON'S RATIO

SPECIMEN	ν_{12}	ν_{21}
1	.625	-
2	-	-
3	.625	.134
4	-	-
5	-	.134
Average	.625	.134

5.0 FUSELAGE DESIGN AND ANALYSIS

5.1 INTRODUCTION

Previous sections of this report have described the point design vehicle, its critical flight conditions and the design concept and materials being used. Complete specification of the design details, and substantiation of the design was accomplished by the stress and stability analysis of the section, the testing of small subcomponents representing the edge closeout design, the fabrication and testing of a full-scale cylindrical shell of the same basic design as the fuselage section, and finally the fabrication and testing of the actual fuselage center section installed on the BQM-34E RPV and subjected to the critical flight conditions. These subjects will be covered in this and the remaining sections of this report, starting with the stress and stability analysis in this section.

5.2 DESIGN DESCRIPTION

The basic design for the composite fuselage is a honeycomb sandwich structure, Figure 5-1, consisting of a 6.4mm (1/4 in.) thick aluminum honeycomb core and two hybrid composite faces. The inner face is made up of one ply of glass fabric next to the core, with the fibers oriented at ±45° to the longitudinal direction, and one ply of unidirectional graphite oriented at 0°. The outer face is similar with a second layer of ±45° glass fabric on the outer surface for additional impact and damage resistance. All areas near bulkheads, doors and other attachments have additional plies for reinforcement and introduction of load into the sandwich. The general approach to this reinforcement was to make each face in the reinforced areas four plies thick, two plies of unidirectional graphite and two plies of glass fabric. The closeout area contained additional plies for load introduction and for riveting, with a total of 16 plies, 8 unidirectional graphite and 8 glass fabric, at the areas where the two faces come together, Figure 5-2.

Both faces contain integral crack arrester strips which run in the 0°, or fore/aft, direction of the fuselage. They are formed by replacing the 0° graphite epoxy with 0° glass epoxy, so that the arrester strip is all glass epoxy while the primary material is a hybrid of both graphite and glass epoxy. The entire layup is shown in Figure 5-3. Table 5-1 lists the materials used.

This composite design for the center fuselage is a replacement primarily for the metal skins of the existing production design. However, due to the stiffness of the sandwich construction, the intermediate frames and the two longerons on either side of the fuselage can also be eliminated. In order to make sure that no concentrated loading is applied to the section in the circumferential direction from the wing attachment bolts, the middle six bolts and attachment fittings are eliminated and the composite design is based on a four bolt wing attachment, rather than a ten bolt as exists on the metal design. Figure 5-4 shows a comparison of the metal and composite designs.
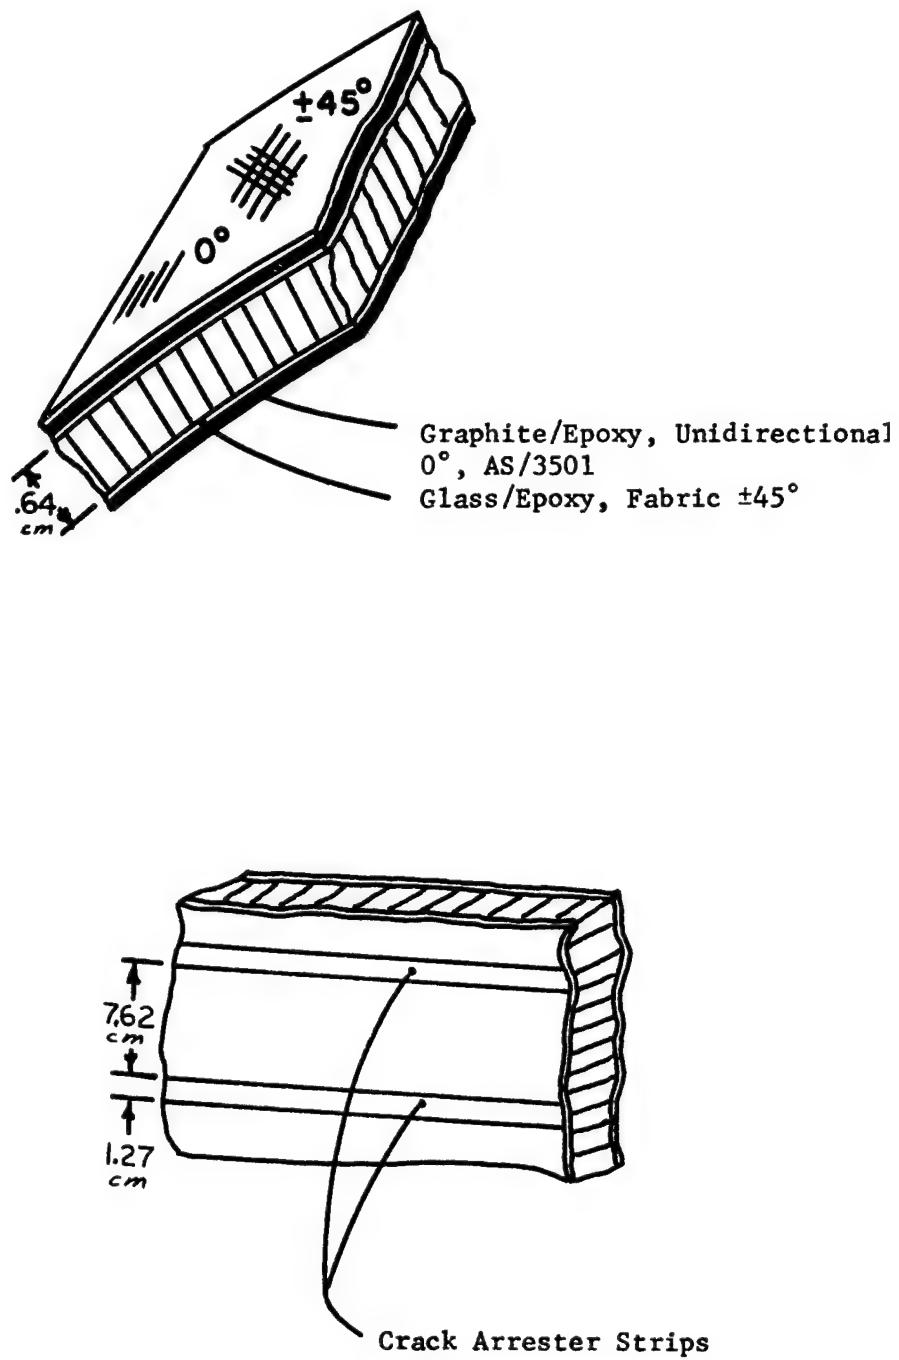
Figure 5-1. Fuselage Honeycomb Sandwich Design

Innerskin, plys 11 thru 16

Closeout reinforcement plys 8, 9 & 10

Outerskin, plys 1 thru 7

20°

low density
epoxy core fill

Aluminum
Honeycomb core
(.64 cm)
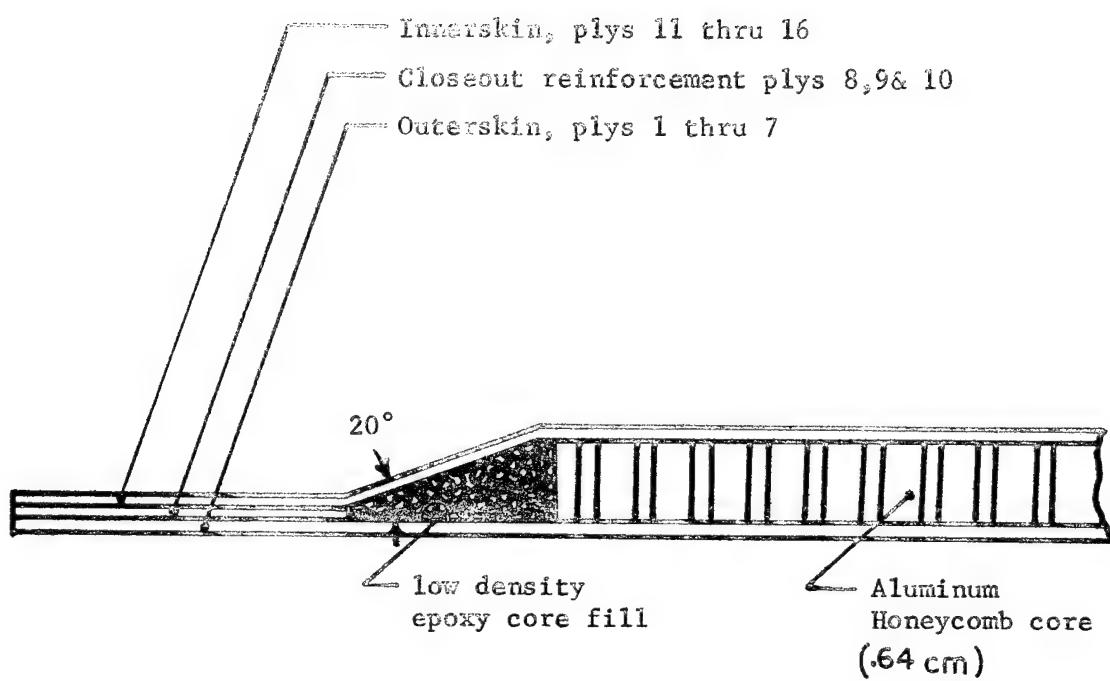
Figure 5-2. Closeout Section Design
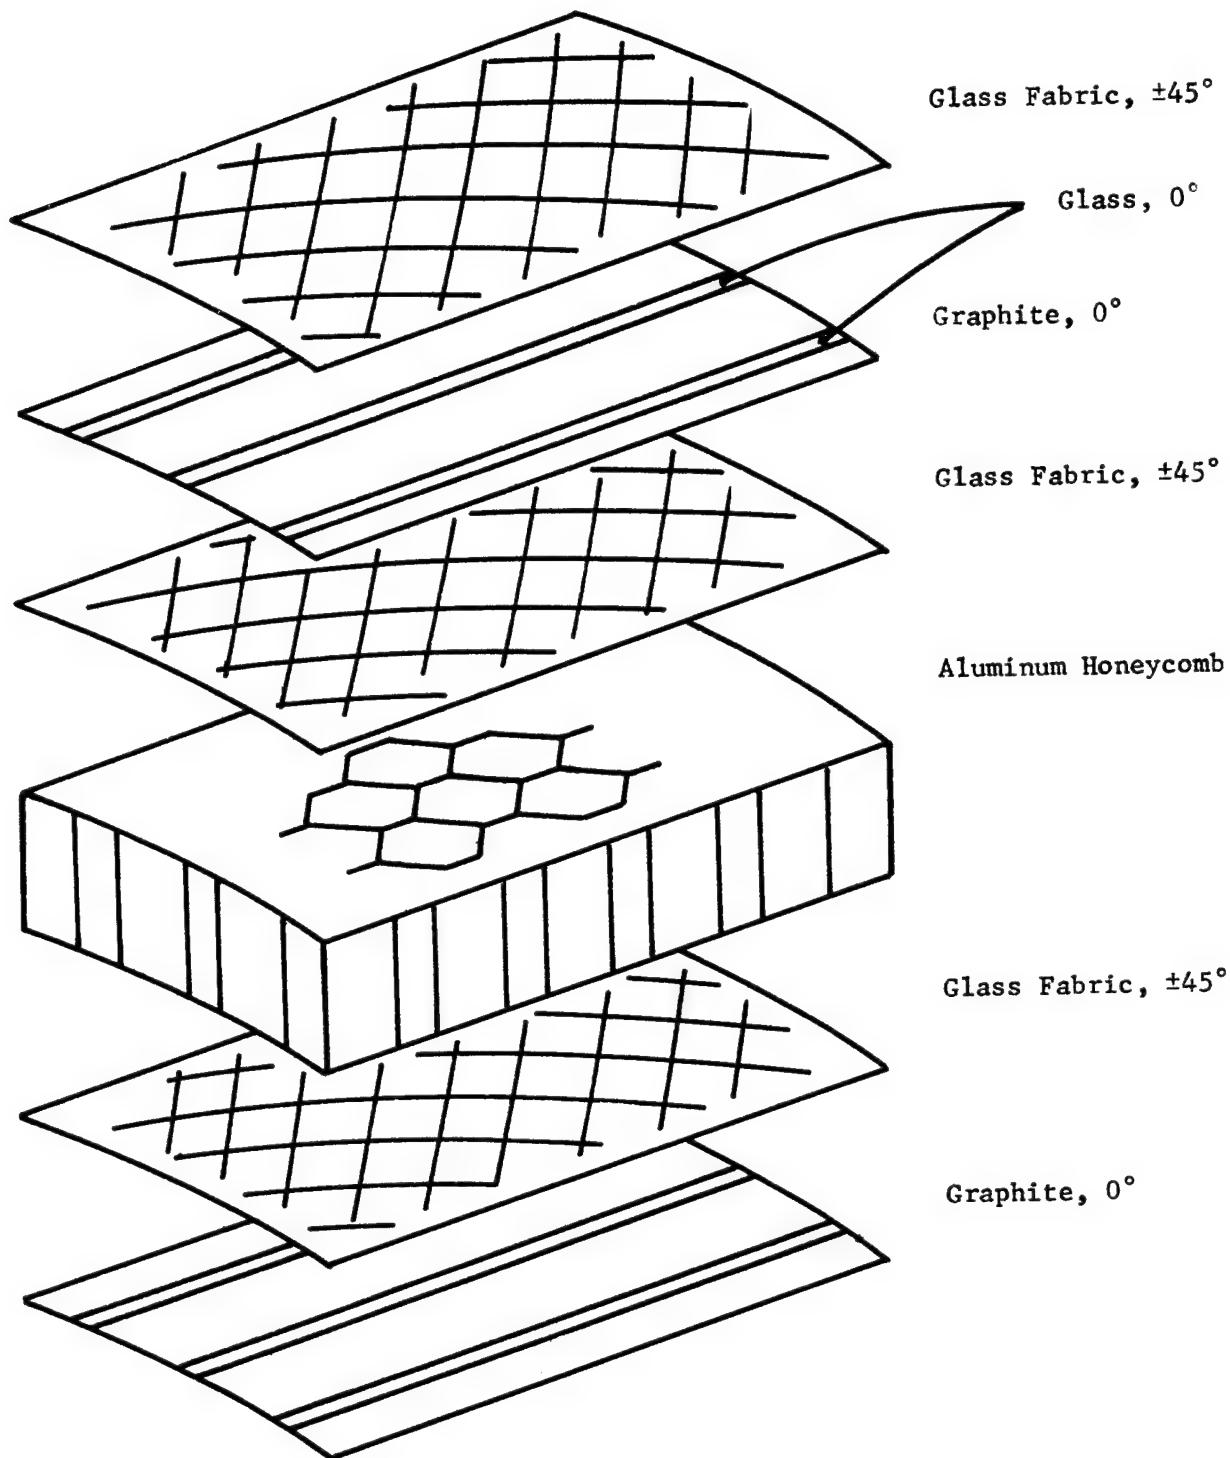
Figure 5-3. Hybrid Sandwich Layup

TABLE 5-1

HYBRID COMPOSITE SANDWICH MATERIALS

FACES

Hercules AS/3501 Unidirectional Graphite Epoxy

CORE

Hexcel   1/8 - 5056 - .0007 - 3.1 Aluminum

ADHESIVE

Fuselage - Narmco Metlbond 329-7

CORE FILLER

Furane   Epocast 1310

ARRESTER STRIPS

3M Scotchply Glass SP-250-SF1
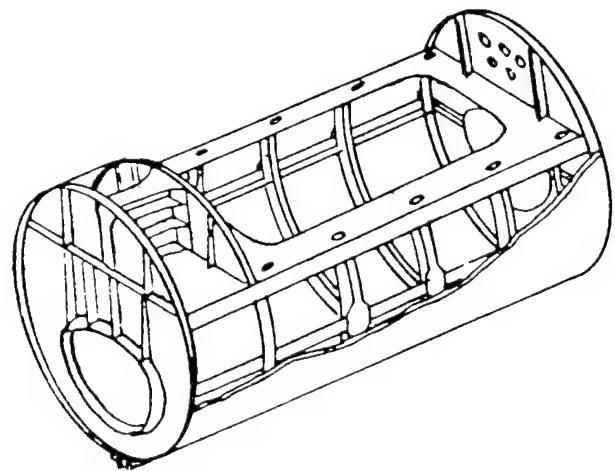
EXISTING METAL DESIGN
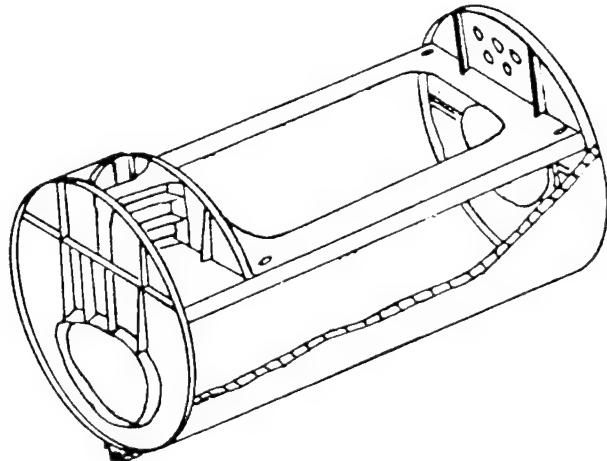
COMPOSITE DESIGN

Figure 5-4. Comparison of Metal and Composite Center Fuselage Designs

31

Complete details of the fuselage design are shown in Figures 5-5 to 5-8 which are the fabrication drawings for the left and right side panels, the left side access door and the bottom fuel tank access door. These four parts comprise the center section composite design. Aside from the parts which have been eliminated, as previously discussed, the rest of the center section remains metal. Figure 5-8a shows composite panel attachment to metal substructure.

5.3 MATERIAL PROPERTIES

Two sets of composite material properties were required for designing this structure; one set, called outer face properties, used for the 3 ply outer face of the sandwich, and the other set, called inner face properties, used for the 2 ply inner face, the 4 ply inner and outer faces in those areas where additional material was added for reinforcement and the 16 ply solid laminate sections. The properties are given in Table 5-2. The basis of these properties is as follows. Allowable strengths were determined by reducing the average valves from the characterization tests by 30%. This allows for scatter in the data and provides a measure of conservatism. The modulus data from the tests were analytically modified to account for the fact that the material characterization specimens were made from .190 mm (.0075 in.) graphite fibers while the actual fuselage was to be made from .152 mm (.006 in.) fiber. This caused the longitudinal modulus to be reduced about 10% from the test values and the transverse and shear modulii to increase slightly.

5.4 NASTRAN MODEL

Figure 5-9 shows the modeling of the skin portion of this center section. In addition, the bulkheads at stations 233.5 and 274.1, the shear fitting between stations 233.5 and 241.8, the partial bulkhead at station 241.8, the strongback, the overwing fairing formers, and the roof structure were also modelled. These are shown in Figures 5-10 to 5-15. In all this modeling) advantage is taken of the left/right symmetry of the fuselage.

For the plate elements which make up the composite fuselage skin elements, general triangular plate elements (CTRIA1) were used for the sandwich elements, and CTRIR2 for the solid laminates. The first is useful for sandwich construction since it allows the specification of separate properties for membrane, bending and shear behavior. As previously mentioned, two sandwich configurations were used, the basic sandwich consisting of a 3 ply outer face and 2 ply inner face, and a reinforced section where both faces are 4 plies. Table 5-3 shows the properties for each configuration.

All the existing metal parts were modelled by taking dimensions from manufacturer's drawings for the BQM-34E vehicle. A complete set of the NASTRAN bulk data for the model is given in Appendix 1.

Only the center portion of the wing, from the bolt line to the centerline, was included in this model since only that part affected the fuselage structural behavior. That model is shown in Figure 5-16. The production BQM-34E utilizes 10 bolts, 5 per side, to attach the wing to the fuselage. In this

DWG. NO. 667A107 "RIGHT SKIN PANEL" WILL BE FOUND IN THE
BACK OF THIS REPORT

DWG. NO. 667A107 "LEFT SKIN PANEL" WILL BE FOUND IN THE
BACK OF THIS REPORT

DWG. NO. 667A107 "FUEL TANK ACCESS DOOR" WILL BE FOUND
IN THE BACK OF THIS REPORT

DWG. NO. 667A107 "ACCESS DOOR – BQM 34E CENTER FUSELAGE SECTION –
HYBRID COMPOSITE DESIGN" WILL BE FOUND IN THE BACK OF THIS REPORT

DWG. NO. 667A109 "ATTACHMENTS" WILL BE FOUND IN THE BACK
OF THIS REPORT

TABLE 5-2

MATERIAL PROPERTIES USED FOR DESIGN

	Inner Face		Outer Face	
	SI	English	SI	English
E_L	63.4 GPa	9.2×10^6 psi	43.4 GPa	6.3×10^6 psi
E_T	15.2 GPa	2.2×10^6 psi	15.2 GPa	2.2×10^6 psi
G	9.0 GPa	1.3×10^6 psi	8.3 GPa	1.2×10^6 psi
ν_{12}	.59	.59	.62	.62
ν_{21}	.09	.09	.13	.13
$F_L{}^t$	469 MPa	68.0 KSI	352 MPa	51.0 KSI
$F_T{}^t$	104 MPa	15.1 KSI	123 MPa	17.0 KSI
$F_L{}^c$	376 MPa	54.5 KSI	316 MPa	45.8 KSI
$F_T{}^c$	153 MPa	22.2 KSI	167 MPa	24.2 KSI
F_S	108 MPa	15.7 KSI	108 MPa	15.7 KSI
$F_S{}^{11}$	36 MPa	5.2 KSI	39 MPa	5.7 KSI
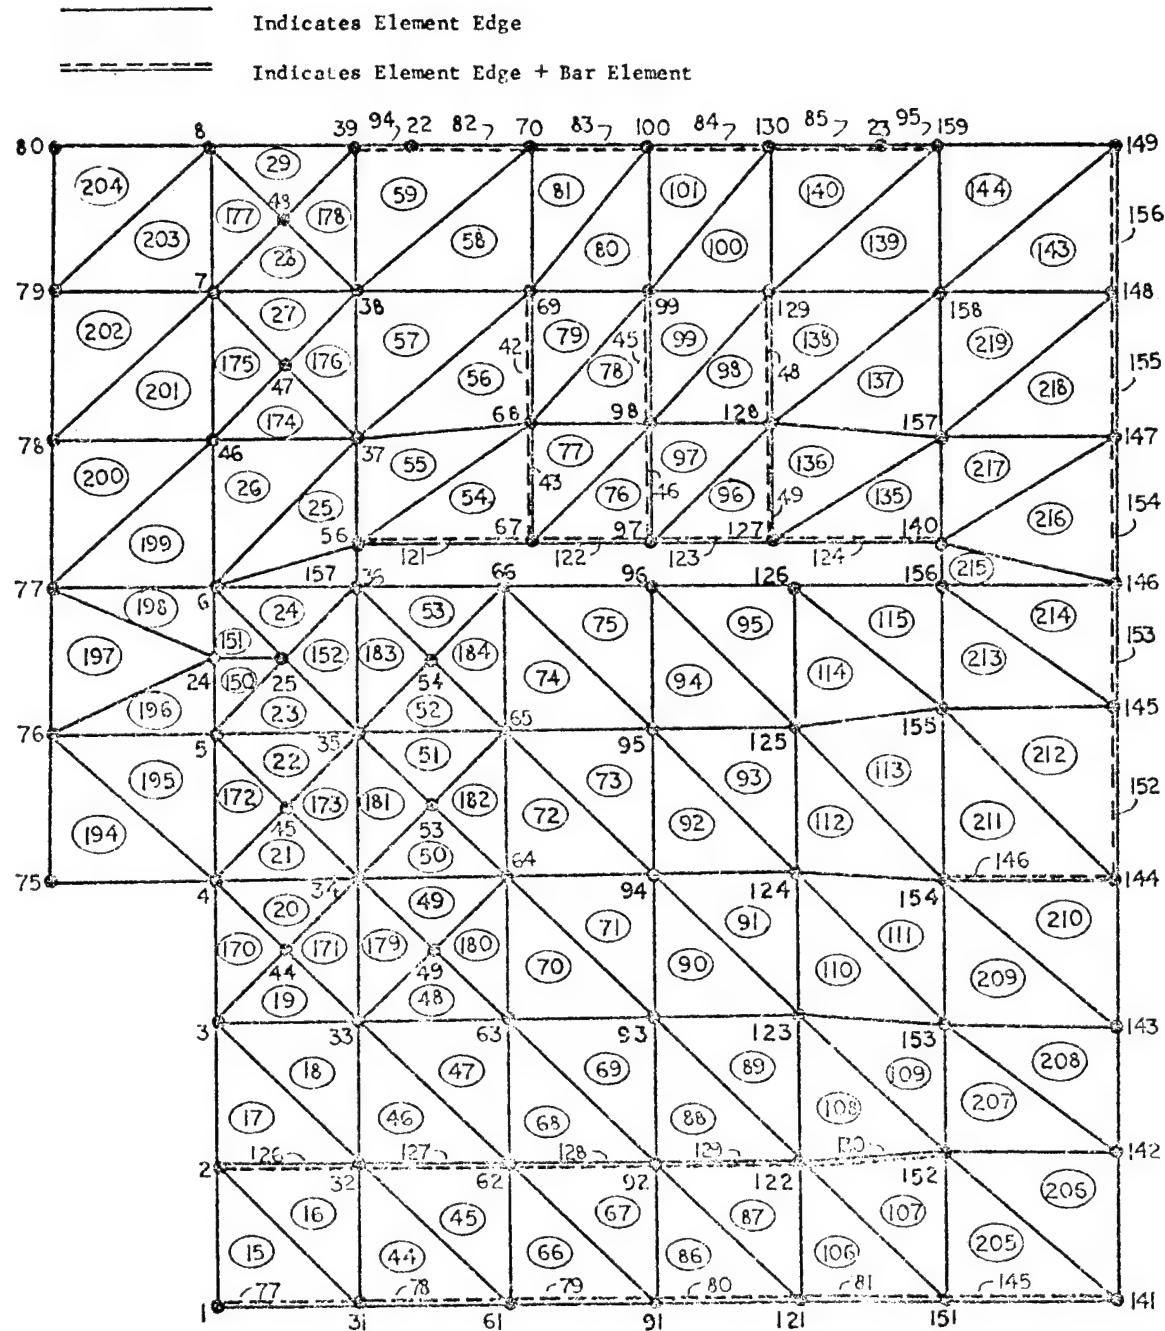
Figure 5-9. Fuselage Center Section Skin Model

Indicates Element Edge
Indicates Element Edge + Bar Element
Indicates Bar Element
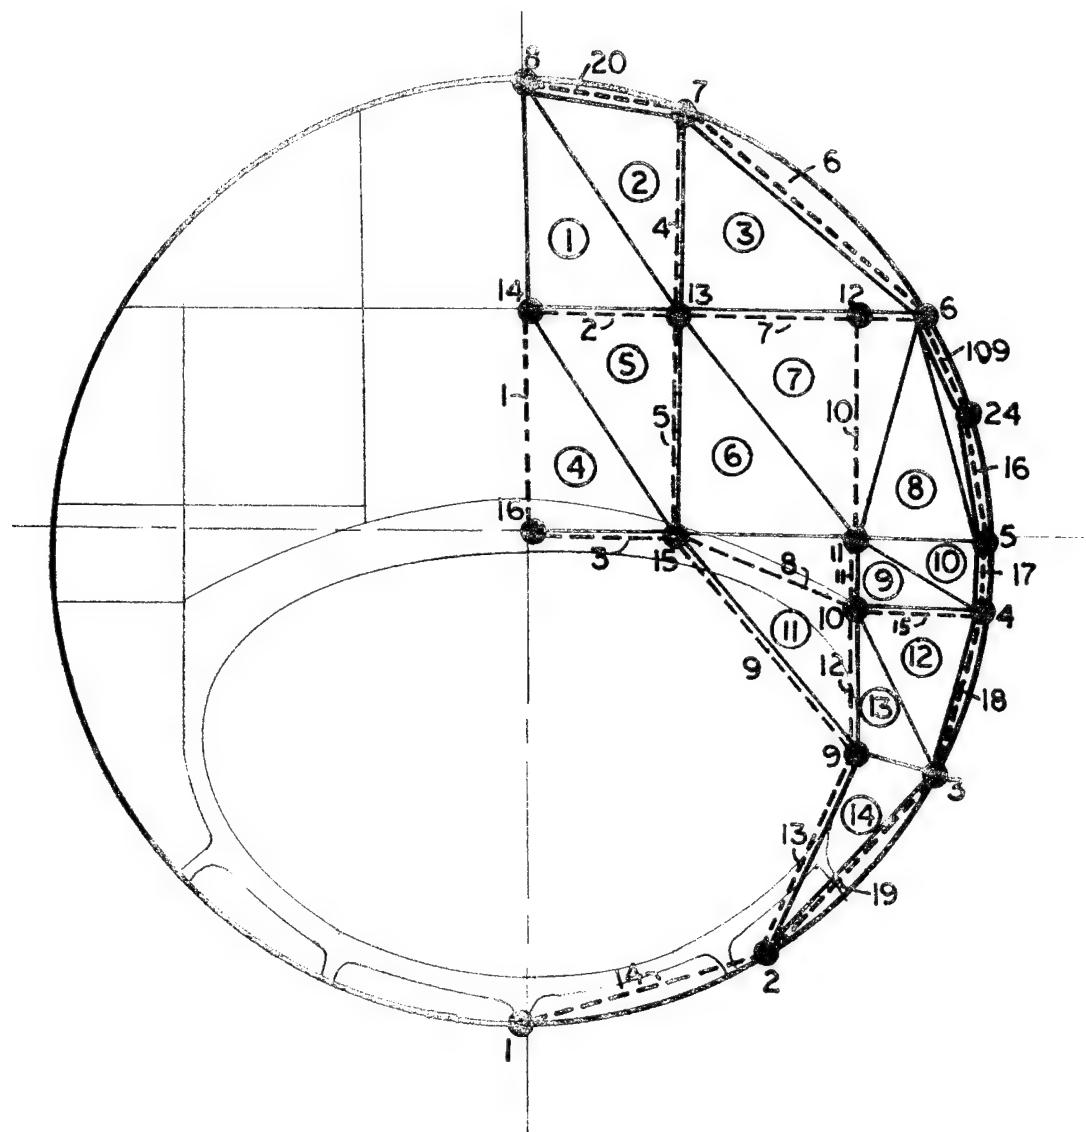
Figure 5-10. Bulkhead 233.5 Model
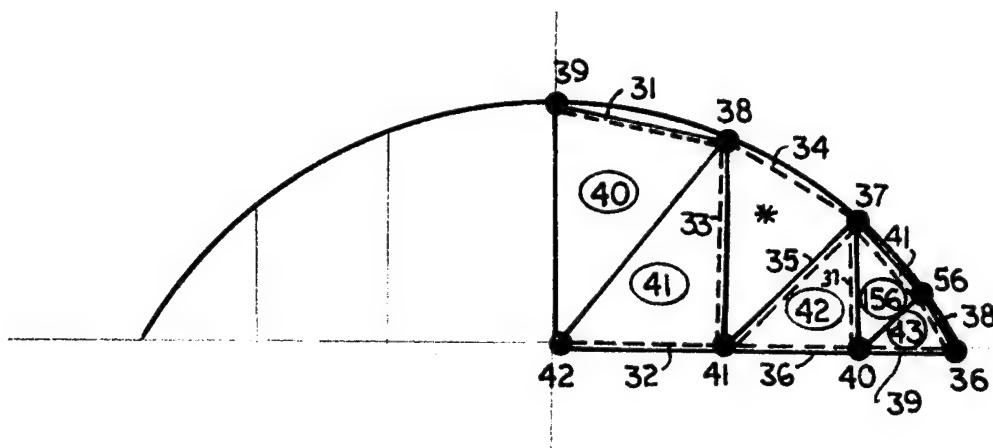
Figure 5-11. Bulkhead 241.8 Model

Indicates Element Edge

Indicates Element Edge + Bar Element

Indicates Bar Element
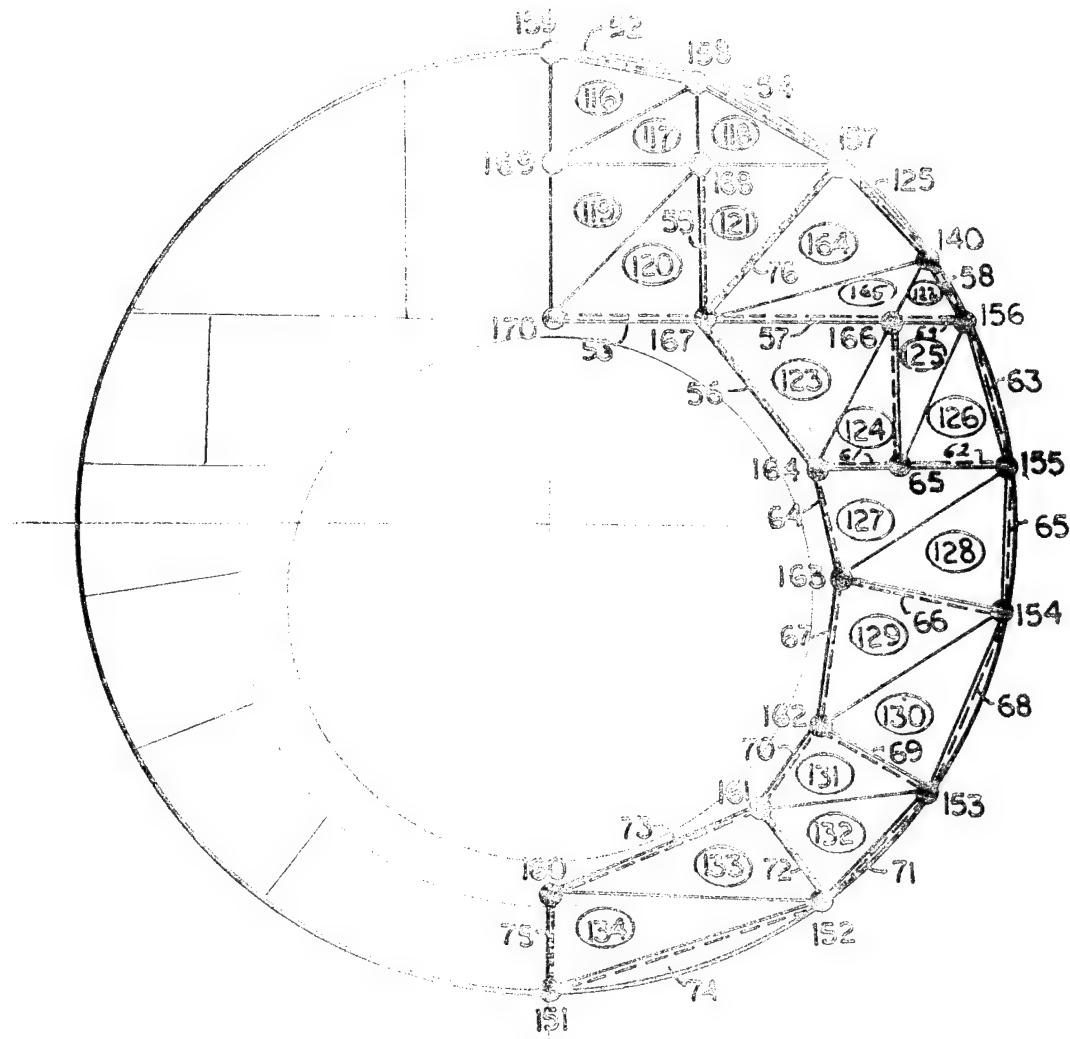
Figure 5-12. Bulkhead 274.1 Model
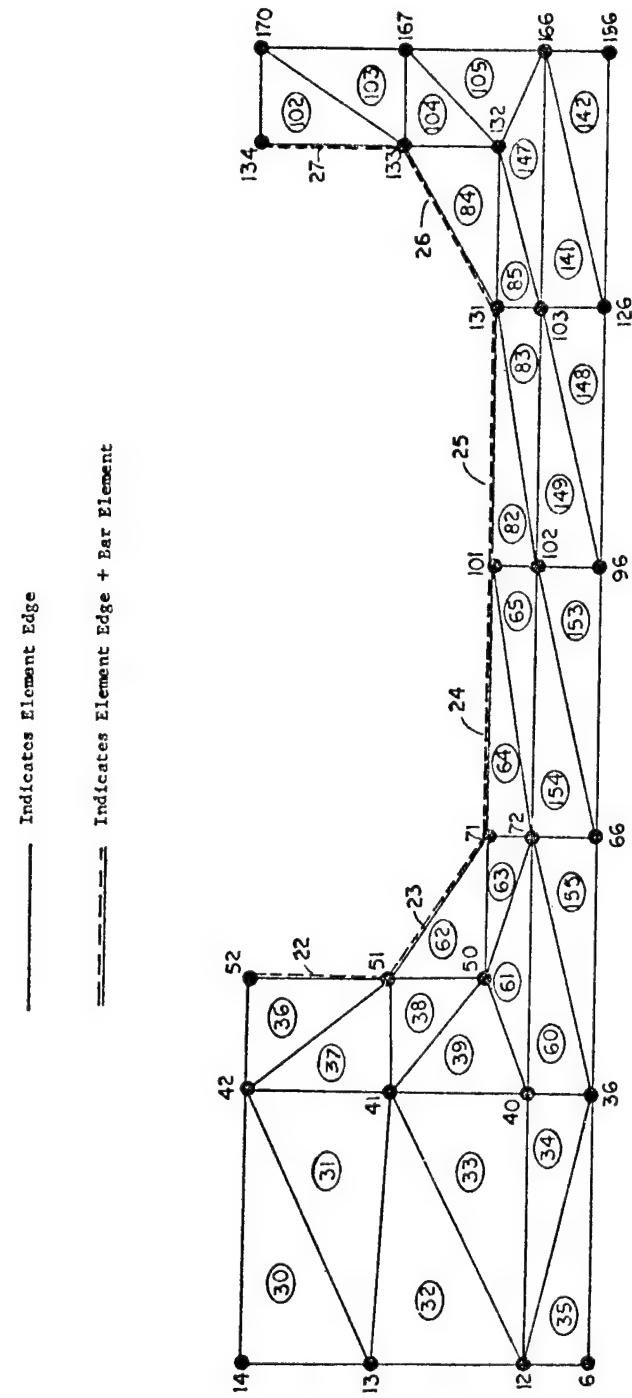
Figure 5-13. Roof Structure Model
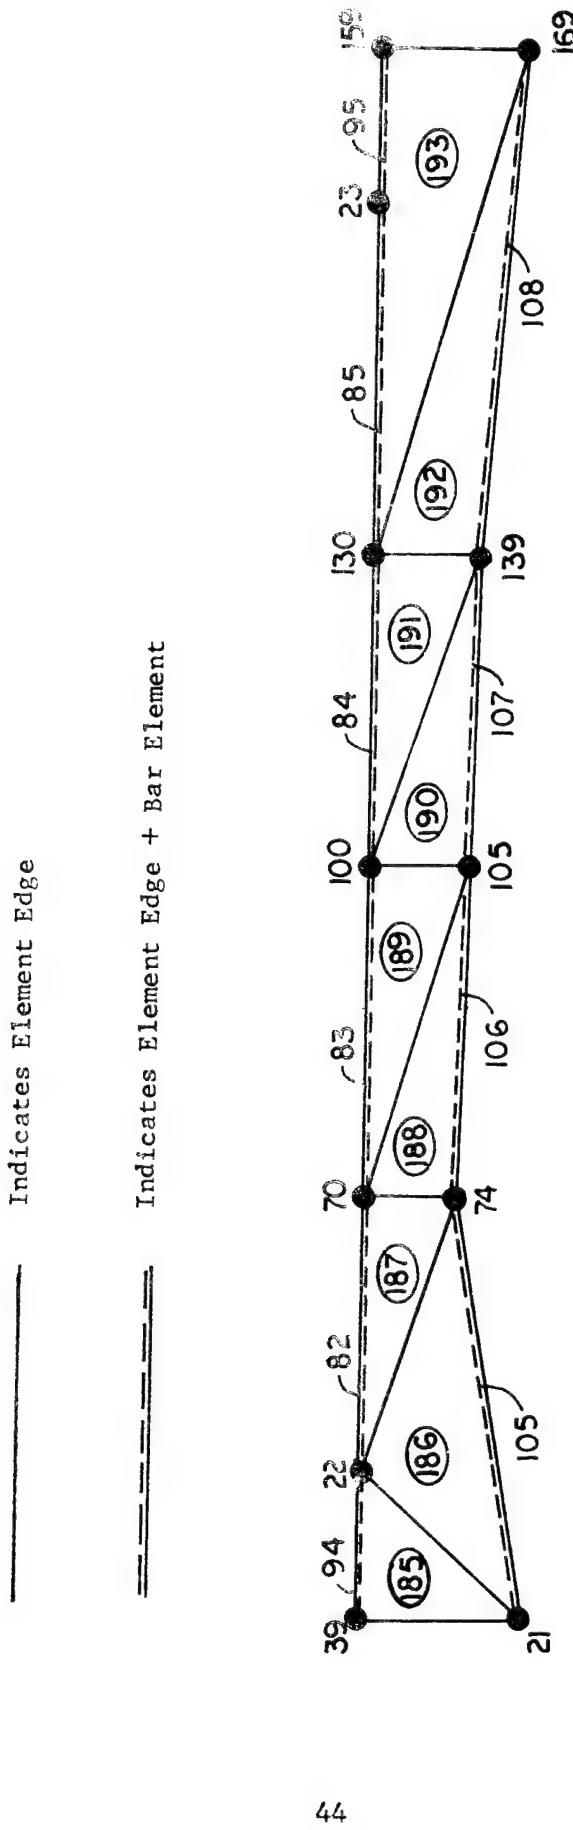
Figure 5-14. Strongback Model

Indicates Element Edge

Indicates Element Edge + Bar Element
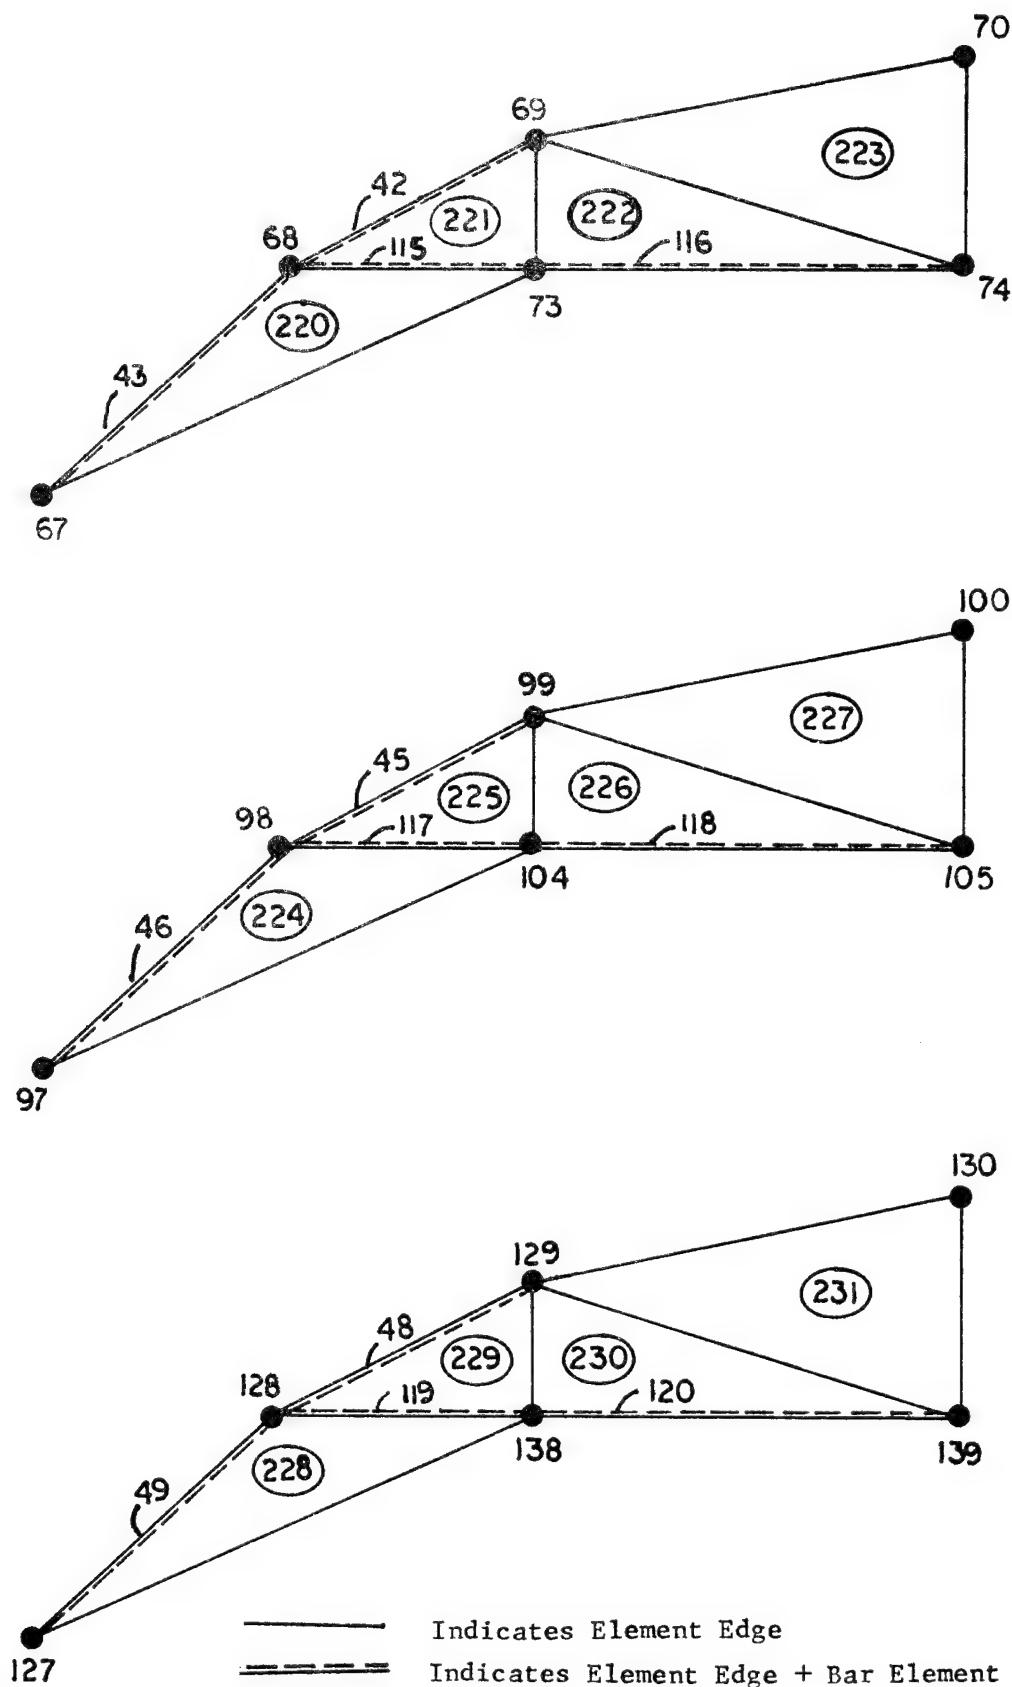
Figure 5-15. Overwing Fairing Formers Model

TABLE 5-3

HYBRID COMPOSITE PLATE ELEMENT PROPERTIES

PROPERTY	BASIC SECTION	REINFORCED SECTION	SOLID LAMINATE
	MEMBRANE PROPERTIES		
Thickness	1.10 (.042)	1.63 (.064)	3.25 (.125)
G_{11}	51.0 (7.4)	63.4 (9.2)	68.2 (9.9)
G_{12}	6.2 (.90)	5.7 (.83)	6.1 (.89)
G_{22}	14.5 (2.1)	15.2 (2.2)	15.8 (2.3)
G_{33}	7.6 (1.1)	7.6 (1.1)	7.6 (1.1)
	BENDING PROPERTIES		
Moment of Inertia	303.8 (.00073)	520.3 (.00125)	
G_{11}	59.3 (8.6)	68.2 (9.9)	
G_{12}	6.2 (.90)	6.1 (.89)	Only one set
G_{22}	15.2 (2.2)	15.8 (2.3)	of properties
G_{33}	7.6 (1.1)	7.6 (1.1)	required for
z_1	2.64 (.104)	3.58 (.141)	homogeneous
z_2	-4.24 (-.167)	-3.58 (-.141)	plate elements
	TRANSVERSE SHEAR PROPERTIES		
Thickness	6.35 (.25)	6.35 (.25)	
E	.67 (.097)	.67 (.097)	
G	.22 (.0325)	.22 (.0325)	

Dimensions are given in mm. and (in.).
Moduli are given in GPa and (10^6 psi).
Moment of inertia is given in mm^4 and ($in.^4$).

TABLE 5-3 (Cont'd)

G_{ij} is defined by:

$$\left\{ \begin{array}{c} \sigma_1 \\ \sigma_2 \\ \sigma_{12} \end{array} \right\} = \begin{bmatrix} G_{11} & G_{12} & G_{13} \\ G_{12} & G_{22} & G_{23} \\ G_{13} & G_{23} & G_{33} \end{bmatrix} \left\{ \begin{array}{c} E_1 \\ E_2 \\ E_3 \end{array} \right\}$$

$$G_{13} = G_{23} = 0$$
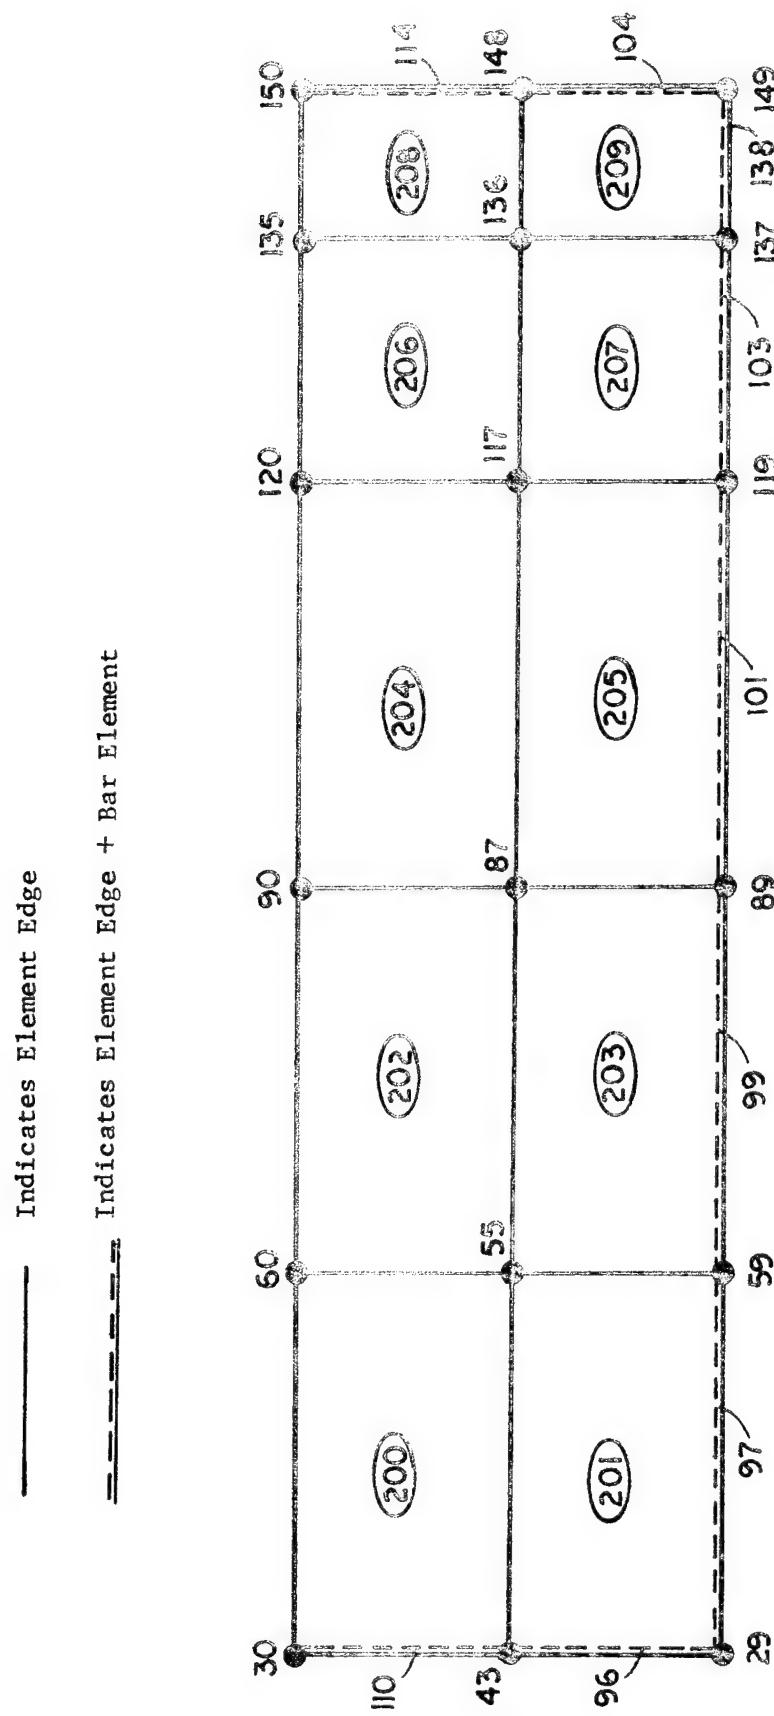
Figure 5-16. Wing Model

design of the composite fuselage the middle three on each side were removed and the design was based on a 4 point wing attachment. These bolts were modelled as scalar elements.

NASTRAN runs were made for the two critical loading conditions previously discussed. The main concern in these runs was the stresses developed in the composite material structure. The stresses in the metal parts were examined and no area of concern was found. Figures 5-17 to 5-19 give the stresses in the composite structure for the recovery condition. Table 5-4 gives a summary of the maximum stresses. In both cases the maximum stresses are compression in the forward part of the fuselage section at the point of discontinuity of the forward fuselage.

5.5 BUCKLING DESIGN

5.5.1 Methodology

The buckling analysis of this design was complicated by the fact that it is a sandwich structure, the faces are of unequal thickness, they are both orthotropic, the elastic properties of the two faces are different, and the sandwich section is not constant, that is, some areas have the additional plies in the faces for reinforcement. No one analytical method was found which pertained directly to this case, and so several techniques were investigated. These techniques are those given in references 4 to 9.

A comparison of all these methods was made for both a complete cylindrical shell and for cylindrical panels. The method of reference 4 was applied in two different ways, one with a sandwich whose faces were the thicker outer face and one where the sandwich faces were the inner face thickness and properties. The former method and the methods of references 5 and 6 all gave close to the same results, while the latter and the methods of references 7 to 9 all gave close to the same results. The first set of results, however, was approximately 70% higher, and so, in order to minimize risk, it was decided not to use these methods. The second set of methods were examined in more detail and the following were selected for analyzing the buckling of the fuselage panels, and the cylindrical shell test component which will be discussed in a later section of this report.

Cylinder:

Axial Buckling Load, N_x -

$$N_x = N_o \left(\frac{N_x}{N_o} \right) \phi \qquad (1)$$

where

$$\frac{N_x}{N_o} = f\left(\frac{N_x}{N_q} \right) \qquad \text{from Figure 10 of reference 8.}$$
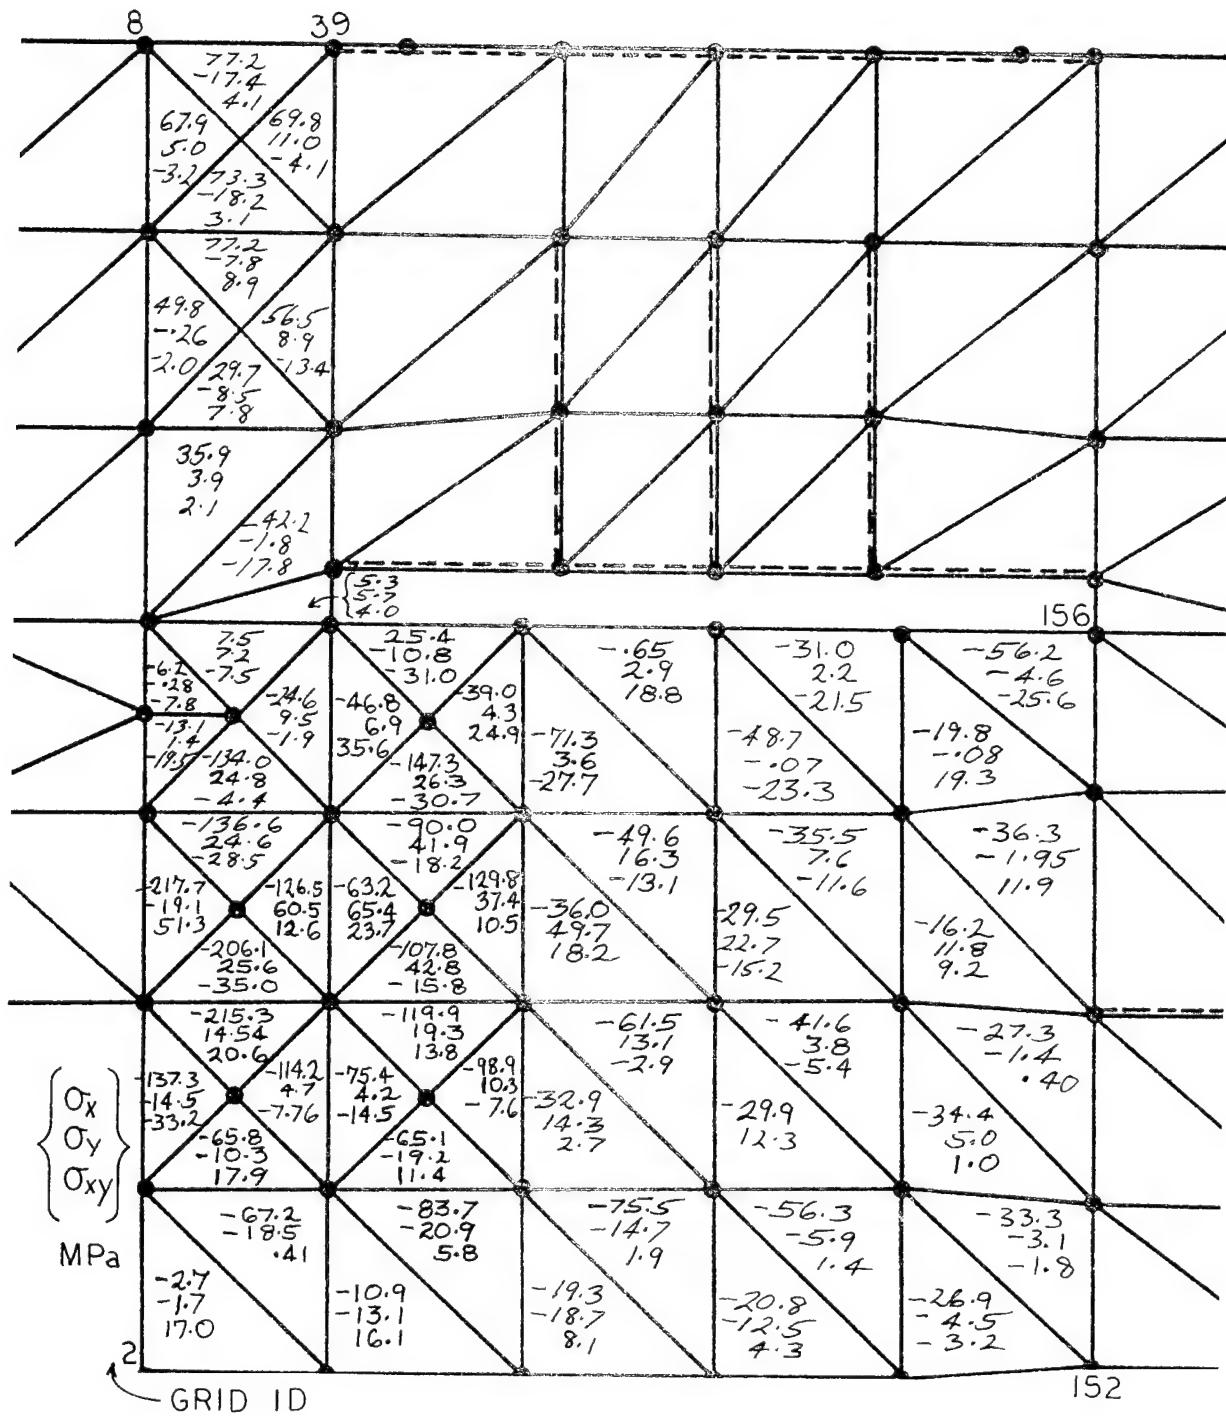
Figure 5-17. Outer Face Stresses - Recovery Condition
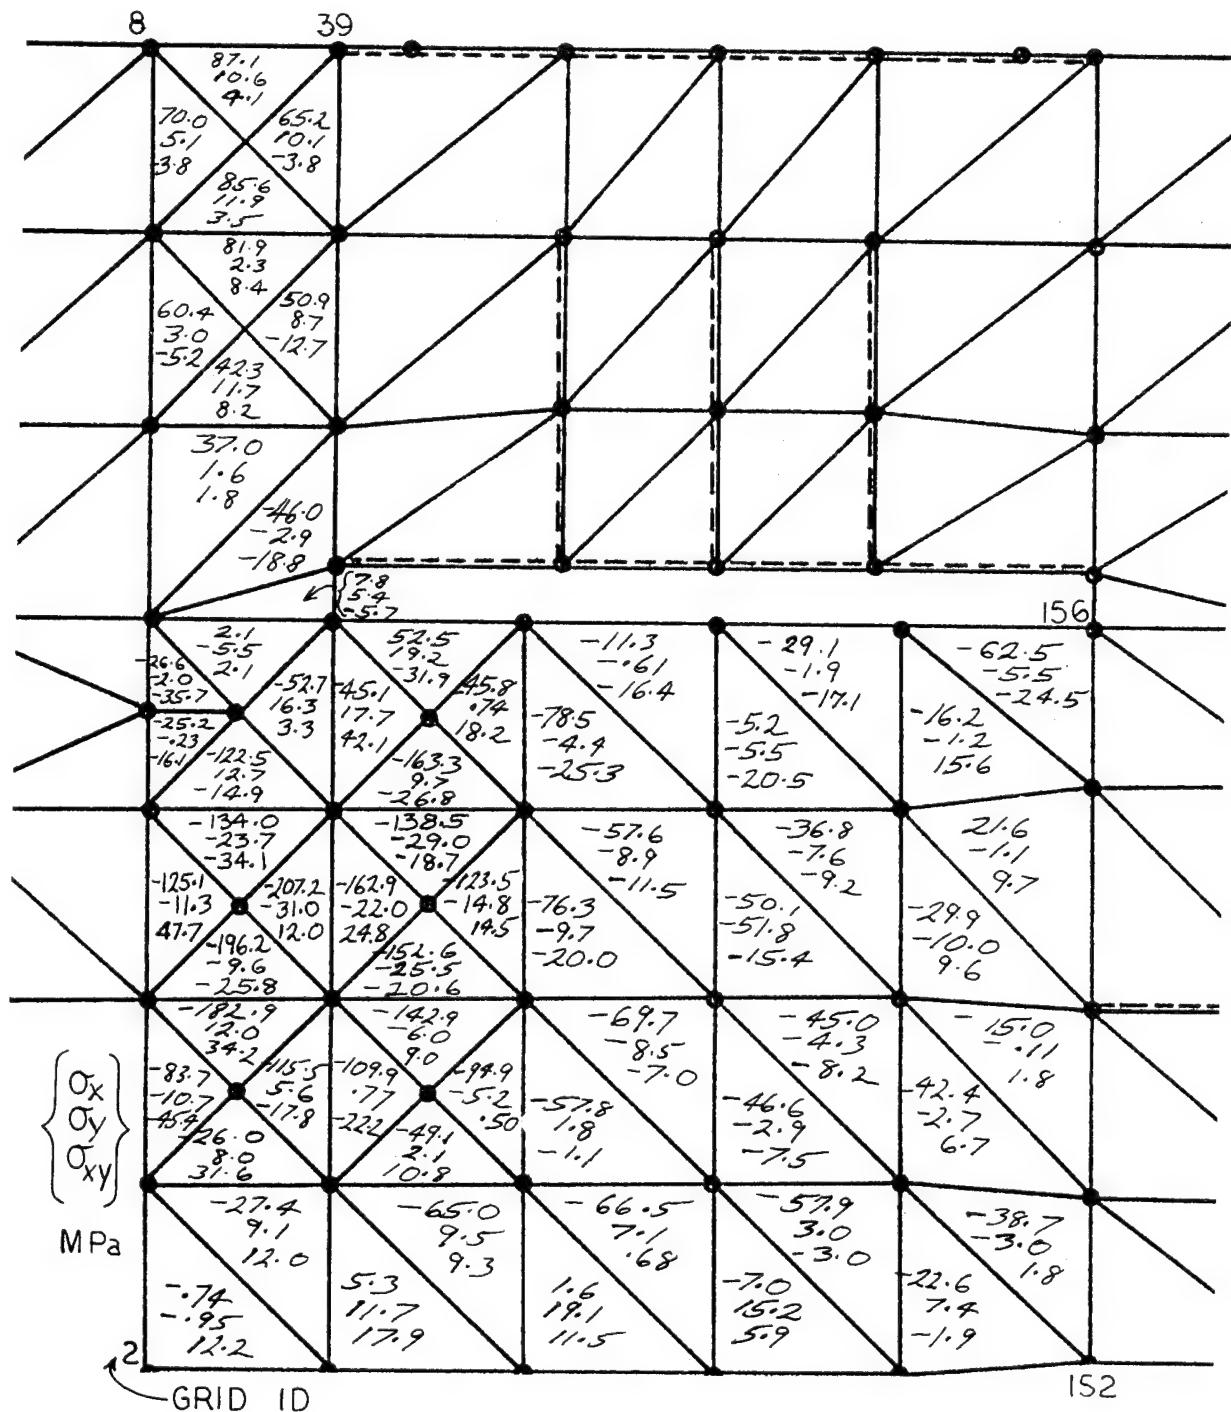
Figure 5-18. Inner Face Stresses - Recovery Condition
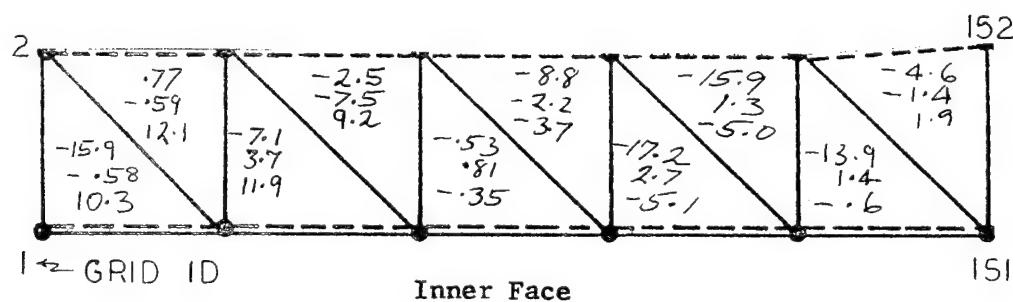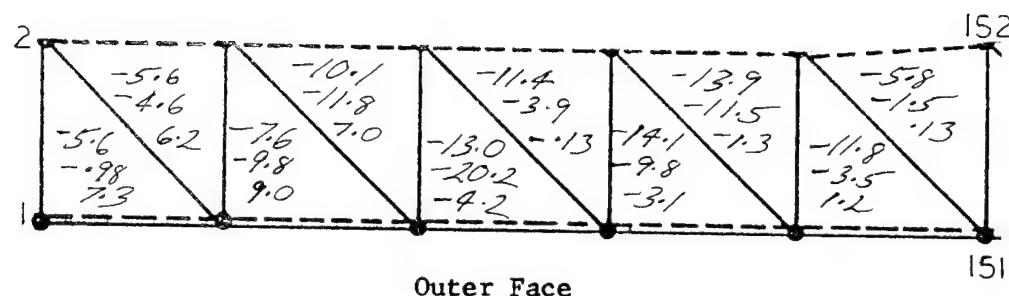
Figure 5-19. Access Door Stresses - Recovery Condition

TABLE 5-4

SUMMARY OF MAXIMUM STRESSES

RECOVERY

	Outer Face (3 Ply)		Inner Face (2 Ply)	
	MPa	PSI	MPa	PSI
AXIAL:				
Tension	*	*	87.1	12635
Compression	162.8	23621	217.7	31589
CIRCUMFERENTIAL:				
Tension	2.1	301	65.4	9486
Compression	29.0	4205	31.0	4493
SHEAR	24.8	3594	51.3	7439

* NOTE - All axial stresses in outer face 3 ply elements were in compression

$$N_o = \frac{2\gamma\overline{E}}{\sqrt{1 - \mathcal{V}_1 \mathcal{V}_2}} \quad \frac{h}{r} \quad \sqrt{t_1 t_2}$$

$$\emptyset = \left\{ G_{LT} \left[1 + (\mathcal{V}_{LT} + \mathcal{V}_{TL})^{1/2} \right] \Big/ (E_L E_T)^{1/2} \right\}^{1/2} \quad \text{(reference 4)}$$

$$D_q = G_{xz} \quad \frac{h^2}{h - \tfrac{1}{2}(t_1 + t_2)}$$

$\emptyset$ is a face shear correction factor taken from reference 4, and γ is a correlation factor defined by Figure 11 of reference 8. D_q is a transverse shear stiffness parameter for the sandwich. The other quantities are defined as follows:

G_{xz} - shear modulus of core longitudinal-transverse plane

h - sandwich depth measured center to center of faces

t_1, t_2 - sandwich face thicknesses

r - radius of cylinder

G_{LT} - in-plane shear modulus of sandwich face

E_L - longitudinal modulus of sandwich face

E_T - circumferential modulus of sandwich face

$\mathcal{V}_{LT}$, $\mathcal{V}_{TL}$ - Poisson's ratio of sandwich face

$\overline{E}$ in the equation for N_o was determined as follows:

$$\overline{E} = \frac{\left(\sqrt{E_L E_T}\right)_{\text{outer face}} + \left(\sqrt{E_L E_T}\right)_{\text{inner face}}}{2}$$

The determination of an equivalent isotropic modulus by the square root technique used here was recommended in reference 10 and is also reflected in the equation for $\emptyset$ from reference 4.

Shear Buckling Load, N_{xy} -

$$N_{xy} = \frac{.34 \, (\gamma Z)^{3/4} \, \pi^2 \, D_1}{L^2} \tag{2}$$

where

$$Z = \frac{2L^2}{rh} \sqrt{1 - \mathcal{V}_{LT} \mathcal{V}_{TL}}$$

$$D_1 = \frac{\left(\sqrt{E_L\ E_T}\right)_o t_o \left(\sqrt{E_L\ E_T}\right)_i t_i h^2}{(1 - \mathcal{V}_{LT}\ \mathcal{V}_{TL})\ \left[\left(\sqrt{E_L\ E_T}\right)_o t_o + \left(\sqrt{E_L\ E_T}\right)_i t_i\right]}$$

L = length of cylinder

γ = .586 (reference 8)

Subscript "o" refers to outer face

Subscript "i" refers to inner face

Equation (2) above may be used for rigid core where $\gamma D_1/L^2 D_q \approx 0$ and $\gamma Z > 170$. Otherwise, Figure 14 of reference 8 should be used to determine k_{xy}, and

$$N_{xy} = \frac{k_{xy}\ \pi^2 D_1}{L^2} \tag{3}$$

Cylindrical Panel:

Axial Buckling Load, N_x -

$$N_x = K N_o \left(\frac{N_x}{N_o}\right) \emptyset \tag{4}$$

Except for the K factor this is identical to equation (1) for a cylinder. Comparative calculations of cylinders and panels using the methods of reference 6 indicate that for a panel with simply-supported edges the buckling load is the same as for a cylinder and, therefore, for this case $\emptyset = 1$.

For the case of clamped edges, section 5 of reference 9 was used to determine the ratio of clamped buckling load to simply-supported buckling load. The procedure for this is as follows:

a. Determine K_{mo} from Figure 5-22 (reference 9)

b. Calculate K_F

$$K_F = \frac{\left[\left(\sqrt{E_L\ E_T}\right)_o t_o^3 + \left(\sqrt{E_L\ E_T}\right)_i t_i^3\right]\left[\left(\sqrt{E_L\ E_T}\right)_o t_o + \left(\sqrt{E_L\ E_T}\right)_i t_i\right]_{K_{MO}}}{12\ h^2\ t_o\ t_i\ \left(\sqrt{E_L\ E_T}\right)_o\ \left(\sqrt{E_L\ E_T}\right)_i} \tag{5}$$

c. Determine K_m from Figures 5-8 to 5-21 (reference 9),

d. Calculate K

$$K = K_M + K_F$$

This procedure is used to obtain a K for clamped edges and a K for simply supported edges. There the factor $\emptyset$ to be used in equation (4) for clamped edges is

$$\emptyset = \frac{K_{clamped}}{K_{simply\ supported}}$$

Shear Buckling Load, N_{xy} -

$$N_{xy} = \bar{N}_{xy} + (N_{xy})_{cyl} \tag{6}$$

The shearing buckling load of the cylindrical panel is the sum of the cylinder shear buckling load and the shear buckling load of a flat panel, reference 10. Therefore, $(N_{xy})_{cyl}$ is calculaged from equation (2). $\bar{N}xy$ is calculaged from section 6 of reference 9, as follows:

a. Determine K_m and K_{mo} from Figures 6-7 to 6-14 (reference 9).

b. Calculate K_F from equation (5)

c. $K = K_F + K_m$

d. $\bar{N}_{xy} = K \dfrac{\pi^2}{b^2} D_1$

where b is the length of the short edge. Linear interaction was assumed between shear and axial load buckling.

In addition to the general instability modes discussed above, the sandwich design must be able to resist local buckling in the form of intercell buckling and face wrinkling.

Intercell Buckling -

$$\bar{\sigma}_f = .764 \sqrt{E_L E_T} \left(\frac{t_f}{d} \right)^{3/2} \tag{7}$$

This is based on reference (11), and

σ_f = face buckling stress

d = cell diameter

Face Wrinkling -

For thin cores the following equations, taken from reference 12, account for initial waviness of the sandwich faces:

$$\sigma_{cr} = \gamma\left[.590 \ (E_L \ E_C \ t_c \ )^{1/2} + .386 \ G_{xz} \ t_c/t_f\right] \qquad (8)$$

γ is the waviness correction factor and is defined as

$$\gamma = \frac{1}{1 + c\beta}$$

where

$$C = \frac{\pi \ G_{xz}}{\lambda \ cr}$$

$$\lambda_{cr} = 1.670 \ t_f \ (E_L \ t_c/E_L \ t_f)^{1/4}$$

$$\beta = 6.3 \times 10^{-6}$$

and

t_c = core thickness

t_f = face thickness

E_c = core modulus in thickness direction

σ_{cr} = face wrinkling stress

Analysis

The configuration and design of the composite fuselage has been described previously. This design was analyzed for buckling using the methodology just presented. The key geometric parameters for this analysis are as follows:

Outer face thickness - .66 mm (.026")

Inner face thickness - .41 mm (.016")

Core thickness - 64 mm (1/4")

h = 6.88 mm (.27")

r = 31.75 cm (12.5")

Panel length, L = 104.1 cm (41")

Panel width - 33.0 cm (13")

Material properties are given in Table 5-2. The core properties are as follows:

$$G_{XZ} = 310 \text{ GPa } (45000 \text{ psi})$$

$$G_{YZ} = 152 \text{ GPa } (22000 \text{ psi})$$

$$E_C = 531 \text{ GPa } (77000 \text{ psi})$$

From these values

$$(\sqrt{E_L E_T})_o = 25.7 \text{ GPa } (3.7 \times 10^6 \text{ psi})$$

$$(\sqrt{E_L E_T})_i = 31.0 \text{ GPa } (4.5 \times 10^6 \text{ psi})$$

$$(\sqrt{E_L E_T})_o \, t_o = 16.96 \text{ MN/m } (96200 \text{ \#/in.})$$

$$(\sqrt{E_L E_T})_i \, t_i = 12.61 \text{ MN/m } (72000 \text{ \#/in.})$$

$$D_1 = 362.8 \text{ Nm } (3211 \text{ in. lb.})$$

$$D_q = 2.31 \text{ MN/m } (13185\text{\#/in.})$$

and the critical buckling loads are

$$N_x = 350 \text{ kN/m } (2000 \text{ \#/in.})$$
$$\text{simply-supported edges}$$
$$N_{xy} = 271 \text{ kN/m } (1550 \text{ \#/in.})$$

$$N_x = 665 \text{ kN/m } (3800 \text{ \#/in.})$$
$$\text{clamped edges}$$
$$N_{xy} = 394 \text{ kN/m } (2250 \text{ \#/in.})$$

For conservatism, the simply supported results were used. The local buckling mode stresses are

$$\sigma_f = 1085 \text{ MPa } (157.4 \text{ KSI}) \quad \text{inner face intercell buckling}$$

$$\sigma_f = 1849 \text{ MPa } (268.2 \text{ KSI}) \quad \text{outer face intercell buckling}$$

and

$$\sigma_{cr} = 471 \text{ MPa } (68.3 \text{ KSI}) \quad \text{inner face wrinkling}$$

$$\sigma_{cr} = 355.1 \text{ MPa } (51.5 \text{ KSI}) \quad \text{outer face wrinkling}$$

The corresponding load on the sandwich to cause these wrinkling stresses in the faces are

$$N_x = 406 \text{ kN/m (2320 #/in.)} \quad \text{inner face}$$

$$N_x = 441 \text{ kN/m (2520 #/in.)} \quad \text{outer face}$$

These results are shown in summary form in Table 5-5.

5.6 STRENGTH AND MARGINS OF SAFETY

The overall strength of the composite fuselage panels is based on the results of the NASTRAN finite element analysis, the buckling analysis and the material properties. NASTRAN stresses and material allowable stresses were converted into equivalent axial and shear loads per unit length, N_x and N_{xz}, by apportioning the load to the two faces according to the ratio of their stiffnesses. The outer face takes 53% of the in-plane compression and 60% of the in-plane shear, while the inner face takes the remainder. The stress to load conversions, therefore, are as follows:

SI		English	
$Nx_{of} = 1.25 \ \sigma x_{of}$		$Nx_{of} = .049 \ \sigma x_{of}$	
$Nx_{if} = .87 \ \sigma x_{if}$		$Nx_{if} = .034 \ \sigma x_{if}$	
$Nxy_{of} = 1.10 \ \sigma xy_{of}$		$Nxy_{of} = .043 \ \sigma xy_{of}$	
$Nxy_{if} = 1.03 \ \sigma xy_{if}$		$Nxy_{if} = .040 \ \sigma xy_{if}$	

$$N - \text{kN/m} \qquad\qquad N - \text{#/in.}$$

$$\sigma - \text{MPa} \qquad\qquad \sigma - \text{psi}$$

Stresses at critical points from the NASTRAN analysis were converted into loads and plotted as on applied load envelope, Figure 5-20. The buckling capability is shown as a straight line interaction between axial load and shear. In addition, the loads which would produce face wrinkling and compression and shear failure in the faces are shown. The resulting strength envelope is one which is dominated by buckling and facing shear strength capabilities, although the minimum margin region is in the area of the intersection of the buckling and inner face compression strengths. The margin of safety in this region is .4.

Figure 5-21, which shows a similar comparison of loads and strength for the reinforced sections where both faces are 4 plies thick, is included for reference without the detail calculations. The margins of safety for this are greater than for those represented by Figure 5-20, and so the thinner sandwich sections are more critical.

TABLE 5-5

SUMMARY OF SANDWICH PANEL BUCKLING CAPABILITY

	N_x		N_{xy}	
	KN/M	#/in.	KN/M	#/in.
Simple Supports	350	2000	271	1550
Clamped	665	3800	394	2250
Face Wrinkling	406	2320		
Intercell Buckling	High			
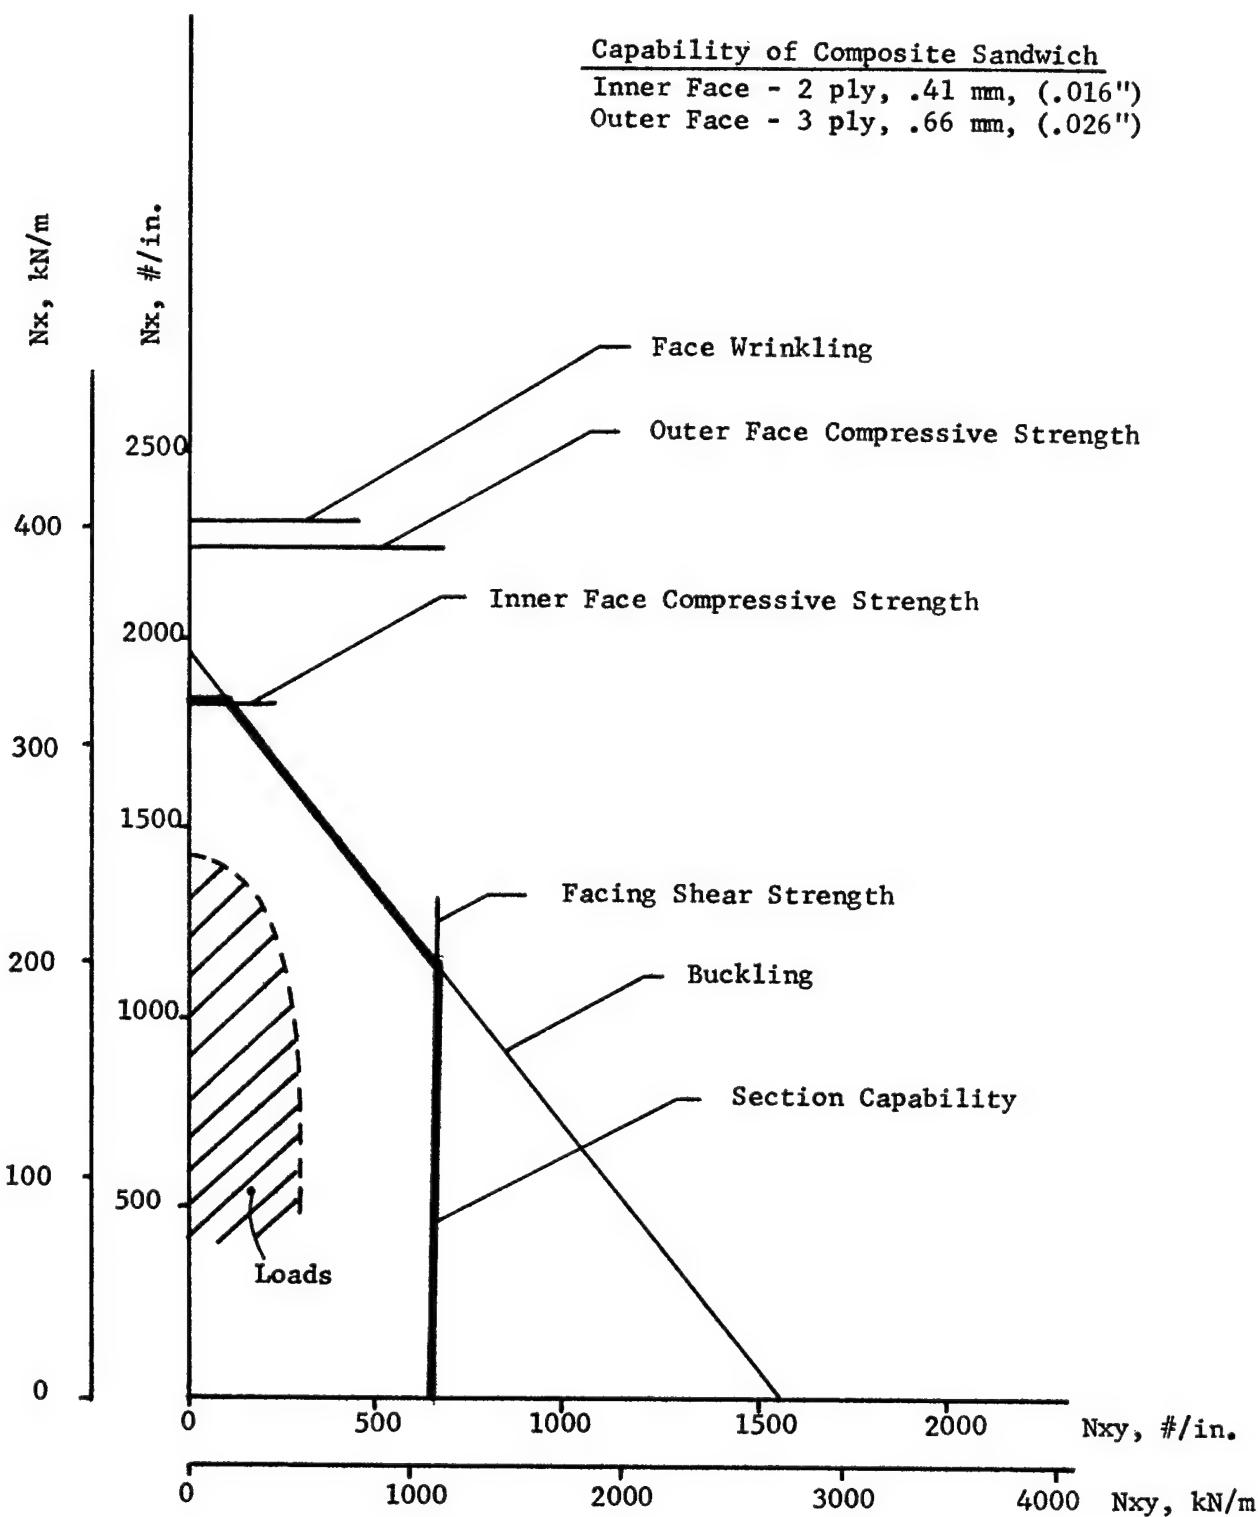
Figure 5-20. Strength of Composite Fuselage Panels,
Basic Section

61
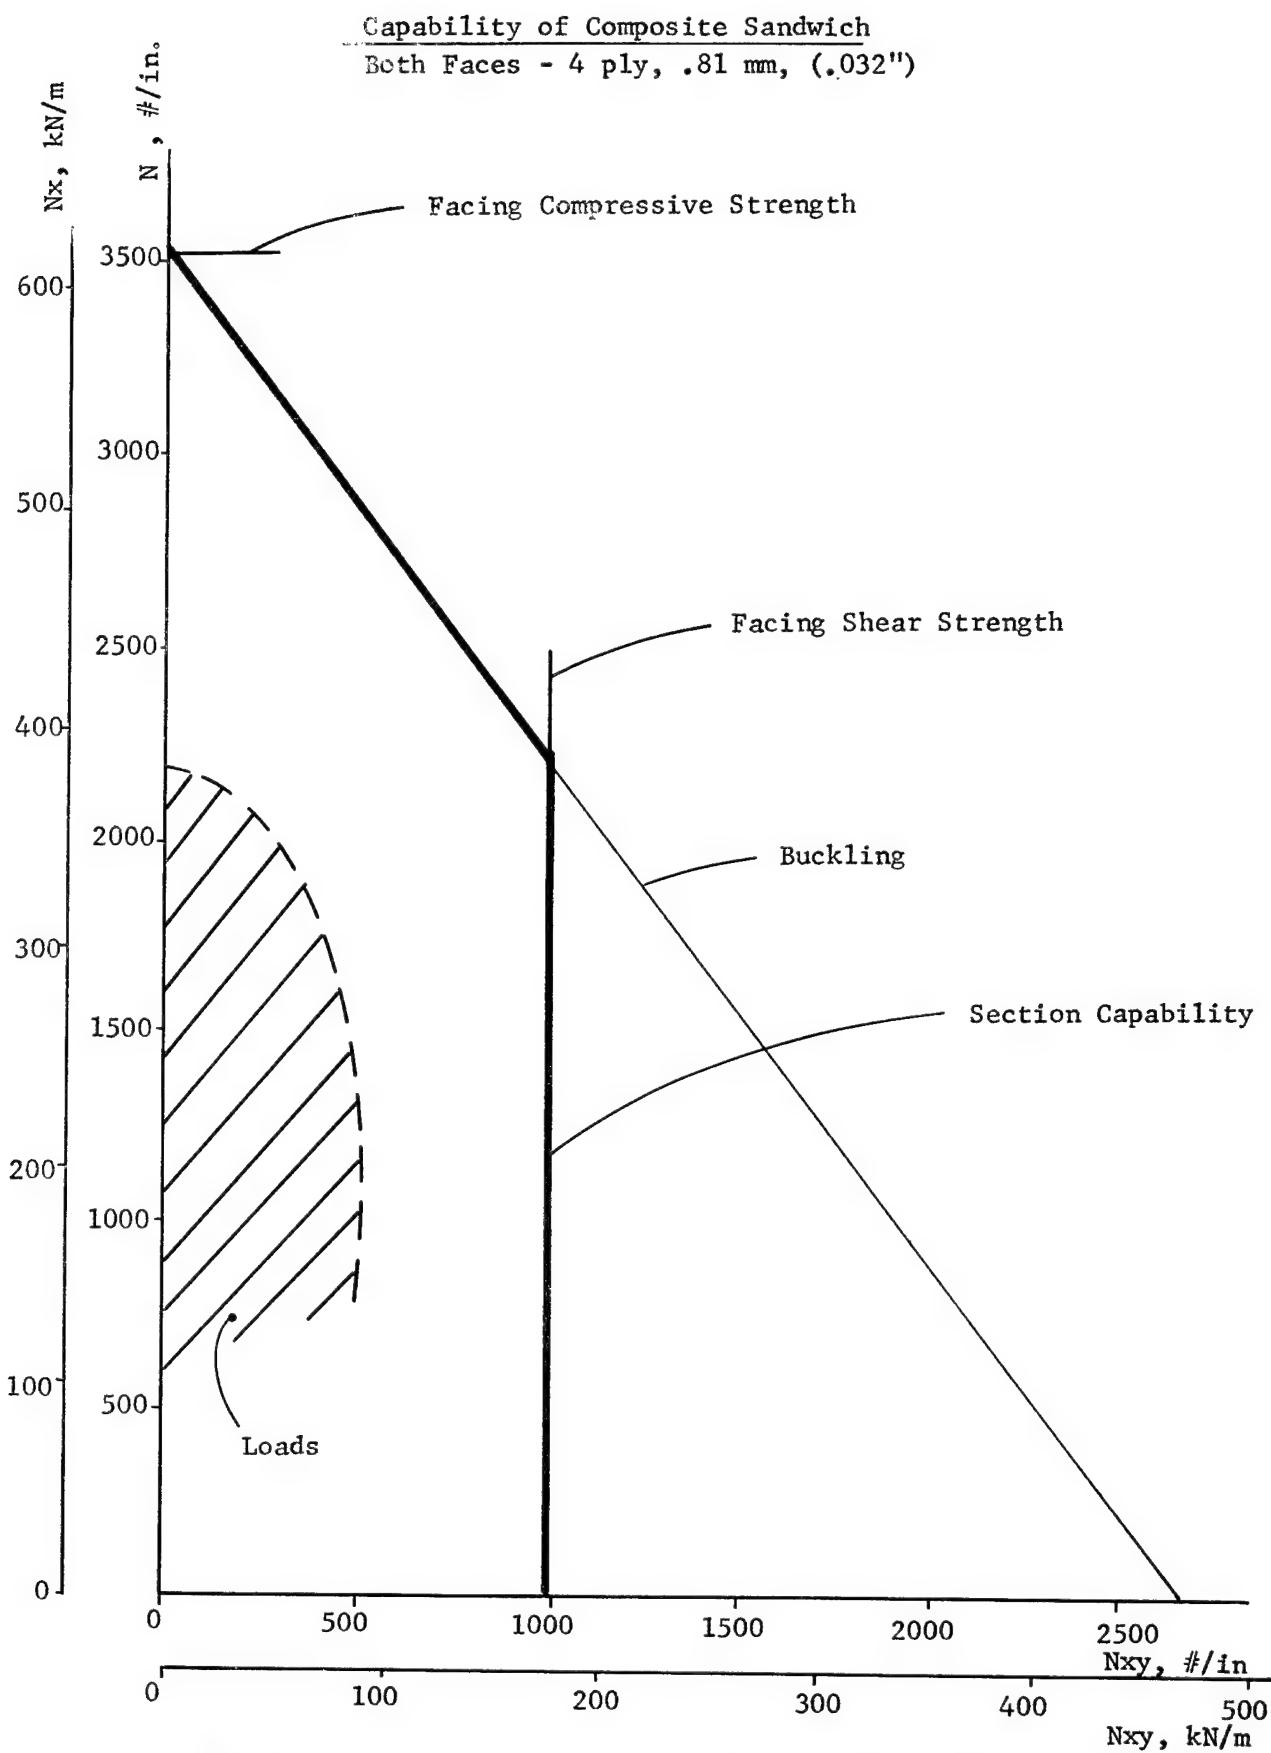
Figure 5-21.   Strength of Composite Fuselage Panels -
Reinforced Section

6.0   E L E M E N T   T E S T S

One of the areas of concern early in the design phase was the strength of the closeout section of the fuselage panels. The closeout is formed by tapering the core and bringing the two faces together, with added plies for reinforcement. In order to evaluate this design, a set of specimens was tested under compressive loading. The configuration of these specimens is shown in Figure 6-1. The goal was to show that the closeout was at least as strong as the main panel area.

Four specimens were tested in the setup shown in Figure 6-3. A lateral support was used to simulate the support conditions in the cylindrical shell configuration. Results of these tests are given in Table 6-1. The failure loads are greater than the design loads, but more important than load magnitudes is the fact that none of the specimens failed in the closeout area. This gave assurance that the closeout design was adequate and would not cause premature failures in that area. A photograph of the failed specimens is given in Figure 6-3.

7.0   S U B C O M P O N E N T   D E S I G N   A N D   T E S T

7.1 DESIGN

In order to substantiate the basic fuselage panel design and its method of attachment to the existing metal bulkheads, a cylinder was designed and fabricated for testing. This shell had the same honeycomb sandwich design as the fuselage panels, and was the same radius and length. It was, however, a complete cylinder rather than a cylindrical panel, Figure 7-1. The complete cylinder is easier to test and, in many respects, easier to make than the panel, hence, its selection as a subcomponent test article. Figure 7-2 gives the design details of this cylinder.

The cylinder is 63.5 cm (25 in.) OD and 104.1 (41 in.) long. It was made in two halves and joined by two longitudinal splices. The splices are honeycomb sandwich plates bonded between the two faces of the main shell sandwich.

7.2 TEST CONDITIONS AND FIXTURES

Two sets of tests were performed on the cylinder to demonstrate the overall structural adequacy of the design to withstand critical flight loads. The first was a compression test to limit load, since the fuselage design is critical in compression. The second set of tests was a series of tension tests performed to demonstrate the ability of the crack arrester strips to stop a crack, and therefore, render the composite design fail-safe.

The test fixture configuration for testing the cylinder in compression and tension is schematically illustrated in Figure 7-3. Compressive and tensile loading was introduced into the cylinder through a pair of concentric aluminum end rings, the inner ring being both bonded (EA 9309) and bolted to
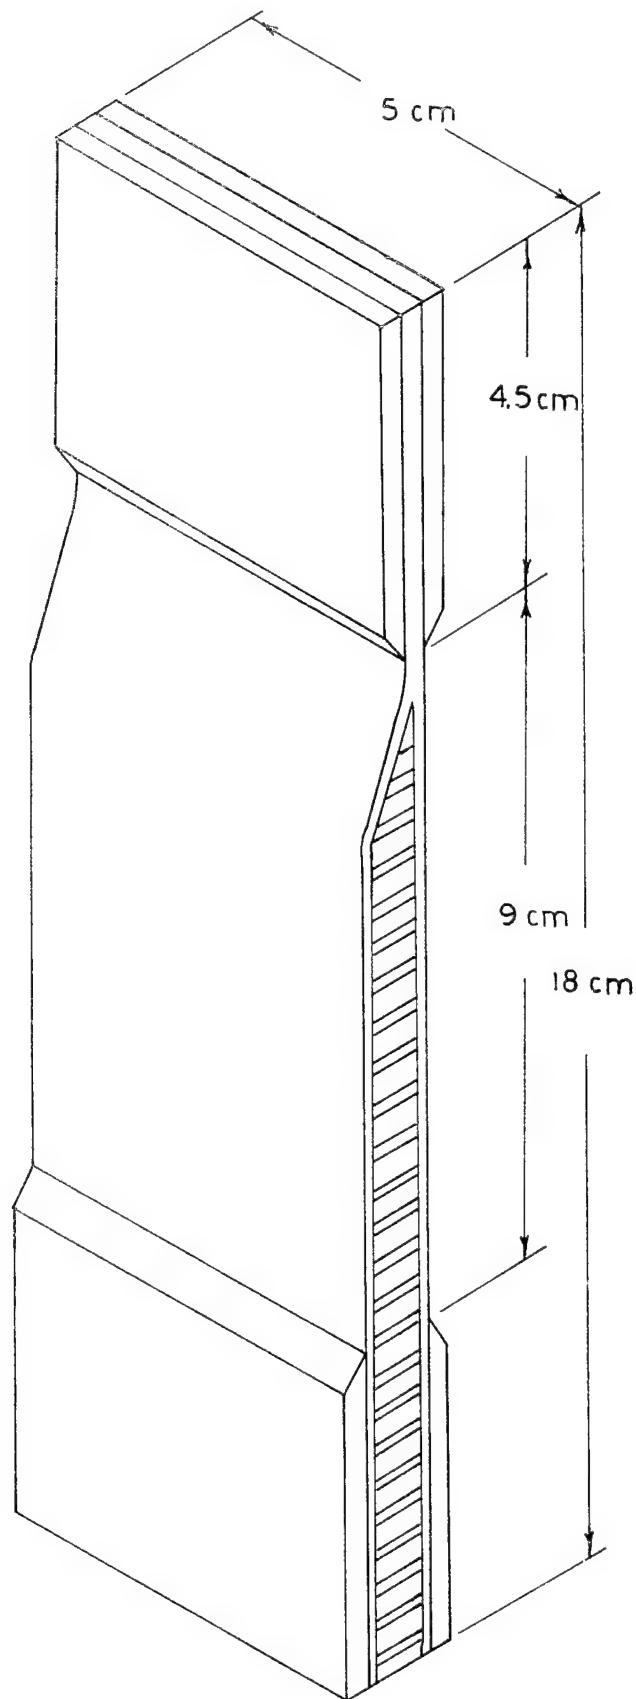
Figure 6-1. Closeout Specimen Configuration
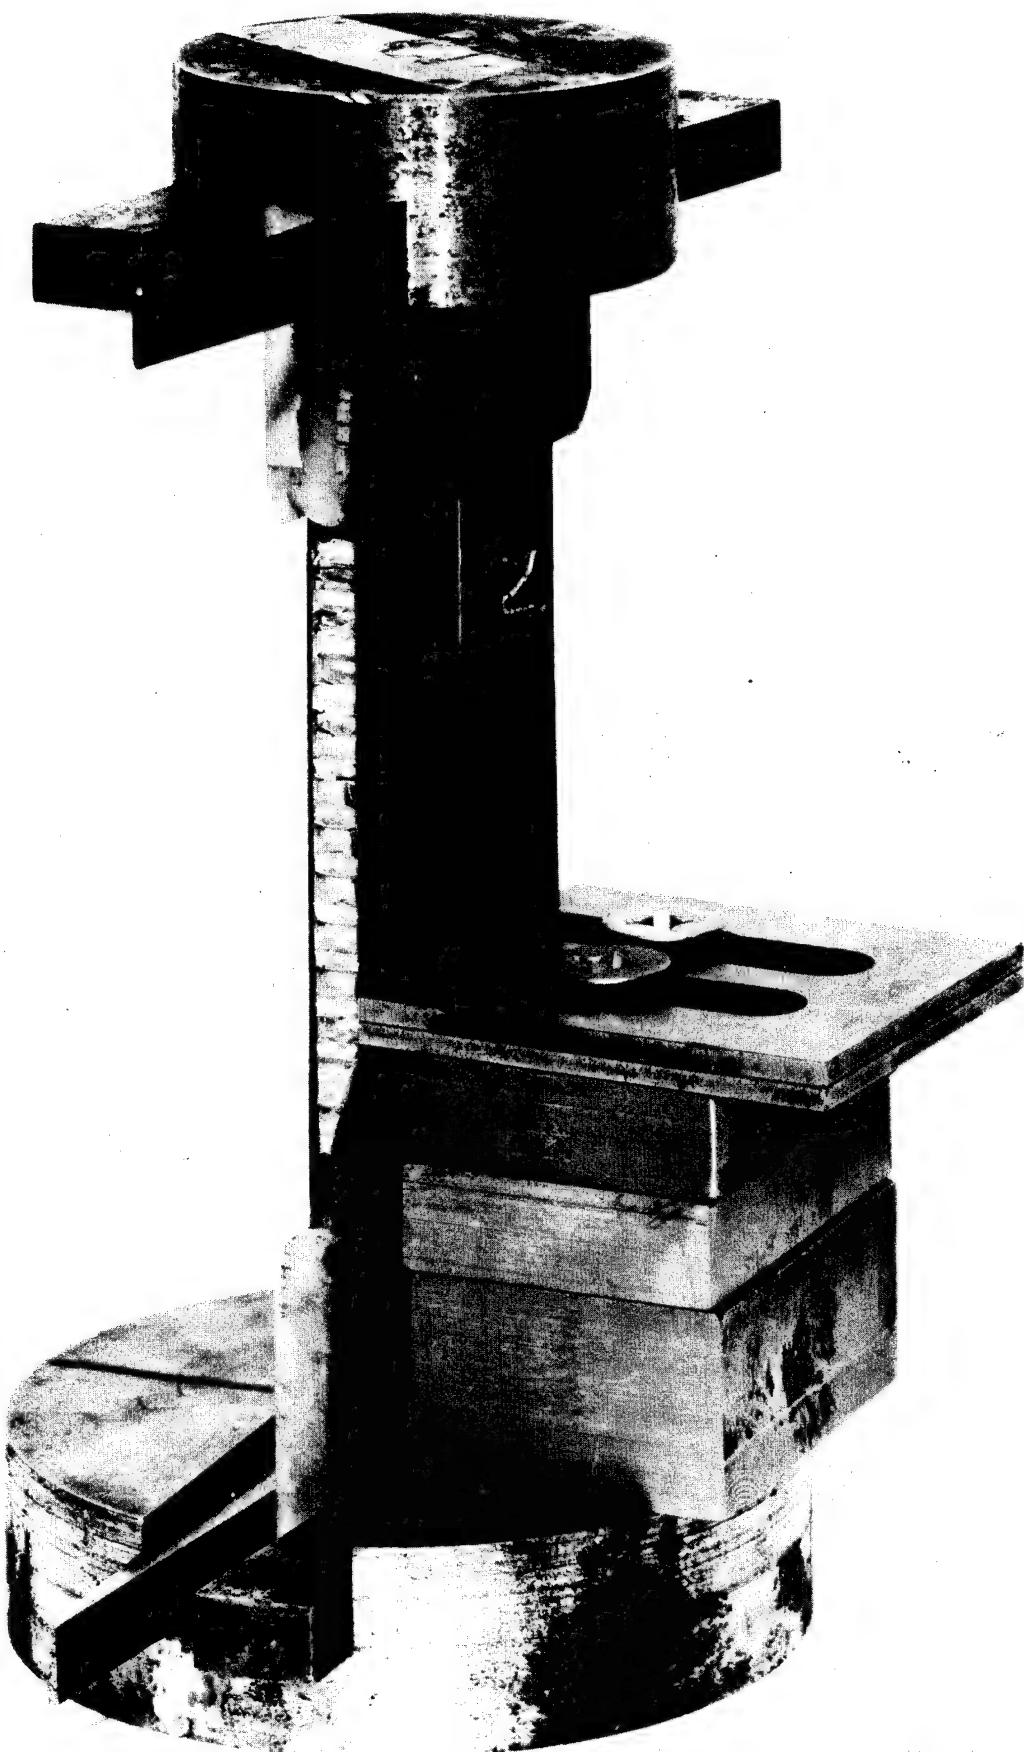
Figure 6-2. Closeout Specimen Test Setup

TABLE 6-1

RESULTS OF CLOSE-OUT SECTION TESTS

SPECIMEN	FAILURE LOAD	FAILURE MODE
1	13678 N(3075#)	Inner Face Crimping-Near Tab
2	13388 N(3010#)	Excessive Lateral Deflection
3	12343 N(2775#)	Gross Section Shear
4	11609 N(2610#)	Gross Section Shear
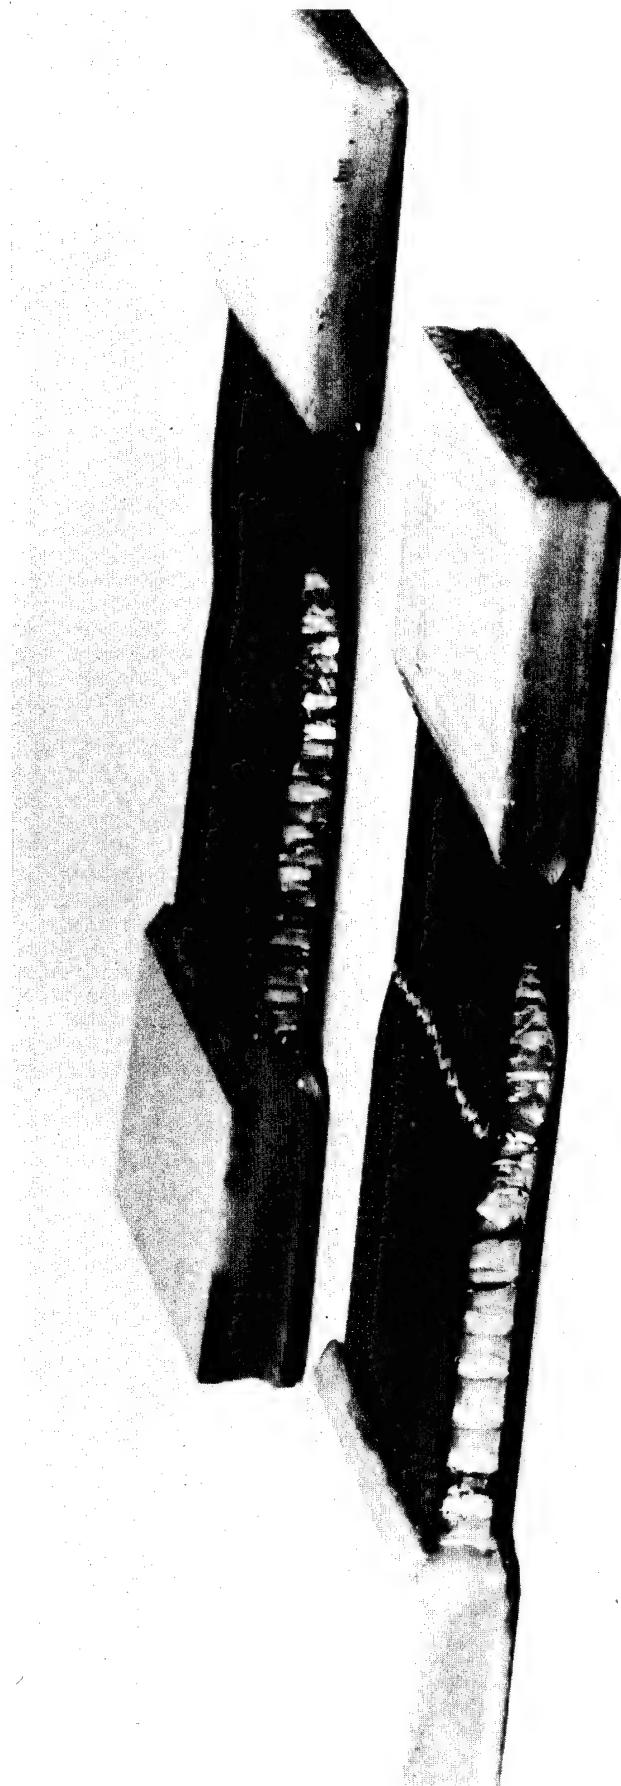
Figure 6-3. Failed Closeout Specimens
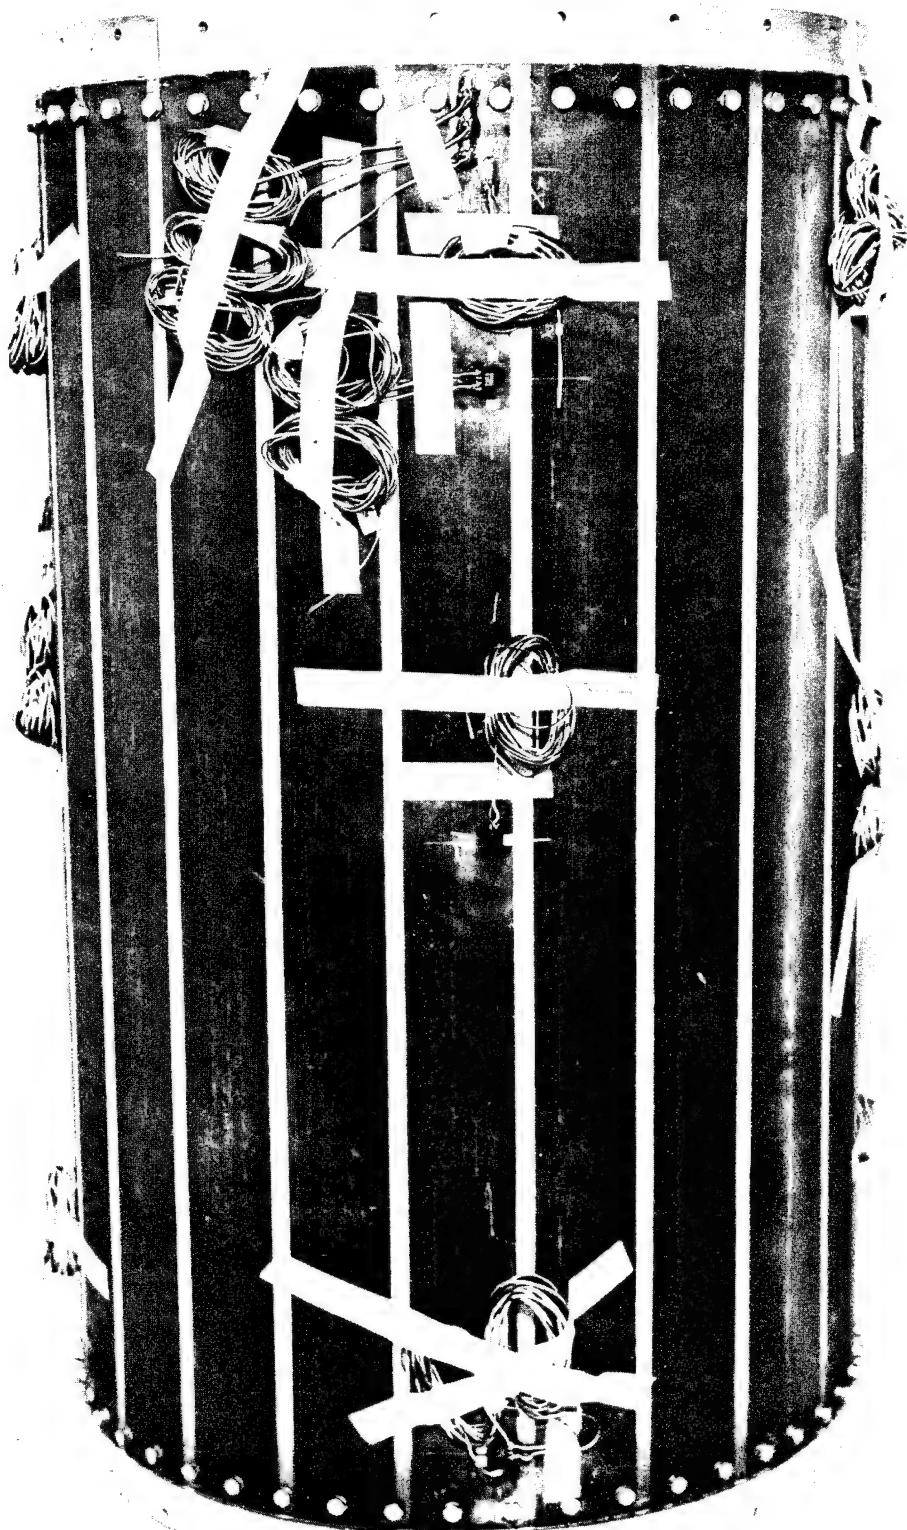
Figure 7-1. Cylinder Subcomponent

DWG. "BQM-34E CYLINDER TEST SPECIMEN" WILL BE FOUND IN THE BACK
OF THIS REPORT
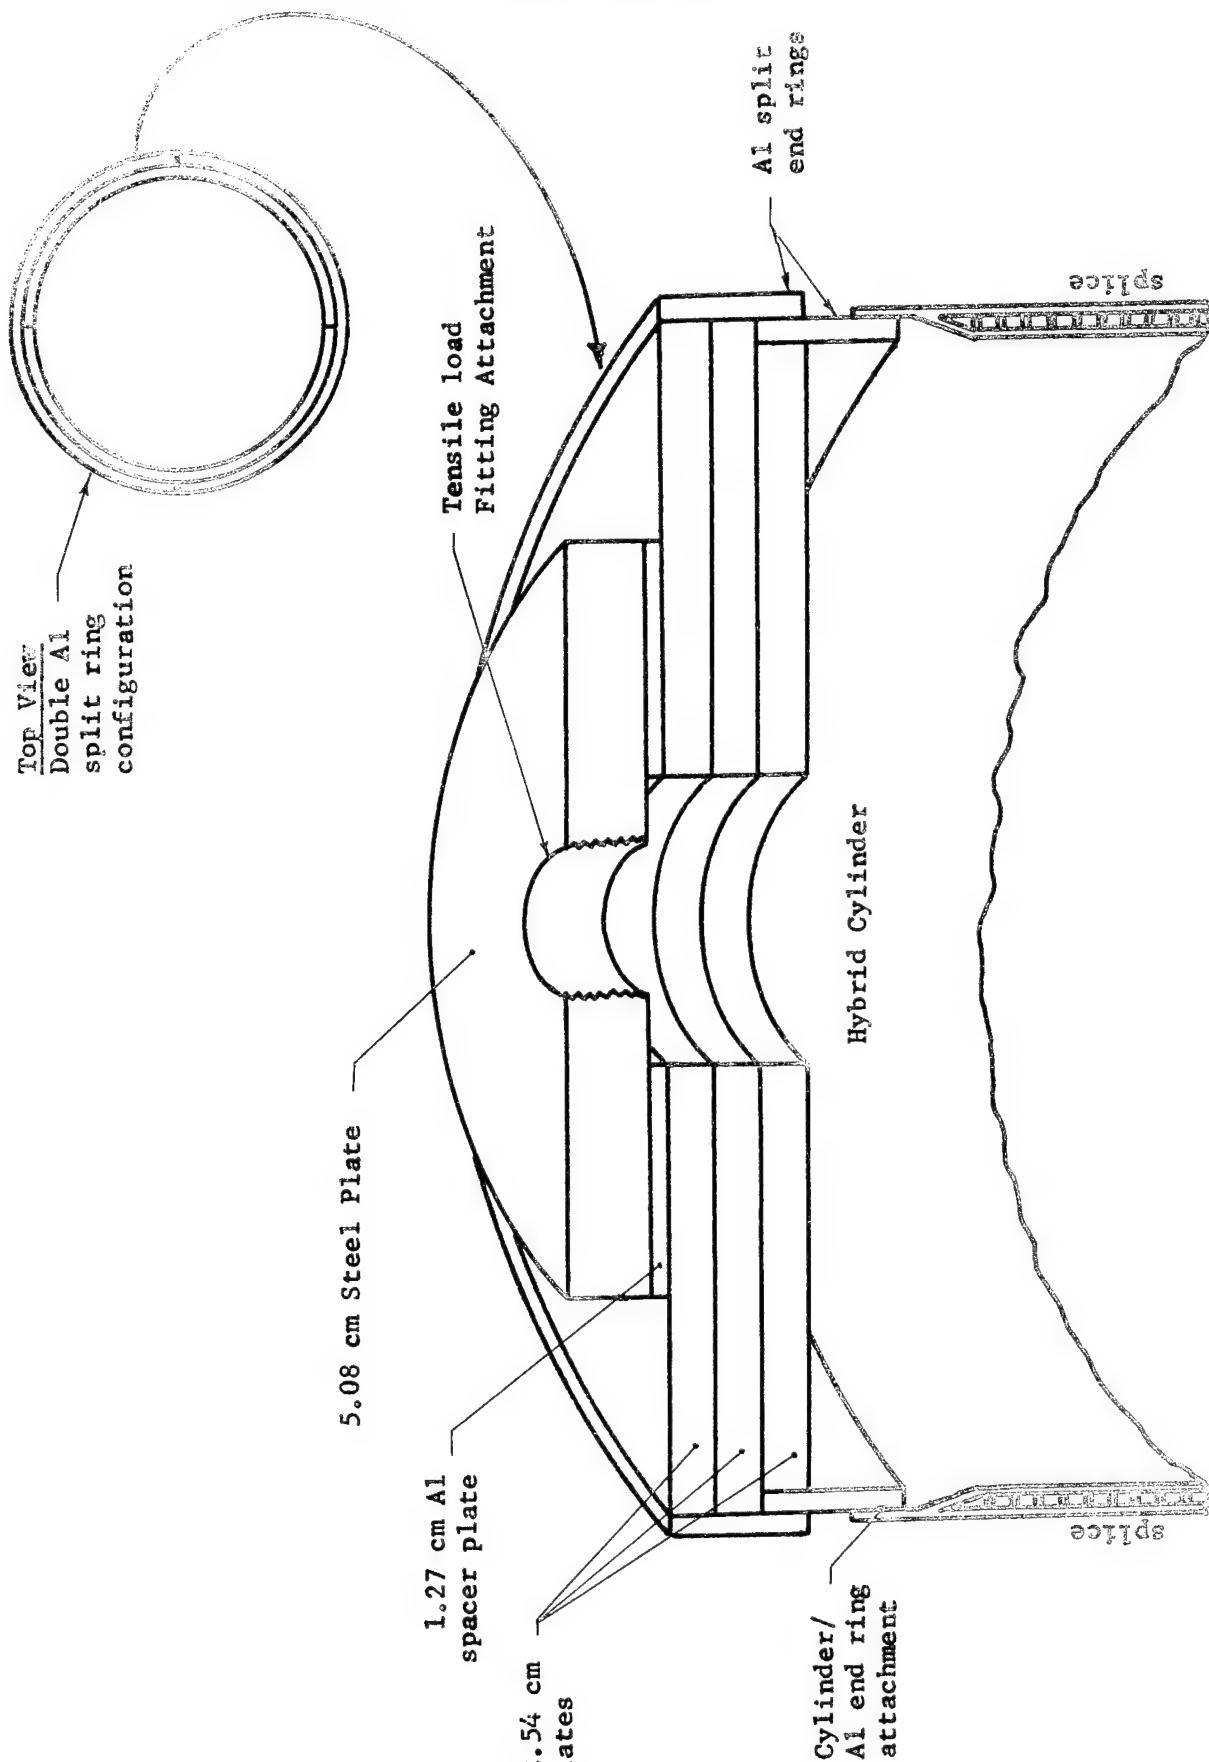
Figure 7-5. Cylinder Test Fixtures

the reinforced solid laminate areas at both ends of the cylinder. The inner and outer end rings were bolted together and in turn bolted to three 2.54 cm (1 in.) thick circular aluminum plates which fit inside the concentric rings. The three circular aluminum plates and an additional 5.08 cm (2 in.) thick steel circular plate were bolted together to form a single unit in order to react the substantial bending moment induced by the centrally applied load. In compression, the load was applied directly through the top steel plate. In tension, load was introduced into the cylinder through a 7.62 cm (3 in.) diameter fitting which is threaded into the center hole in the steel circular plate. The steel pl.:e is repositioned internal to the three aluminum plates for tensile loading.

7.3 INSTRUMENTATION

Instrumentation for the tests consisted of strain gages and deflection gages. Figure 7-4 and Table 7-1 show the locations of the strain gages. There were 6 biaxial gages and 32 uniaxial gages giving a total of 34 strain readings. Eight of the gages were on the inner face and the remainder on the outside face.

Four deflection gages spaced 90° apart were used to measure axial deflection in both the compression and tension tests. For the compression test four more gages were used, also spaced 90° apart, to measure lateral deformation of the cylinder at its mid-length. These are shown in Figure 7-5.

Strains were recorded on the portable B & W recorder. Deflections were measured using LVDT's.

7.4 HYBRID COMPOSITE TESTING

The cylinder tests were performed in the 1334 KN (300,000 pound) capacity test machine. Figure 7-6 shows the composite sandwich cylinder in the testing machine. The first two tests performed were compression tests to 50% and 100% of limit load, 186.8 Kn (42000 lb.) and 373.6 Kn (84000 lb.) respectively. The cylinder withstood these loads successfully, and no unusual behavior was observed. This was the basic demonstration of the ability of the design to take critical flight loads.

A second, and more comprehensive, series of tests was then performed to evaluate the crack arrestment design. First, proof tests were run at 50%, 75%, and 100% of design ultimate load as a demonstration of basic tensile strength. Then five additional tests were run with induced damage, as depicted in the tensile test setup as shown in Figure 7-7. For test 2, a 2.54 cm (1 in.) sawcut crack was formed midway between two adjacent crack arrester strips. Load was applied until the crack propagated. (See Figure 7-8.) This occurred at 120% of design limit load (DLL). Propagation in this hybrid material was not at all sudden. The crack started to propagate at a particular load and continued to propagate gradually as the load was increased, until it reached the arrester strip. The propagation loads given here represent the load when the crack reached the arrester strip. Test 3 was a repeat of test 2 with identical results.
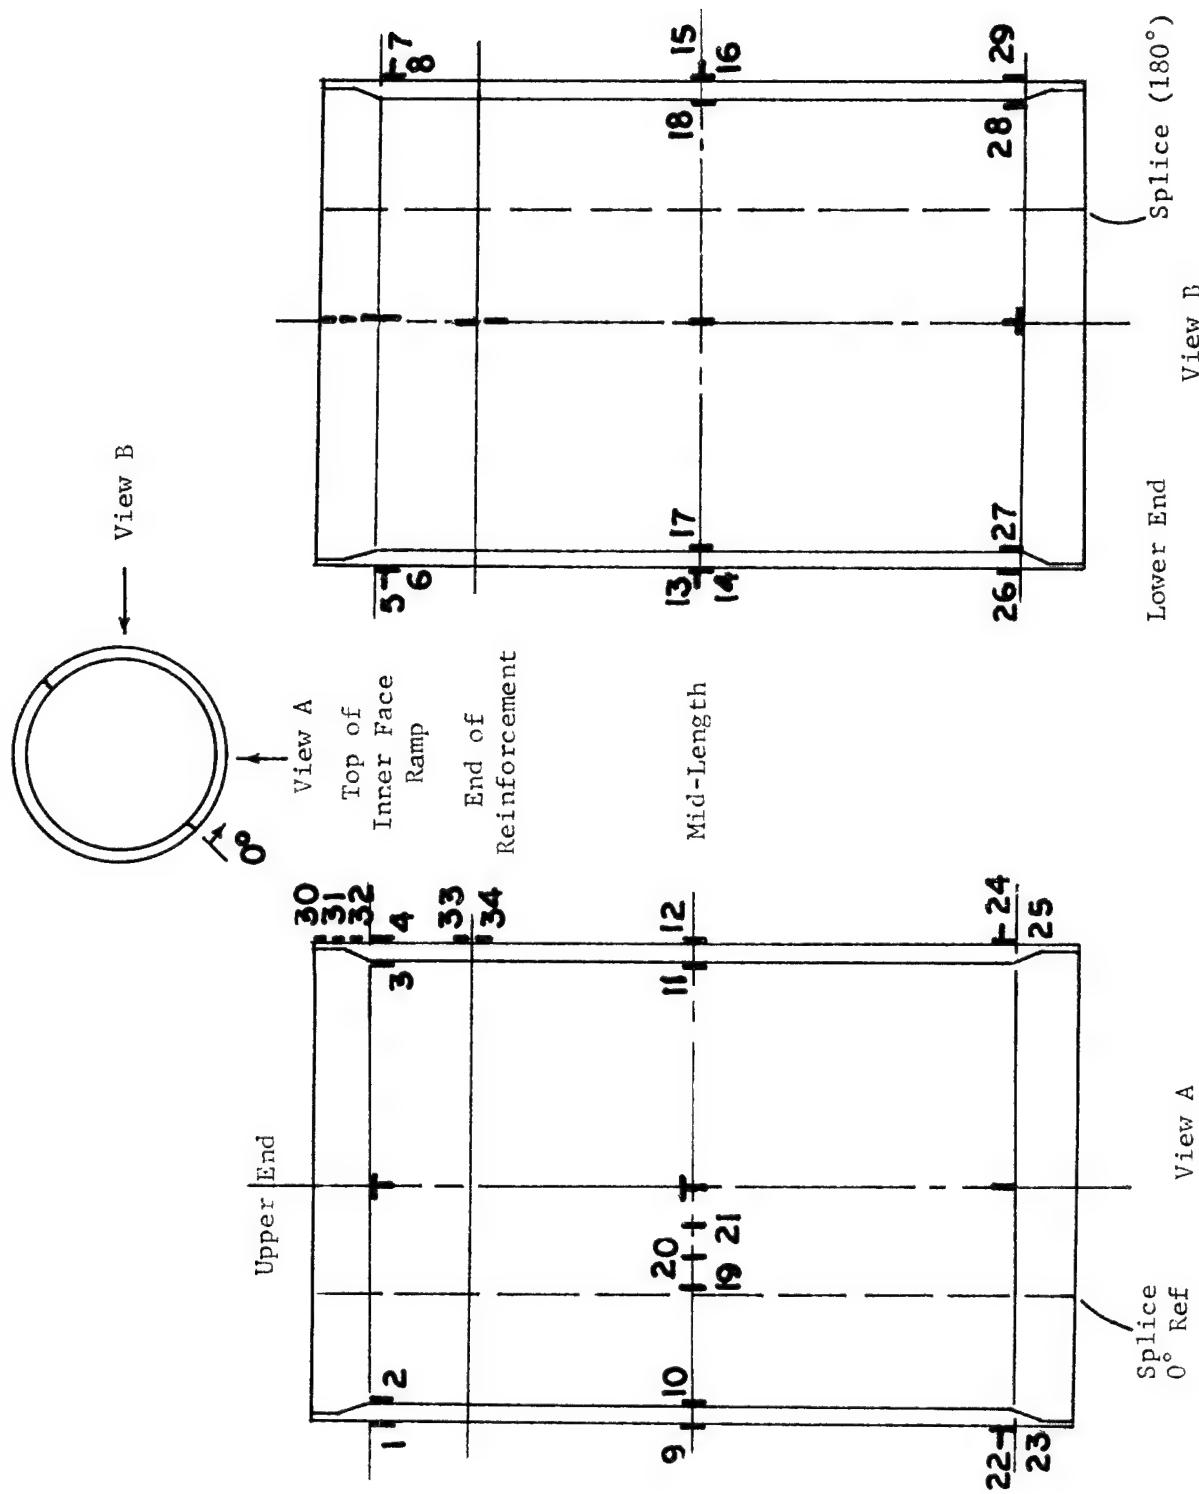
Figure 7-4. Cylinder Strain Gage Locations

TABLE 7-1

STRAIN GAGE LOCATIONS

GAGE NO.	FACE	AXIAL LOCATION	CIRC LOCATION
1	Outer	Upper End	315°
2	Inner	"	315°
3	Inner	"	135°
4	Outer	"	135°
5,6	Outer	"	45°
7,8	"	"	225°
9	"	Mid-Length	315°
10	Inner	"	315°
11	"	"	135°
12	Outer	"	135°
13,14	"	"	45°
15,16	"	"	225°
17	Inner	"	45°
18	"	"	225°
19	Outer	"	0°
20	"	"	15°
21	"	"	30°
22,23	"	Lower End	315°
24,25	"	"	135°
26	"	"	45°
27	Inner	"	45°
28	"	"	225°
29	Outer	"	225°
30	"	Upper End	135°
31	"	"	135°
32	"	"	135°
33	"	8" from Upper End	135°
34	"	"	135°

Radial Gages (4)
(Used for Com-
pression test
only)

Splice

Axial Gages (4)

Mid Length
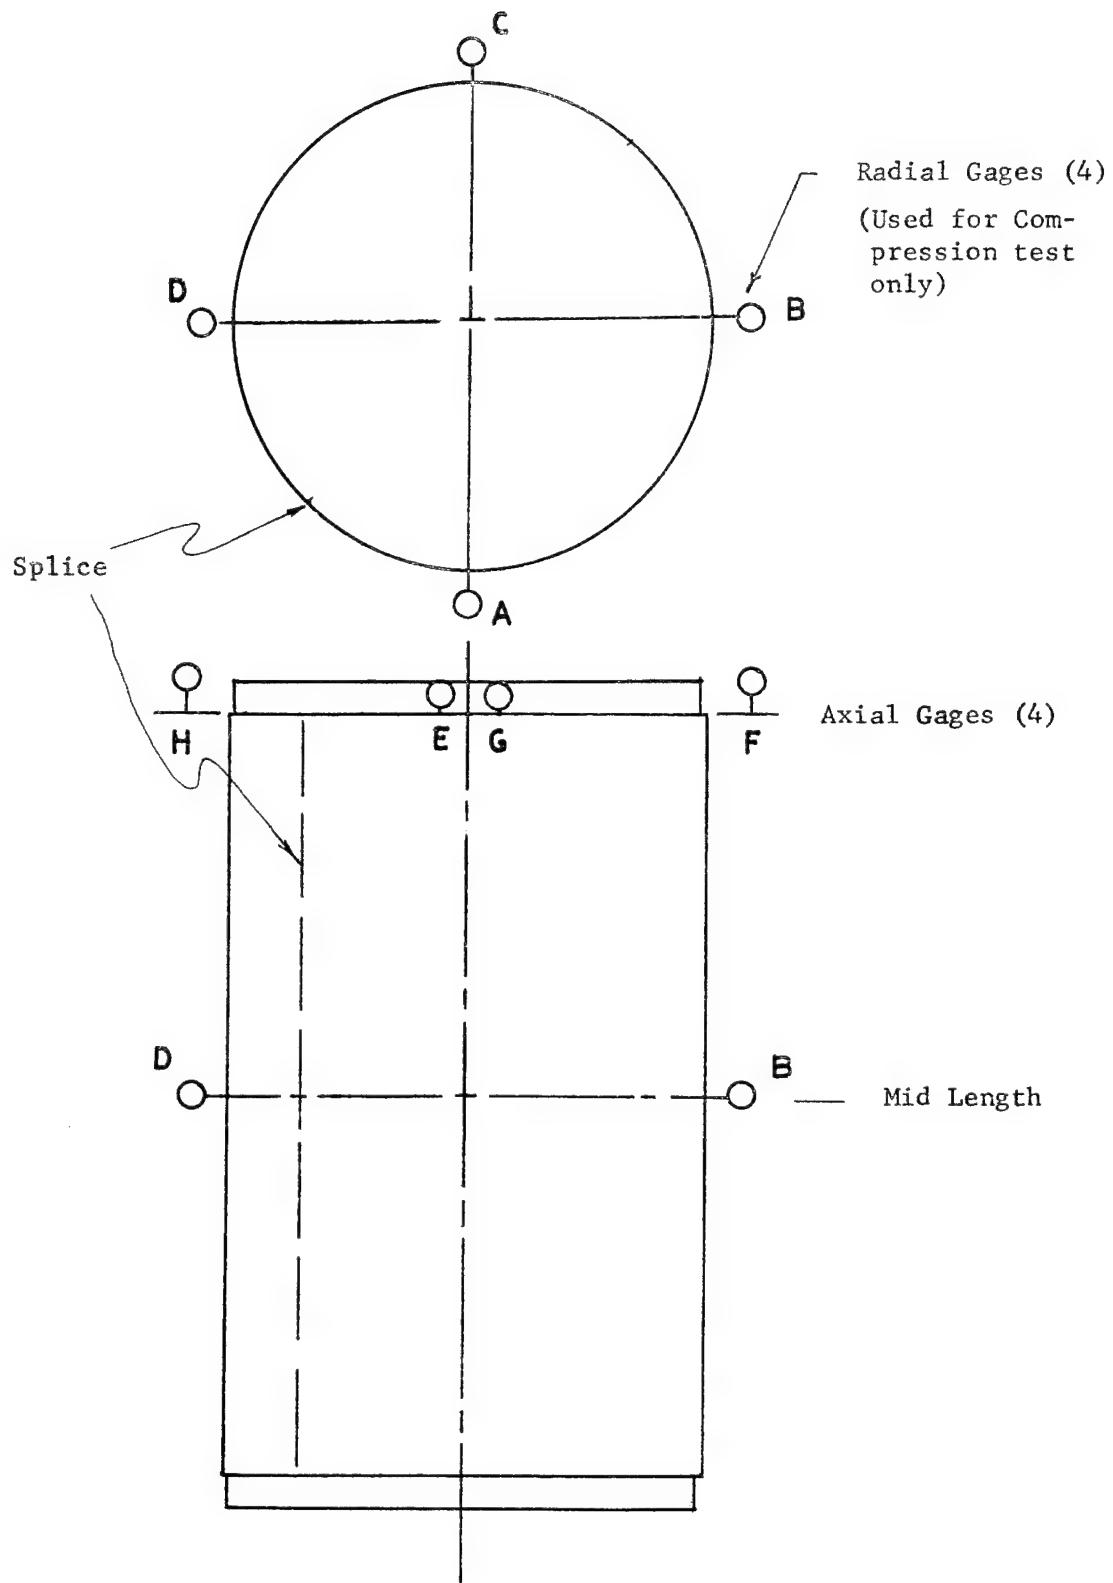
Figure 7-5. Deflection Gage Locations
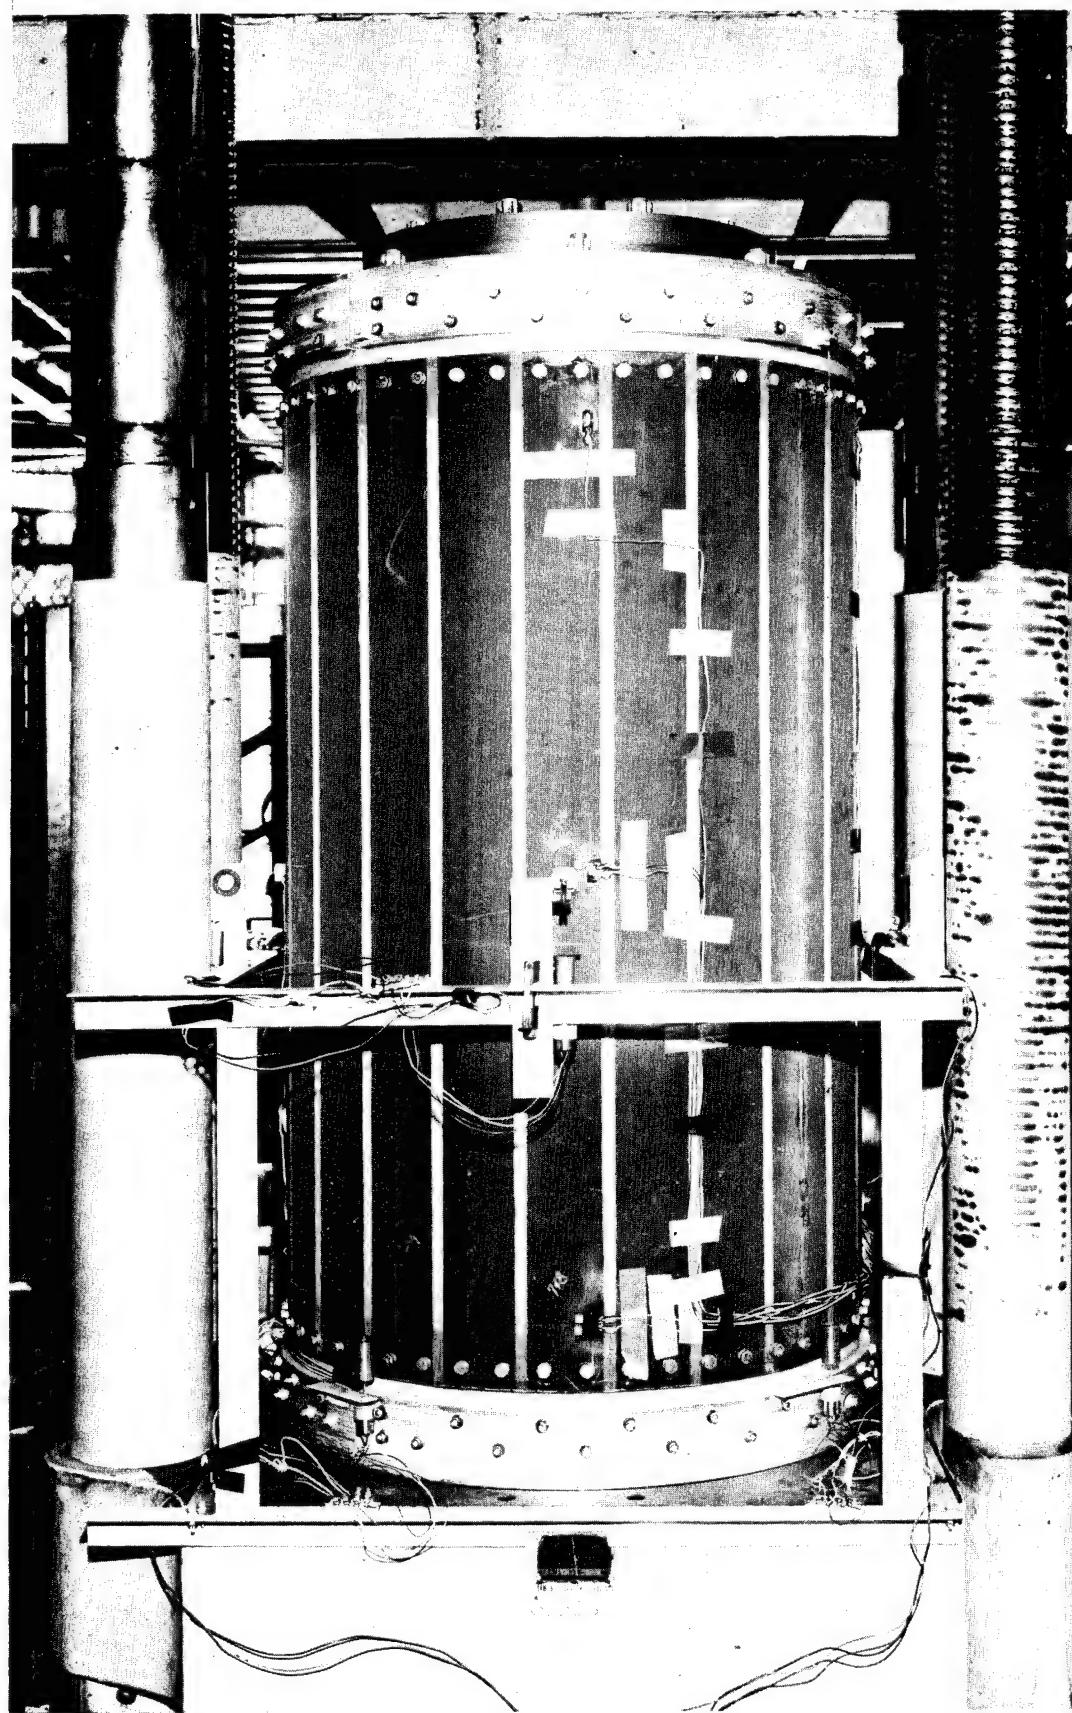
Figure 7-6. Cylinder Subcomponent Compression Test Setup
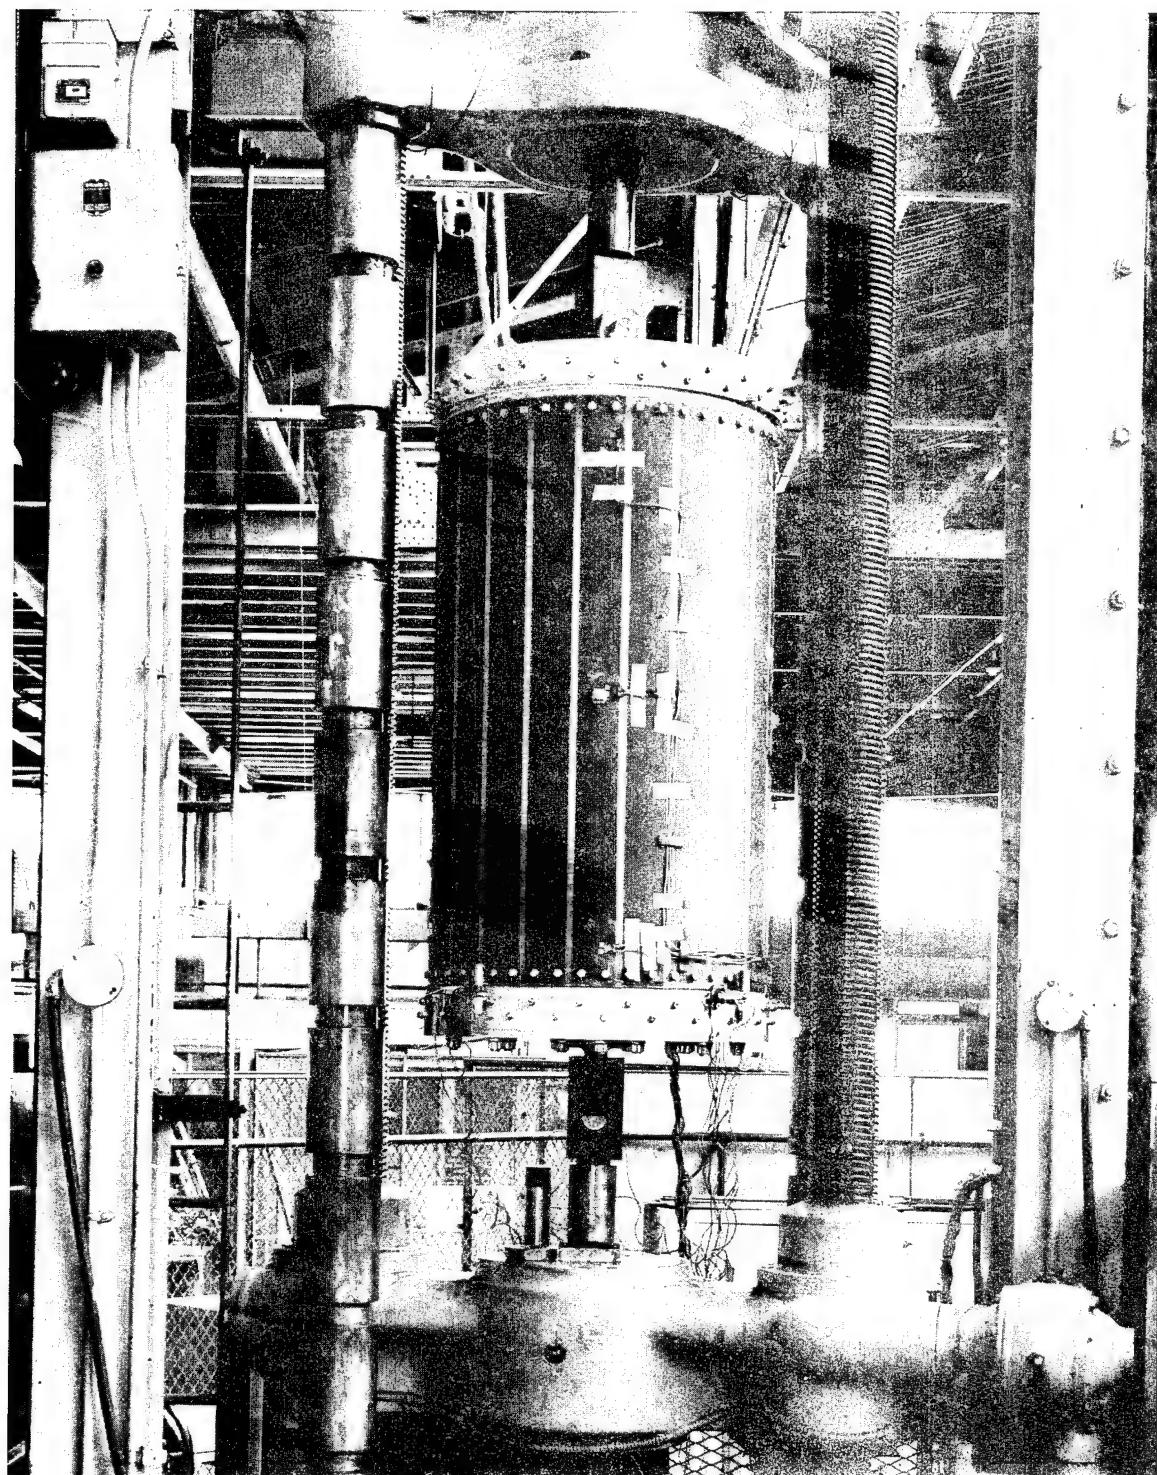
Figure 7-7. Cylinder Subcomponent Tension Test Setup
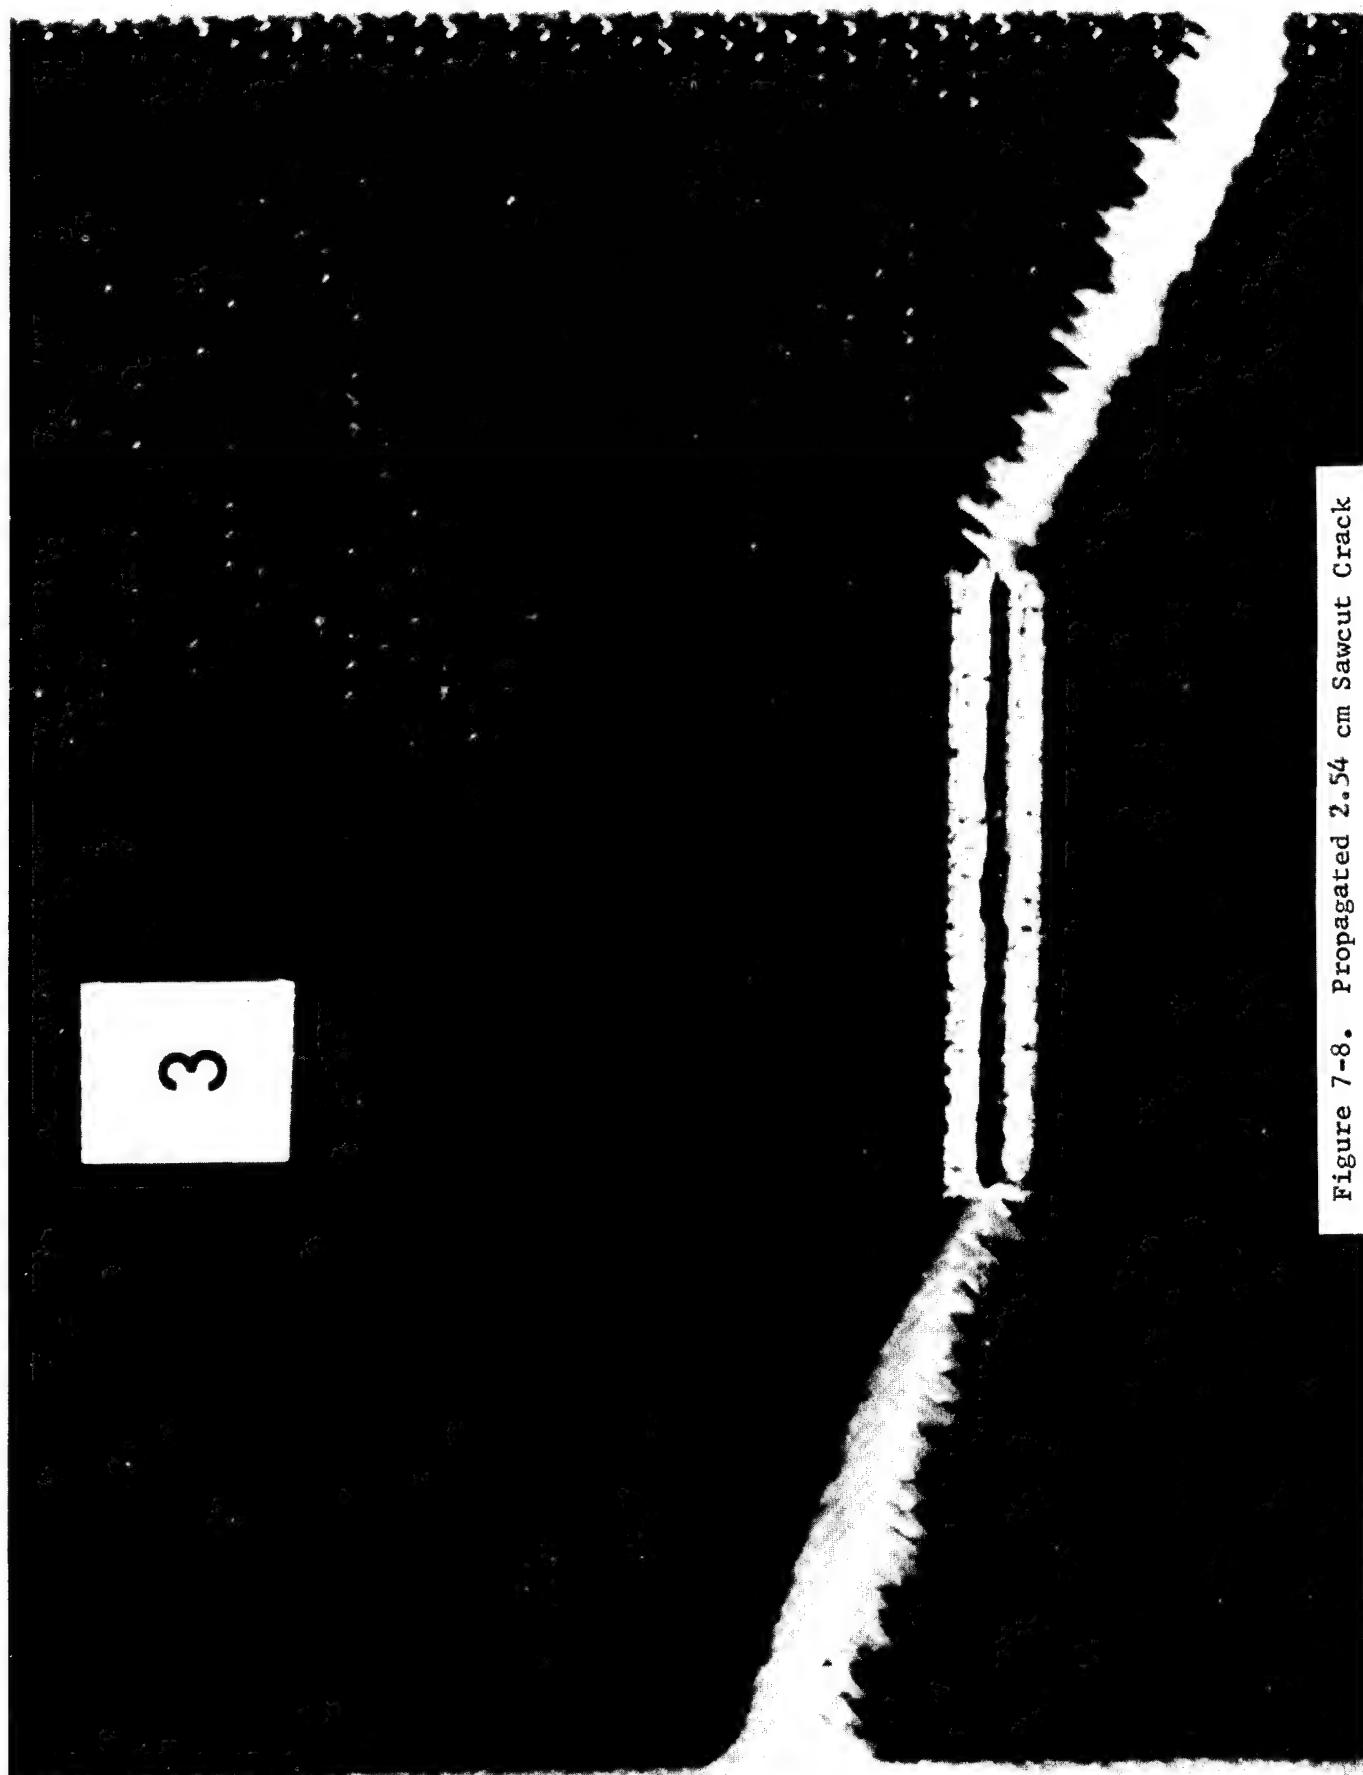
Figure 7-8. Propagated 2.54 cm Sawcut Crack

Tests 4 and 5 were different in two respects. First, the damage was induced ballistically, and secondly, the structure was under a preload when the damage was induced. In test 4, a .95 cm (3/8 in.) projectile was fired into the cylinder. The damage which was produced had a maximum overall dimension of 2.2 cm (7/8 in.). The preload was 50% DLL. At the time of impact the damage did not propagate, but, upon subsequent application of load, propagation occurred at 114% DLL, Figure 7-9. In test 5, a 2.54 cm (1 in.) projectile was fired with 75% DLL preload. Again, the damage did not propagate at time of impact and in this case no subsequent load was applied, Figure 7-10.

The last test was with a 1.59 cm (5/8 in.) sawcut crack. Propagation in this case was at 129% DLL, Figure 7-11. It should be pointed out that at this time, with 129% DLL on the cylinder, six of the twenty-two sections between crack arrester strips were cracked over their 7.62 cm (3 in.) width, so that even with considerable damage the structure still withstood a high level of loading.

Figure 7-12 shows the cylinder after the testing had been completed. The complete set of crack arrestment tests is summarized in Figure 7-13.

In Figure 7-14, both the stress corresponding to the beginning of propagation and the stress, when the crack reached the arrester strips, are shown and compared to a curve drawn from the equations using the hybrid composite fracture data discussed in reference 13. The data agrees reasonably well with the analysis, although it covers only a narrow range of crack sizes.

8.0   F U S E L A G E   T E S T I N G

8.1 INSTRUMENTATION

The three hybrid fuselage components were instrumented with a total of eleven axial strain gages and seven strain rosettes according to the layout diagram shown in Figures 8-1, 8-2 and 8-3. Gages internal and external to the fuselage center section are specified. Gage locations were selected to monitor regions of predicted high stress and areas which are buckling critical. Gage placements also checked load transfer in the closeout sections and load symmetry between the left and right fuselage center section panels.

8.2 TEST METHODS AND EQUIPMENT

The entire BQM-34E fuselage was tested in a self-contained test fixture erected from 30 cm (12 in.) wide - flange beams. Loading was accomplished at fuselage frame stations by means of continuous aluminum bonds supported on 2 cm (3/4 in.) thick elastomer compression pads, Figure 8-4a. Where obstacles such as the vertical stabilizer prevented use of continuous bands, aluminum straps were bonded to the fuselage with RTV-88 silicone rubber, Figure 8-4b. Separate wiffle tree arrangements, used to test each of the two load conditions, were attached to the fuselage frame loading points. Additional wiffles were used to load the wing in the 5g maneuver test. In both tests, loads were introduced into the structure through a single load point by means
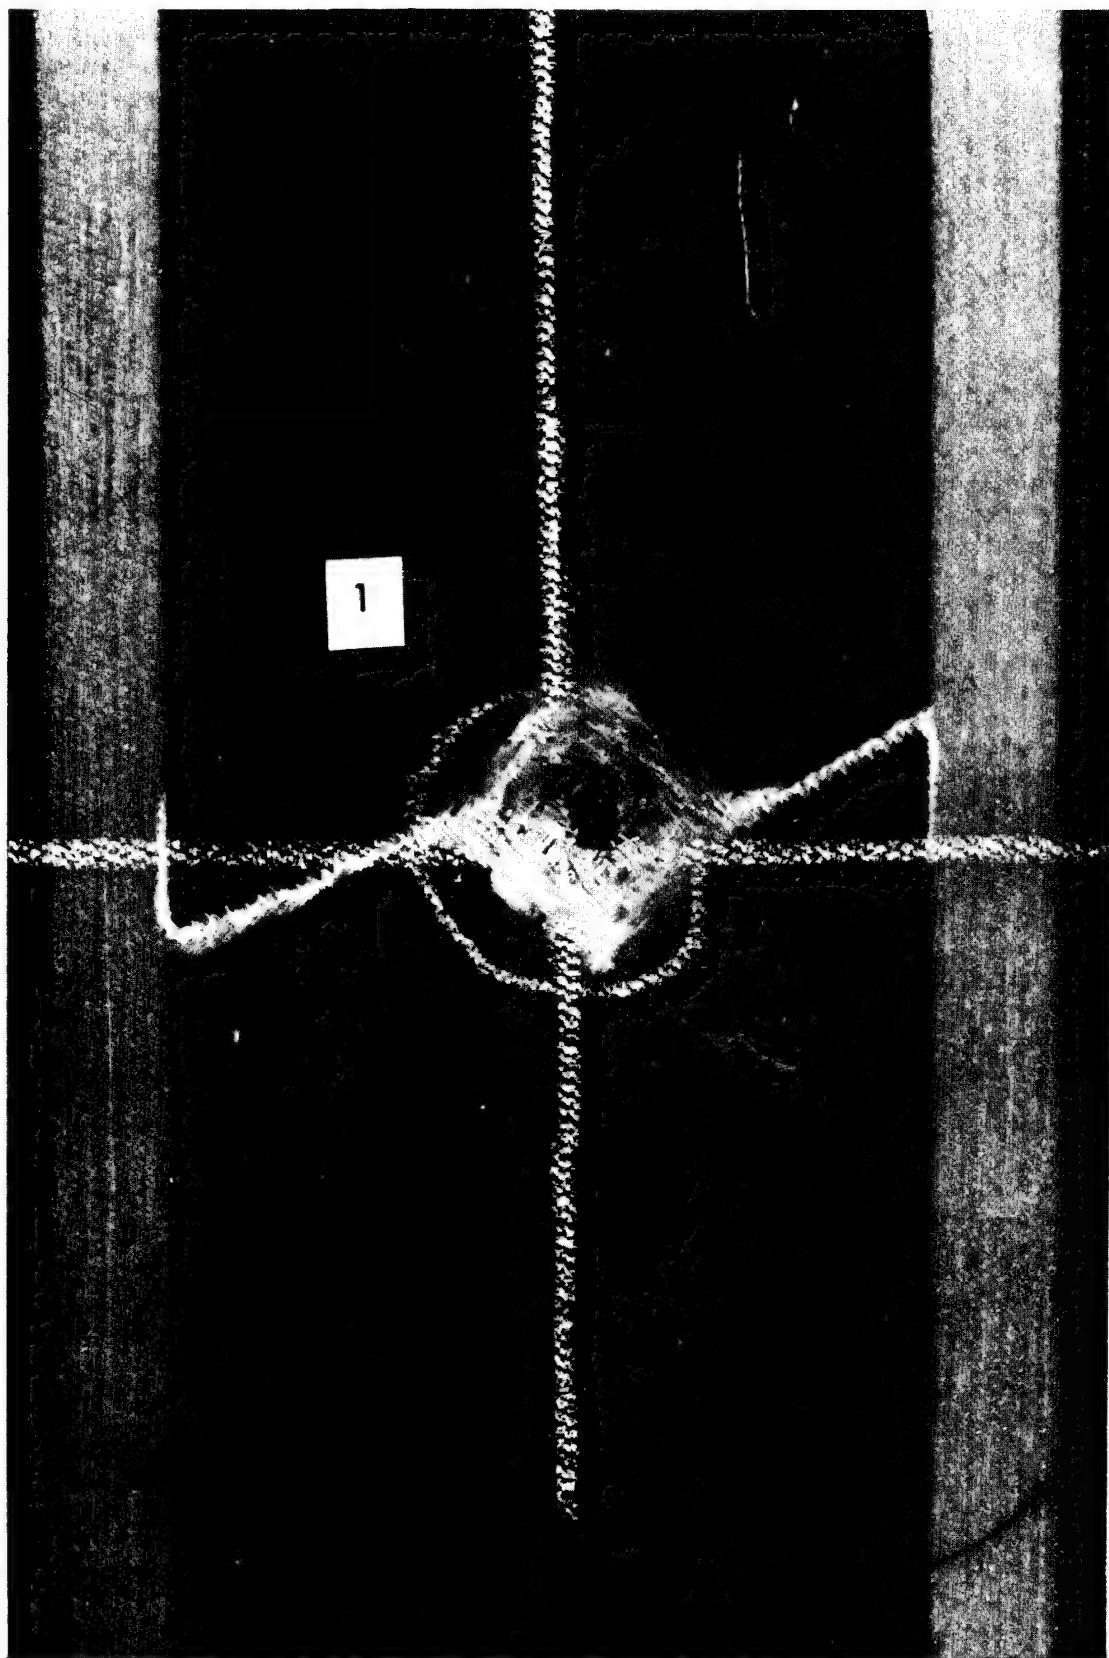
Figure 7-9. Crack Propagation from .95 cm Projectile Damage
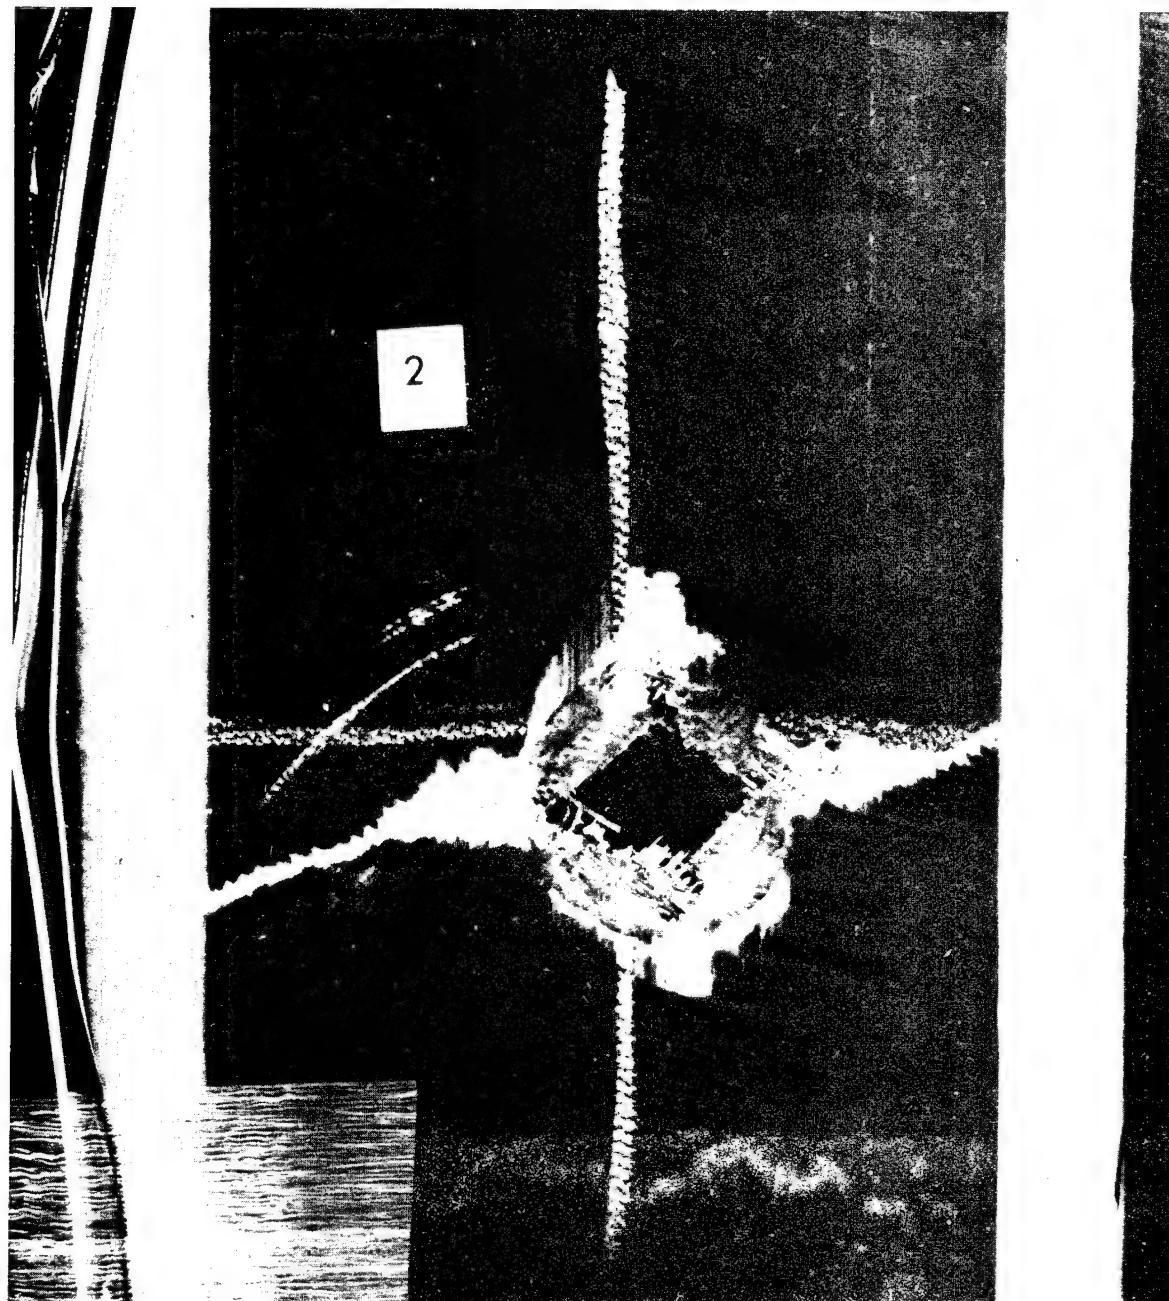
Figure 7-10. Crack Propagation from 2.54 cm Projectile Damage
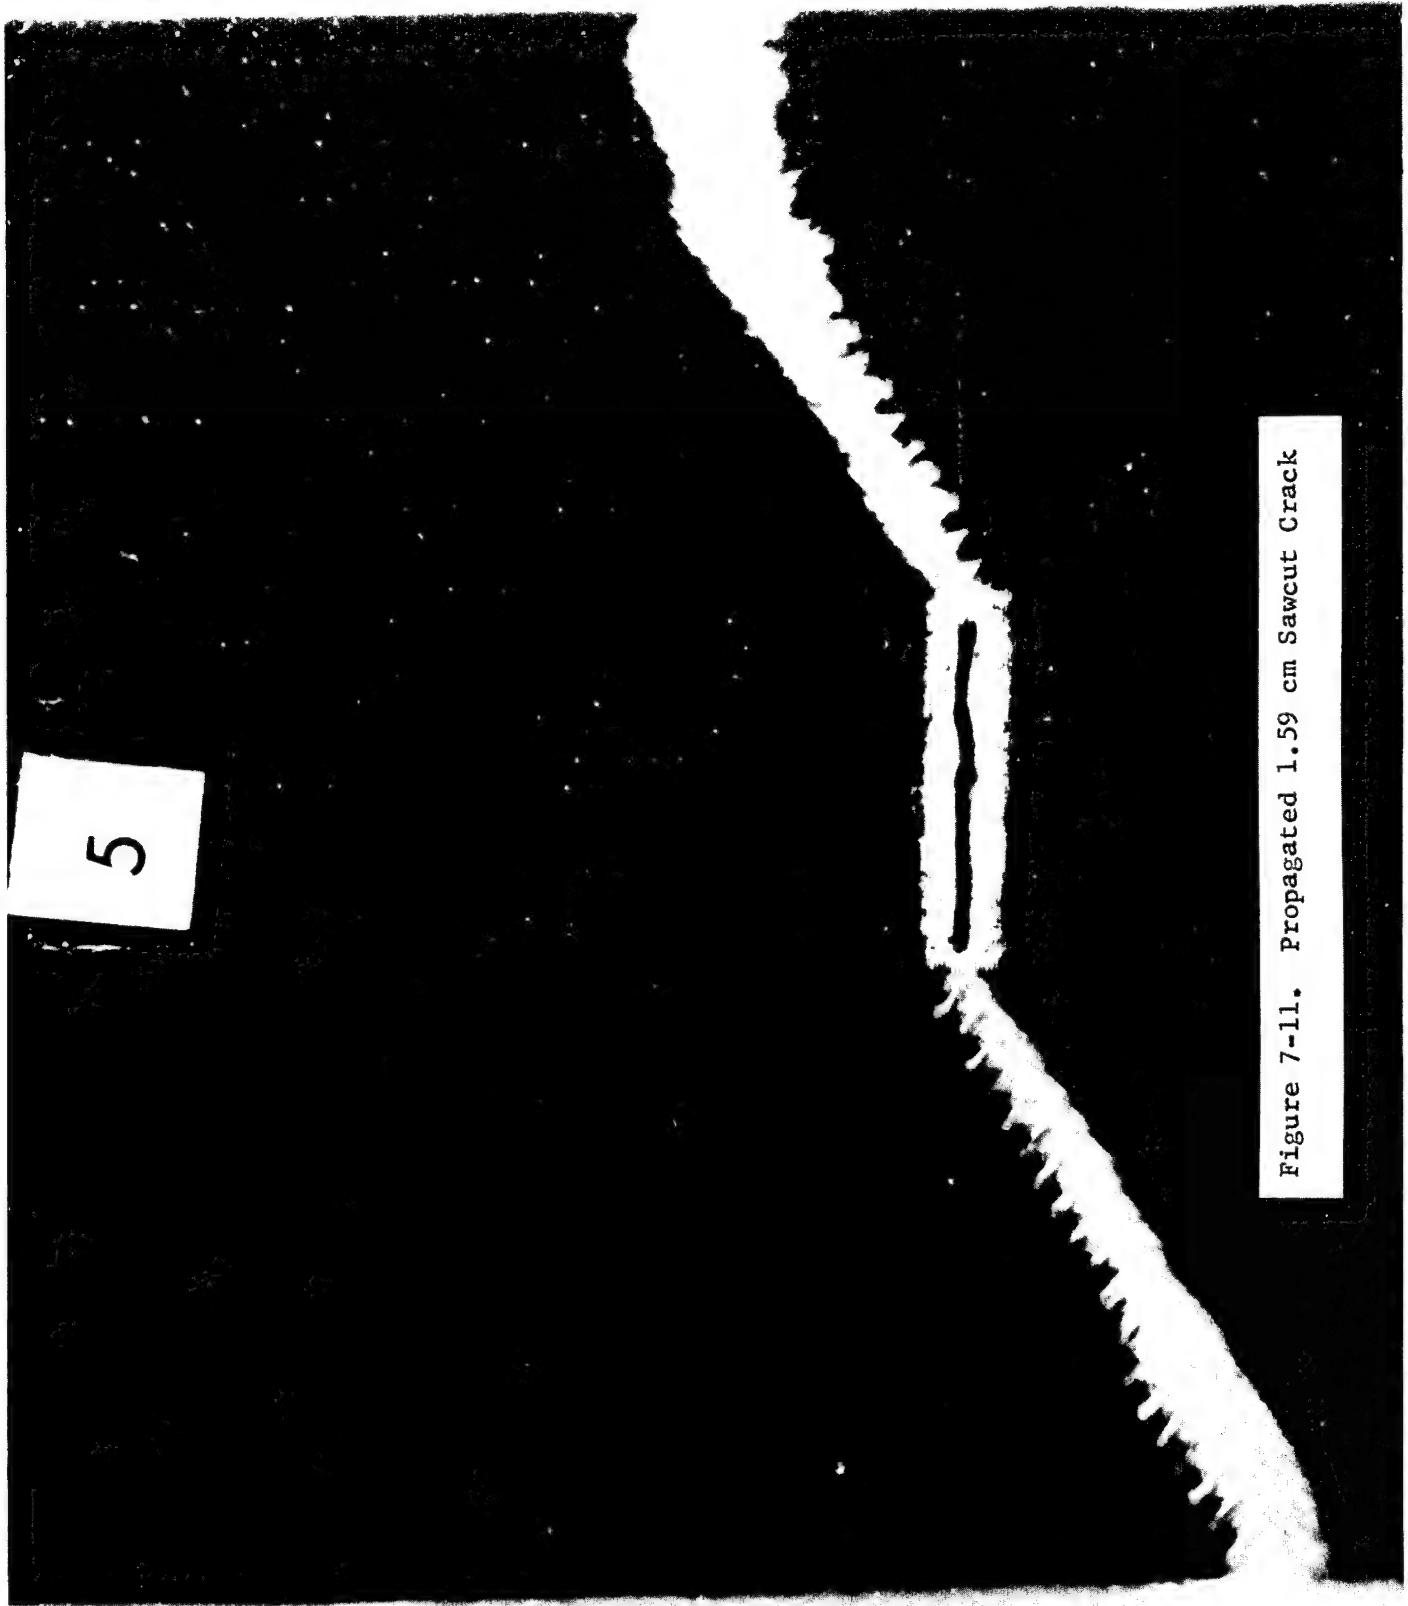
Figure 7-11. Propagated 1.59 cm Sawcut Crack
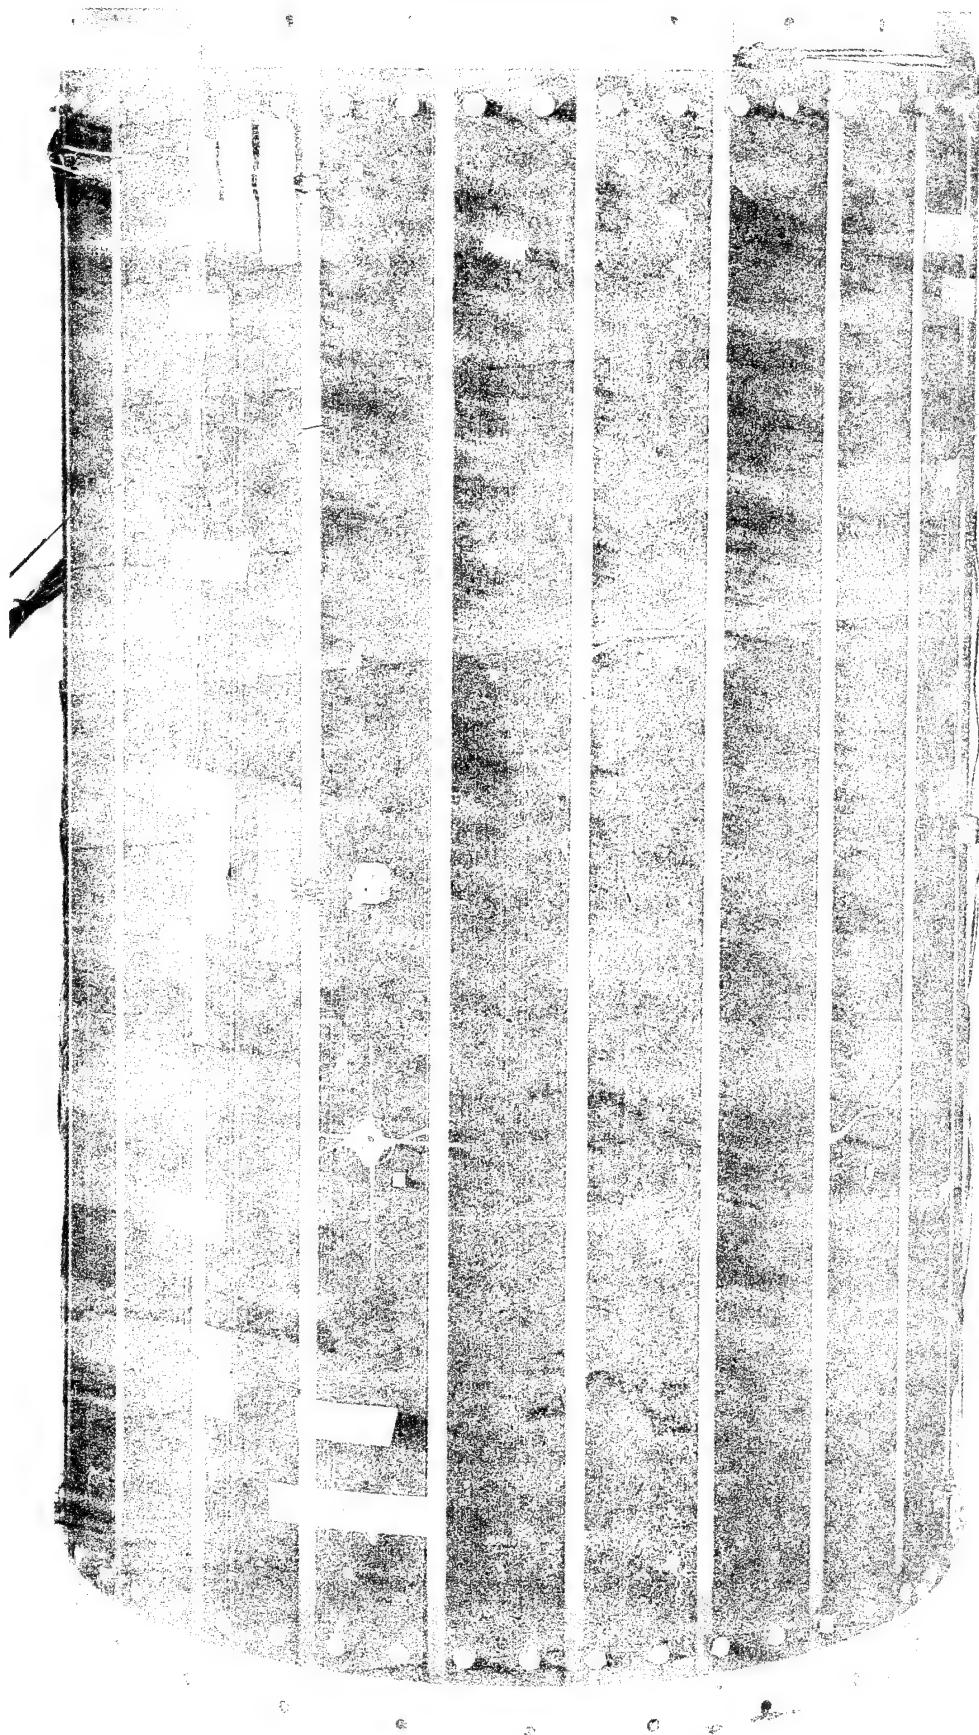
Figure 7-12. Cylinder After Testing
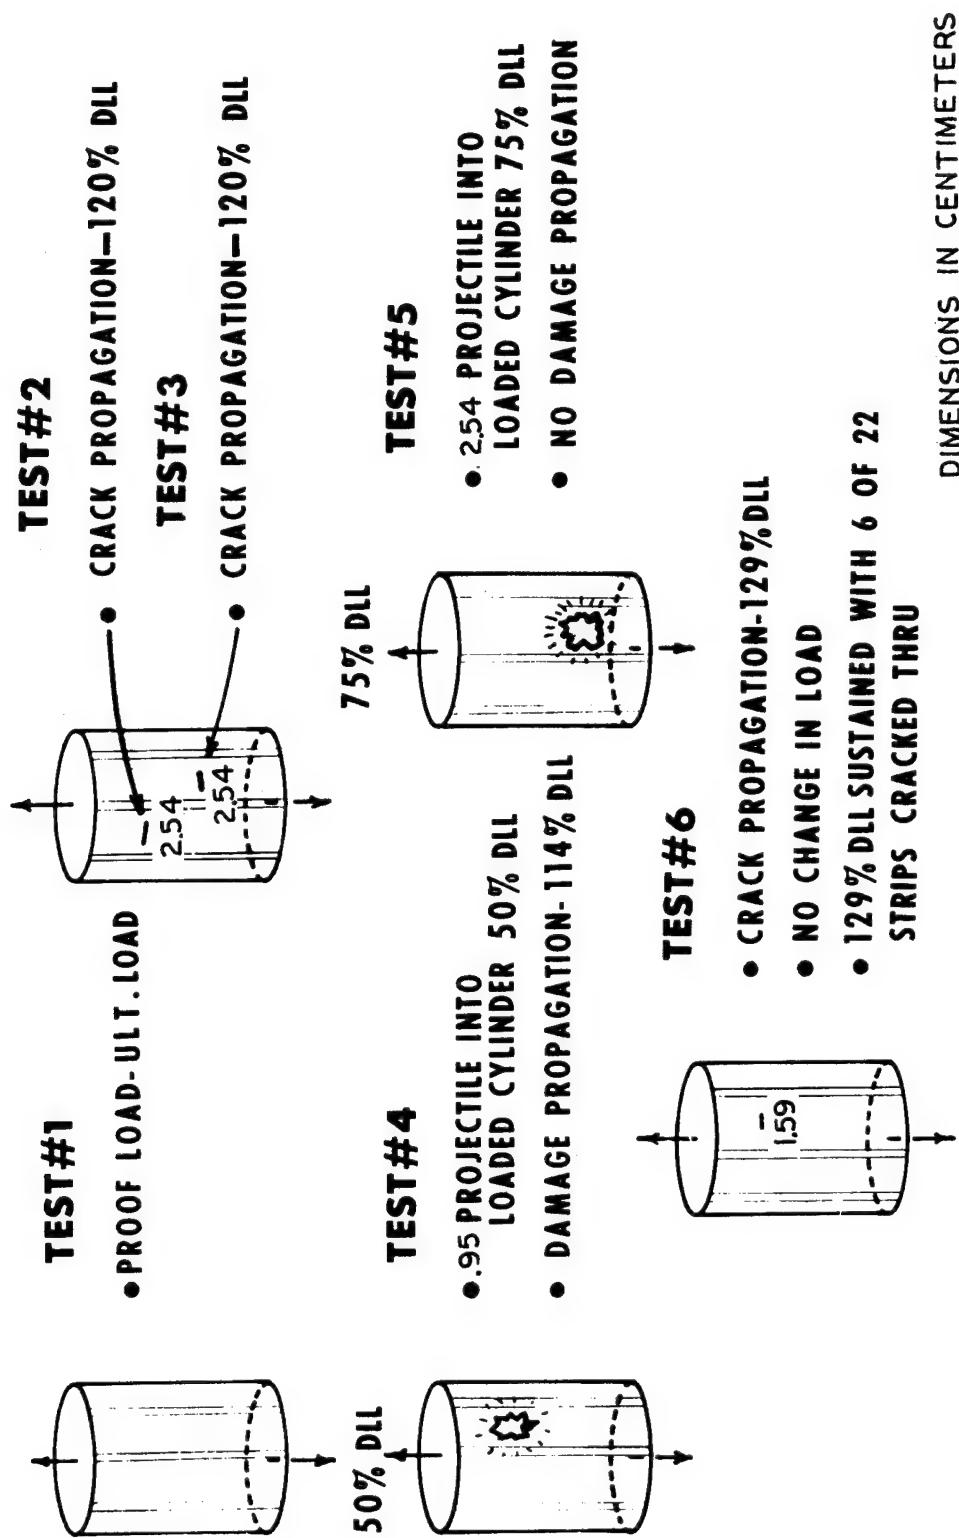
Figure 7-13. Summary of Crack Arrestment Tests
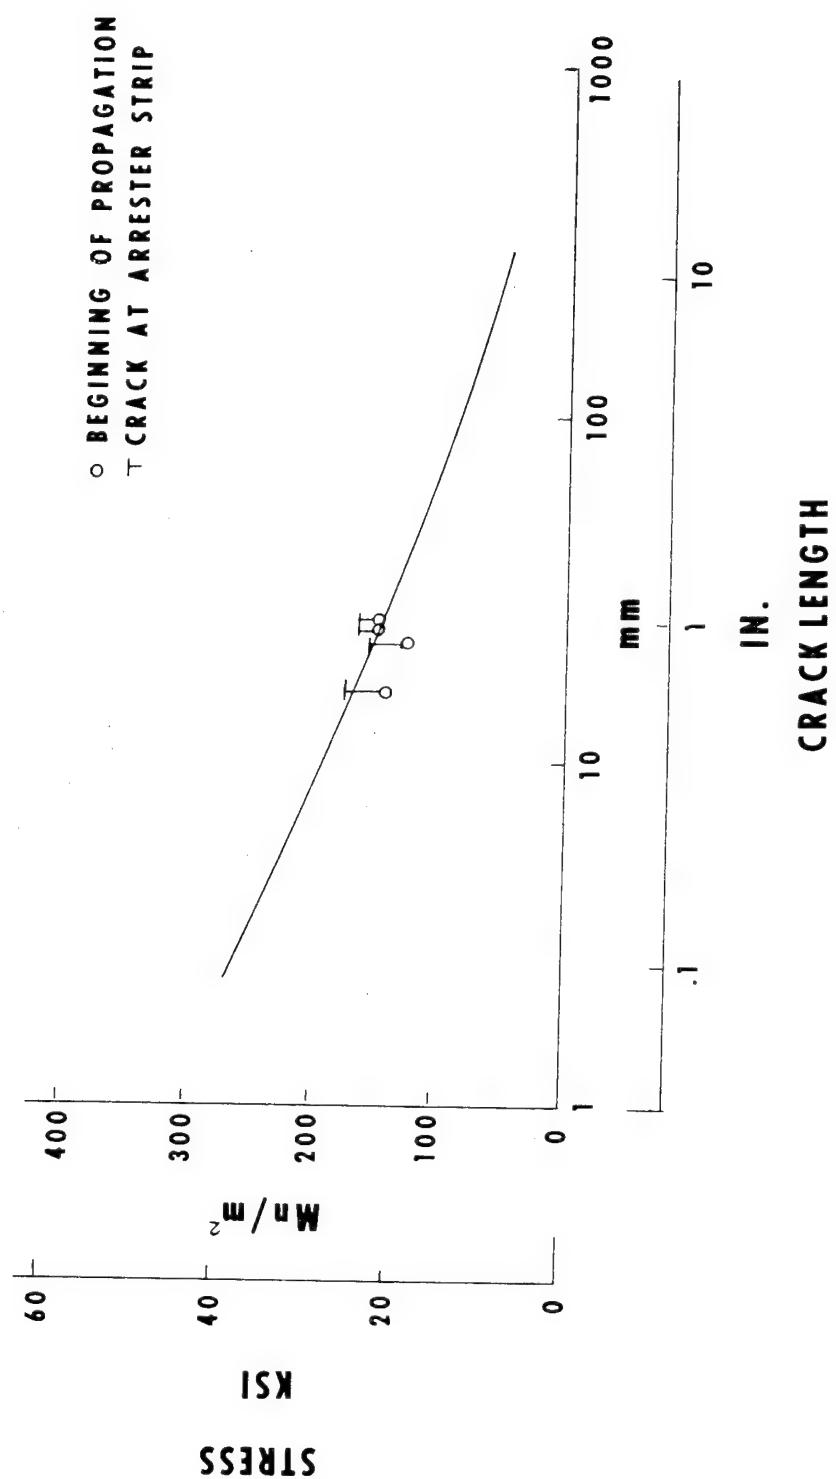
Figure 7-14. Hybrid Cylinder Crack Propagation Comparison to Theory

Gages 2,4,6,8,10,12,14,16,18,20,22,24,26,27,28 -- Internal

Gages 1,3,5,7,9,11,13,15,17,19,21,23,25 -- External
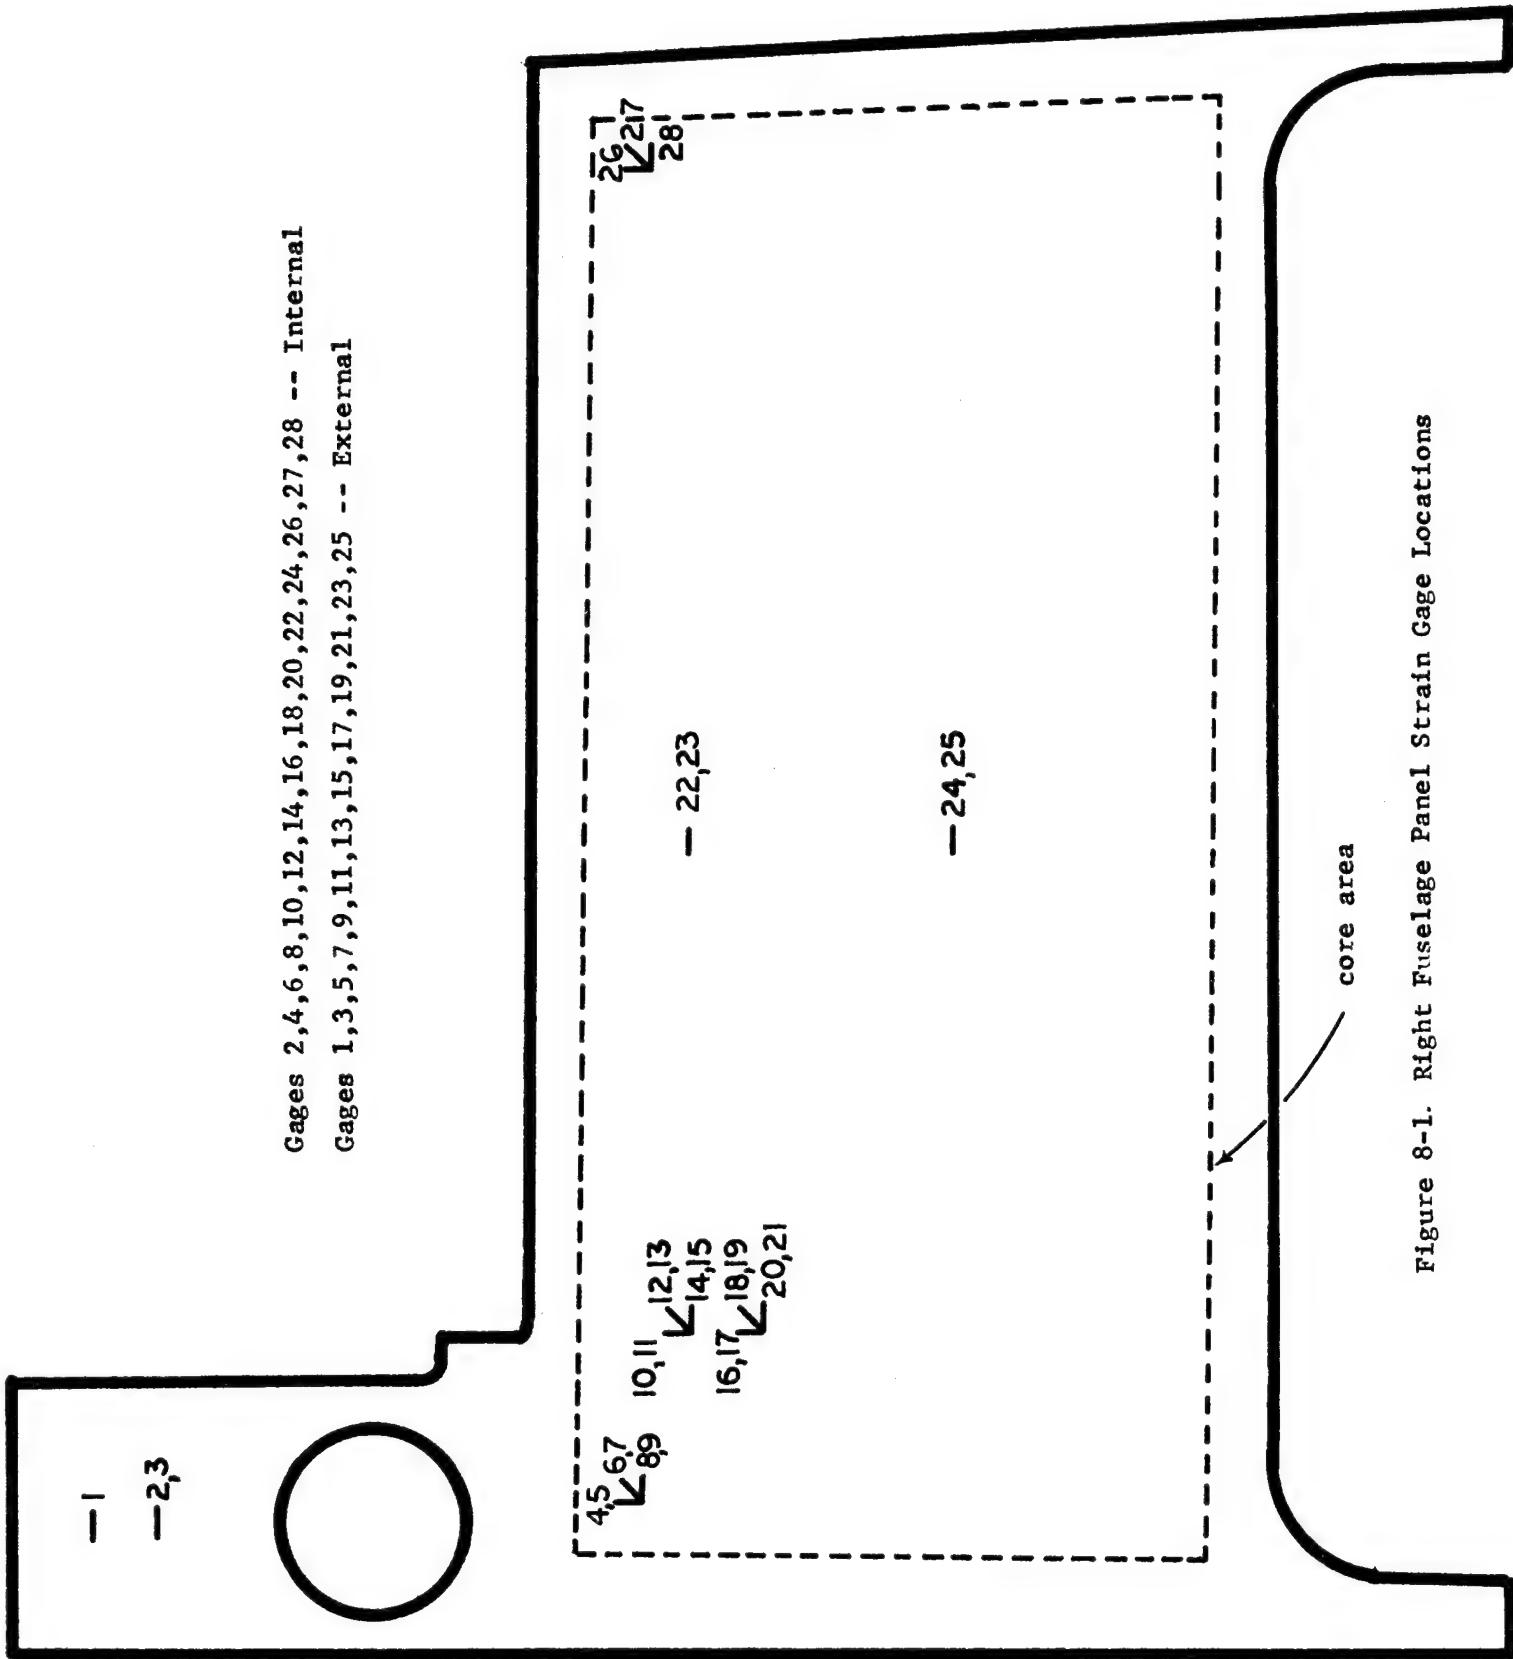
Figure 8-1. Right Fuselage Panel Strain Gage Locations

Gage 29 - External

Gage 30 - Internal

—29,30

core area
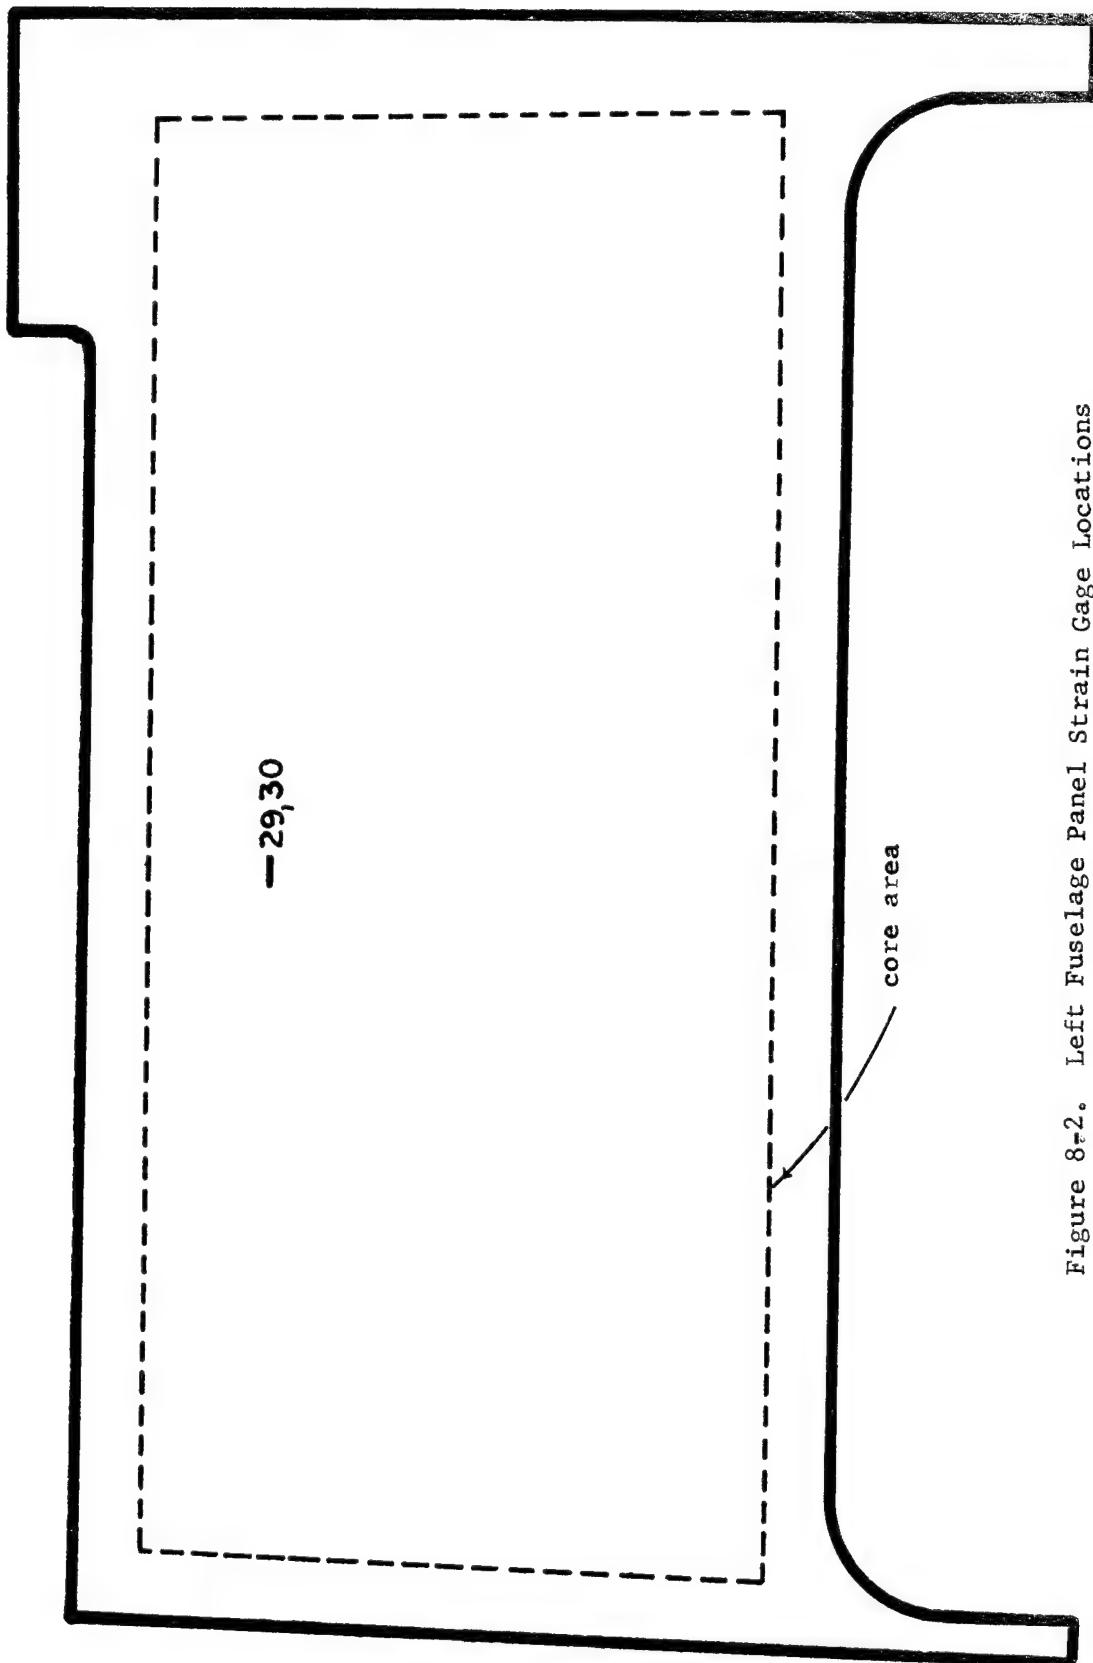
Figure 8-2. Left Fuselage Panel Strain Gage Locations

Gage 31 - External

Gage 32 - Internal
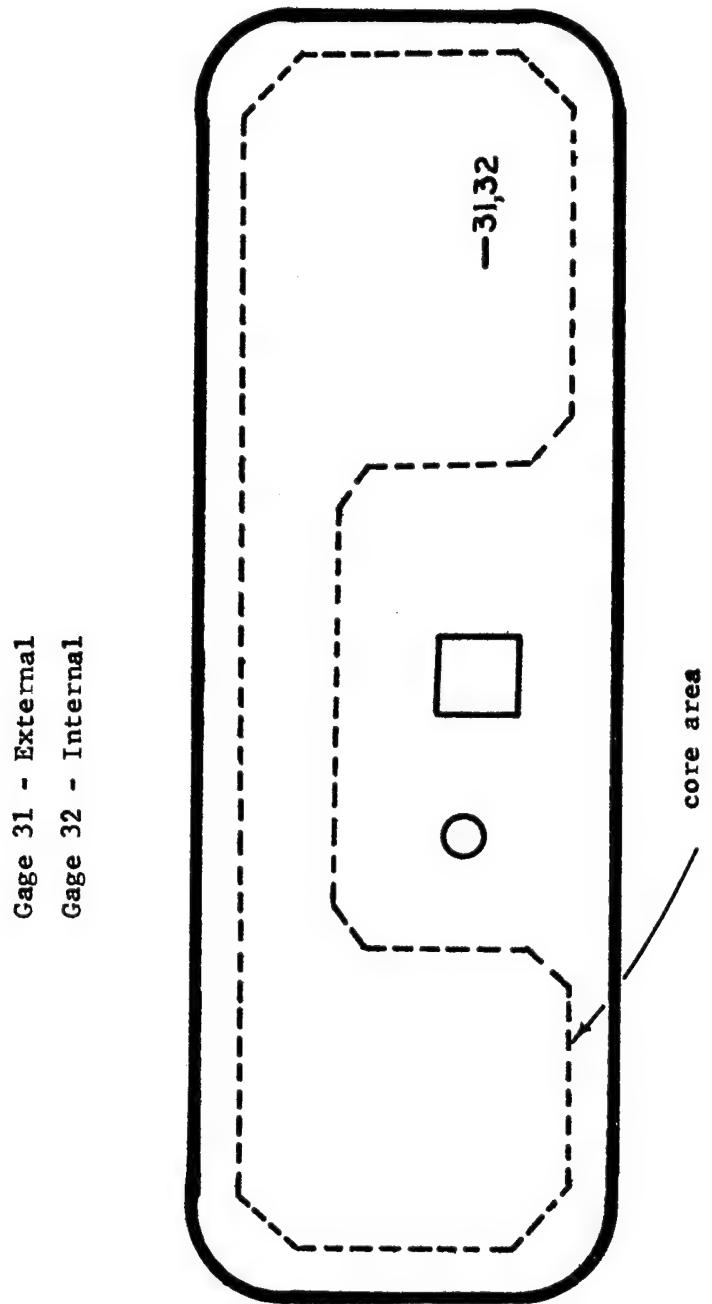
Figure 8-3. Access Door Strain Gage Locations

.16 cm Al band

2 cm elastimer pad

Typical
Fuselage
Frame

Al. channel

.64 cm steel angle

Pull Point
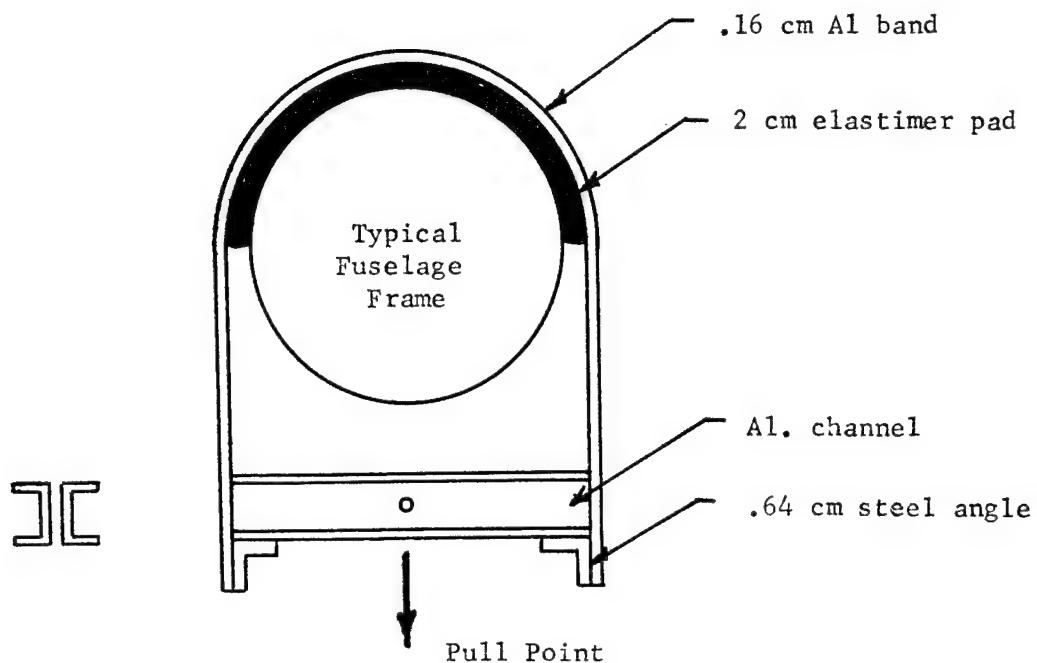
Figure 8-4a. Aluminum Band Loading Station

.16 cm Al Strap

.3 cm RTV-88
Silicone Rubber

Typical
Fuselage
Frame

Pull Point
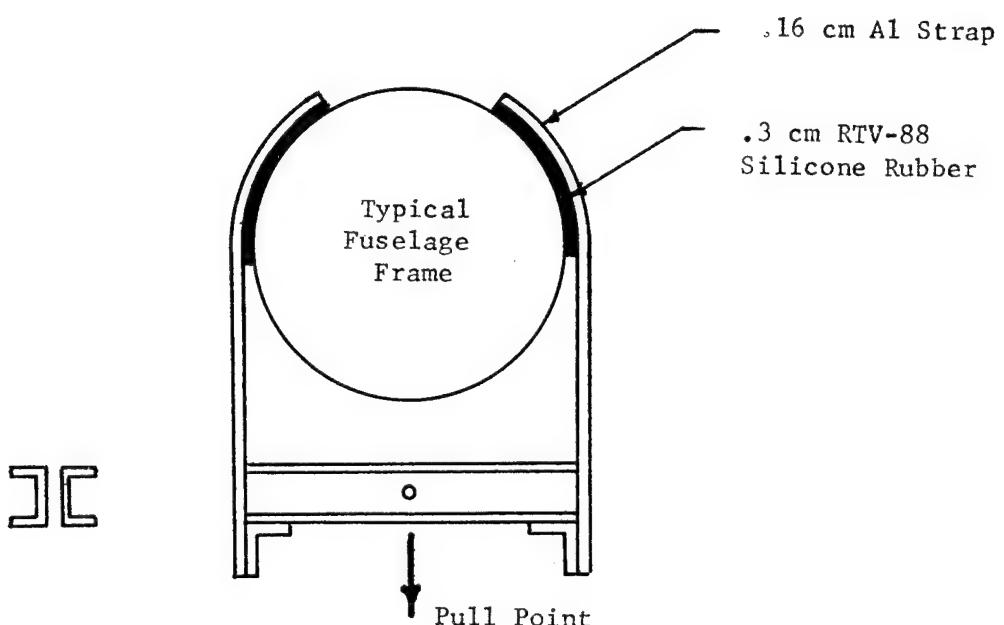
Figure 8-4b. Aluminum Strap Loading Station

of a manually operated hydraulic jack. Figures 8-5 and 8-6 are photographs of the test setup.

8.3 TEST LOAD CONDITIONS AND LOADING SEQUENCE

Two critical flight load conditions were ground tested to demonstrate the overall structural adequacy of the hybrid fuselage design. The two ground tests included a main recovery chute deployment load test and a simulated 5g maneuver loads test, discussed in "Design Conditions".

The loading sequence for both ground tests were identical and the procedure is listed below.

    a. Apply 30% Limit Load

       o Checkout Instrumentation and Test Set-Up

    b. Apply 50% Limit Load 10 Times

       o Extrapolate Strain Data to Limit Load and Compare for First and Last Cycle Data with Analytical Data.

    c. Apply Limit Load

       o Record Strain Data

       o Evaluate Strain

    d. Apply Limit Load 5 Times

       o Record Data

Actual fuselage station applied loads are listed in Tables 8-1 and 8-2, for the recovery loads test and the 5g maneuver loads test, respectively. Loading stations are illustrated in Figure 8-7. Fuselage station shear diagrams for both load conditions are shown in Figures 8-8 and 8-9. Moment diagrams are also included in Figures 8-10 and 8-11. Limit loads developed on the fuselage center section for both conditions are shown in Figures 8-12 and 8-13.

8.4 FUSELAGE TESTING, RECOVERY LOADS

The hybrid fuselage was initially set up for the main recovery chute deployment load test. The loading sequence followed during this test was previously described.

Testing of the recovery load condition ran smoothly through steps (a) and (b) of the test procedure, the gages behaving linearly to the applied loads. Step (c) in the test procedure to limit load was next applied to the fuselage. At 80% DLL the onset of nonlinear strain behavior was observed in most of the forward gages, the most significant nonlinear strain response being observed by gages 4, 5, 6, 7, 10 (refer to Figures 8-1 and 8-2). A second cycle to
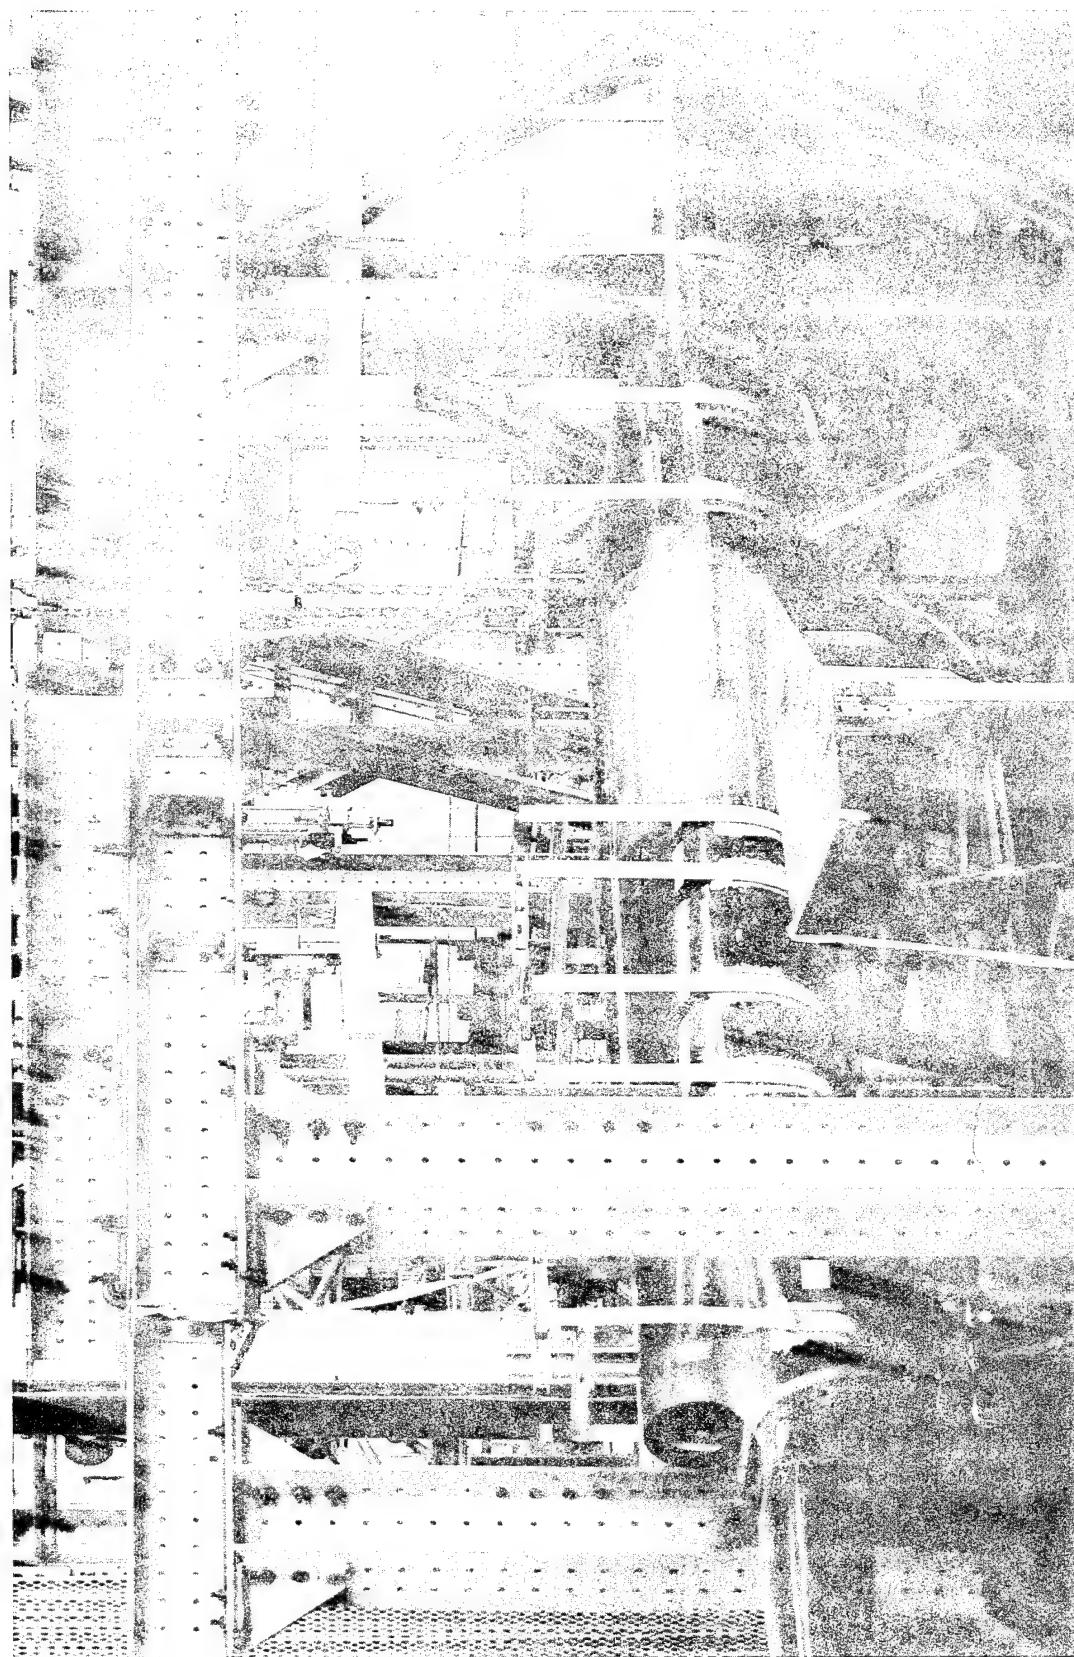
Figure 8-5. Recovery Load Test Setup
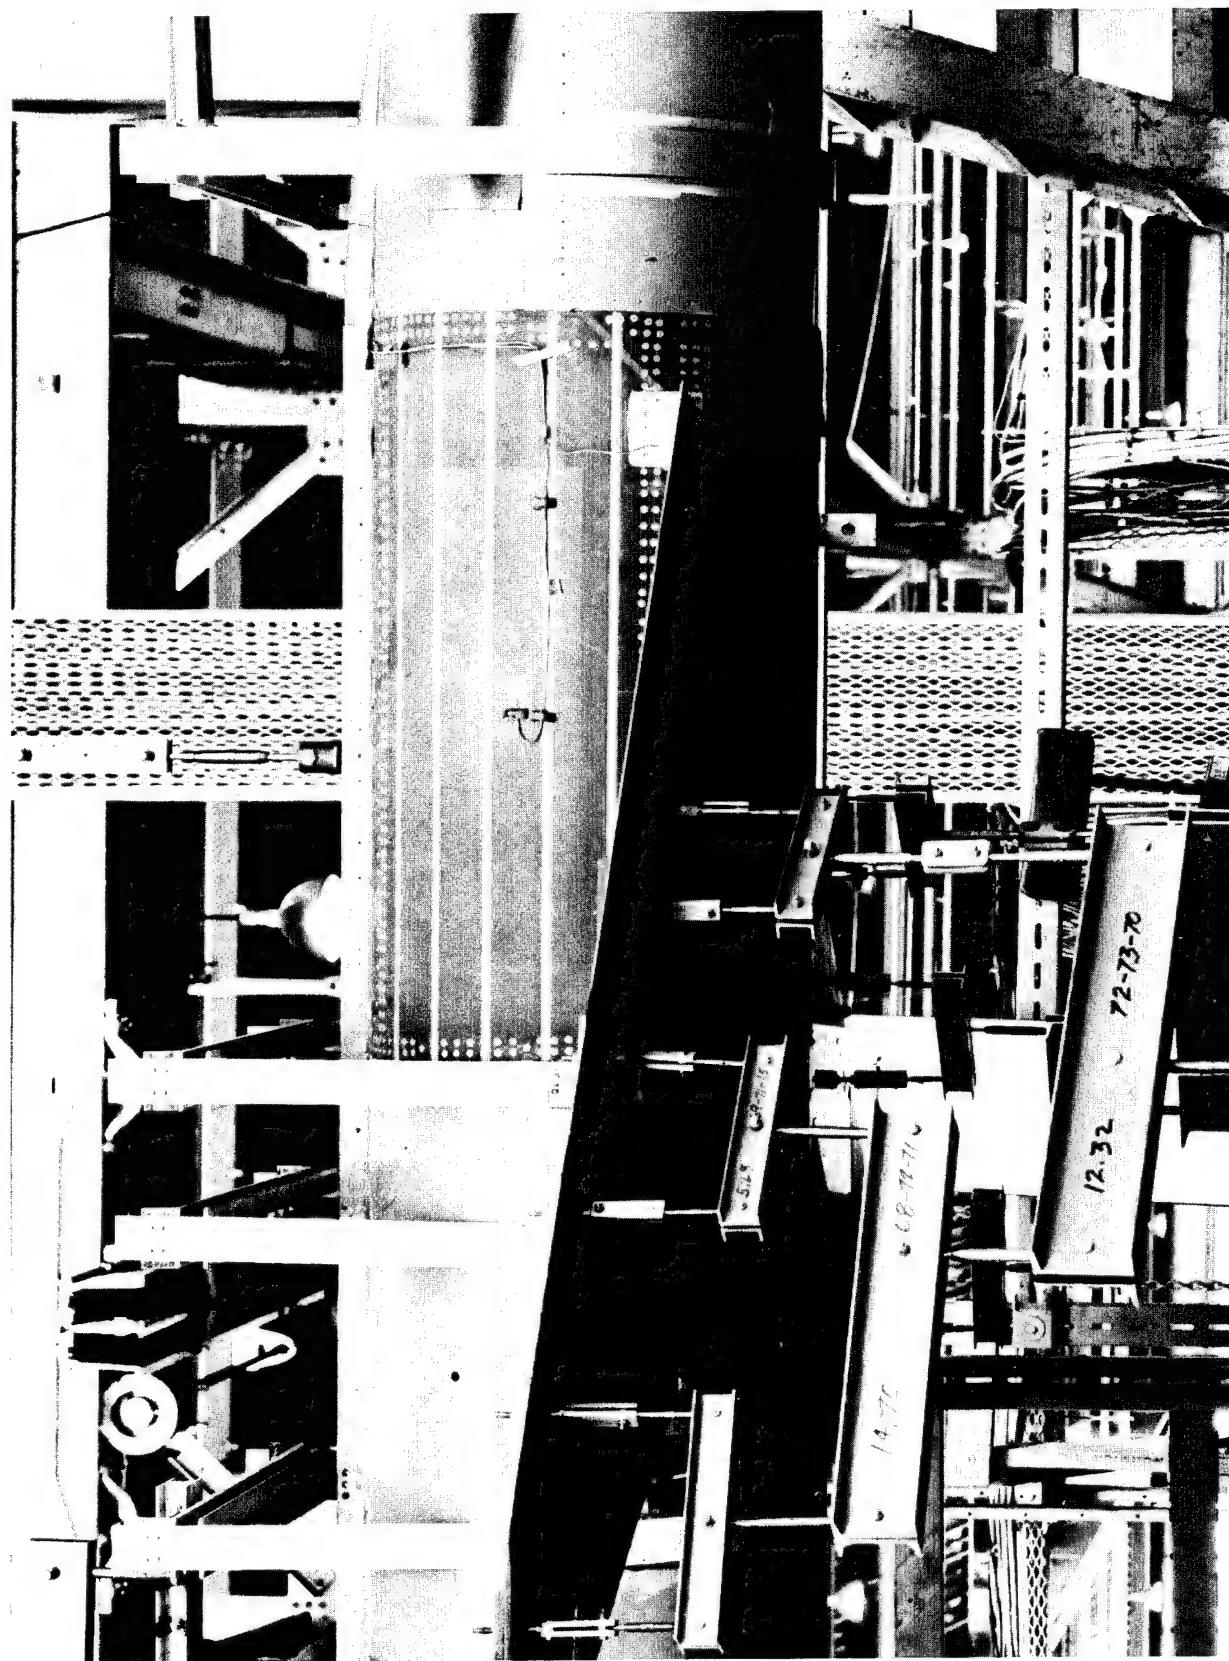
Figure 8-6. 5g Maneuver Load Test Setup

TABLE 8-1

APPLIED LOADS - RECOVERY CONDITION

FUSELAGE STATION	APPLIED LOAD	
	N	LBS
118.50	-2558	-575
134.30	-2224	-500
166.30	-6672	-1500
182.50	-3670	-825
209.00	-5462	-1228
224.80	-2175	-489
245.00	51155	11500
274.10	-6615	-1487
285.20	-4875	-1096
301.90	-6228	-1400
315.20	-6672	-1500
325.00	-2669	-600
350.00	-1334	-300

TABLE 8-2

APPLIED LOADS - 5G MANEUVER CONDITION

FUSELAGE STATION	APPLIED LOAD	
	$\underline{N}$	$\underline{LBS}$
166.30	-2891	-650
182.50	-2891	-650
209.00	-2211	-497
224.80	- 903	-203
258.34	-13122	-2950
Wing Loading	39189	8810
301.90	-3550	-798
315.20	-1610	-362
325.00	-2669	-600
350.00	-9341	-2100

350.00

325.00

315.20

301.90

285.20

274.10

258.34

245.00

224.80

209.00

182.50

166.30

134.30

118.50
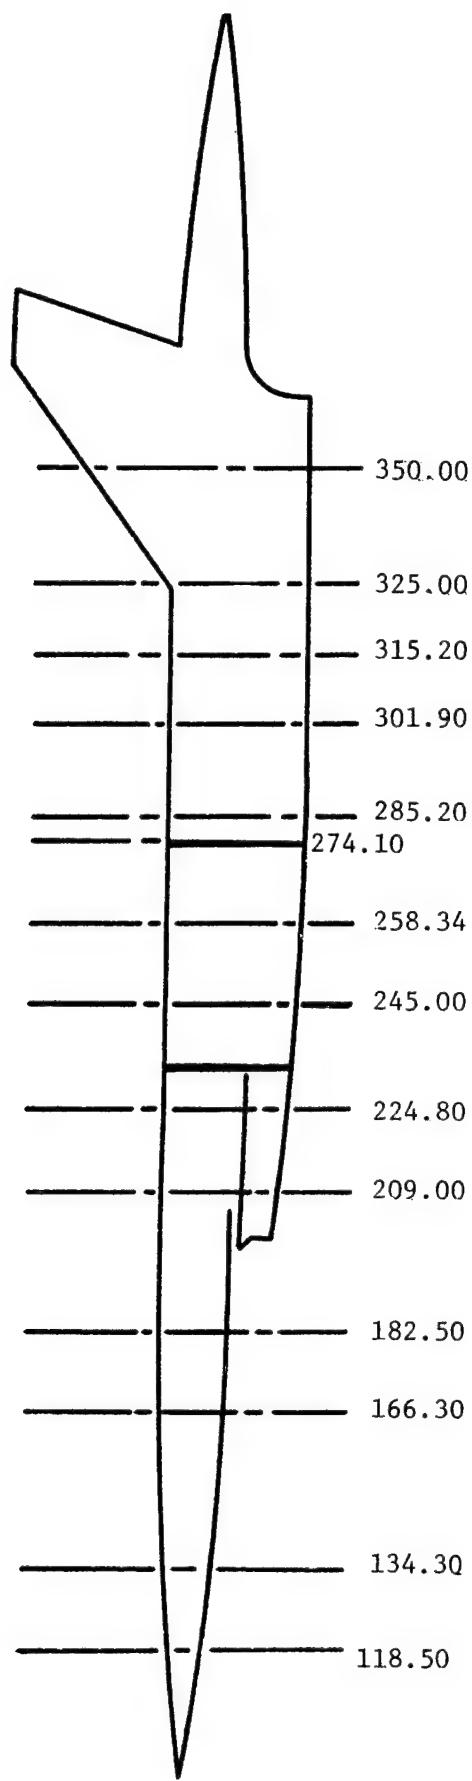
Figure 8-7. Frame Loading Stations
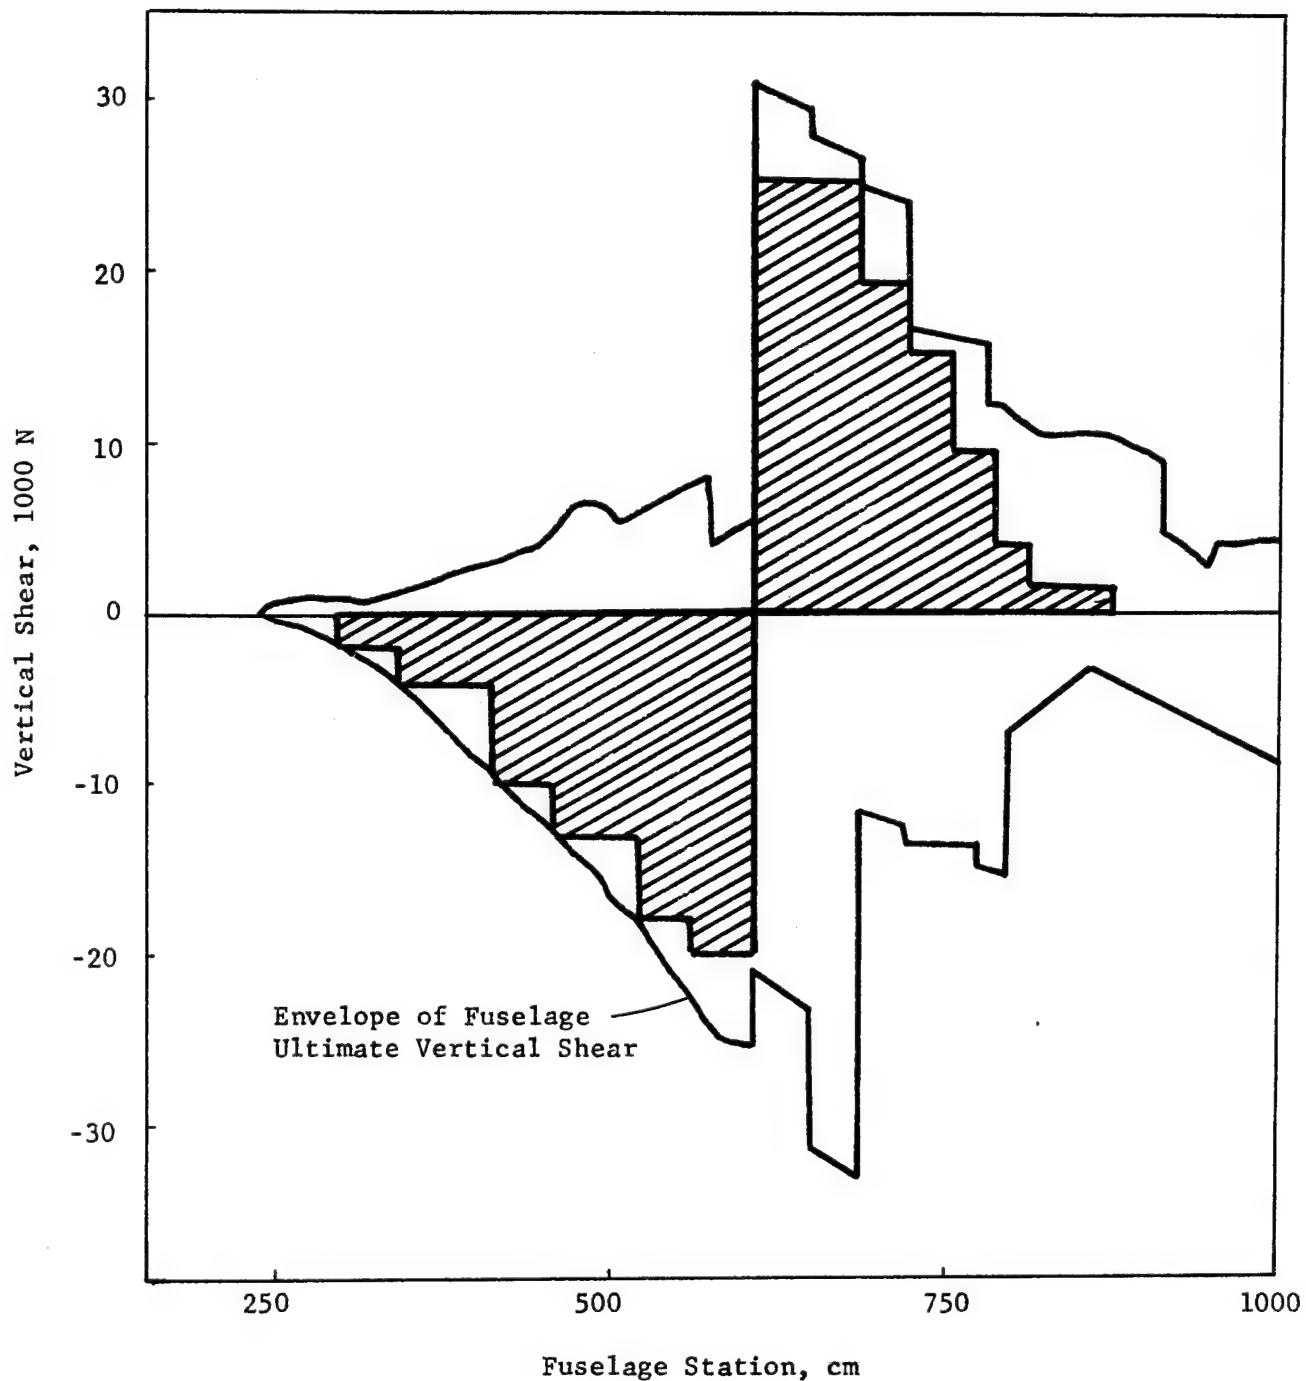
Figure 8-8. Fuselage Shear Diagram - Simulated Recovery Loads
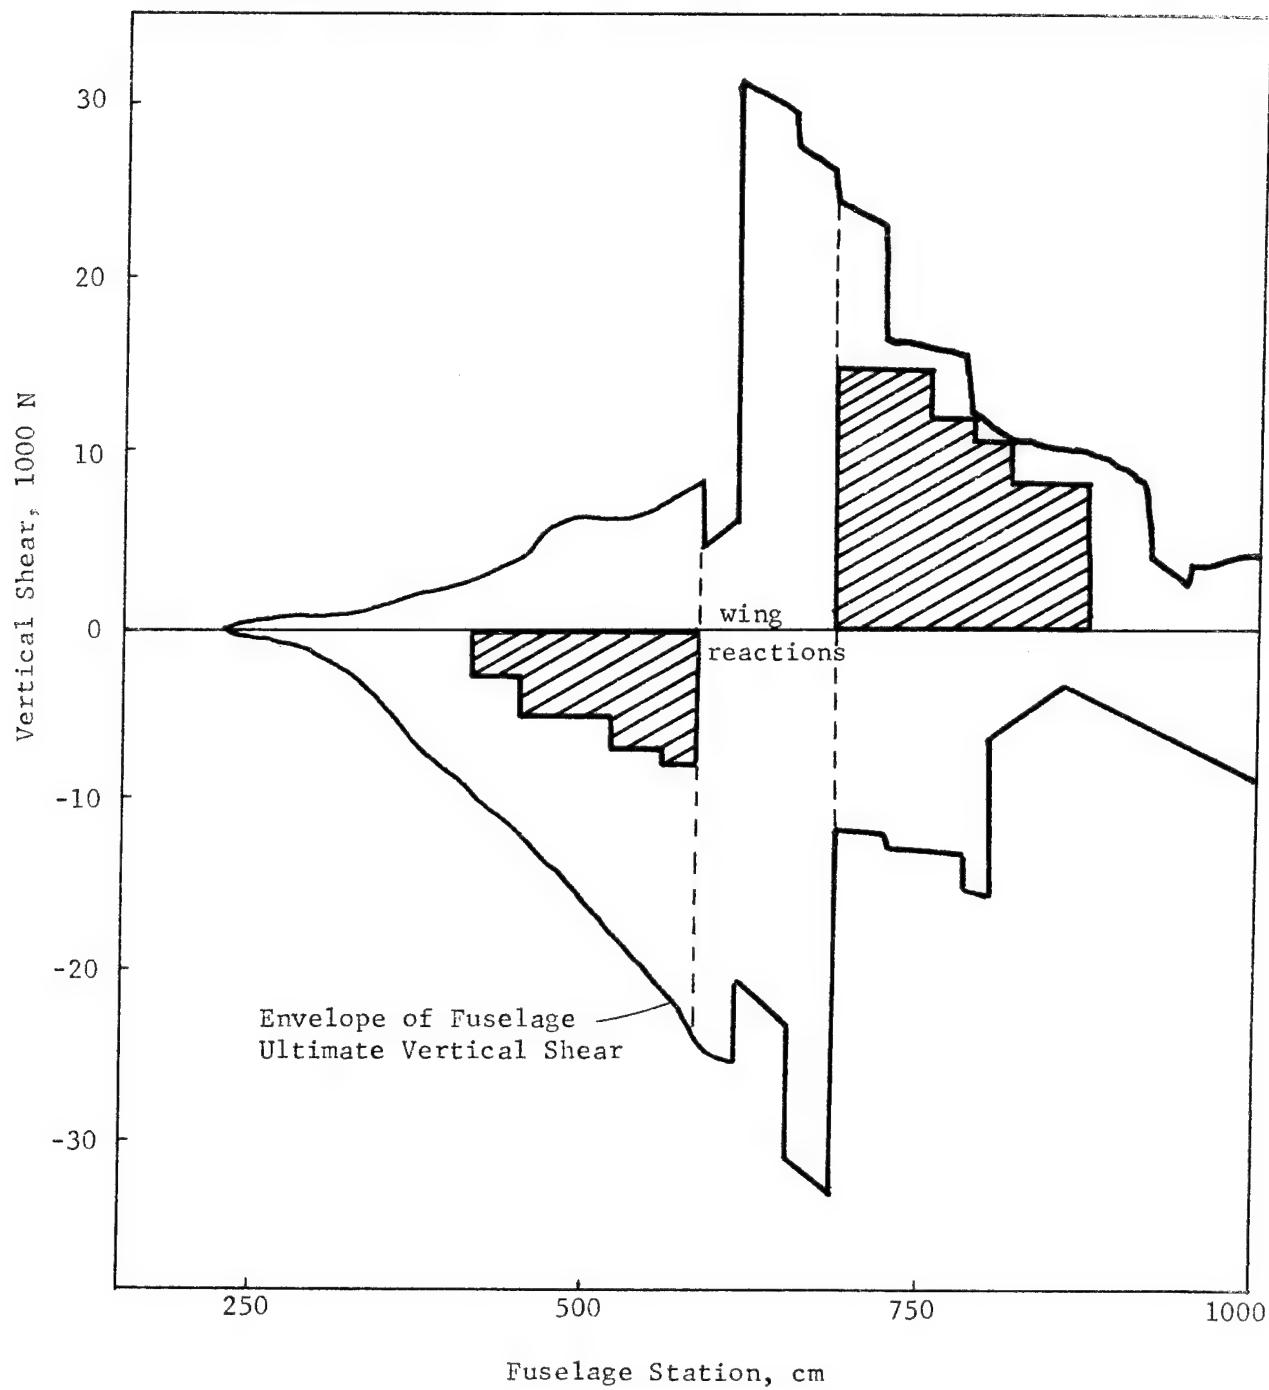
Figure 8-9. Fuselage Shear Diagram - Simulated 5g Maneuver Loads
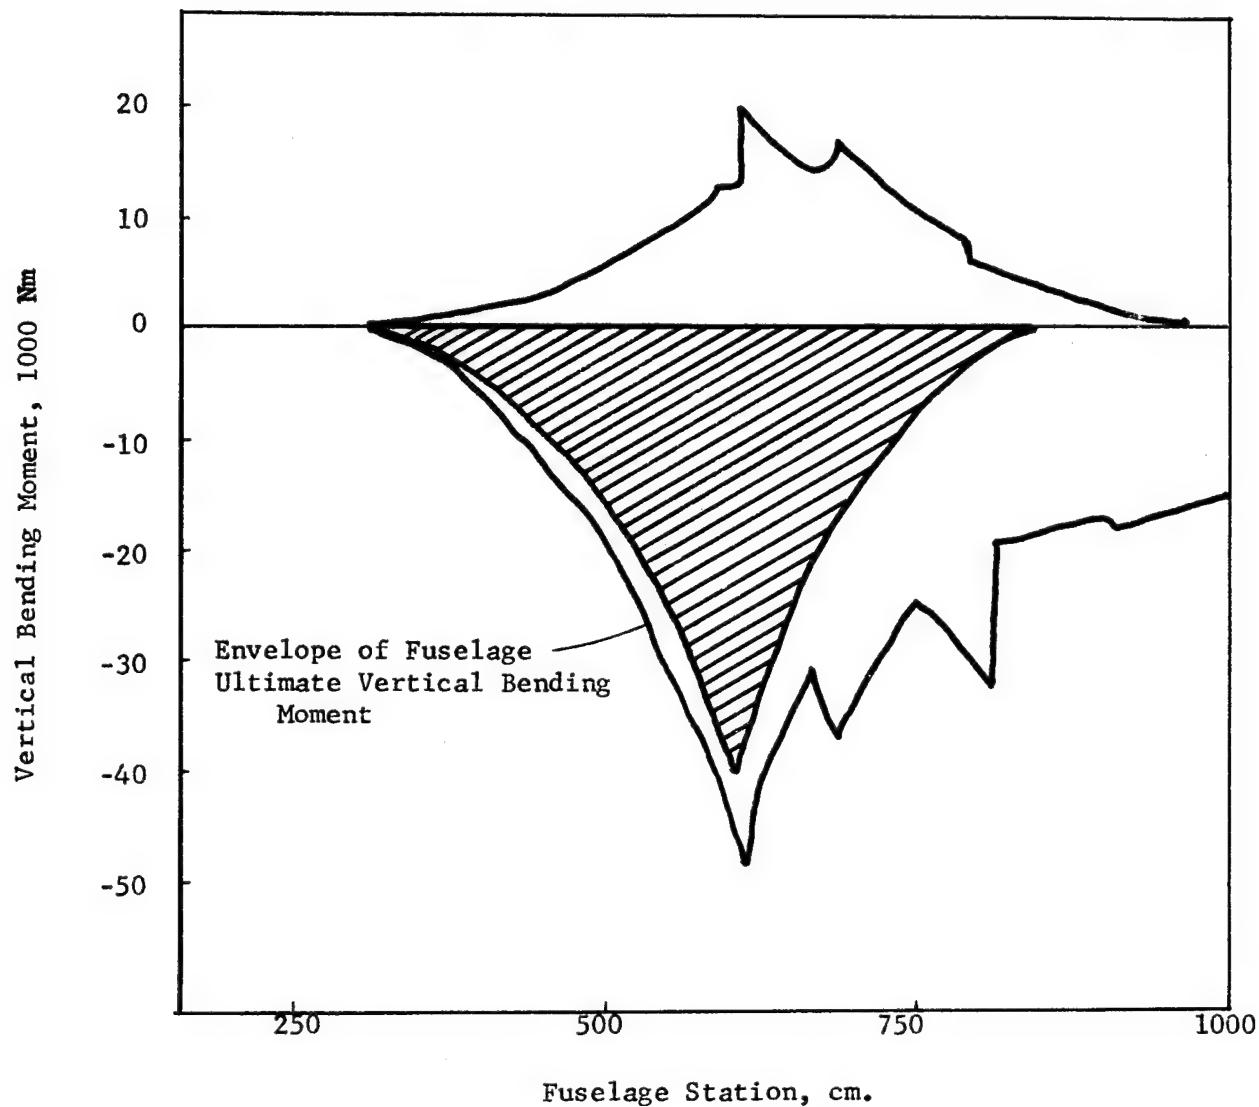
Figure 8-10. Fuselage Moment Diagram - Simulated Recovery Loads
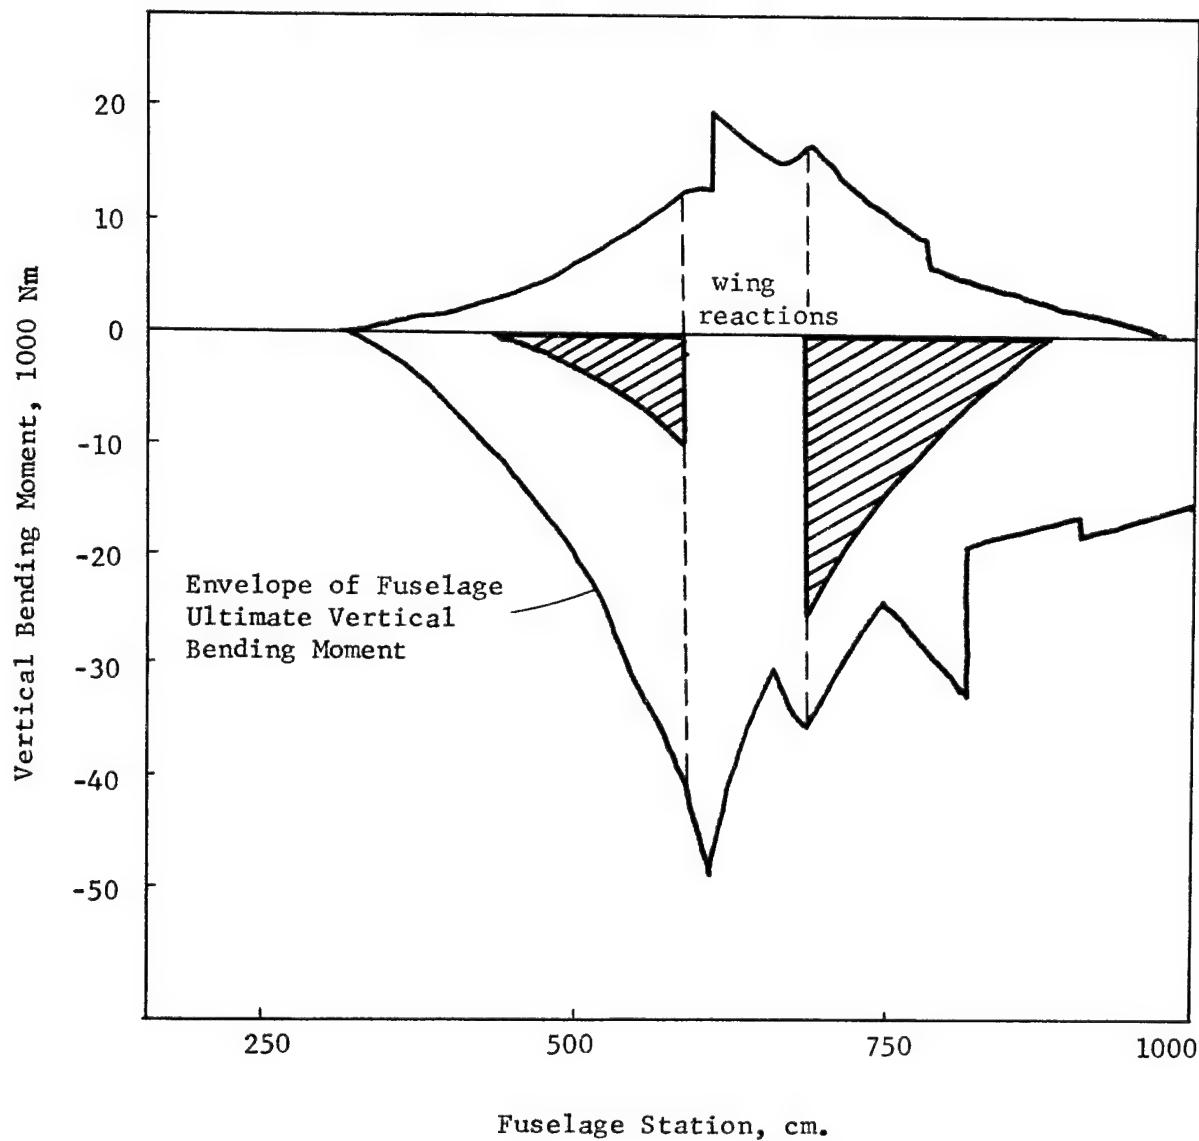
Figure 8-11. Fuselage Moment Diagram - Simulated 5g Maneuver Loads
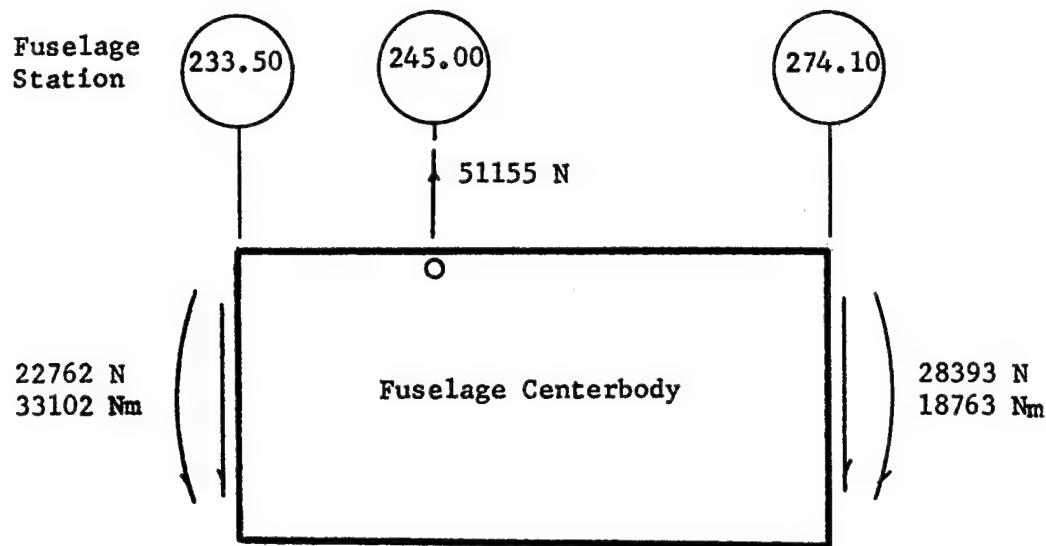
Figure 8-12.   Simulated Recovery Loads
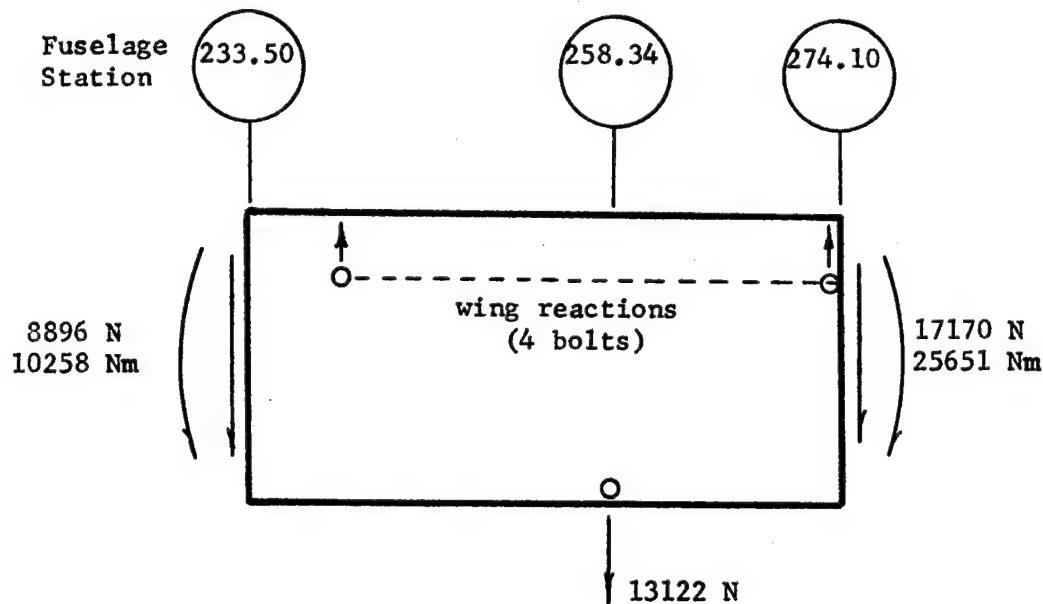
Figure 8-13.   Simulated 5g Maneuver Loads

limit load was applied with the same nonlinear strain behavior initiating at 80% DLL. Typical strain data showing the nonlinear behavior is shown in Figures 8-14 and 8-15.

After applying 50% DLL of the third DLL cycle, it was decided to terminate the testing and examine the fuselage for possible damage. Inspection revealed that cracks of approximately 7.62 cm (3 in.) in length had propagated on both left and right fuselage panels, from the 90° corner where the solid laminate area extends above the forward wing attachment bolt hole, see Figures 8-16 and 8-17. The cracks which run parallel to the Gr/Ep longitudinal fibers are shown in detailed photographs by Figures 8-18 and 8-19.

8.5 FUSELAGE FAILURE ANALYSIS AND REPAIRS

After an examination of the crack and a review of the substructure drawings, the cause of the failure was readily determined. The parachute load which goes into the partial bulkhead at station 241 must be transferred into the fuselage skin, or outer shell. In the metal design, this is done by frame at station 241. However, in the composite version, this frame was removed along with the other intermediate frames, and this forced the load to take a path through the composite material in the circumferential direction for a short distance. Since no fibers run in this direction in the composite fuselage design, the induced stresses were excessive and cracking resulted.

The course of action to prevent this would most likely have been to leave part of the frame at station 241 in the fuselage. Alternately, 90° fibers could have been added at that point to increase the load carrying capability. The failure which did occur, however, is a local problem and in no way detracts from the basic composite design. A repair was designed which would provide an adequate load path for the parachute loads to be transferred into the composite honeycomb shell.

The damaged areas on the left and right fuselage panels were repaired with fiberglass patches which were both bonded and bolted to the hybrid laminate.

The fiberglass patches were fabricated from SP 250 prepreg and consisted of 16 plys with $(0°, +45°, 0°)_{2S}$ orientations, the 0° fibers running in the circumferential direction. The patches were laid up on the small center fuselage section access door which substituted as a curing tool. Using the access door as a tool insured the patch would have the exact fitting inside diameter. After cure, the patches were cut to fit the damaged area; the patch configurations are illustrated in Figure 8-20. Existing rivet holes in the damaged area of the fuselage were located and the patches were drilled with 4.76 cm (3/16 in.) diameter bolt holes.

EA9309 room temperature curing adhesive was applied to the finished patches and, in turn, the patches were bolted to the fuselage panels. Care was taken to hold the bond line thickness constant, by positioning .1 mm (.005 in.) diameter fiberglass thread between the patch and the fuselage panels. The 4.76 mm (3/16 in.) diameter bolts were finger-tightened to
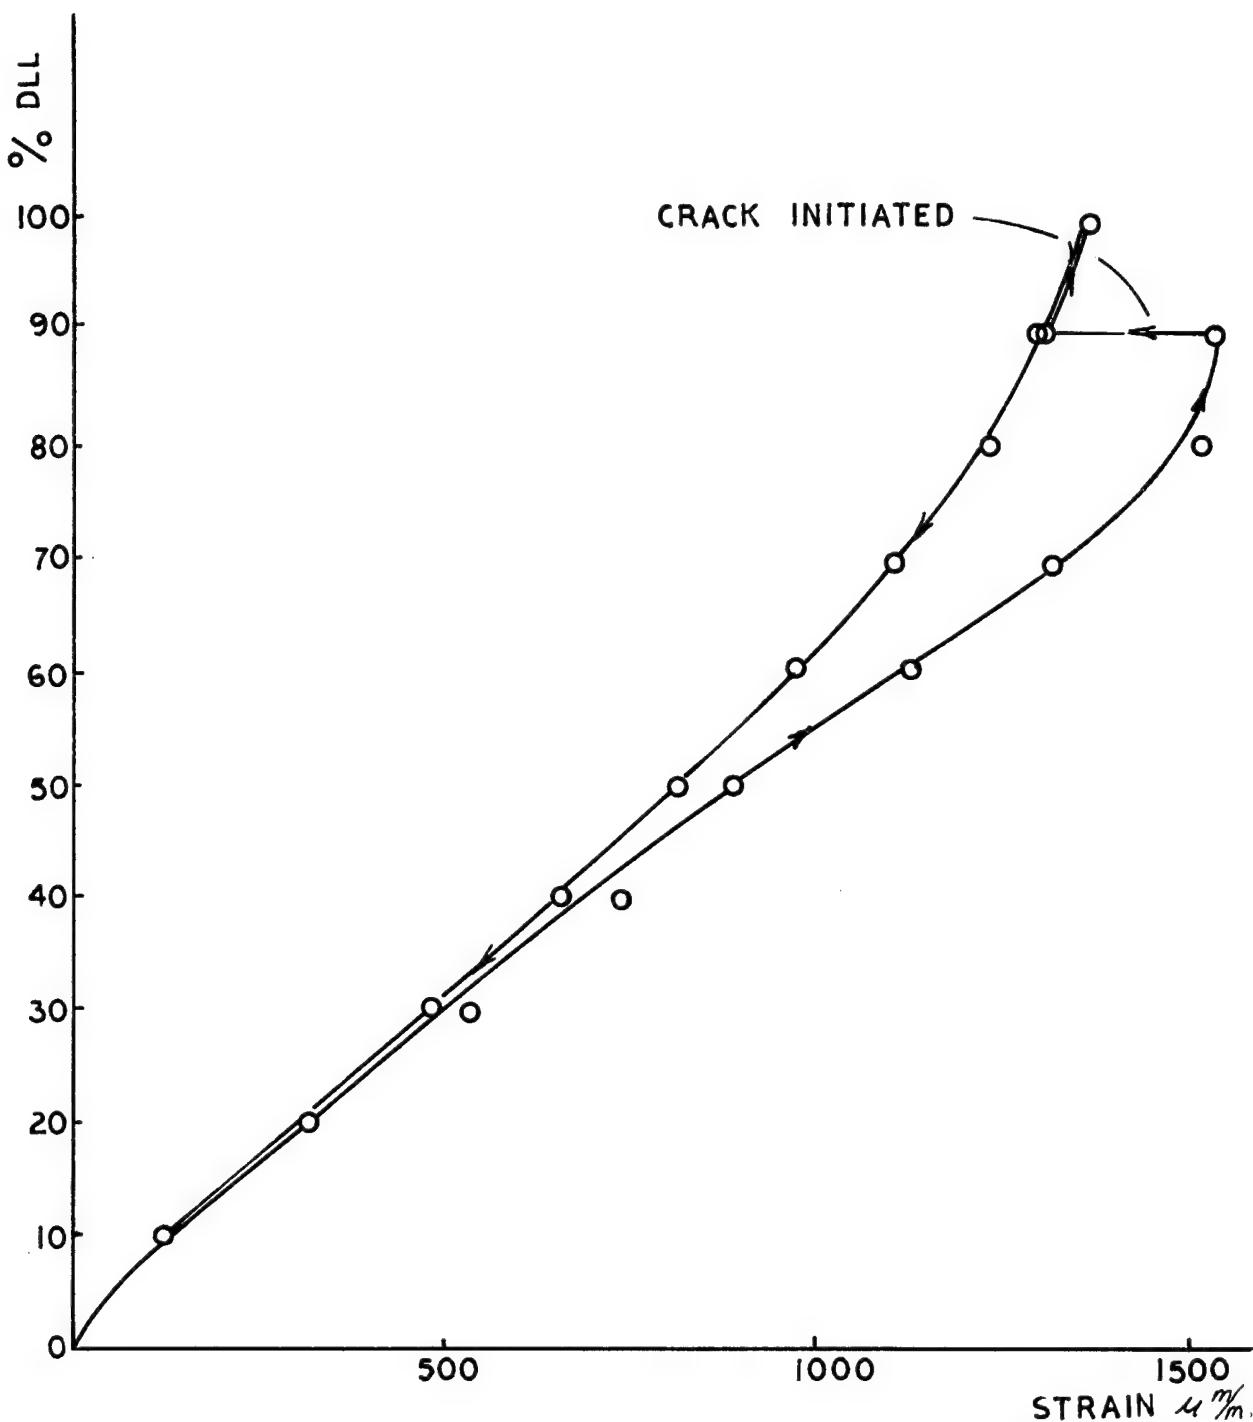
Figure 8-14. Gage 4 Strains on 1st Run to DLL
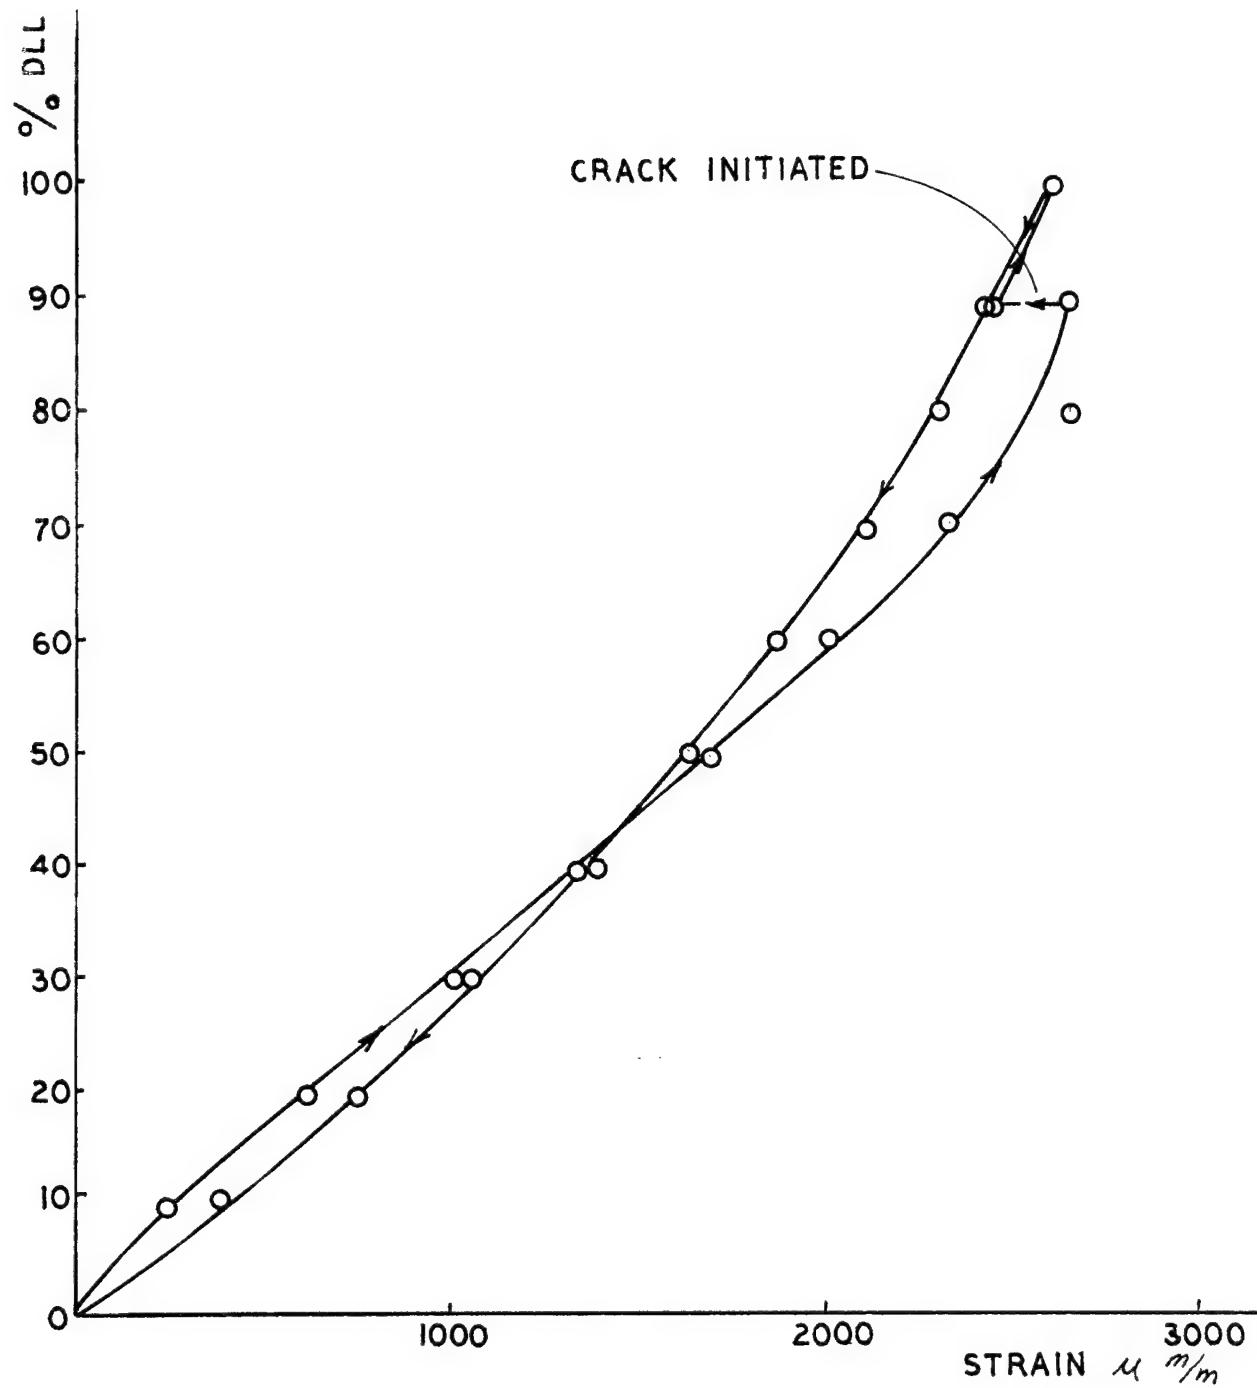
Figure 8-15. Gage 10 Strains on 1st Run to DLL
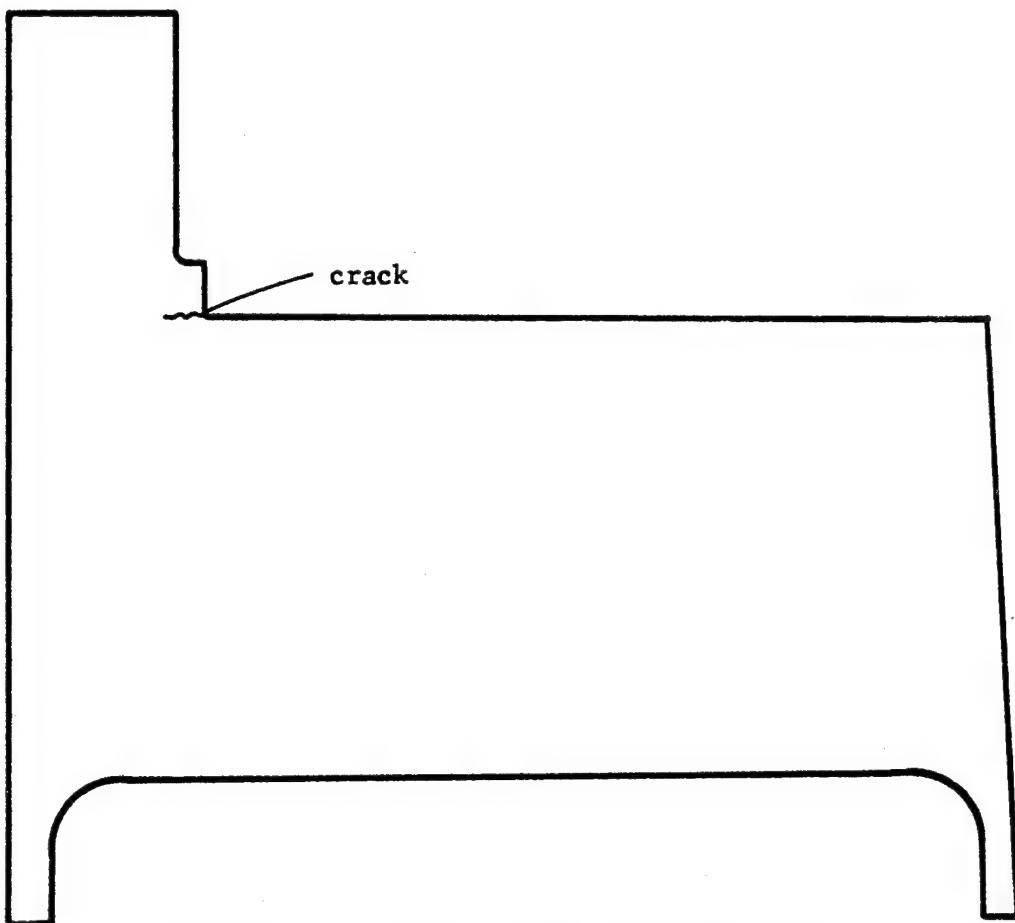
Figure 8-16. Crack in Right Fuselage Panel
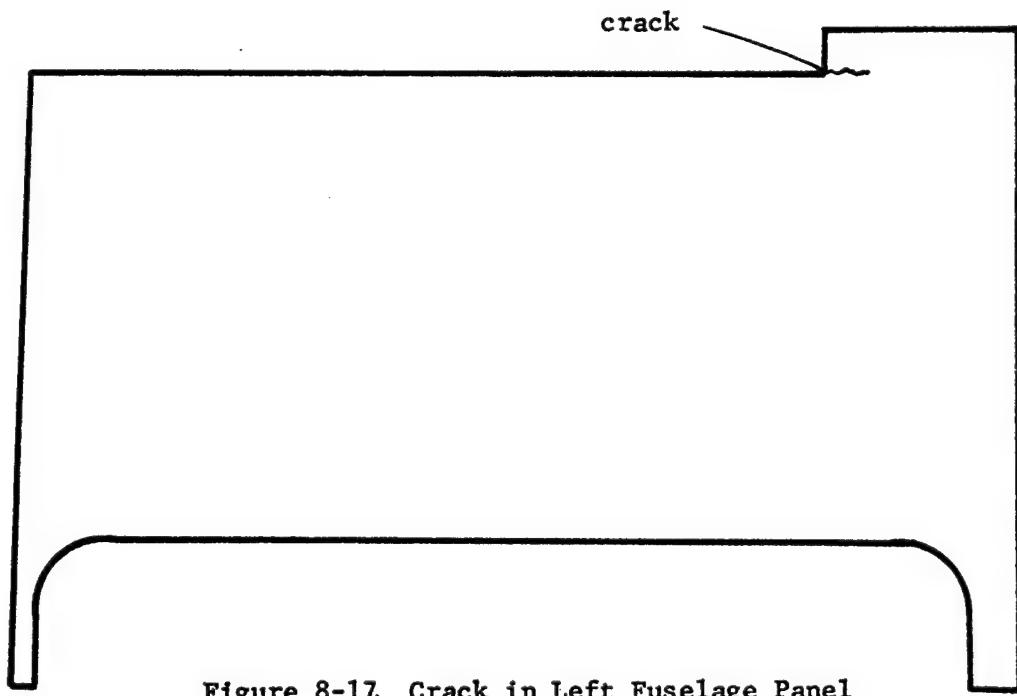
Figure 8-17. Crack in Left Fuselage Panel
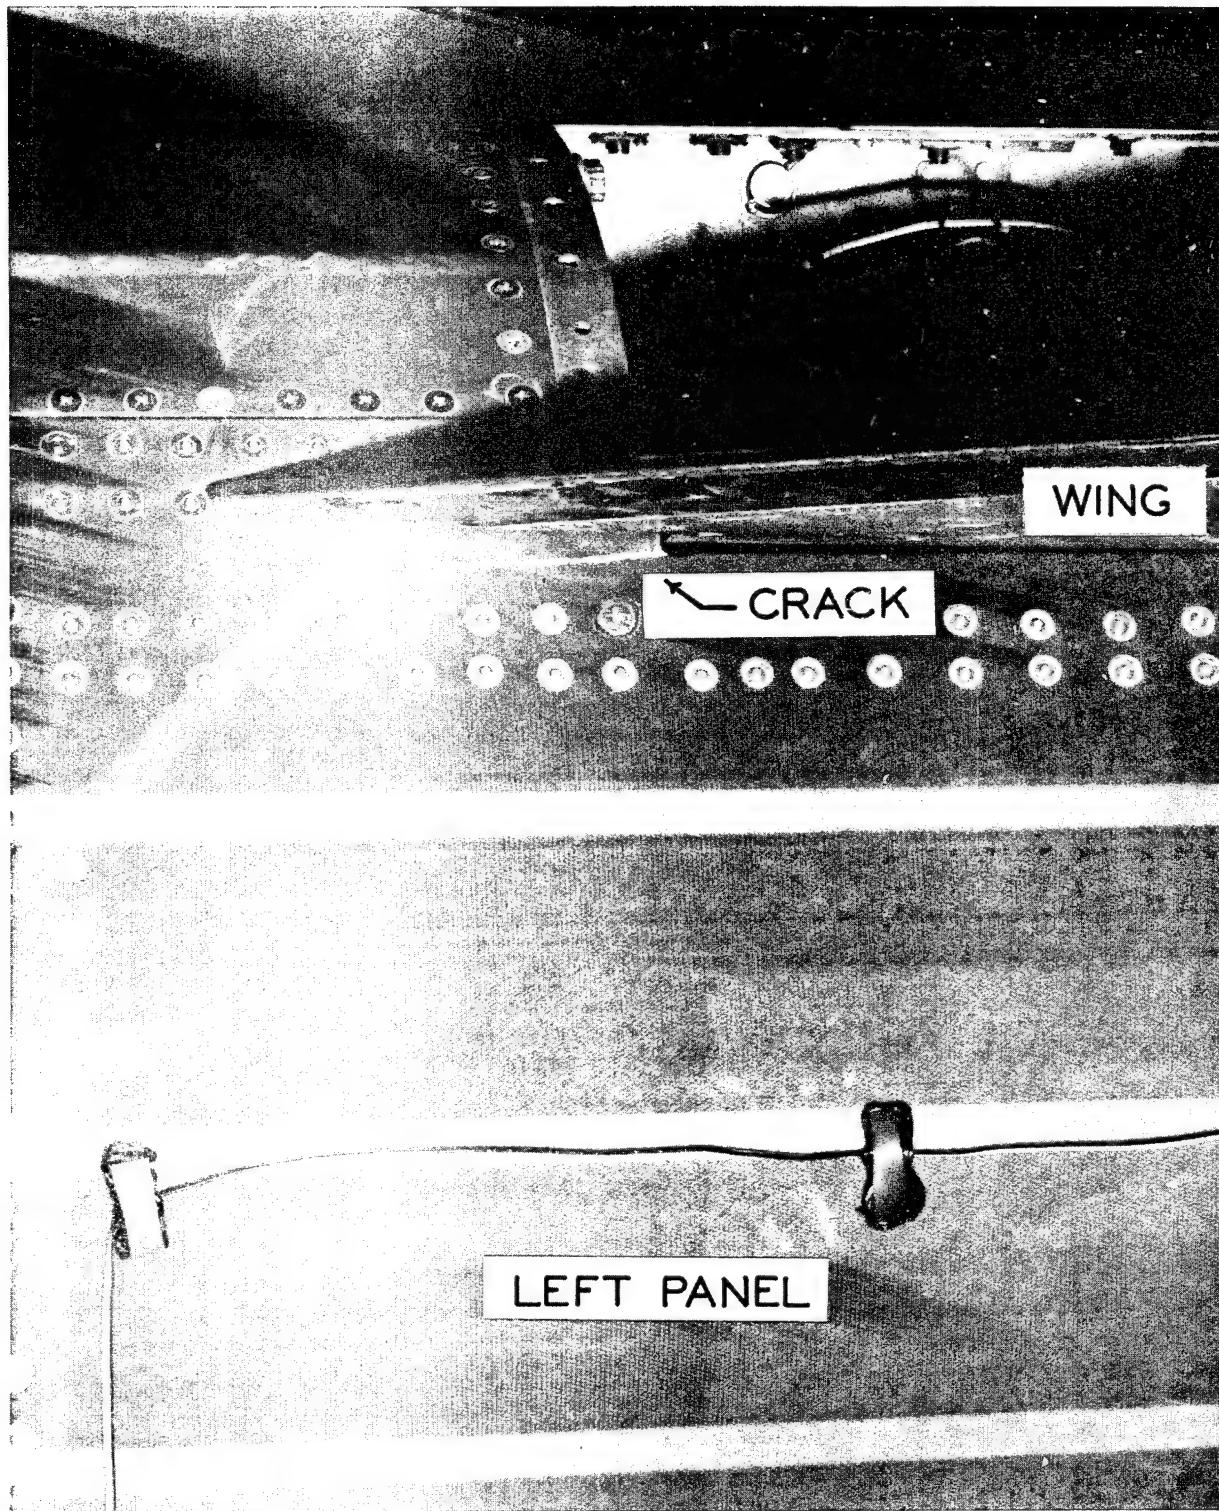
Figure 8-18. Photograph of Crack in Left Fuselage Panel
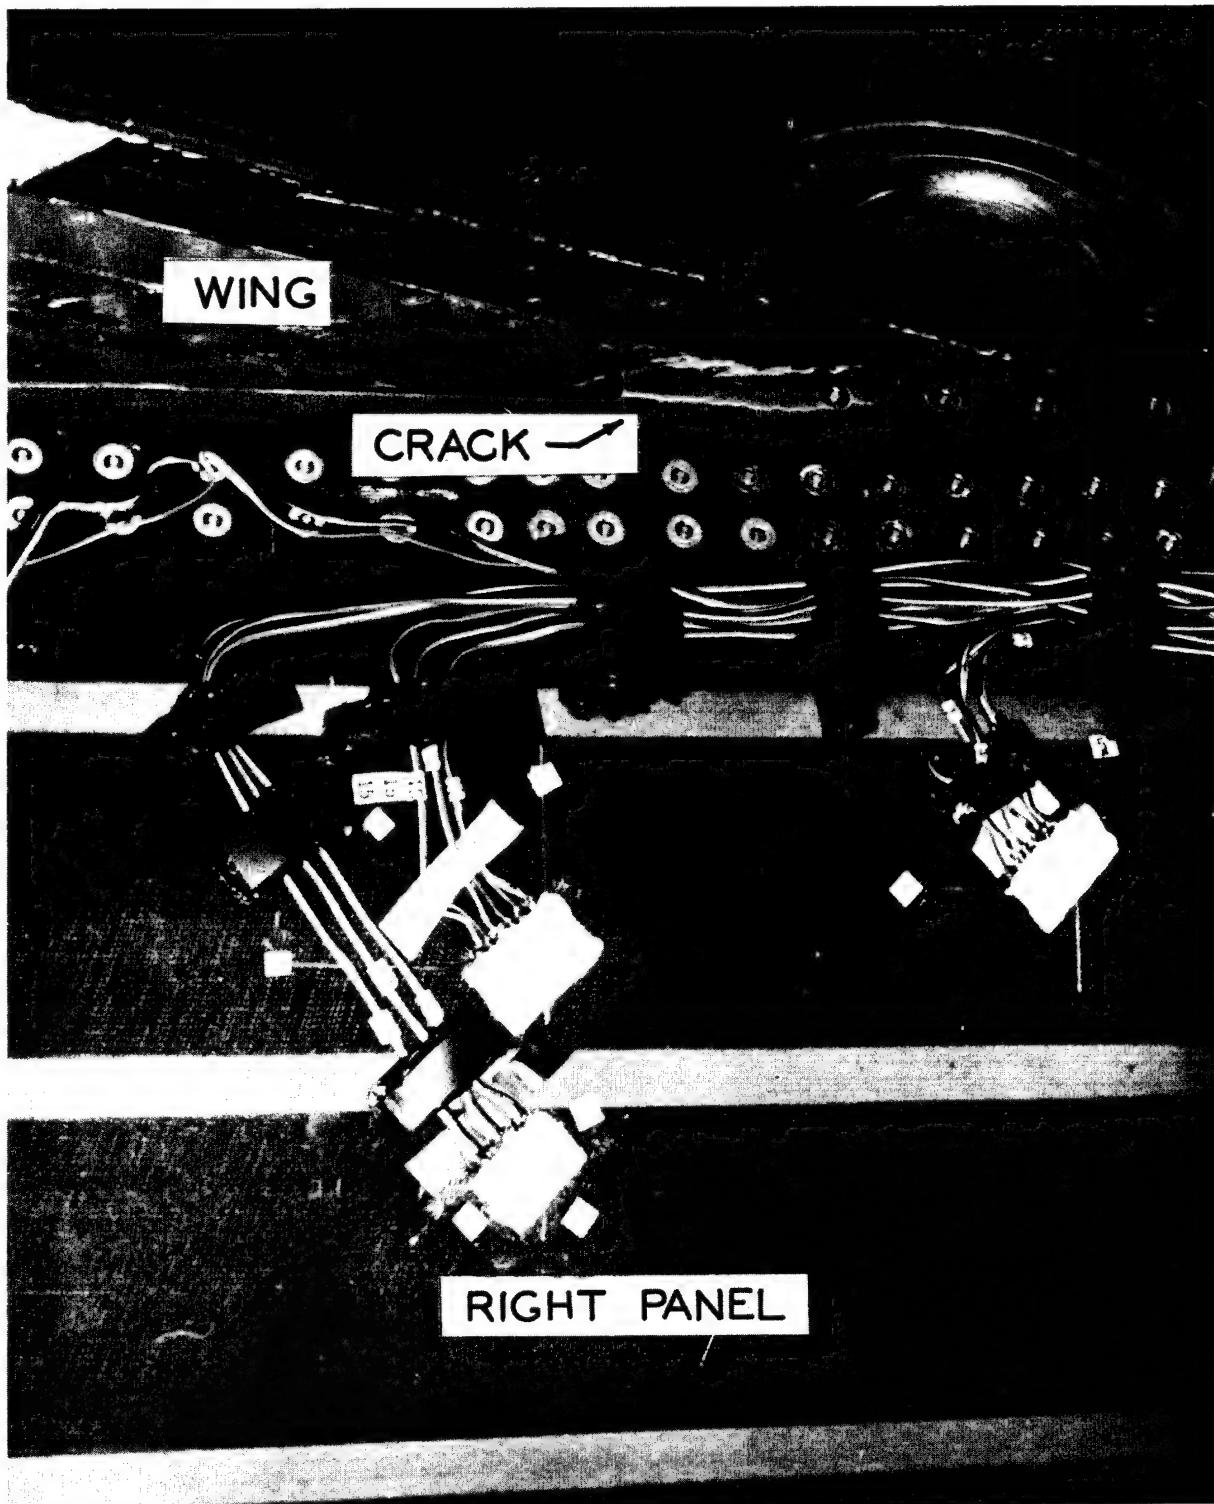
Figure 8-19. Photograph of Crack in Right Fuselage Panel

16 PLY SP250 FIBER GLASS

$(0,\pm45,0)_{2s}$
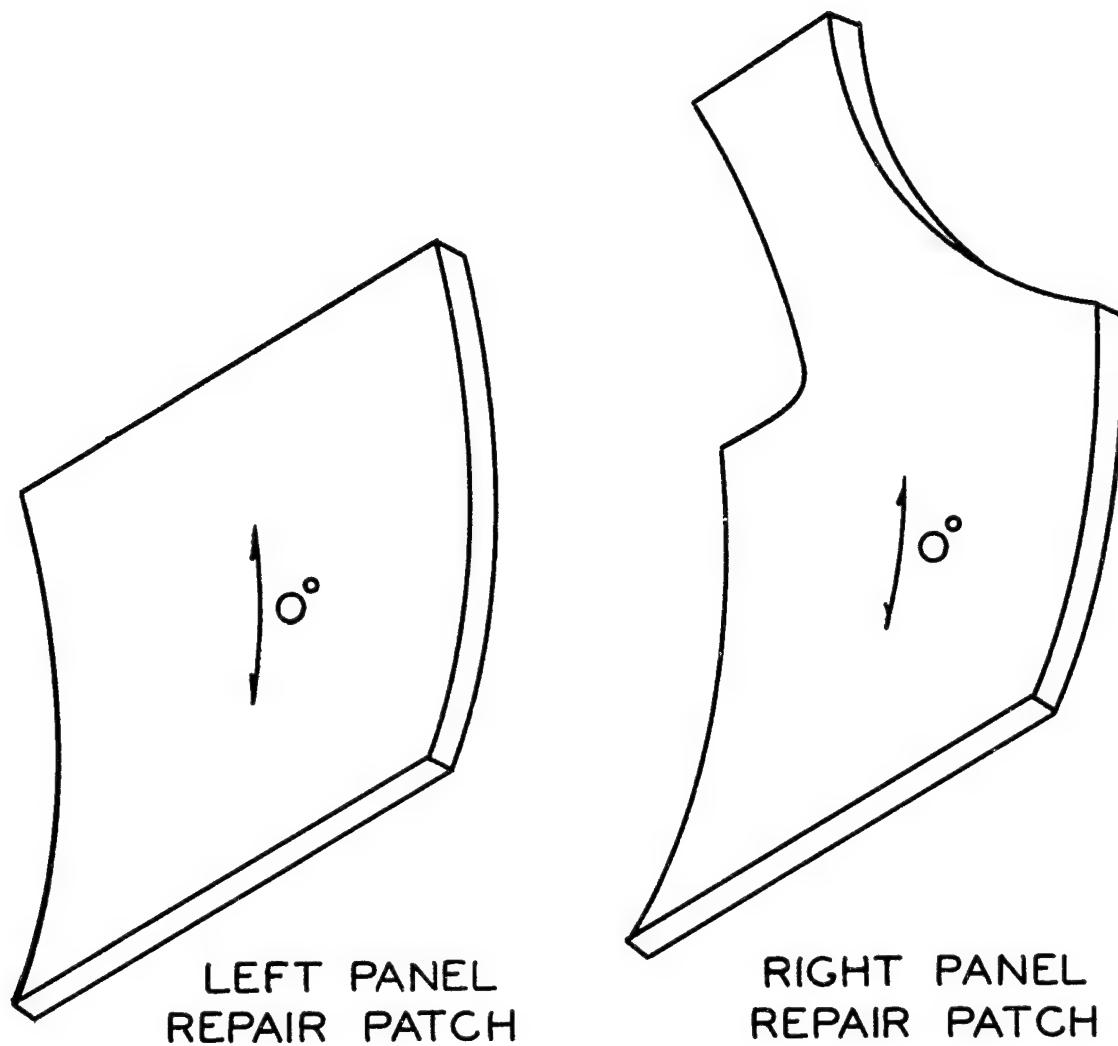
Figure 8-20. Fuselage Repair Configuration

prevent squeezing out the adhesive from between the patch and the fuselage.
After the adhesive cured, the bolts were wrench-tightened. The repaired
areas are shown in photographs in Figures 8-21 and 8-22.

Figures 8-23 and 8-24 show the patch locations on the damaged areas of
the right and left hybrid fuselage panels, respectively. Each patch was
instrumented with an axial gage aligned circumferentially.

8.6 RECOVERY LOADS TEST II (AFTER REPAIR)

The hybrid composite fuselage was successfully tested under the recovery
loads condition after the damaged areas had been repaired with the fiberglass
patches. Test procedures already outlined in the Test Load Conditions and
Loading Sequence section were again repeated for this test.

The only unusual occurrence in this test was a sharp noise which was
heard at 90% DLL during the first cycle to 100% DLL. A discontinuity was
observed in the strain data recorded from the single axial gage located
on the right panel fiberglass patch. Inspection revealed no visible damage
around the repair area, a partial bond failure between the patch and the
fuselage may explain the strain discontinuity. Cycles 2 through 6 resulted
in linear strain data, without any other noises being heard.

8.7 5G MANEUVER LOADS TEST

After the hybrid composite fuselage was successfully tested under the
recovery load conditions, the test assembly was rearranged for the second test
condition, the 5g maneuver loads test. The hybrid composite fuselage
successfully withstood the 5g maneuver test to 100% DLL. Strains
were relatively low for this loading condition as compared with the more
critical recovery loads test. Maximum strains did not exceed 1000 μ m/m
at 100% DLL. No unusual noises or nonlinear strain recordings were noted
during this test.

8.8 DAMAGE PROOF TEST

At the completion of the original test program, it was decided to in-
duce damage into the right fuselage panel in the areas of highest recorded
stress and re-test to 100% DLL. Two holes, approximately 2.5 cm (1 in.) in
diameter were punched through the right panel with a sharp 2.5 cm (1 in.)
diameter steel bar to simulate ballistic damage. Photos of the holes and
their location are shown in Figure 8-25.

It was decided to test the fuselage under the 5g maneuver loads condi-
tion for convenience since the fuselage was currently assembled for that
test. The fuselage was loaded to 100% DLL with no cracks initiating from
the damaged areas. Some noises were heard during the test, although their
origin could not be visibly detected.

After the initial test, additional testing was done with more damage
being inflicted into the panel after each test. Cutouts of approximately
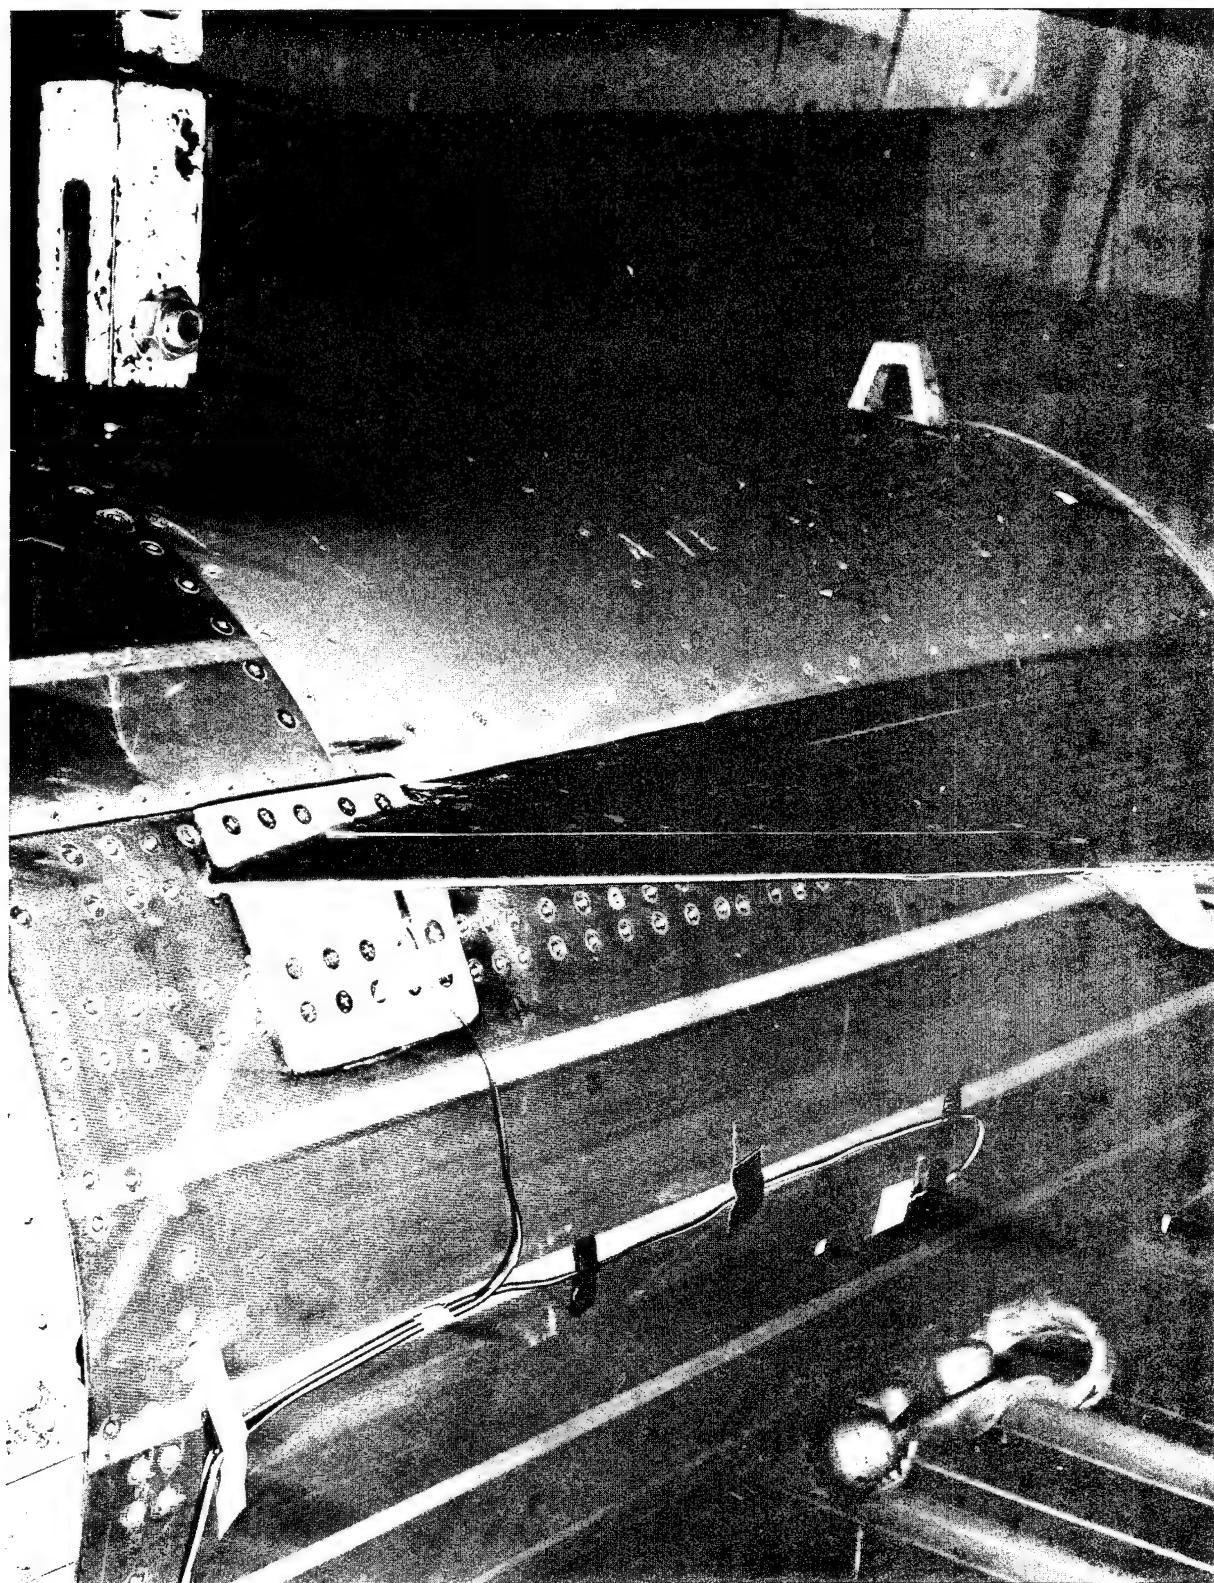
Figure 8-21.   Installed Patch on Left Fuselage Panel
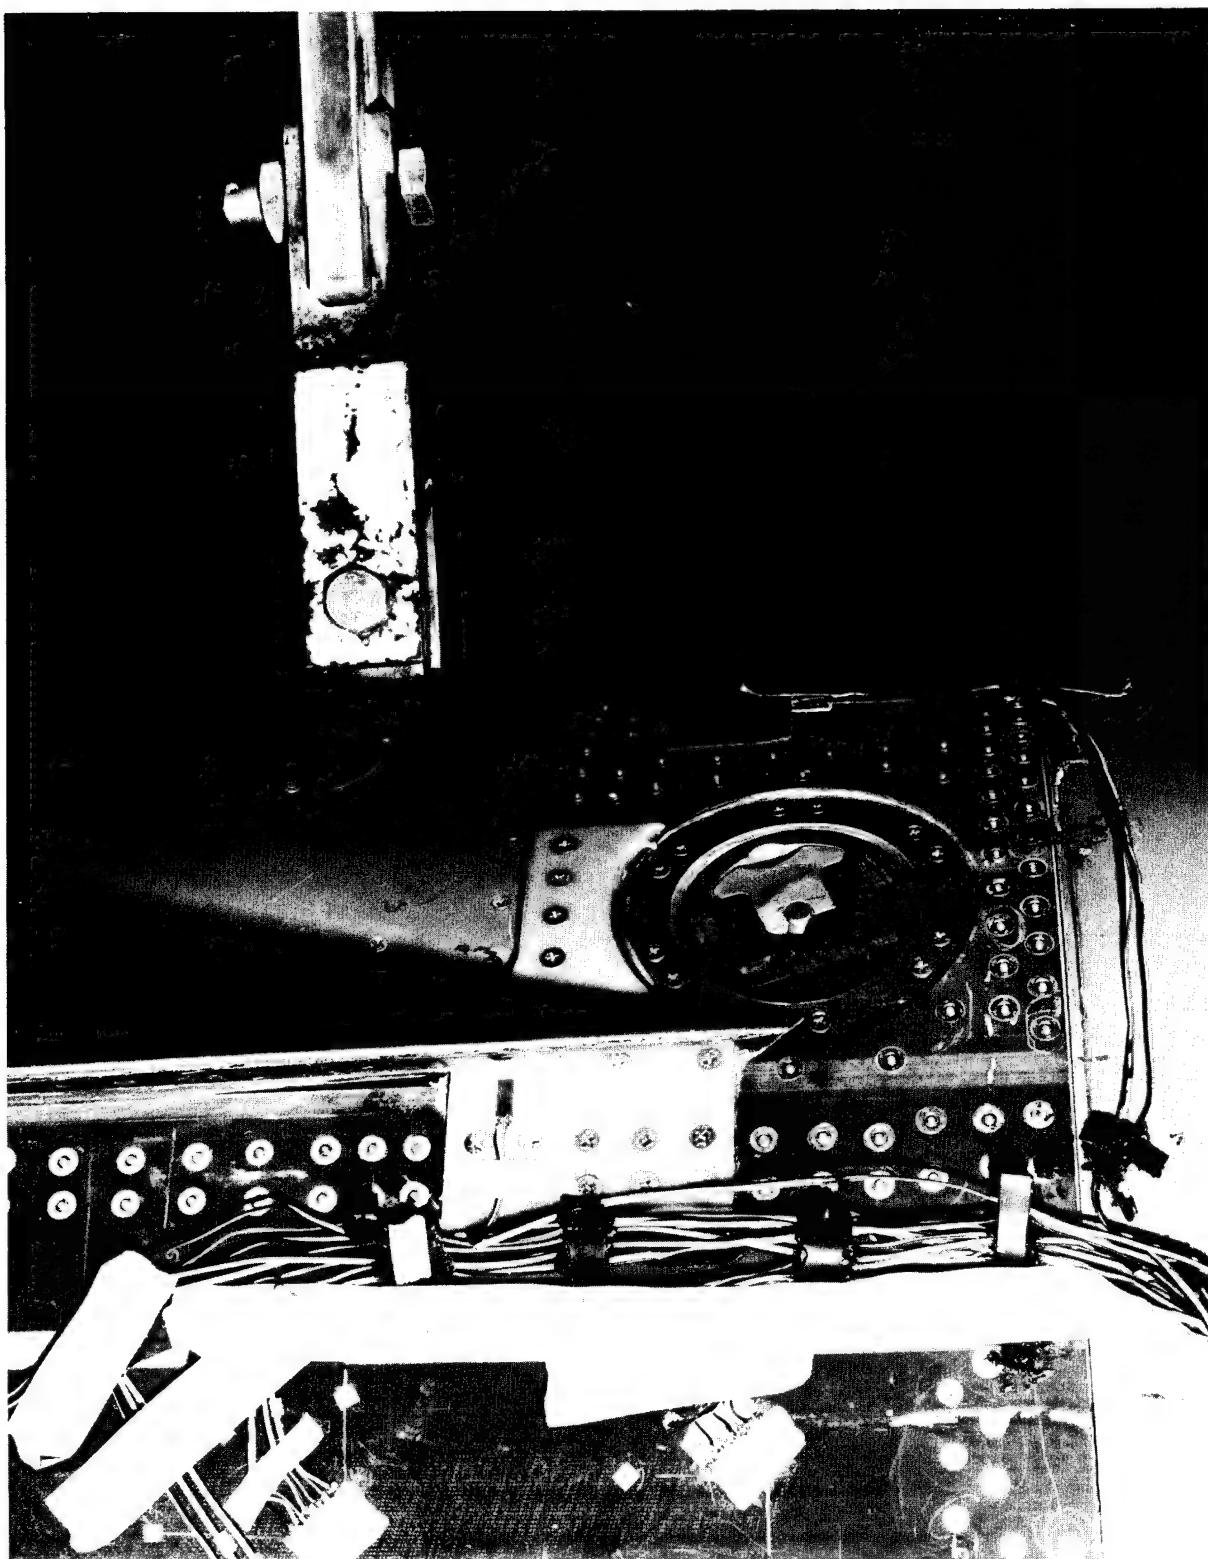
Figure 8-22. Installed Patch on Right Fuselage Panel
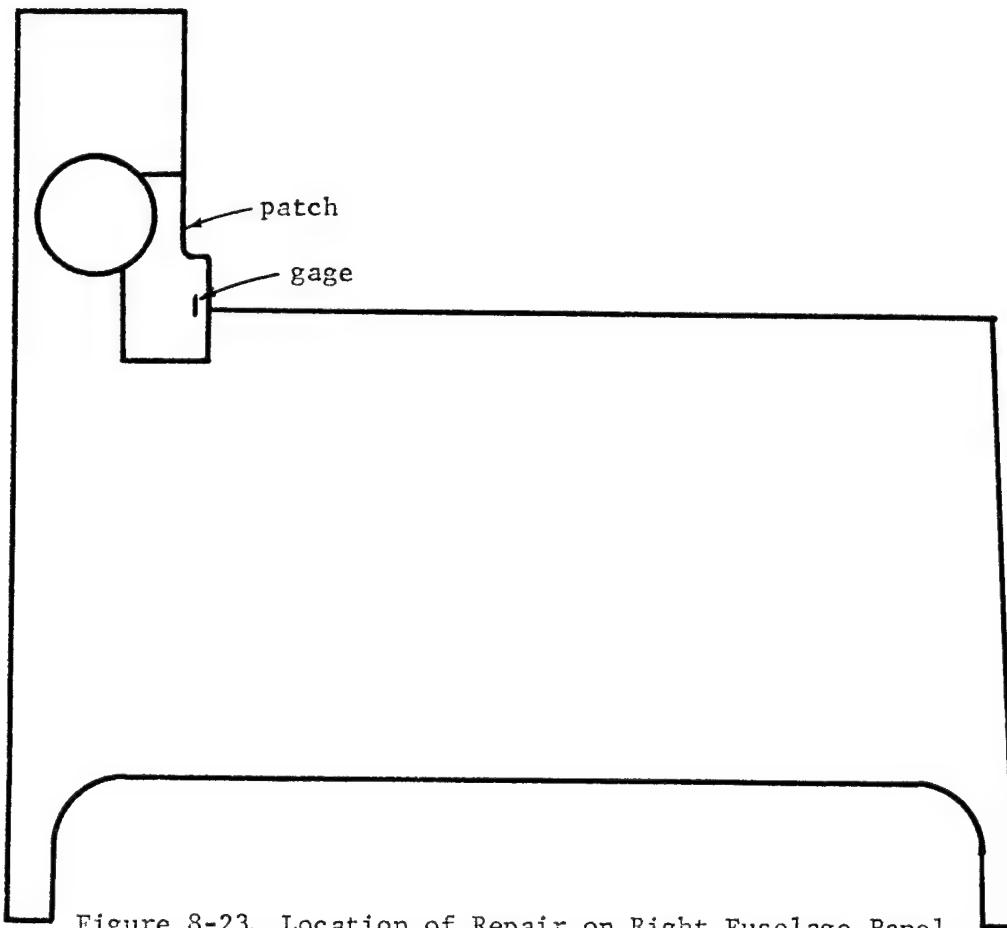
Figure 8-23. Location of Repair on Right Fuselage Panel
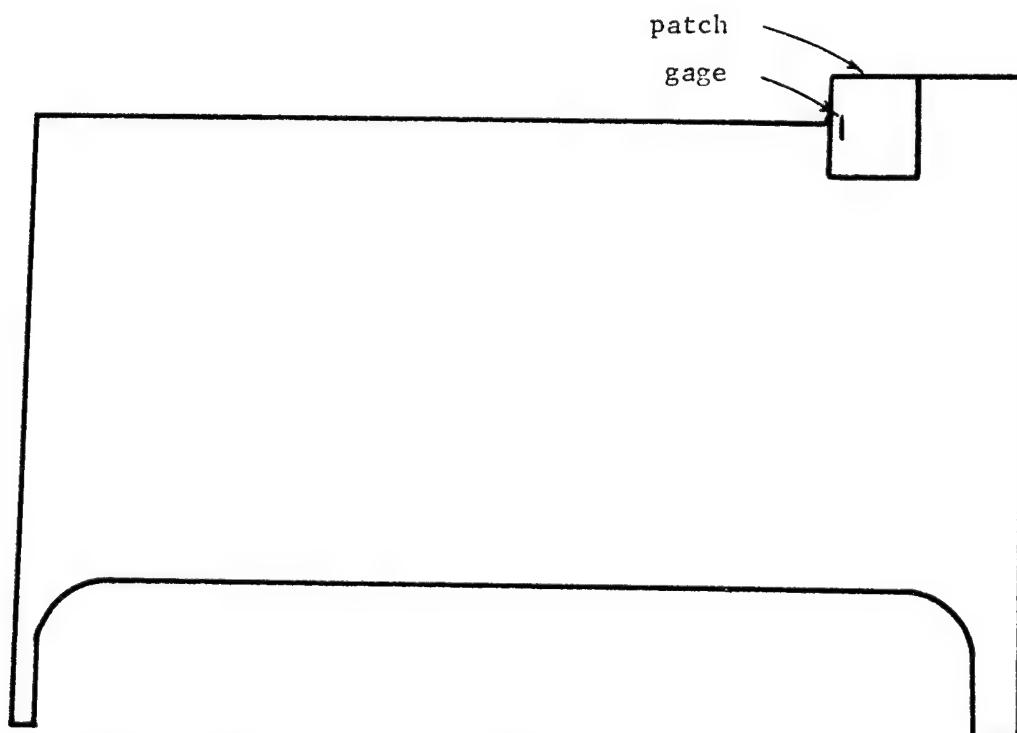
Figure 8-24. Location of Repair on Left Fuselage Panel

110
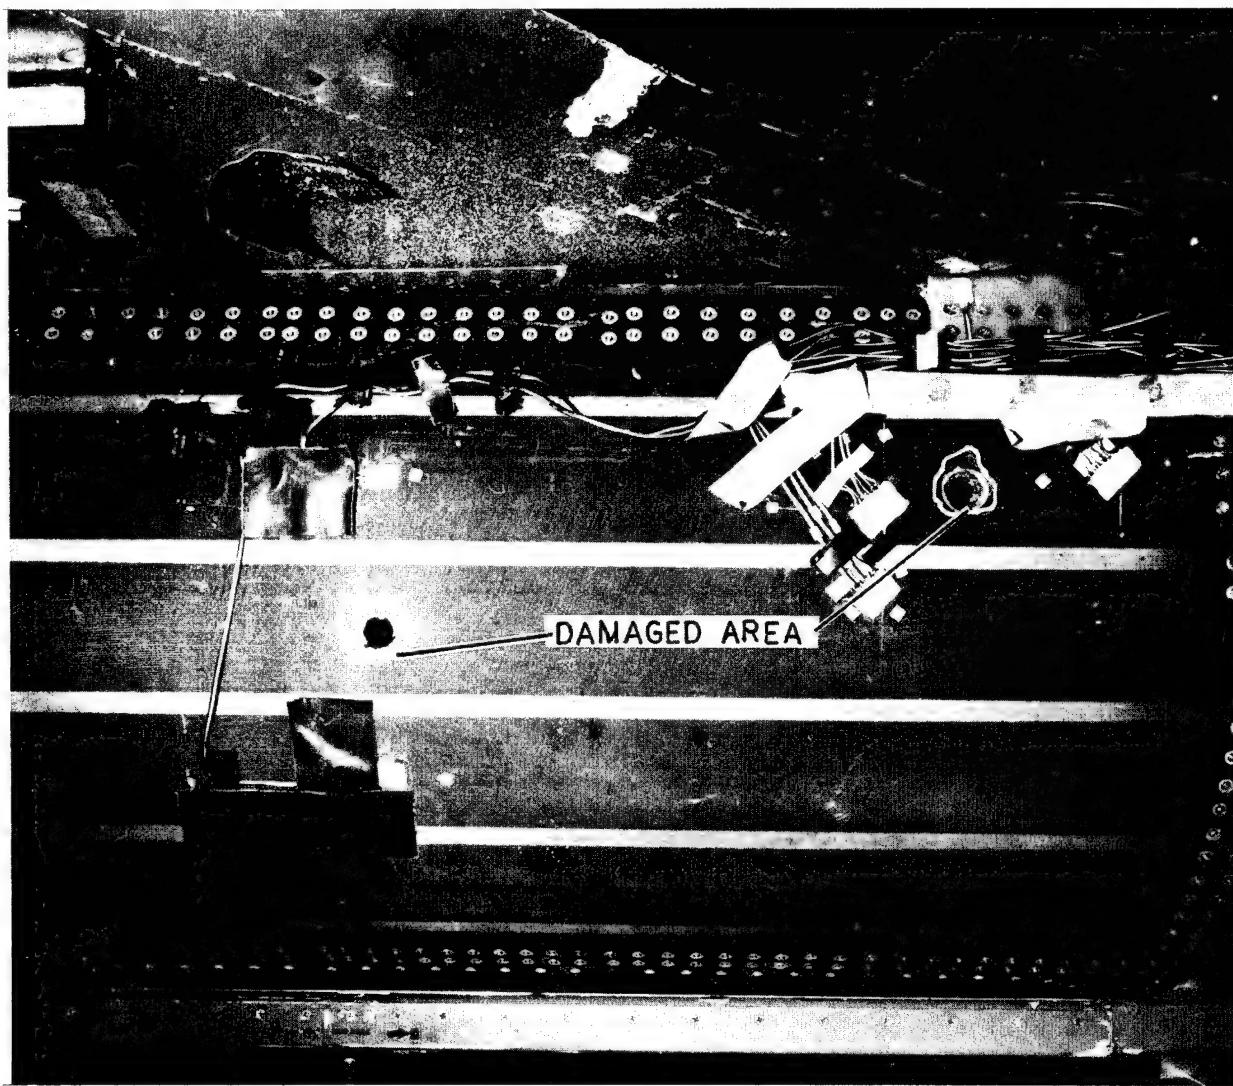
Figure 8-25. Induced Damage in Right Fuselage Panel

7.62 cm (3 in.) maximum diameter cut with a saber saw were contained at 100%
DLL. Again, note that strains in the hybrid composite laminate were low,
(under 1000μ m/m) for the 5g maneuver load condition. Crack propagation may
have occurred under the more critical recovery loads condition. It was decided
not to switch the test assembly back to the recovery condition at this point,
but to conclude the testing.

Previous testing of composite structures incorporating crack arrestment
fiberglass softening strips, namely the cylinder subcomponent described in this
report, demonstrated the ability of these crack arrestment features, to stop
propagating cracks.

CONCLUSIONS

The design which was developed and demonstrated in this program resulted in
a 26% reduction of the weight of the metal parts which were replaced. The cost
of the design was estimated to be 20% less, in a production situation, than the
metal design. The crack arrester strips which were incorporated into the fuselage
section represent the first application of this concept to a primary structure
design. These strips met and exceeded expectations with regard to their ability
to arrest and locally contain propagating damage, both statically and ballistically
induced damage. Thus, the program demonstrated and verified their feasibility,
capability and practical usability as a concept for damage tolerant design. In
addition, the crack arrestment testing which was performed in this program demon-
strated the superior fracture tolerance characteristics of the hybrid composite
material and indicated that its slow crack propagation behavior might be useful
as a failure warning device for a structure.

The objectives of this program have been met and the results have been
disseminated in references 13 to 16. The success experienced here with crack
arrester designs has provided some impetus for work which is now being pursued
in industry in conjunction with composite structures studies.

REFERENCES

1. "Fuselage Structural Analysis for BQM-34E Supersonic Aerial Target", Ryan Report No. TRA K642-13B, 20 Feb 1973 (Volumes 1 and 2).

2. "Structural Loads Report for BQM-34E Supersonic Aerial Target", Final Report, Volume 1, Basic Report, 15 July 1970.

3. "NAVAIRDEVCEN Graphite-Epoxy Composite Wing for BQM-34E; Stress and Vibration Analysis", Thomas F. Neu, Shih L. Huang, Report No. NADC 73235-30, 15 November 1973.

4. "Structural Efficiency of Orthotropic Cylindrical Shells Subjected to Axial Compression", Norris F. Dow, B. Walter Rosen, AIAA Journal, March 1966.

5. "Pastbuckling Behavior of Orthotropic Cylinders Under Axial Compression", B. O. Almroth, AIAA Journal, October, 1964.

6. "Compressive Buckling of Simply Supported Curved Plates and Cylinders of Sandwich Construction", Manuel Stein, J. Mayers, NACA TN 2601, January 1952.

7. "Stability of Orthotropic Cylindrical Shells Under Combined Loading", T. E. Hess, American Rocket Society Journal, 1961.

8. "Buckling of Thin-Walled Circular Cylinders", NASA SP-8007, August 1968.

9. "Structural Sandwich Composites", MIL-HDBK-23A.

10. "Fabrication and Full-Scale Structural Evaluation of Glass-Fabric Reinforced Plastic Shells", Charles W. Bert, W. C. Crisman, Gene M. Nordby, Journal of Aircraft, Jan-Feb 1968.

11. "Buckling Design Handbook", T. E. Hess.

12. "Buckling of Cylindrical and Conical Sandwich Shells with Orthotropic Facings", Charles W. Best, W. C. Crisman, Gene M. Nordby, AIAA Journal, February 1969.

13. "A Hybrid Composite Fuselage Design with Integral Crack Arresters", S. L. Huang, T. E. Hess, 3rd Conference on Fibrous Composites in Flight Vehicle Design, Williamsburg, VA, November 1975.

14. "Fracture Control in Composite Materials Using Integral Crack Arresters", T. E. Hess, S. L. Huang, H. Rubin, AIAA/ASME/SAE 17th Structures, Structural Dynamics and Materials Conference, Valley Forge, May 1976.

15. "Fracture Control in Composite Materials Using Integral Crack Arresters", T. E. Hess, S. L. Huang, H. Rubin, Journal of Aircraft (To Be Published).

16. "Fatigue and Fracture Control of Graphite/Epoxy Composite Laminates with Stress Raiser", S. L. Huang, T. E. Hess, M. S. Rosenfeld, International Conference on Fracture Mechanics and Technology, Hong Kong, March, 1977.

THIS PAGE INTENTIONALLY LEFT BLANK

APPENDIX A

NASTRAN BULK DATA

BGM-34E COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

CARD COUNT	. 1	.. 2	.. 3	.. 4	.. 5	.. 6	.. 7	.. 8	.. 9	.. 10
1-	CBAR	1001	31	14	16	15			2	
2-	CBAR	1002	31	13	14	15			2	
3-	CBAR	1003	37	16	15	13			2	
4-	CBAR	1004	32	7	13	6			2	
5-	CBAR	1005	31	13	15	11			2	
6-	CBAR	1006	35	6	7	13			2	
7-	CBAR	1007	31	12	13	11			2	
8-	CBAR	1008	31	10	15	9			2	
9-	CBAR	1009	34	15	9	10			2	
10-	CBAR	1010	32	11	12	13			2	
11-	CBAR	1011	33	10	11	15			2	
12-	CBAR	1012	31	9	10	15			2	
13-	CBAR	1013	34	2	9	15			2	
14-	CBAR	1014	38	1	2	16			2	
15-	CBAR	1015	31	10	4	11			2	
16-	CBAR	1016	36	5	24	11			2	
17-	CBAR	1017	36	4	5	11			2	
18-	CBAR	1018	36	3	4	10			2	
19-	CBAR	1019	36	2	3	9			2	
20-	CBAR	1020	35	7	8	14			2	
21-	CBAR	1021	31	6	12	11			2	
22-	CBAR	1022	16	51	52	41			2	176
23-	+76									
24-	CBAR	1023	16	71	51	50			2	177
25-	+77									
26-	CBAR	1024	16	101	71	96			2	178
27-	+78									
28-	CBAR	1025	16	131	101	126			2	179
29-	+79									
30-	CBAR	1026	16	133	131	132			2	180
31-	+80									
32-	CBAR	1027	16	134	133	170			2	181
33-	+81									
34-	CBAR	1028	17	18	8	19			2	
35-	CBAR	1029	17	39	18	21			2	
36-	CBAR	1030	18	19	17	14			2	
37-	CBAR	1031	39	38	39	42			2	
38-	CBAR	1032	40	42	41	38			2	
39-	CBAR	1033	41	38	41	37			2	
40-	CBAR	1034	42	37	38	41			2	
41-	CBAR	1035	43	41	37	38			2	
42-	CBAR	1036	44	41	40	37			2	
43-	CBAR	1037	41	37	40	36			2	
44-	CBAR	1038	45	36	56	40			2	
45-	CBAR	1039	46	40	36	37			2	
46-	CBAR	1041	45	56	37	40			2	
47-	CBAR	1042	10	69	68	73			2	129
48-	CBAR	1043	10	68	67	73			2	130
49-	CBAR	1045	10	99	98	104			2	148
50-	CBAR	1046	40	98	97	104			2	149

CARD COUNT	. 1	.. 2	.. 3	.. 4	.. 5	.. 6	.. 7	.. 8	.. 9	.. 10
51-	CBAR	1048	10	129	128	138			2	166
52-	CBAR	1049	10	128	127	138			2	167
53-	CBAR	1050	18	21	19	20			2	
54-	CBAR	1051	51	159	170	168			2	1512
55-	+512			0.122	8.05	0.0	0.25	16.96	0.0	
56-	CBAR	1052	57	158	159	170			2	
57-	CBAR	1053	50	170	167	168			2	
58-	CBAR	1054	57	157	158	168			2	
59-	CBAR	1055	52	168	167	157			2	
60-	CBAR	1056	62	167	164	166			2	
61-	CBAR	1057	51	167	166	157			2	
62-	CBAR	1058	58	156	140	167			2	
63-	CBAR	1059	51	156	166	165			2	
64-	CBAR	1060	53	166	165	156			2	
65-	CBAR	1061	54	164	165	166			2	
66-	CBAR	1062	54	165	155	156			2	
67-	CBAR	1063	59	155	156	165			2	
68-	CBAR	1064	63	164	163	155			2	
69-	CBAR	1065	59	154	155	163			2	
70-	CBAR	1066	54	163	154	155			2	
71-	CBAR	1067	63	163	162	153			2	
72-	CBAR	1068	60	153	154	163			2	
73-	CBAR	1069	54	162	153	154			2	
74-	CBAR	1070	63	162	161	152			2	
75-	CBAR	1071	60	152	153	162			2	
76-	CBAR	1072	55	161	152	153			2	
77-	CBAR	1073	64	161	160	152			2	
78-	CBAR	1074	61	151	152	161			2	
79-	CBAR	1075	56	160	151	153			2	
80-	CBAR	1076	52	167	157	168,			2	
81-	CBAR	1077	70	1	31	16			2	17
82-	+7			.422			.422			
83-	CBAR	1078	70	31	61	16			2	18
84-	+8			.422			.422			
85-	CBAR	1079	70	61	91	16			2	19
86-	+9			.422			.422			
87-	CBAR	1080	70	91	121	16			2	110
88-	+10			.422			.422			
89-	CBAR	1081	70	121	151	16			2	111
90-	+11			.422			.422			
91-	CBAR	1082	5	70	22	16			2	116
92-	CBAR	1083	5	100	70	16			2	117
93-	CBAR	1084	5	130	100	16			2	118
94-	CBAR	1085	5	23	130	16			2	119
95-	CBAR	1086	19	20	14	1			2	
96-	CBAR	1087	19	42	20	1			2	
97-	CBAR	1088	19	8	17	170			2	
98-	CBAR	1090	20	39	21	170			2	
99-	CBAR	1091	19	17	14	170			2	
100-	CBAR	1093	20	21	42	170			2	

```
                                    S O R T E D   B U L K   D A T A   E C H O
CARD
COUNT        •   1   ••   2   ••  3   ••   4   ••  5   ••  6   ••   7   ••   8   ••   9   ••  10
101-      CBAR   1094    94       22      39     16                              2        196
102-      CBAR   1095    94      159      23     16                              2        197
103-      CBAR   1096   205       43      29    0.0       1.         0.0         1
104-      CBAR   1097   215       29      59    0.0       1.         0.0         1
105-      CBAR   1099   214       59      89    0.0       1.         0.0         1
106-      CBAR   1101   213       89     119    0.0       1.         0.0         1
107-      CBAR   1103   212      119     137    0.0       1.         0.0         1
108-      CBAR   1104   202      149     148    0.0       1.         0.0         1
109-      CBAR   1105   185       74      21     22                              2
110-      CBAR   1106   105      105      74     70                              2
111-      CBAR   1107   107      139     105    100                              2
112-      CBAR   1108   108      169     139     23                              2
113-      CBAR   1109    36       24       6     15                              2
114-      CBAR   1110   204       30      43    0.0       1.         0.0         1
115-      CBAR   1114   201      148     150    0.0       1.         0.0         1
116-      CBAR   1115   115       73      68     69                              2
117-      CBAR   1116   115       74      73     69                              2
118-      CBAR   1117   115      104      98     99                              2
119-      CBAR   1118   115      105     104     99                              2
120-      CBAR   1119   115      138     128    129                              2
121-      CBAR   1120   115      139     138    129                              2
122-      CBAR   1121   121       67      56    0.0      1.0        0.0          1
123-      CBAR   1122   121       67      97    0.0      1.0        0.0          1
124-      CBAR   1123   121       97     127    0.0      1.0        0.0          1
125-      CBAR   1124   122      127     140    0.0      1.0        0.0          1
126-      CBAR   1125    58      140     157    167                              2
127-      CBAR   1126   126        2      32    1.0       .0         .0          1
128-      CBAR   1127   126       32      62    1.0       .0         .0          1
129-      CBAR   1128   126       62      92    1.0       .0         .0          1
130-      CBAR   1129   126       92     122    1.0       .0         .0          1
131-      CBAR   1130   126      122     152    1.0       .0         .0          1
132-      CBAR   1138   211      137     149    0.0       1.         0.0         1
133-      CBAR   1139   139       75       4     .0      -1.0        .0          1
134-      CBAR   1140   140       75      76     80                              2
135-      CBAR   1141   140       76      77     80                              2
136-      CBAR   1142   140       77      78     80                              2
137-      CBAR   1143   140       78      79     80                              2
138-      CBAR   1144   140       79      80    1.0       .0         .8          1
139-      CBAR   1145    70      151     141     16                              2        C145
140-      +C145                  .422            .422
141-      CBAR   1146   146      154     144     .0      -1.0        .0          1
142-      CBAR   1147   147       58      81     80                              2        C147
143-      +C147                   0.0    -.85    0.0      0.0        -.5         0.0
144-      CBAR   1148   148       57      58     80                              2        C148
145-      +C148                   0.8     .75    0.0      0.0        -.85        0.0
146-      CBAR   1149   148       75      57     80                              2        C149
147-      +C149                   0.0     .65    0.0      0.0         .75        0.0
148-      CBAR   1152   152      144     145    179                              2
149-      CBAR   1153   152      145     146    179                              2
150-      CBAR   1154   152      146     147    179                              2
```

SORTED BULK DATA ECHO

CARD COUNT	. 1	.. 2	.. 3	.. 4	.. 5	.. 6	.. 7	.. 8	.. 9	.. 10
151-	CBAR	1155	152	147	178	179			2	
152-	CBAR	1156	152	178	179	1.0	.0	.0	1	
153-	CELAS1	2018	2001	29	1	40	1			
154-	CELAS1	2019	2002	29	2	40	2			
155-	CELAS1	2020	2001	29	3	40	3			
156-	CELAS1	2021	2003	29	4	40	4			
157-	CELAS1	2022	2004	29	5	40	5			
158-	CELAS1	2023	2003	29	6	40	6			
159-	CELAS1	2024	2001	149	1	166	1			
160-	CELAS1	2025	2002	149	2	166	2			
161-	CELAS1	2026	2001	149	3	166	3			
162-	CELAS1	2027	2003	149	4	166	4			
163-	CELAS1	2028	2004	149	5	166	5			
164-	CELAS1	2029	2003	149	6	166	6			
165-	CONM2	143	119	2	.01	-22.	.0	.0		
166-	CONM2	144	149	2	.04	-22.	.0	.0		
167-	CONM2	147	155	2	.0155					
168-	CONM2	148	156	2	.031					
169-	CONM2	149	157	2	.0078					
170-	CORD2C	1	0	0.0	0.0	0.0	0.0	0.0	1.0	11
171-	+1	8.8	1.0	0.0						
172-	CORD2R	2	0	.0	6.0	0.0	0.0	6.0	1.0	185
173-	+85	1.0	6.0	0.0						
174-	CQUAD1	200	200	60	30	43	55	.0		
175-	CQUAD1	201	201	55	43	29	59	.0		
176-	CQUAD1	202	202	90	60	55	87	.0		
177-	CQUAD1	203	203	87	55	59	89	.0		
178-	CQUAD1	204	204	120	90	87	117	.0		
179-	CQUAD1	205	205	117	87	89	119	.0		
180-	CQUAD1	206	286	135	120	117	136	.0		
181-	CQUAD1	207	207	136	117	119	137	.0		
182-	CQUAD1	208	208	150	135	136	148	.0		
183-	CQUAD1	209	209	148	136	137	149	.0		
184-	CROD	899	119	18	19	920	119	19	20	
185-	CSHEAR	143	118	18	8	17	19			
186-	CSHEAR	144	118	39	18	19	21			
187-	CSHEAR	145	118	19	17	14	20			
188-	CSHEAR	146	118	21	19	20	42			
189-	CTRIA1	15	47	1	31	2				
190-	CTRIA1	16	47	32	2	31				
191-	CTRIA1	17	47	2	32	3				
192-	CTRIA1	18	47	33	3	32				
193-	CTRIA1	19	47	3	33	44				
194-	CTRIA1	20	47	34	4	44				
195-	CTRIA1	21	47	4	34	45				
196-	CTRIA1	22	47	35	5	45				
197-	CTRIA1	23	47	5	35	25				
198-	CTRIA1	44	47	31	61	32				
199-	CTRIA1	45	47	62	32	61				
200-	CTRIA1	46	47	32	62	33				

```
                                   S O R T E D   B U L K   D A T A   E C H O
CARD
COUNT       .   1   ..   2   ..   3   ..   4   ..   5   ..   6  ..   7  ..   8  ..   9  ..  10
 201-     CTRIA1   47       47       63       33       62
 202-     CTRIA1   48        3       33       63       49
 203-     CTRIA1   49        3       64       34       49
 204-     CTRIA1   50        3       34       64       53
 205-     CTRIA1   51        3       65       35       53
 206-     CTRIA1   52       47       35       65       54
 207-     CTRIA1   53       47       66       36       54
 208-     CTRIA1   66       47       61       91       62
 209-     CTRIA1   67       47       92       62       91
 210-     CTRIA1   68       47       62       92       63
 211-     CTRIA1   69       47       93       63       92
 212-     CTRIA1   70        3       63       93       64
 213-     CTRIA1   71        3       94       64       93
 214-     CTRIA1   72        3       64       94       65
 215-     CTRIA1   73        3       95       65       94
 216-     CTRIA1   74       47       65       95       66
 217-     CTRIA1   75       47       96       66       95
 218-     CTRIA1   86       47       91      121       92
 219-     CTRIA1   87       47      122       92      121
 220-     CTRIA1   88       47       92      122       93
 221-     CTRIA1   89       47      123       93      122
 222-     CTRIA1   90        3       93      123       94
 223-     CTRIA1   91        3      124       94      123
 224-     CTRIA1   92        3       94      124       95
 225-     CTRIA1   93        3      125       95      124
 226-     CTRIA1   94       47       95      125       96
 227-     CTRIA1   95       47      126       96      125
 228-     CTRIA1  106       47      121      151      122
 229-     CTRIA1  107       47      151      152      122
 230-     CTRIA1  108       47      123      122      152      90.
 231-     CTRIA1  109       47      152      153      123      90.
 232-     CTRIA1  110       47      124      123      153      90.
 233-     CTRIA1  111       47      153      154      124      90.
 234-     CTRIA1  112       47      125      124      154      90.
 235-     CTRIA1  113       47      154      155      125      90.
 236-     CTRIA1  114       47      126      125      155      90.
 237-     CTRIA1  115       47      156      126      155
 238-     CTRIA1  152       47       35       36       25      90.
 239-     CTRIA1  170       47        4        3       44      90.
 240-     CTRIA1  171       47       33       34       44      90.
 241-     CTRIA1  172       47        5        4       45      90.
 242-     CTRIA1  173       47       34       35       45      90.
 243-     CTRIA1  179        3       34       33       49      90.
 244-     CTRIA1  180        3       63       64       49      90.
 245-     CTRIA1  181        3       35       34       53      90.
 246-     CTRIA1  182        3       64       65       53      90.
 247-     CTRIA1  183       47       36       35       54      90.
 248-     CTRIA1  184       47       65       66       54      90.
 249-     CTRIA2    1        1       14       13        8
 250-     CTRIA2    2        1       13        7        8
```

A-6

CARD COUNT	. 1 ..	2 ..	3 ..	4 ..	5 ..	6 ..	7 ..	8 ..	9 ..	10
						S O R T E D	B U L K	D A T A	E C H O		
251-	CTRIA2 3	1	13	6	7					
252-	CTRIA2 4	1	16	15	14					
253-	CTRIA2 5	1	13	14	15					
254-	CTRIA. 6	1	15	11	13					
255-	CTRIA2 7	1	6	13	11					
256-	CTRIA 8	1	11	5	6					
257-	CTRIA 9	1	10	4	11					
258-	CTRIA2 10	1	5	11	4					
259-	CTRIA2 11	1	11	15	9					
260-	CTRIA2 12	1	4	10	3					
261-	CTRIA2 13	1	10	9	3					
262-	CTRIA. 14	1	3	9	2					
263-	CTRIA2 24	67	36	6	25					
264-	CTRIA2 25	67	56	37	6		90.			
265-	CTRIA 26	67	37	46	6					
266-	CTRIA2 27	67	38	7	47					
267-	CTRIA 28	67	7	38	48					
268-	CTRIA2 29	67	39	8	48					
269-	CTRIA2 30	14	14	13	42					
270-	CTRIA 31	14	41	42	13					
271-	CTRIA2 32	14	13	12	41					
272-	CTRIA2 33	14	40	41	12					
273-	CTRIA2 34	14	36	40	12					
274-	CTRIA2 35	14	12	6	36					
275-	CTRIA 36	14	51	52	42					
276-	CTRIA2 37	14	42	41	51					
277-	CTRIA 38	14	50	51	41					
278-	CTRIA2 39	14	41	40	50					
279-	CTRIA2 40	2	39	42	38					
280-	CTRIA 41	2	42	41	38					
281-	CTRIA 42	22	41	40	37					
282-	CTRIA2 43	22	40	36	56					
283-	CTRIA2 54	4	67	68	36					
284-	CTRIA2 55	4	37	56	68					
285-	CTRIA2 56	4	68	69	37					
286-	CTRIA2 57	4	69	38	37					
287-	CTRIA2 58	4	38	69	70					
288-	CTRIA2 59	4	70	39	38					
289-	CTRIA2 60	14	40	36	72					
290-	CTRIA2 61	14	40	72	61					
291-	CTRIA 62	14	51	50	71					
292-	CTRIA 63	14	72	71	50					
293-	CTRIA2 64	14	71	72	101					
294-	CTRIA 65	14	102	101	72					
295-	CTRIA2 76	4	67	97	98					
296-	CTRIA 77	4	98	68	67					
297-	CTRIA2 78	4	68	98	99					
298-	CTRIA2 79	4	99	69	68					
299-	CTRIA2 80	4	69	99	100					
300-	CTRIA2 81	4	100	70	69					

CARD COUNT	• 1 • •	2 • •	3 • •	4 • •	5 • •	6 • • 7 • • 8 • • 9 • • 10
301-	CTRIA2 82	14	101	102	131	
302-	CTRIA2 83	14	103	131	102	
303-	CTRIA2 84	14	132	133	131	
304-	CTRIA2 85	14	131	103	132	
305-	CTRIA2 96	4	97	127	128	
306-	CTRIA2 97	4	128	98	97	
307-	CTRIA2 98	4	98	128	129	
308-	CTRIA2 99	4	129	99	98	
309-	CTRIA2 100	4	99	129	130	
310-	CTRIA2 101	4	130	100	99	
311-	CTRIA2 102	14	134	133	170	
312-	CTRIA2 103	14	167	170	133	
313-	CTRIA2 104	14	133	132	167	
314-	CTRIA2 105	14	165	167	132	
315-	CTRIA2 116	11	159	169	158	
316-	CTRIA2 117	11	169	168	158	
317-	CTRIA2 118	11	168	157	158	
318-	CTRIA2 119	11	168	169	170	
319-	CTRIA2 120	11	170	167	168	
320-	CTRIA2 121	11	157	168	167	
321-	CTRIA2 122	11	166	156	140	
322-	CTRIA2 123	11	166	167	164	
323-	CTRIA2 124	11	164	165	166	
324-	CTRIA2 125	11	156	166	165	
325-	CTRIA2 126	11	165	155	156	
326-	CTRIA2 127	11	155	164	163	
327-	CTRIA2 128	11	163	154	155	
328-	CTRIA2 129	11	154	163	162	
329-	CTRIA2 130	11	162	153	154	
330-	CTRIA2 131	21	153	162	161	
331-	CTRIA2 132	21	161	152	153	
332-	CTRIA2 133	21	152	161	160	
333-	CTRIA2 134	21	160	151	152	
334-	CTRIA2 135	4	156	157	127	
335-	CTRIA2 136	4	128	127	157	
336-	CTRIA2 137	4	157	158	128	
337-	CTRIA2 138	4	129	128	158	
338-	CTRIA2 139	4	158	159	129	
339-	CTRIA2 140	4	159	130	129	
340-	CTRIA2 141	14	126	166	103	
341-	CTRIA2 142	14	156	166	126	
342-	CTRIA2 143	220	158	178	179	
343-	CTRIA2 144	220	179	159	158	
344-	CTRIA2 147	14	103	166	132	
345-	CTRIA2 148	14	126	103	96	
346-	CTRIA2 149	14	102	96	103	
347-	CTRIA2 150	67	25	24	5	
348-	CTRIA2 151	67	24	25	6	
349-	CTRIA2 153	14	96	102	66	
350-	CTRIA2 154	14	72	66	102	

CARD COUNT	• 1 ••	2 ••	3 ••	4 ••	5 ••	6 ••	7 ••	8 ••	9 •• 10
				S O R T E D B U L K D A T A E C H O					
351-	CTRIA2 155	14	36	66	72				
352-	CTRIA2 156	22	40	37	56				
353-	CTRIA2 157	67	6	36	56				
354-	CTRIA2 158	7	16	81	15				
355-	CTRIA2 159	7	58	15	81				
356-	CTRIA2 160	7	15	58	10				
357-	CTRIA2 161	7	57	10	58				
358-	CTRIA2 162	7	10	57	4				
359-	CTRIA2 163	7	75	4	57				
360-	CTRIA2 164	11	140	157	167				
361-	CTRIA2 165	11	167	166	140				
362-	CTRIA2 174	67	46	37	47				
363-	CTRIA2 175	67	7	46	47	90.			
364-	CTRIA2 176	67	37	38	47	90.			
365-	CTRIA2 177	67	8	7	48	90.			
366-	CTRIA2 178	67	38	39	48	90.			
367-	CTRIA2 185	185	39	21	22				
368-	CTRIA2 186	186	21	74	22				
369-	CTRIA2 187	187	74	70	22				
370-	CTRIA2 188	187	70	74	105				
371-	CTRIA2 189	187	105	100	70				
372-	CTRIA2 190	187	100	105	139				
373-	CTRIA2 191	187	139	130	100				
374-	CTRIA2 192	187	130	139	169				
375-	CTRIA2 193	193	169	159	130				
376-	CTRIA2 194	5	75	4	76				
377-	CTRIA2 195	5	5	76	4				
378-	CTRIA2 196	5	76	5	24				
379-	CTRIA2 197	5	77	76	24				
380-	CTRIA2 198	5	6	77	24				
381-	CTRIA2 199	5	77	6	46				
382-	CTRIA2 200	5	46	78	77				
383-	CTRIA2 201	5	78	46	7				
384-	CTRIA2 202	5	7	79	78				
385-	CTRIA2 203	5	79	7	8				
386-	CTRIA2 204	5	8	80	79				
387-	CTRIA2 205	6	151	141	152				
388-	CTRIA2 206	6	142	152	141				
389-	CTRIA2 207	6	152	142	153				
390-	CTRIA2 208	6	143	153	142				
391-	CTRIA2 209	6	153	154	143				
392-	CTRIA2 210	6	144	154	143				
393-	CTRIA2 211	220	154	144	155				
394-	CTRIA2 212	220	145	155	144				
395-	CTRIA2 213	220	155	145	156				
396-	CTRIA2 214	220	146	156	145				
397-	CTRIA2 215	220	140	156	146				
398-	CTRIA2 216	220	146	147	140				
399-	CTRIA2 217	220	147	157	140				
400-	CTRIA2 218	220	157	147	178				

```
                              S O R T E D   B U L K   D A T A   E C H O
CARD
COUNT       .   1  ..    2  ..    3   ..    4  ..    5   ..    6  ..    7   ..    8  ..    9  ..   10
401-    CTRIA2  219     220      178       158      157
402-    CTRIA2  220     220      73        68       67
403-    CTRIA2  221     220      68        73       69
404-    CTRIA2  222     220      73        74       69
405-    CTRIA2  223     220      74        70       69
406-    CTRIA2  224     220      104       98       97
407-    CTRIA2  225     220      98        104      99
408-    CTRIA2  226     220      104       105      99
409-    CTRIA2  227     220      105       100      99
410-    CTRIA2  228     220      138       128      127
411-    CTRIA2  229     220      128       138      129
412-    CTRIA2  230     220      138       139      129
413-    CTRIA2  231     220      139       130      129
414-    FORCE   1       57       0         1000.    .0       .0       .454
415-    FORCE   1       58       0         1000.    .0       .0       .454
416-    FORCE   1       75       0         1000.    .0       -.527    7.85
417-    FORCE   1       76       0         1000.    .0       -.486    2.5
418-    FORCE   1       77       0         1000.    .0       -.728    -.26
419-    FORCE   1       78       0         1000.    .0       -.604    -3.266
420-    FORCE   1       79       0         1000.    .0       -.480    -5.226
421-    FORCE   1       80       0         1000.    .0       -.050    -3.595
422-    FORCE   1       81       0         1000.    .0       .0       .454
423-    FORCE   1       141      0         1000.    .0       -.113    -.953
424-    FORCE   1       142      0         1000.    .0       -.344    -.488
425-    FORCE   1       143      0         1000.    .0       -.394    -.263
426-    FORCE   1       144      0         1000.    .0       -.921    -.26
427-    FORCE   1       145      0         1000.    .0       -.794    .044
428-    FORCE   1       146      0         1000.    .0       -.422    .189
429-    FORCE   1       147      0         1000.    .0       -.283    .290
430-    FORCE   1       178      0         1000.    .0       -.235    .341
431-    FORCE   1       179      0         1000.    .0       -.188    .172
432-    GRAV    2       0        386.4     0.0      -9.25    -2.32
433-    GRID    1       1        12.5      180.0    0.0      1
434-    GRID    2       1        12.5      148.5    0.0      1
435-    GRID    3       1        12.5      119.0    0.0      1
436-    GRID    4       1        12.5      98.0     0.0      1
437-    GRID    5       1        12.5      90.0     0.0      1
438-    GRID    6       1        12.5      61.0     0.0      1
439-    GRID    7       1        12.5      22.0     0.0      1
440-    GRID    8       1        12.5      .0       0.0      1
441-    GRID    9       1        10.75     122.5    0.0      1
442-    GRID    10      1        8.73      101.5    0.0      1
443-    GRID    11      1        9.06      90.0     0.0      1
444-    GRID    12      1        10.87     56.5     0.0      1
445-    GRID    13      1        7.28      34.5     0.0      1
446-    GRID    14      1        6.0       .0       0.0      1
447-    GRID    15      1        4.12      90.0     0.0      1
448-    GRID    16      1        .0        .0       0.0      1
449-    GRID    17      2        .0        3.25     .0       2
450-    GRID    18      2        .0        6.5      4.25     2
```

SORTED BULK DATA ECHO

CARD COUNT	. 1 ..	2 ..	3 ..	4 ..	5 ..	6 ..	7 ..	8 ..	9 ..	10
451-	GRID	19	2	.0	3.25	4.25	2			
452-	GRID	20	2	.0	.0	4.25	2			
453-	GRID	21	2	.00	3.25	8.5	2			
454-	GRID	22	1	12.5	.0	11.5	1			
455-	GRID	23	1	12.5	0.0	39.6	1			
456-	GRID	24	1	12.5	75.5	.0	1			
457-	GRID	25	1	12.5	75.5	4.25	1			
458-	GRID	29	2	-9.0	.81	8.5	2			
459-	GRID	30	2	.0	.81	8.5	2			
460-	GRID	31	1	12.5	180.0	8.5	1			
461-	GRID	32	1	12.5	148.5	8.5	1			
462-	GRID	33	1	12.5	119.0	8.5	1			
463-	GRID	34	1	12.5	98.0	8.5	1			
464-	GRID	35	1	12.5	90.0	8.5	1			
465-	GRID	36	2	-10.96	.0	8.5	2			
466-	GRID	37	1	12.5	40.0	8.5	1			
467-	GRID	38	1	12.5	22.0	8.5	1			
468-	GRID	39	1	12.5	.0	8.5	1			
469-	GRID	40	1	10.82	56.3	8.5	2			
470-	GRID	41	1	7.6	38.0	8.5	1			
471-	GRID	42	1	6.0	.0	8.5	1			
472-	GRID	43	2	-4.5	.81	8.5	2			
473-	GRID	44	1	12.5	108.5	4.25	1			
474-	GRID	45	1	12.5	94.0	4.25	1			
475-	GRID	46	1	12.5	40.0	.0	1			
476-	GRID	47	1	12.5	31.0	4.25	1			
477-	GRID	48	1	12.5	11.0	4.25	1			
478-	GRID	49	1	12.5	108.5	12.5	1			
479-	GRID	50	2	-7.625	.0	12.0	2	5		
480-	GRID	51	2	-4.625	.0	12.0	2			
481-	GRID	52	2	.0	.0	12.0	2			
482-	GRID	53	1	12.5	94.0	12.5	1			
483-	GRID	54	1	12.5	75.5	12.5	1			
484-	GRID	55	2	-4.5	.81	16.5	2	5		
485-	GRID	56	1	12.5	51.5	8.5	1			
486-	GRID	57	1	8.73	101.5	-8.5	2			
487-	GRID	58	1	4.12	90.0	-8.5	2			
488-	GRID	59	2	-9.0	.81	16.5	2	5		
489-	GRID	60	2	.0	.81	16.5	2			
490-	GRID	61	1	12.5	180.0	16.5	1			
491-	GRID	62	1	12.5	148.5	16.5	1			
492-	GRID	63	1	12.5	119.0	16.5	1			
493-	GRID	64	1	12.5	98.0	16.5	1			
494-	GRID	65	1	12.5	90.0	16.5	1			
495-	GRID	66	2	-10.96	.0	16.5	2			
496-	GRID	67	1	12.5	51.5	17.5	2			
497-	GRID	68	1	12.5	33.7	17.5	1			
498-	GRID	69	1	12.5	22.	17.5	0			
499-	GRID	70	1	12.5	0.0	17.5	1			
500-	GRID	71	2	-7.625	.0	16.5	2			

SORTED BULK DATA ECHO

CARD COUNT	1	2	3	4	5	6	7	8	9	10
501-	GRID	72	2	-9.0	.0	16.5	2	5		
502-	GRID	73	2	-4.55	4.40	17.5	2			
503-	GRID	74	1	10.40	.0	17.5	1			
504-	GRID	75	1	12.5	98.0	-8.5	2			
505-	GRID	76	1	12.5	90.0	-8.5	1			
506-	GRID	77	1	12.5	61.0	-8.5	1			
507-	GRID	78	1	12.5	40.0	-8.5	1			
508-	GRID	79	1	12.5	22.0	-8.5	1			
509-	GRID	80	1	12.5	.0	-8.5	1			
510-	GRID	81	1	.0	.0	-8.5	2			
511-	GRID	87	2	-4.5	.81	24.84	2	5		
512-	GRID	89	2	-9.0	.81	24.84	2	5		
513-	GRID	90	2	.0	.81	24.84	2			
514-	GRID	91	1	12.5	180.0	24.84	1			
515-	GRID	92	1	12.5	148.5	24.84	1			
516-	GRID	93	1	12.5	119.0	24.84	1			
517-	GRID	94	1	12.5	98.0	24.84	1			
518-	GRID	95	1	12.5	90.0	24.84	1			
519-	GRID	96	2	-10.96	.0	24.84	2			
520-	GRID	97	1	12.5	51.5	24.84	2			
521-	GRID	98	1	12.5	35.71	24.84	1			
522-	GRID	99	1	12.5	22.	24.84	0			
523-	GRID	100	1	12.5	0.0	24.84	1			
524-	GRID	101	2	-7.625	.0	24.84	2			
525-	GRID	102	2	-9.0	.0	24.84	2	5		
526-	GRID	103	2	-9.0	.0	33.1	2	5		
527-	GRID	104	2	-4.55	4.15	24.84	2			
528-	GRID	105	1	10.15	.0	24.84	1			
529-	GRID	117	2	-4.5	.81	33.1	2	5		
530-	GRID	119	2	-9.0	.81	33.1	2	5		
531-	GRID	120	2	.0	.81	33.1	2			
532-	GRID	121	1	12.5	180.0	33.1	1			
533-	GRID	122	1	12.5	148.5	33.1	1			
534-	GRID	123	1	12.5	119.0	33.1	1			
535-	GRID	124	1	12.5	98.0	33.1	1			
536-	GRID	125	1	12.5	90.0	33.1	1			
537-	GRID	126	2	-10.96	.0	33.1	2			
538-	GRID	127	1	12.5	51.5	31.1	2			
539-	GRID	128	1	12.5	37.25	31.1	1			
540-	GRID	129	1	12.5	22.	31.1	0			
541-	GRID	130	1	12.5	0.0	31.1	1			
542-	GRID	131	2	-7.625	.0	33.1	2			
543-	GRID	132	2	-7.625	.0	38.1	2	5		
544-	GRID	133	2	-4.5	.0	38.1	2			
545-	GRID	134	2	.0	.0	38.1	2			
546-	GRID	135	2	.0	.81	38.1	2			
547-	GRID	136	2	-4.5	.81	38.1	2	5		
548-	GRID	137	2	-9.0	.81	38.1	2	5		
549-	GRID	138	2	-4.55	3.35	31.1	2			
550-	GRID	139	1	9.95	.0	31.1	1			

```
                        S O R T E D   B U L K   D A T A   E C H O
CARD
COUNT     .  1  ..  2  ..  3  ..  4  ..  5  ..  6  ..  7  ..  8  ..  9  ..  10
551-    GRID   140    1       12.5    51.5    41.1     1
552-    GRID   141    1       12.5    180.0   51.9     1
553-    GRID   142    1       12.5    144.0   51.9     1
554-    GRID   143    1       12.5    124.0   51.9     1
555-    GRID   144    1       12.5    100.0   51.9     1
556-    GRID   145    1       12.5    84.0    51.9     1
557-    GRID   146    2       -10.96  .0      51.9     1
558-    GRID   147    1       12.5    40.0    51.9     1
559-    GRID   148    2       -4.5    .81     41.1     2
560-    GRID   149    2       -9.0    .81     41.1     2
561-    GRID   150    2       .0      .81     41.1     2
562-    GRID   151    1       12.5    180.0   42.1     1
563-    GRID   152    1       12.5    144.0   41.959   1
564-    GRID   153    1       12.5    124.0   41.803   1
565-    GRID   154    1       12.5    100.0   41.334   1
566-    GRID   155    1       12.5    84.0    41.256   1
567-    GRID   156    2       -10.96  .0      41.1     1
568-    GRID   157    1       12.5    40.0    41.1     1
569-    GRID   158    1       12.5    19.5    41.1     1
570-    GRID   159    1       12.5    .0      41.1     1
571-    GRID   160    1       10.0    180.0   41.959   1
572-    GRID   161    1       9.5     144.0   41.878   1
573-    GRID   162    1       9.0     125.5   41.75    1
574-    GRID   163    1       8.0     100.0   41.3     1
575-    GRID   164    1       7.54    77.5    41.256   1
576-    GRID   165    1       7.52    80.0    41.256   1
577-    GRID   166    1       10.82   56.3    41.1     2
578-    GRID   167    1       7.5     37.0    41.1     1
579-    GRID   168    1       10.4    23.0    41.1     1
580-    GRID   169    1       9.58    .0      41.1     1
581-    GRID   170    1       6.0     .0      41.1     1
582-    GRID   178    1       12.5    19.5    51.9     1
583-    GRID   179    1       12.5    .0      51.9     1
584-    LOAD   3      1.8     1.0     1       1.0      2
585-    MAT1   1      1.03+7  3.9+6   .33     2.56-4                            12
586-    +2     75.+3  65.+3   42.+3
587-    MAT1   2      1.03+7  3.9+6   .33     2.6-4                             13
588-    +3     77.+3  64.+3   46.+3
589-    MAT1   3      1.03+7          .33     2.6-4                             114
590-    +14        74.+3   63.+3   43.+3
591-    MAT1   4      9.7+4   3.25+4                                            16
592-    +6     360.   360.    200.
593-    MAT1   5      29.+6   12.5+6  .3      7.4-4                             MTL5
594-    +TL5   75.+3  27.+3   50.+3
595-    MAT1   10     16.0+6  6.2+6
596-    MAT1   12     2.5+6   5.166+6         .14245-3
597-    MAT1   14     1.03+7  3.9+6   .33     2.6-4                             115
598-    +15    78.+3  69.+3   47.+3
599-    MAT1   16     1.05+7          .33     2.58-4                            184
600-    +84    61.+3  38.+3   38.+3
```

S O R T E D   B U L K   D A T A   E C H O

CARD COUNT	. 1	.. 2	.. 3	.. 4	.. 5	.. 6	.. 7	.. 8	.. 9	.. 10
601-	MAT1	117	1.01+7	3.85+6	.33	2.52-4				193
602-	+93	3.4+4	2.3+4	2.0+4						
603-	MAT1	200	3.0+4	7.0+4						SHEAR
604-	+HEAR									
605-	MAT2	7	8.6+6	.90+6		2.2+6		1.1+6	1.7-4	MTL7
606-	+TL7						50.+3	45.+3	15.+3	
607-	MAT2	8	9.9+6	.89+6		2.3+6		1.1+6	1.7-4	MTL8
608-	+TL8						50.+3	45.+3	15.+3	
609-	MAT2	9	9.2+6	.83+6		2.2+6		1.1+6		MTL9
610-	+TL9						50.+3	45.+3	15.+3	
611-	MAT2	13	7.4+6	.90+6		2.1+6		1.1+6	1.7-4	MTL13
612-	+TL13						50.+3	45.+3	15.+3	
613-	MAT2	40	2.344+6	1.291+6	0.0	1.743+7	0.0	1.6+6		
614-	MPC	1	67	2	1.0	59	2	-1.0		
615-	MPC	1	97	2	1.0	89	2	-1.0		
616-	MPC	1	127	2	1.0	119	2	-1.0		
617-	PARAM	GRDPNT	22							
618-	PBAR	5	3	.063	2.08-5	.00525	8.33-5			BAR5
619-	+AR5	.5	0.0	-.5	0.0					
620-	PBAR	10	3	.0276	3.6-6	.0011	1.47-4			BAR10
621-	+AR10	.35	0.0	-.35	0.0					
622-	PBAR	12	3	.08	6.35-3	.0114	4.27-5			172
623-	+72	0.0	0.0	-.77	-.26	0.0	.74			173
624-	+73	.417	.417							
625-	PBAR	13	3	.323	.266	.0006	4.26-4			174
626-	+74	0.0	0.0							175
627-	+75	.417	.417							
628-	PBAR	16	16	.0675	3.16-3	4.56-5	1.82-4			182
629-	+82	0.0	0.0							183
630-	+83	.834	.834							
631-	PBAR	17	117	.125	.163-4	.042	.042			187
632-	+87	0.0	0.0							188
633-	+88	.834	.834							
634-	PBAR	18	117	.25	.33	.083	.085			189
635-	+89	0.0	0.0							190
636-	+90	.834	.834							
637-	PBAR	19	117	.25	.0156	.083	.085			191
638-	+91	0.0	0.0							192
639-	+92	.834	.834							
640-	PBAR	20	117	.188	.141	.001	.141			194
641-	+94	0.0	0.0							195
642-	+95	.833	.833							
643-	PBAR	31	1	.16	4.33-3	1.44-2	5.38-4			131
644-	+31	0.0	0.0	0.0	0.275					1311
645-	+311	.416	.416							
646-	PBAR	32	1	.08	5.67-4	3.31-2	2.67-4			132
647-	+32	0.0	8.0	0.0	0.175					1321
648-	+321	.416	.416							
649-	PBAR	33	1	.16	1.43-3	4.36-3	3.73-3			133
650-	+33	8.0	0.0	0.0	0.238					1331

```
                            S O R T E D   B U L K   D A T A   E C H O
CARD
COUNT      .   1  ..   2  ..   3  ..   4  ..   5  ..   6  ..   7  ..   8  ..   9  ..  10
651-       +331        .208       .624
652-       PBAR   34        1         .28      6.89-2    2.39-2   9.30-4                        134
653-       +34         0.0        0.0  -.425     +.7      -.425     -.7                         1341
654-       +341        .416       .416
655-       PBAR   35        1         .468      .256      .20     1.56-3                         135
656-       +35         0.0        0.0  -.66     1.17      -.66    -1.17                         1351
657-       +351        .416       .416
658-       PBAR   36        1         .46       .267      .19     1.53-3                         136
659-       +36         0.0        0.0  -.65     1.088     -.65    -1.088                        1361
660-       +361        .416       .416
661-       PBAR   37        1         .40       .152      5.32-2  1.33-3                         137
662-       +37         0.0        0.8  -.745     .995      .515     .495    1.255   -.335       1371
663-       +371        .416       .416
664-       PBAR   38        1         1.053     1.447     .23     2.34-2                         138
665-       +38         0.0        0.0  1.725    -.235     -1.     -1.885    -1.      1.415       1381
666-       +381        .216       .618
667-       PBAR   39        2         .396      .119      .117    2.53-3                         139
668-       +39         0.0        0.0  -.547    1.378     1.076   -.272                         1391
669-       +391        .556       .278
670-       PBAR   40        2         .427      .095      .078    3.02-3                         140
671-       +40         0.0        0.0  -.386    1.224     1.114   -.276                         1401
672-       +401        .468       .365
673-       PBAR   41        2         .189      6.76-3    .018    7.00-4                         141
674-       +41         0.0        0.0  0.0       .605      -.45    -.295                         1411
675-       +411        .436       .396
676-       PBAR   42        2         .487      .133      .137    4.20-3                         142
677-       +42         0.0        0.0  -.273    1.167     1.377   -.483     .45     -.295       1421
678-       +421        .311       .523
679-       PBAR   43        2         .279      7.30-3    .029    2.80-3                         143
680-       +43         0.0        0.0  0.0       .52       .45     -.38    -.45     -.38        1431
681-       +431        .296       .538
682-       PBAR   44        2         .202      .073      .078    1.60-3                         144
683-       +44         0.0        0.0  .322     1.13      1.178   -.37                          1441
684-       +441        .39        .444
685-       PBAR   45        2         .314      .088      .076    1.01-3                         145
686-       +45         0.0        0.0  -.456    1.326     1.196   -.324                         1451
687-       +451        .483       .350
688-       PBAR   46        2         .540      .078      .123    8.50-3                         146
689-       +46         0.0        0.0  -.191    1.017     1.309   -.483                         1461
690-       +461        .256       .579
691-       PBAR   50        1         .256      .0192     .0595   7.16-4                         150
692-       +50         0.0        0.0  0.0      1.044     .76     -.416                         1501
693-       +501        .364       .453
694-       PBAR   51        1         .072      4.6-4     .9-3    2.02-4                         151
695-       +51         0.0        0.0  0.0       .362      .25     -.078                         1511
696-       +511        .37        .463
697-       PBAR   52        1         .081      6.45-4    2.185-3 2.30-4                         152
698-       +52         0.0        0.0  0.0       .343      .275    -.147                         1521
699-       +521        .370       .463
708-       PBAR   53        1         .22       .009      .0317   8.22-4                         153
```

```
                                     S O R T E D   B U L K   D A T A   E C H O
CARD
COUNT        .  1    ..  2   ..  3    ..  4   ..  5   ..  6   ..  7   ..  8   ..  9   .. 10
 701-      +53      0.0     C.0     0.0     1.129    .61     -.354                       1531
 702-      +531      .33     .5
 703-      PBAR    54      1       .159     .008     .0199   3.02-4                       154
 704-      +54      0.0     8.0     0.0      .834     .57     -.266                       1541
 705-      +541      .444    .389
 706-      PBAR    55      1       .17      .008     .218    3.60-4                       155
 707-      +55      0.0     0.0     C.0      .815     .57     -.285                       1551
 708-      +551      .416    .416
 709-      PBAR    56      1       .131    2.65-3   3.54-3   3.67-4                       156
 710-      +56      0.0     8.0     0.0      0.72     .41     -.05                        1561
 711-      +561      .372    .464
 712-      PBAR    57      1       .342     .13      .057    9.58-4                       157
 713-      +57      0.0     0.8    1.505     0.0     -.445    .99     -.455    -.99       1571
 714-      +571      .37     .463
 715-      PBAR    58      1       .33      .085     .0209   5.38-3                       158
 716-      +58      0.0     8.0     .852     0.0     -.273    .5      -.273    -.5        1581
 717-      +581      .202    .531
 718-      PBAR    59      1       .799     .359     .259    .013                        159
 719-      +59      0.0     8.0    2.221     0.0     -.324   1.21     -.324   -1.21       1591
 720-      +591      .202    .631
 721-      PBAR    60      1       .436     .266     .118    1.22-3                       160
 722-      +63      8.0     0.0    1.91      0.0     -.56    1.21     -.56    -1.21       1601
 723-      +601      .37     .462
 724-      PBAR    61      1       .311     .899     .0432   8.72-4                       161
 725-      +61      0.0     0.0    1.37      0.3     -.407    .865    -.407    -.865      1611
 726-      +611      .371    .464
 727-      PBAR    62      1       .176     .0252    .0103   4.63-4                       162
 728-      +62      0.0     0.0     .75     -.168    -.54    -.168    -.18     .562       1621
 729-      +621      .489    .346
 730-      PBAR    63      1       .212     .0285    .0587   1.04-3                       163
 731-      +63      C.0     0.0     .776    -.198    -.504   -.198    -.154    .532       1631
 732-      +631      .406    .430
 733-      PBAR    64      1       .249     .034     .0154   2.19-3                       164
 734-      +64      0.0     0.0     .798    -.226    -.492   -.226    -.132    .544       1641
 735-      +641      .345    .489
 736-      PBAR    70      2       .324     .07              .0012                        112
 737-      +12      0.0     0.0   -.778    1.0       .422    0.0      .422    1.75        113
 738-      +13      .474    .36
 739-      PBAR    72     14       .2      1.6-4    6.67-2   6.7-2                        1172
 740-      +172     .95     0.    -.05     0.        0.      1.0      0.      -1.0
 741-      PBAR    73     14       .5      2.6-3     .167    .169                         1173
 742-      +173     .125    0.    -.125    0.        0.      1.0      0.      -1.0
 743-      PBAR    94      3       .190    5.7-4     .0158   2.29-3                       BAR94
 744-      +AR94    .5      0.8   -.5      0.0
 745-      PBAR   105      3       .072    2.39-5    .008    9.57-5                       BAR105
 746-      +AR105   .57     0.0   -.57     0.0
 747-      PBAR   106      3       .089    2.95-5    .015    1.18-4                       BAR106
 748-      +AR106   .71     0.0   -.71     0.0
 749-      PBAR   107      3       .898    3.22-5    .0196   1.29-4                       BAR107
 750-      +AR107   .78     0.0   -.78     0.0
```

```
                            S O R T E D   B U L K   D A T A   E C H O
CARD
COUNT      .  1  ..  2  ..  3  ..  4  ..  5  ..  6  ..  7  ..  8  ..  9  .. 10  .
 751-      PBAR     108     3        .116    3.85-5  .0332   1.54-4                      BAR108
 752-      +AR108   .92     0.0      -.92    0.0                                         
 753-      PBAR     115     3        .0785   5.74-3  3.73-3  6.54-5                       BAR115
 754-      +AR115  -.435   -.635     .235    .535                                        AR115A
 755-      +R115A   .17     1.0                                                          
 756-      PBAR     121     14       .035    .00278  .0381   7.1-5                        PBAR121
 757-      +BAR121 -.146    .371     -.146   -.529   .42     -.195                        
 758-      PBAR     122     14       .085    .00278  .0381   7.1-5                        PBAR122
 759-      +BAR122 -.146   -.371     -.146   .523    .42     .195                         
 760-      PBAR     126     14       .2058   1.6-4   .0849   5.4-4              1         PBAR126
 761-      +BAR126  0.0     0.0      0.0     -1.176  0.0     1.144                         
 762-      PBAR     139     3        .39     .125    .195    .0013                        PBAR139
 763-      +BAR139 -.44    -1.56     -.44    .64     1.36    .64                          BAR139
 764-      +AR139   1.0     1.0                                                          
 765-      PBAR     140     3        .211    .061    .011                                PBAR140
 766-      +BAR140  .63    -.24      .63     .51     -.8     -.24    -.8      .51         BAR140
 767-      +AR140   1.0     1.0                                                          
 768-      PBAR     146     3        .234    .065    .0033   6.9-4                        PBAR146
 769-      +BAR146  0.0    -.45      1.01    0.0     -1.01   0.0                          BAR146
 770-      +AR146   1.0     1.0                                                          
 771-      PBAR     147     3        .27     .14     .022    3.4-4                        PBAR147
 772-      +BAR147  .75    -.66      -1.13   -.65    .75     .84     -1.13    .09         BAR147
 773-      +AR147   1.0     1.0                                                          
 774-      PBAR     148     3        .354    .312    .029    4.2-4                        PBAR148
 775-      +BAR148  .95    -.63      -1.57   -.63    .90     .87     -1.57    .09         BAR148
 776-      +AR148   1.0     1.0                                                          
 777-      PBAR     152     5        .114    .0043   .0168   .95-4                        PBAR152
 778-      +BAR152  .25     .69      .25     -.69    -.25    0.0                          BAR152
 779-      +AR152   1.0     1.0                                                          
 780-      PBAR     201     12       .1308   1.3131  1.      .6976-4 0.0                 PBAR201
 781-      +BAR201  .68     0.       -.68    0.      .67     0.      -.67     0.          PBAR201A
 782-      +BAR201A .4128   1.       0.                                                  
 783-      PBAR     202     12       .1304   1.1571  1.      .6955-4 0.0                 PBAR202
 784-      +BAR202  .67     0.       -.67    0.      .67     0.      -.67     0.          PBAR202A
 785-      +BAR202A .4110   1.       0.                                                  
 786-      PBAR     204     12       .1324   .9839   1.      .7061-4 0.0                 PBAR204
 787-      +BAR204  .70     0.       -.70    0.      .69     0.      -.69     0.          PBAR204A
 788-      +BAR204A .4199   1.       0.                                                  
 789-      PBAR     205     12       .1316   1.0587  1.      .7019-4 0.0                 PBAR205
 790-      +BAR205  .69     0.       -.69    0.      .68     0.      -.68     0.          PBAR205A
 791-      +BAR205A .4164   1.       0.                                                  
 792-      PBAR     211     12       .2910   1.2357  1.      .7012-3 0.0                 PBAR211
 793-      +BAR211  .67     0.       -.67    0.      .67     0.      -.67     0.          PBAR211A
 794-      +BAR211A .2302   1.       0.                                                  
 795-      PBAR     212     12       .29025  .29059  1.      .6987-3 0.0                 PBAR212
 796-      +BAR212  .67     0.       -.67    0.      .655    0.      -.655    0.          PBAR212A
 797-      +BAR212A .22825  1.       0.                                                  
 798-      PBAR     213     12       .28955  .29607  1.      .6962-3 0.0                 PBAR213
 799-      +BAR213  .655    0.       -.655   0.      .655    0.      -.655    0.          PBAR213A
 800-      +BAR213A .22625  1.       0.                                                  
```

```
                              S O R T E D   B U L K   D A T A   E C H O
CARD
COUNT       .  1  ..  2  ..  3  ..  4  ..  5  ..  6  ..  7  ..  8  ..  9  ..  10  .
801-    PBAR      214     12       .22145  .26377  1.      .3184-3 0.0              PBAR214
802-    +BAR214  .655     8.      -.655    0.      .68     0.     -.68             3.      PBAR214A
803-    +BAR214A .2412    1.       0.
804-    PBAR      215     12       .22245  .25345  1.      .3205-3 0.0              PBAR215
805-    +BAR215  .58      0.      -.68     0.      .68     0.     -.68             0.      PBAR215A
806-    +BAR215A .2446    1.       0.
807-    PELAS    2001    7.68+4           16.2
808-    PELAS    2002    2.76+6           18.2
809-    PELAS    2003    1.35+4           550.
810-    PELAS    2004    2.04+4           277.
811-    PQUAD1    200     40       .177    40      .122    200     1.60             PQU200
812-    +QU200   .81     -.81
813-    PQUAD1    201     40       .206    40      .141    200     1.60             PQU201
814-    +QU201   .81     -.81
815-    PQUAD1    202     40       .175    40      .120    200     1.60             PQU202
816-    +QU202   .81     -.81
817-    PQUAD1    203     40       .204    40      .140    200     1.62             PQU203
818-    +QU203   .81     -.81
819-    PQUAD1    204     40       .197    40      .135    200     1.62             PQU204
820-    +QU204   .81     -.81
821-    PQUAD1    205     40       .250    40      .171    200     1.60             PQU205
822-    +QU205   .81     -.81
823-    PQUAD1    206     40       .197    40      .135    200     1.62             PQU206
824-    +QU206   .81     -.81
825-    PQUAD1    207     40       .212    40      .145    200     1.62             PQU207
826-    +QU207   .81     -.81
827-    PQUAD1    208     10       .206    10      .141    200     1.60             PQU208
828-    +QU208   .81     -.81
829-    PQUAD1    209     10       .212    10      .145    200     3.31             PQU209
830-    +QU209   .81     -.81
831-    PROD      119    117       .125    .042    .5
832-    PSHEAR    118    117       .125
833-    PTRIA1    3      13        .042    7       7.3-4   4       .25     1.16-6  14
834-    +4       .194    -.157
835-    PTRIA1    47     8         .064    8       12.5-4  4       .25     1.16-6  1333
836-    +333     .141    -.141
837-    PTRIA2    1      1         0.1             11      1       .08
838-    PTRIA2    4      14        .09     .0
839-    PTRIA2    5      14        .098    .0
840-    PTRIA2    6      3         .050    .0      7       16      .008    .0
841-    PTRIA2    8      14        .950    0.0
842-    PTRIA2    14     16        .072
843-    PTRIA2    21     1         0.12            2       2       .11
844-    PTRIA2    22     2         0.16
845-    PTRIA2    67     8         .128
846-    PTRIA2    185    3         .38             186     3       .25
847-    PTRIA2    187    3         .053            193     3       .125
848-    PTRIA2    220    3         .04
849-    SPC1      1      123456    22
850-    SPC1      2      246       1       8       14      16      39      42      198
```

```
                              S O R T E D   B U L K   D A T A   E C H O
CARD
COUNT        •   1  ••   2  ••   3  ••   4  ••   5  ••   6  ••   7  ••   8  ••   9  ••  10
851-         +98     151     159     160       169     170       31       61       91    199
852-         +99    121     100     130      70     141     179      80      81
853-         SPC1   3      156      52      134      30       60       90      120       1533
854-         +533    150    135
855-         SPC1   77      246      23
856-         SPCADD  5       1        2        3       77
             ENDDATA
```

THIS PAGE LEFT INTENTIONALLY BLANK

APPENDIX B

NASTRAN ELEMENT STRESSES

BQM- COMPOSITE FUSELAGE FINE GRID MODEL — DECEMBER 18, 1975 - NASTRAN - 9/16/74 — PAGE 47
FREE FLIGHT-5G

CALC ONLY

STRESSES IN ROD ELEMENTS (C R O D)

ELEMENT ID.	AXIAL STRESS	SAFETY MARGIN	TORSIONAL STRESS	SAFETY MARGIN	ELEMENT ID.	AXIAL STRESS	SAFETY MARGIN	TORSIONAL STRESS	SAFETY MARGIN
890	1.025085E+03	1.7E+01	-9.613543E+00	2.1E+03	920	1.571204E+03	1.9E+01	1.032467E+01	2.0E+03

STRESSES IN SHEAR PANELS (C S H E A R)

ELEMENT ID.	MAX SHEAR	AVG SHEAR	SAFETY MARGIN	ELEMENT ID.	MAX SHEAR	AVG SHEAR	SAFETY MARGIN
143	1.329212E+03	1.329212E+03	1.4E+01	144	2.503327E+03	2.503327E+03	7.0E+00
145	2.733977E+03	2.733977E+03	6.3E+00	146	1.436218E+03	1.436218E+03	1.3E+01

STRESSES IN SCALAR SPRINGS (C E L A S 1)

ELEMENT ID.	STRESS	ELEMENT ID.	STRESS	ELEMENT ID.	STRESS
2018	-1.584551E+03	2019	-1.917241E+03	2020	-3.577154E+03	2021	1.009444E+05
2022	6.607431E+03	2023	-4.597779E+03	2024	-2.350494E+03	2025	-4.664450E+03
2026	2.736505E+03	2027	-7.307515E+03	2028	8.665799E+03	2029	1.435858E+04

BQM-34C COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-56

CALC ONLY

STRESSES IN GENERAL TRIANGULAR ELEMENTS (CTRIA)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM NORMAL-X	NORMAL-Y	SHEAR-XY	PRINCIPAL STRESSES (ZERO SHEAR) ANGLE	MAJOR	MINOR	MAX SHEAR
15	1.41000E-01	-8.064399E+02	-1.424596E+02	1.064297E+03	53.6630	6.404043E+02	-1.589364E+03	1.114884E+03
	-1.41000E-01	-2.303835E+03	-8.394782E+01	1.492181E+03	63.3217	6.658341E+02	-3.053617E+03	1.859725E+03
16	1.41000E-01	-7.558542E+02	-6.656857E+02	8.925607E+02	46.4618	1.024540E+02	-1.604994E+03	8.937240E+02
	-1.41000E-01	1.106651E+02	-8.529551E+01	1.753351E+03	43.4008	1.768771E+03	-1.743402E+03	1.756087E+03
17	1.41000E-01	-1.077333E+02	-1.383210E+02	1.767007E+03	44.7521	1.644046E+03	-1.890101E+03	1.767074E+03
	-1.41000E-01	-3.978972E+02	-2.434190E+02	2.465468E+03	45.8624	2.142928E+03	-2.790244E+03	2.466536E+03
18	1.41000E-01	-3.970285E+03	-1.325710E+03	1.740498E+03	73.3418	1.846502E+03	-4.491077E+03	3.168789E+03
	-1.41000E-01	-9.743133E+03	-2.687210E+03	5.987599E+02	85.1838	-2.636761E+03	-9.793583E+03	3.578411E+03
19	1.41000E-01	-3.771367E+03	1.157890E+03	4.587523E+03	59.1232	3.909941E+03	-6.514358E+03	5.207649E+03
	-1.41000E-01	-9.545101E+03	-1.493409E+03	2.601007E+03	73.5672	-7.262729E+02	-1.031224E+04	4.792982E+03
20	1.41000E-01	-2.653285E+04	1.735346E+03	4.899565E+03	80.4406	2.560474E+03	-2.735798E+04	1.495222E+04
	-1.41000E-01	-3.123517E+04	-2.108258E+03	2.981471E+03	84.9304	2.372754E+03	-3.149966E+04	1.693621E+04
21	1.41000E-01	-2.645939E+04	-1.387542E+03	-3.748532E+03	-82.2604	-8.780848E+02	-2.896885E+04	1.404538E+04
	-1.41000E-01	-2.989654E+04	3.711796E+03	-5.073804E+03	-61.5995	4.461076E+03	-3.064582E+04	1.755345E+04
22	1.41000E-01	-1.543438E+04	-3.432655E+03	-4.952289E+03	-74.1219	-2.024003E+03	-2.094303E+04	9.409516E+03
	-1.41000E-01	-1.361903E+04	3.568823E+03	-4.140687E+03	-80.2504	4.280296E+03	-2.052950E+04	1.240430E+04
23	1.41000E-01	-1.775130E+04	1.842025E+03	-2.163561E+03	-83.7762	2.077971E+03	-1.799725E+04	1.003761E+04
	-1.41000E-01	-1.943761E+04	3.600948E+03	-6.409108E+02	-88.4077	3.618764E+03	-1.945543E+04	1.153709E+04
44	1.41000E-01	-1.103981E+03	-1.416442E+03	1.305656E+03	41.5861	5.467030E+01	-2.572294E+03	1.314932E+03
	-1.41000E-01	-1.022773E+03	5.325597E+02	1.732180E+03	57.0589	1.653633E+03	-2.143847E+03	1.898740E+03
45	1.41000E-01	-1.461148E+03	-1.711337E+03	1.021737E+03	41.5099	-5.568758E+02	-2.615609E+03	1.029367E+03
	-1.41000E-01	-3.605262E+02	-1.091525E+03	1.340261E+03	37.3730	6.631785E+02	-2.115230E+03	1.389204E+03
46	1.41000E-01	7.630434E+02	1.703342E+03	2.603195E+03	50.1188	3.878503E+03	-1.412117E+03	2.645310E+03
	-1.41000E-01	-1.578284E+03	-1.905309E+03	2.342146E+03	43.0032	6.060506E+02	-4.089644E+03	2.347847E+03
47	1.41000E-01	-9.424787E+03	1.370935E+03	1.349284E+03	82.9828	1.537018E+03	-9.593870E+03	5.563444E+03
	-1.41000E-01	-1.214641E+04	-3.026209E+03	8.370278E+02	84.7994	-2.950025E+03	-1.222259E+04	4.536284E+03
48	1.41000E-01	-7.199676E+03	3.011940E+02	1.562481E+03	78.6914	6.136531E+02	-7.512136E+03	4.062894E+03
	-1.41000E-01	-9.441131E+03	-2.780680E+03	1.656709E+03	76.7754	-2.391351E+03	-9.830460E+03	3.719554E+03
49	1.04000E-01	-2.073344E+04	-8.693650E+02	1.300892E+03	85.2690	-7.845323E+02	-2.081827E+04	1.001587E+04
	-1.67000E-01	-1.739766E+04	2.794938E+03	1.993159E+03	84.4226	2.990766E+03	-1.759349E+04	1.029213E+04
50	1.04000E-01	-2.242970E+04	-3.701928E+03	-2.994081E+03	-80.9991	-3.227665E+03	-2.260396E+04	9.688149E+03
	-1.67000E-01	-1.564284E+04	6.206463E+03	-2.293739E+03	-84.0712	6.444658E+03	-1.588134E+04	1.116285E+04

BQM-3 - COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

CALC ONLY

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN GENERAL TRIANGULAR ELEMENTS STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR) (CTRIA1)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
51	1.04000E-01	-2.006281E+04	-4.204941E+03	-2.710199E+03	-80.5755	-3.755082E+03	-2.053267E+04	8.388796E+03
	-1.67000E-01	-1.306028E+04	6.083749E+03	-2.644767E+03	-82.2772	6.442407E+03	-1.341894E+04	9.930673E+03
52	1.41000E-01	-2.365348E+04	1.405495E+03	-3.882137E+03	-81.4021	1.992464E+03	-2.427045E+04	1.313145E+04
	-1.41000E-01	-2.137060E+04	3.818566E+03	-4.447125E+03	-80.2760	4.580646E+03	-2.213268E+04	1.335666E+04
53	1.41000E-01	7.615341E+03	2.791366E+03	-4.622718E+03	-31.2229	1.041749E+04	-1.078164E+01	5.214135E+03
	-1.41000E-01	3.688254E+03	-1.571503E+03	-4.500588E+03	-29.8503	6.271009E+03	-4.154258E+03	5.212634E+03
56	1.41000E-01	-1.881147E+03	-2.932650E+03	-6.138379E+02	-24.7073	-1.598718E+03	-3.215279E+03	8.082803E+02
	-1.41000E-01	-7.686892E+01	1.177317E+02	-5.067942E+02	-50.4340	5.364823E+02	-4.956175E+02	5.160499E+02
67	1.41000E-01	-1.654438E+03	-5.673898E+02	-2.020006E+01	-88.9358	-5.670146E+02	-1.654813E+03	5.438933E+02
	-1.41000E-01	-1.203006E+03	-3.166838E+02	-5.306725E+02	-66.1584	-8.215947E+02	-1.517520E+03	7.176753E+02
68	1.41000E-01	2.303246E+02	2.768095E+03	1.669628E+03	63.6217	3.596872E+03	-5.976974E+02	2.097334E+03
	-1.41000E-01	-2.805370E+03	-2.716469E+03	1.181084E+03	46.0774	-1.579910E+03	-3.942849E+03	1.181920E+03
69	1.41000E-01	-9.649318E+03	-1.028026E+03	9.799333E+01	89.5742	-1.028926E+03	-9.650217E+03	5.339571E+03
	-1.41000E-01	-1.409495E+04	-2.029287E+03	1.181084E+03	88.1996	-2.012569E+03	-1.409508E+04	4.201325E+03
70	1.05000E-01	-6.390990E+03	2.503245E+02	1.572773E+02	-88.9587	2.611795E+02	-2.203845E+03	6.325421E+03
	-1.67000E-01	-4.770507E+03	2.073423E+02	3.955651E+02	85.5952	2.097131E+02	-4.793436E+03	5.053086E+03
71	1.05000E-01	-1.011411E+04	-1.239083E+03	-1.018099E+03	83.0378	-1.012752E+03	-1.012606E+04	4.554354E+03
	-1.67000E-01	-8.021621E+03	-1.034498E+03	-5.178351E+02	87.2910	-1.019606E+03	-8.037739E+03	4.509426E+03
72	1.05000E-01	-1.106912E+04	-1.401450E+03	-2.890266E+03	-74.5270	-5.991592E+02	-1.187191E+04	5.636012E+03
	-1.67000E-01	-5.215866E+03	-2.242534E+03	-2.633454E+03	-78.5169	-1.247510E+03	-6.157003E+03	2.454913E+03
73	1.05000E-01	-6.353692E+03	-1.294604E+03	-1.671172E+03	-77.3403	-9.058067E+02	-8.726027E+03	3.909979E+03
	-1.67000E-01	-7.196495E+03	-2.365406E+03	-1.092491E+03	-79.0168	-2.726478E+03	-7.557009E+03	3.424325E+03
74	1.41000E-01	-1.139100E+04	-5.321063E+02	-3.662591E+03	-72.0730	-4.944311E+02	-1.251973E+04	6.507079E+03
	-1.41000E-01	-8.034129E+03	5.457910E+02	-4.015379E+03	-71.7552	-3.394059E+02	-1.166496E+04	6.752209E+03
75	1.41000E-01	-1.640144E+03	8.770486E+02	-2.376686E+03	-54.0506	1.634405E+03	-3.362254E+03	2.498330E+03
	-1.41000E-01	-9.408622E+01	4.168457E+02	-2.726003E+03	-47.6754	2.900918E+03	-2.578157E+03	2.739537E+03
86	1.41000E-01	-2.050099E+03	-1.417928E+03	-4.454136E+02	-52.6805	-1.187842E+03	-2.280185E+03	5.461717E+02
	-1.41000E-01	-2.492661E+03	3.895379E+02	-7.316801E+02	-76.5409	5.646406E+02	-2.667772E+03	1.616210E+03
87	1.41000E-01	-2.008545E+03	-1.672729E+03	-1.924926E+02	-84.0952	-1.473643E+03	-2.028454E+03	9.405448E+02
	-1.41000E-01	-2.306773E+03	-1.059769E+03	-7.233957E+02	-72.8555	3.618348E+01	-2.531933E+03	1.028454E+03
88	1.41000E-01	-1.008875E+03	2.209401E+03	8.591015E+02	75.9180	2.415906E+03	-1.224380E+03	1.820143E+03
	-1.41000E-01	-3.021030E+03	-1.611900E+03	6.206830E+02	67.4232	-1.550009E+03	-3.282921E+03	8.664565E+02

B-4

BQM-3.. COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

CALC ONLY

S T R E S S E S   I N   G E N E R A L   T R I A N G U L A R   E L E M E N T S   (C T R I A 1)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
89	1.410000E-01	-8.397933E+03	4.276098E+02	-4.320803E+02	-87.2038	4.487131E+02	-8.419036E+03	4.433875E+03
	-1.410000E-01	-8.163657E+03	-8.583332E+02	2.045088E+02	88.3977	-8.526125E+02	-8.169378E+03	3.658383E+03
90	1.040000E-31	-6.765177E+03	-4.208421E+02	-1.087046E+03	-80.5422	-2.397550E+02	-6.946264E+03	3.353255E+03
	-1.670000E-01	-4.338330E+03	1.791458E+03	-3.346738E+02	-86.3841	1.809677E+03	-4.356548E+03	3.083113E+03
91	1.040000E-01	-6.530891E+03	-6.276641E+02	-1.184401E+03	-79.0343	-3.975006E+02	-6.761155E+03	3.181827E+03
	-1.670000E-01	-6.037913E+03	5.553936E+02	-7.858315E+02	-83.2954	6.477722E+02	-6.129392E+03	3.388582E+03
92	1.040000E-01	-7.273017E+03	-1.511973E+03	-2.226667E+03	-71.1478	-7.516910E+02	-8.033298E+03	3.640904E+03
	-1.670000E-01	-4.278799E+03	3.297136E+03	-2.199760E+03	-74.9276	3.889539E+03	-4.871202E+03	4.380370E+03
93	1.040000E-01	-5.330574E+03	-1.898798E+03	-1.339699E+03	-73.6298	-7.103344E+02	-5.719037E+03	2.504351E+03
	-1.670000E-01	-5.155730E+03	1.108406E+03	-1.682759E+03	-75.8761	1.531832E+03	-5.579127E+03	3.555479E+03
94	1.410000E-01	-7.059998E+03	-7.956759E+02	-2.971821E+03	-58.2524	3.898188E+02	-8.245492E+03	4.317656E+03
	-1.410000E-01	-7.298742E+03	-1.011289E+01	-3.373653E+03	-68.6043	1.311714E+03	-8.620569E+03	4.966142E+03
95	1.410000E-01	-4.225249E+03	-2.811507E+02	-2.481712E+03	-64.2359	9.166378E+02	-5.423038E+03	3.169638E+03
	-1.410000E-01	-4.501317E+03	-3.249804E+02	-3.125036E+03	-61.8755	1.345348E+03	-6.171646E+03	3.758497E+03
106	1.410000E-01	-1.743285E+03	-5.077113E+02	1.814950E+02	81.6217	-4.809805E+02	-1.749016E+03	6.295175E+02
	-1.410000E-01	-2.023275E+03	2.055712E+02	-9.254303E+01	-87.6243	2.095144E+02	-2.027118E+03	1.118316E+03
107	1.410000E-01	-2.217000E+02	-8.477062E+02	1.938656E+01	1.7721	-2.211002E+02	-8.483060E+02	3.136029E+02
	-1.410000E-01	-2.103598E+02	-6.626815E+02	2.762859E+02	25.3485	-7.947357E+01	-7.935677E+02	3.570471E+02
108	1.410000E-01	1.069488E+03	-3.272372E+02	-2.610331E+02	-3.6389	1.087603E+03	-3.290487E+03	2.189045E+03
	-1.410000E-01	-6.561851E+02	-3.900607E+02	-4.586554E+02	-7.8937	-5.925926E+02	-3.964199E+03	1.685803E+03
109	1.410000E-01	-4.353077E+02	-5.611860E+03	2.603411E+02	2.8719	-4.222474E+02	-5.624920E+03	2.601336E+03
	-1.410000E-01	-4.456936E+02	-4.830284E+03	-2.620172E+02	-3.4078	-4.300913E+02	-4.845866E+03	2.207897E+03
110	1.410000E-01	-3.903670E+02	-6.144072E+03	9.679075E+02	9.2977	-2.319065E+02	-6.302533E+03	3.035313E+03
	-1.410000E-01	7.227955E+02	-4.983949E+03	1.413111E+02	1.4176	7.262925E+02	-4.987446E+03	2.856869E+03
111	1.410000E-01	-1.570402E+02	-2.172594E+03	2.581964E+02	6.7320	1.477341E+01	-2.203072E+03	1.109123E+03
	-1.410300E-01	-1.971820E+02	-3.961277E+03	5.787794E+01	.8807	-1.962922E+02	-3.962167E+03	1.882937E+03
112	1.410000E-01	-1.448276E+03	-4.340627E+03	1.387648E+03	21.9084	-8.902082E+02	-4.898694E+03	2.004243E+03
	-1.410000E-01	1.713431E+03	-2.346679E+03	1.328796E+03	16.6036	2.109654E+03	-2.742901E+03	2.426278E+03
113	1.410000E-01	-1.577565E+02	-3.138026E+03	1.405365E+03	21.6615	4.004132E+02	-3.696196E+03	2.048304E+03
	-1.410000E-01	-2.828868E+02	-5.265144E+03	1.720865E+03	17.3183	2.537043E+02	-5.801737E+03	3.027721E+03
114	1.410000E-01	-1.804826E+02	-2.354139E+03	2.256320E+03	32.1404	1.237120E+03	-3.771742E+03	2.504431E+03
	-1.410000E-01	-1.113922E+02	-2.876767E+03	2.793919E+03	31.8348	1.623260E+03	-4.611420E+03	3.117340E+03

BQM-34 COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-55

CALC ONLY

STRESSES IN GENERAL TRIANGULAR ELEMENTS (CTRIA 1)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
115	1.41000E-01	-9.062974E+03	-7.960617E+02	-3.559209E+03	-59.6346	5.251522E+02	-1.038419E+04	5.454670E+03
	-1.41000E-01	-8.148715E+03	-6.622530E+02	-3.712916E+03	-67.6165	8.668516E+02	-9.677819E+03	5.272336E+03
152	1.41000E-01	2.370120E+03	-7.645328E+03	4.771640E+02	2.7215	2.392802E+03	-7.668011E+03	5.030406E+03
	-1.41000E-01	1.383093E+03	-3.575343E+03	-2.773800E+02	-3.1919	1.398561E+03	-3.590811E+03	2.494685E+03
170	1.41000E-01	-1.548033E+03	-1.213477E+04	-6.587375E+03	-25.6080	1.609234E+03	-1.529204E+04	8.450530E+03
	-1.41000E-01	-2.185072E+03	-1.991864E+04	-4.817731E+03	-14.2046	-8.855866E+02	-2.113813E+04	1.012527E+04
171	1.41000E-01	8.061981E+02	-1.675195E+04	-2.584401E+03	-8.2017	1.178696E+03	-1.712444E+04	9.151570E+03
	-1.41000E-01	6.756670E+02	-1.655804E+04	-1.125223E+03	-3.7199	7.482455E+02	-1.663120E+04	8.690013E+03
172	1.41000E-01	-1.64260E+03	-1.814736E+04	6.922146E+03	19.9951	8.761268E+02	-2.066614E+04	1.077114E+04
	-1.41000E-01	-2.776514E+03	-3.158949E+04	7.438730E+03	13.6547	-9.694726E+02	-3.339663E+04	1.521358E+04
173	1.41000E-01	-4.492515E+03	-3.005719E+04	1.734172E+03	3.8631	-4.375513E+03	-3.017429E+04	1.289939E+04
	-1.41000E-01	8.779574E+03	-1.834902E+04	1.830725E+03	3.8433	8.902559E+03	-1.847200E+04	1.368728E+04
179	1.04000E-01	1.114549E+02	-1.594505E+04	-3.226687E+03	-10.9475	7.355921E+02	-1.656999E+04	8.652789E+03
	-1.67000E-01	6.060878E+02	-1.093730E+04	-2.098919E+03	-9.9921	9.758849E+02	-1.130710E+04	6.141492E+03
180	1.04000E-01	-7.602213E+02	-1.377065E+04	6.740776E+01	.2968	-7.598721E+02	-1.377100E+04	6.505566E+03
	-1.67000E-01	1.493468E+03	-1.433905E+04	-1.104234E+03	-3.9705	1.570112E+03	-1.441569E+04	7.992903E+03
181	1.04000E-01	-3.189822E+03	-2.362107E+04	3.593903E+03	9.6911	-2.576082E+03	-2.423481E+04	1.082936E+04
	-1.67000E-01	9.486039E+03	-9.166315E+03	3.437698E+03	10.1171	1.009945E+04	-9.779723E+03	9.939585E+03
182	1.04000E-01	-2.150524E+03	-1.790539E+04	2.102492E+03	7.4720	-1.874772E+03	-1.815114E+04	8.153183E+03
	-1.67000E-01	5.424080E+03	-1.883347E+04	1.521655E+03	3.5754	5.519160E+03	-1.892855E+04	1.222386E+04
183	1.41000E-01	2.567935E+03	-6.544110E+03	6.102838E+03	26.6285	5.627815E+03	-9.603390E+03	7.615303E+03
	-1.41000E-01	9.957950E+02	-6.784293E+03	5.171333E+03	26.5242	3.576851E+03	-9.365349E+03	6.471100E+03
184	1.41000E-01	1.060504E+02	-6.646116E+03	2.637068E+03	18.9951	1.014614E+03	-7.553679E+03	4.284246E+03
	-1.41000E-01	6.229751E+02	-5.650631E+03	3.612387E+03	24.5154	2.270404E+03	-7.298060E+03	4.784232E+03

BQM-3 COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-56

CALC ONLY

STRESSES IN GENERAL TRIANGULAR ELEMENTS (CTRIA2)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
1	-5.000000E-02	-1.360221E+03	-1.022184E+02	-9.729043E+02	-61.4417	4.273075E+02	-1.889747E+03	1.158527E+03
	5.000000E-02	-1.620354E+03	4.818369E+02	-1.236959E+03	-65.1780	1.053969E+03	-2.192486E+03	1.623228E+03
2	-5.000000E-02	-1.239876E+02	-1.173665E+03	1.104067E+03	32.3405	5.700671E+02	-1.872719E+03	1.221393E+03
	5.000000E-02	5.262525E+02	-8.585501E+02	1.142750E+03	29.3940	1.170901E+03	-1.502299E+03	1.336150E+03
3	-5.000000E-02	-5.795767E+02	-5.533576E+01	-1.069079E+03	-51.8881	7.832873E+02	-1.418200E+03	1.100744E+03
	5.000000E-02	-1.207929E+02	1.426812E+03	-6.840632E+02	-69.2612	1.685828E+03	-3.798083E+02	1.032818E+03
4	-5.000000E-02	1.399059E+03	8.389907E+02	-1.545174E+03	-39.8639	2.689369E+03	-4.513196E+02	1.570344E+03
	5.000000E-02	-7.972042E+02	1.330098E+03	-5.333001E+02	-76.6057	1.456306E+03	-9.234113E+02	1.189858E+03
5	-5.000000E-02	-1.673355E+03	-3.956913E+02	-1.830641E+03	-54.6186	9.043822E+02	-2.973428E+03	1.938905E+03
	5.000000E-02	-1.171255E+03	1.187326E+03	-1.151759E+03	-67.8383	1.656451E+03	-1.640381E+03	1.648416E+03
6	-5.000000E-02	1.026727E+02	1.841638E+03	-9.639568E+02	-66.0251	2.270313E+03	-3.260021E+02	1.298157E+03
	5.000000E-02	1.439204E+02	-3.078771E+01	-9.842404E+02	-42.4641	1.044676E+03	-9.315429E+02	9.881093E+02
7	-5.000000E-02	-5.888466E+02	-1.433163E+02	-1.753584E+03	-48.6199	1.401595E+03	-2.133758E+03	1.767676E+03
	5.000000E-02	-5.450276E+02	2.011430E+02	-1.035091E+03	-54.9105	9.283336E+02	-1.272210E+03	1.100276E+03
8	-5.000000E-02	-1.365999E+03	-2.764029E+02	-1.562895E+03	-54.7719	8.272444E+02	-2.489646E+03	1.658445E+03
	5.000000E-02	1.681914E+03	4.559150E+02	-1.044037E+03	-29.7905	2.279610E+03	-1.417801E+02	1.210595E+03
9	-5.000000E-02	1.732659E+03	5.143949E+03	-9.193558E+02	-75.8375	5.375941E+03	1.500666E+03	1.337638E+03
	5.000000E-02	-5.617595E+02	-3.416321E+03	-1.382163E+03	-22.0400	-2.207581E+00	-3.975873E+03	1.936333E+03
10	-5.000000E-02	-2.678671E+03	-7.258763E+02	-2.479169E+03	-55.7483	9.622398E+02	-4.366787E+03	2.664513E+03
	5.000000E-02	3.218392E+03	1.644196E+03	-2.027012E+02	-7.2208	3.244074E+03	1.618514E+03	8.127803E+02
11	-5.000000E-02	1.169613E+03	2.943784E+03	-3.992842E+02	-77.8036	3.029503E+03	1.083894E+03	9.720046E+02
	5.000000E-02	-1.810015E+03	-3.820800E+03	-1.352224E+03	-26.6844	-1.130378E+03	-4.500438E+03	1.685030E+03
12	-5.000000E-02	-5.192969E+02	4.748321E+02	-5.890431E+02	-65.0797	7.465107E+02	-7.929755E+02	7.707431E+02
	5.000000E-02	2.952444E+02	-2.974331E+03	-1.232967E+03	-18.5119	7.080746E+02	-3.387161E+03	2.047618E+03
13	-5.000000E-02	1.666855E+03	4.418247E+03	-2.210762E+02	-65.4353	4.435897E+03	1.649204E+03	1.393347E+03
	5.000000E-02	-2.416256E+03	-3.902712E+03	1.336962E+03	30.4644	-1.629877E+03	-4.689090E+03	1.529606E+03
14	-5.000000E-02	4.749098E+03	1.336906E+03	-1.613824E+03	-21.7040	5.391446E+03	6.945567E+02	2.348455E+03
	5.000000E-02	-3.662264E+03	-2.340845E+03	6.990967E+02	56.6915	-2.039643E+03	-3.963465E+03	9.619112E+02
24	-6.400000E-02	2.983215E+02	-7.970310E+02	3.062551E+02	14.6067	3.781335E+02	-8.768430E+02	6.274883E+02
	6.400000E-02	1.082719E+03	1.046527E+03	-1.085637E+03	-44.5225	2.150411E+03	-2.116510E+01	1.085788E+03
25	-6.400000E-02	-4.155854E+02	-6.667996E+03	-2.727564E+03	-20.5521	6.070364E+02	-7.690617E+03	4.148827E+03
	6.400000E-02	-2.641147E+02	-6.122991E+03	-2.576484E+03	-20.6661	7.077132E+02	-7.094819E+03	3.901266E+03

BQM-34E COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-56

CALC ONLY

S T R E S S E S   I N   G E N E R A L   T R I A N G U L A R   E L E M E N T S   (C T R I A 2)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
26	-6.400000E-02	5.363581E+03	2.298703E+02	2.573909E+02	2.8631	5.376453E+03	2.169977E+02	2.579728E+03
	6.400000E-02	5.207374E+03	5.602471E+02	2.995419E+02	3.6729	5.226602E+03	5.410190E+02	2.342791E+03
27	-6.400000E-02	1.187728E+04	3.338943E+02	1.214011E+03	5.9392	1.200357E+04	2.075992E+02	5.897987E+03
	6.400000E-02	1.119933E+04	-1.134070E+03	1.291569E+03	5.9146	1.133313E+04	-1.267873E+03	6.300502E+03
28	-6.400000E-02	1.241385E+04	1.726951E+03	5.074413E+02	2.7149	1.242792E+04	1.702888E+03	5.362514E+03
	6.400000E-02	1.062946E+04	-2.639014E+03	4.440765E+02	1.9148	1.064430E+04	-2.653860E+03	6.649082E+03
29	-6.400000E-02	1.263462E+04	1.543803E+03	5.957305E+02	3.0658	1.266653E+04	1.511896E+03	5.577316E+03
	6.400000E-02	1.119647E+04	-2.528500E+03	5.966962E+02	2.4843	1.224436E+04	-2.554369E+03	6.889276E+03
30	3.600000E-02	-2.255643E+03	-1.630044E+03	3.499431E+03	-46.5359	1.436624E+03	-5.572310E+03	3.504467E+03
	3.600000E-02	-1.982241E+03	-1.367611E+03	3.652203E+03	-47.4049	1.990104E+03	-5.340035E+03	3.665109E+03
31	3.600000E-02	-1.896357E+03	-9.806253E+02	3.013002E+03	-49.2832	1.605503E+03	-4.409465E+03	3.045094E+03
	3.600000E-02	-1.754466E+03	-6.720556E+02	3.047384E+03	-50.0352	1.831816E+03	-4.300318E+03	3.050507E+03
32	3.600000E-02	-1.665717E+03	-9.054271E+02	3.091075E+03	-46.6096	2.962770E+03	-5.239195E+03	4.085343E+03
	3.600000E-02	-1.613033E+03	-9.962779E+02	3.982138E+03	-48.6627	3.512940E+03	-5.168750E+03	4.149907E+03
33	3.600000E-02	-8.594959E+02	5.737482E+02	3.266092E+03	-51.1077	3.200912E+03	-3.495660E+03	3.437366E+03
	3.600000E-02	-6.073405E+02	4.073495E+02	3.543543E+03	-50.6428	3.379205E+03	-3.547904E+03	3.443464E+03
34	3.600000E-02	-1.619757E+02	7.011990E+02	4.681107E+03	-47.6150	5.023422E+03	-4.784190E+03	4.903306E+03
	3.600000E-02	-7.772054E+02	4.022264E+02	4.697994E+03	-47.6011	4.901905E+03	-4.955534E+03	4.928534E+03
35	3.600000E-02	1.803265E+03	9.500565E+02	5.140942E+03	-54.0540	6.110069E+03	-4.163940E+03	5.146004E+03
	3.600000E-02	1.000782E+03	1.019604E+03	5.241909E+03	-45.5604	6.241315E+03	-4.194758E+03	5.243037E+03
36	3.600000E-02	6.669321E+02	2.593400E+03	2.593400E+03	-29.1786	2.115060E+03	-9.725005E+02	5.073055E+03
	3.600000E-02	6.207752E+02	2.043146E+03	2.043146E+03	-29.6498	2.091848E+03	-9.931846E+02	5.013048E+03
37	3.600000E-02	-2.327034E+03	2.353355E+03	1.366480E+03	-64.7240	9.736535E+02	-3.706745E+03	2.365465E+03
	3.600000E-02	-1.637653E+03	2.504704E+03	1.208932E+03	-59.0735	5.137405E+02	-2.409072E+03	2.461065E+03
38	3.600000E-02	2.694415E+03	1.324186E+03	1.058376E+03	-26.5126	7.974188E+02	-1.352153E+03	1.324791E+03
	3.600000E-02	5.470710E+02	3.186963E+03	8.781442E+02	-61.2956	1.318421E+03	-4.526534E+03	8.055371E+02
39	-3.600000E-02	1.247704E+03	2.556736E+03	1.187395E+03	-55.0378	5.734063E+02	1.954984E+03	1.264195E+03
	3.600000E-02	3.082559E+03	2.174686E+03	1.355745E+03	-66.6934	2.758748E+03	9.723179E+02	1.365533E+03
40	5.500000E-02	1.726846E+03	1.425442E+03	4.559015E+03	46.0534	6.137649E+03	2.905362E+03	4.561505E+03
	5.500000E-02	1.702958E+03	4.597801E+03	4.611232E+03	43.3147	6.050593E+03	3.187053E+03	4.692223E+03
41	5.500000E-02	1.467360E+03	2.702174E+01	3.524626E+03	-50.9845	2.982786E+03	4.323124E+03	3.602355E+03
	5.500000E-02	1.557017E+03	3.146601E+01	3.560573E+03	-51.2874	2.865306E+03	4.100577E+03	3.648081E+03

BQM-34 COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-55

CALC CVLF

S T R E S S E S   I N   G E N E R A L   T R I A N G U L A R   E L E M E N T S   (C T R I A 2)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
42	-8.000000E-02	-1.206769E+03	-7.061127E+02	-2.096971E+03	-48.4172	1.156538E+03	-3.067419E+03	2.111979E+03
	8.000000E-02	-1.177620E+03	-1.426253E+02	-2.392825E+03	-51.1017	1.788022E+03	-3.108267E+03	2.448145E+03
43	-8.000000E-02	5.917503E+01	1.797866E+03	-1.692533E+03	-58.5933	2.831263E+03	-9.742225E+02	1.902743E+03
	8.000000E-02	6.910140E+02	2.682845E+03	-1.539246E+03	-62.7251	3.676456E+03	-1.025967E+02	1.889526E+03
54	-4.500000E-02	-3.723328E+03	-2.159643E+04	-1.074613E+02	-.3445	-3.722682E+03	-2.159712E+04	8.937222E+03
	4.500000E-02	-2.322678E+03	-2.068208E+04	5.421261E+02	1.6899	-2.306684E+03	-2.069808E+04	9.195697E+03
55	-4.500000E-02	4.297809E+03	9.560344E+03	9.844566E+03	52.4821	1.711922E+04	-3.261068E+03	1.019014E+04
	4.500000E-02	4.980191E+03	1.194404E+04	1.055931E+04	54.1250	1.958070E+04	-2.655468E+03	1.111858E+04
56	-4.500000E-02	-9.369547E+02	3.631160E+03	-3.294290E+03	-62.3675	5.355756E+03	-2.661530E+03	4.008643E+03
	4.500000E-02	1.599401E+03	4.709696E+03	-2.280462E+03	-52.1459	5.914800E+03	3.942962E+02	2.760252E+03
57	-4.500000E-02	1.208610E+04	6.734238E+03	-3.331212E+03	-25.6127	1.368306E+04	5.137281E+03	4.272890E+03
	4.500000E-02	1.373652E+04	7.122581E+03	-3.666142E+03	-23.9743	1.536682E+04	5.492280E+03	4.937270E+03
58	-4.500000E-02	1.111708E+04	2.371205E+03	2.829378E+03	16.4518	1.195260E+04	1.535692E+03	5.205453E+03
	4.500000E-02	1.210008E+04	3.590279E+03	2.774331E+03	16.5528	1.292465E+04	2.765702E+03	5.079476E+03
59	-4.500000E-02	1.515514E+04	7.809188E+03	5.352548E+02	4.1456	1.519394E+04	7.770392E+03	3.711774E+03
	4.500000E-02	1.554093E+04	8.383664E+03	6.116622E+02	4.8497	1.559282E+04	8.331767E+03	3.630528E+03
60	-3.500000E-02	-2.617007E+02	4.107976E+02	-3.127086E+03	-48.0687	3.219661E+03	-3.070564E+03	3.145113E+03
	3.600000E-02	3.123665E+02	2.196892E+03	-3.106718E+03	-53.4362	4.501097E+03	-1.991839E+03	3.246468E+03
61	-3.600000E-02	2.410241E+03	3.278760E+03	9.742391E+02	57.0126	3.911114E+03	1.777887E+03	1.066513E+03
	3.600000E-02	2.296717E+03	3.122414E+03	1.209096E+03	54.4263	3.987203E+03	1.431929E+03	1.277637E+03
62	-3.600000E-02	2.685542E+02	-1.642061E+03	-1.813076E+03	-31.1077	1.362602E+03	-2.736109E+03	2.043355E+03
	3.600000E-02	-2.029221E+02	-1.636824E+03	-1.799500E+03	-34.1247	1.016562E+03	-2.858308E+03	1.937435E+03
63	-3.600000E-02	-4.955727E+02	-1.362574E+03	1.111021E+03	31.1459	4.758536E+02	-2.034000E+03	1.254927E+03
	3.600000E-02	-7.035285E+02	-2.236673E+03	9.931101E+02	26.1679	-2.155488E+02	-2.724653E+03	1.254552E+03
64	-3.600000E-02	-2.806334E+02	-1.622186E+03	-1.414995E+03	-32.3113	6.137124E+02	-2.516531E+03	1.565122E+03
	3.600000E-02	-4.942396E+02	-1.600612E+03	-1.487979E+03	-34.8032	5.400552E+02	-2.634907E+03	1.587481E+03
65	-3.600000E-02	1.476098E+02	-3.723357E+02	7.511246E+01	8.0576	1.582433E+02	-3.829691E+02	2.705062E+02
	3.600000E-02	4.309594E+02	-1.067312E+03	1.178087E+02	4.4686	4.401661E+02	-1.076519E+03	7.583426E+02
76	-4.500000E-02	-8.147165E+03	-1.561724E+03	-1.993615E+03	-74.4034	-1.005223E+03	-8.703666E+03	3.849221E+03
	4.500000E-02	-8.772143E+03	-1.756255E+03	-2.030539E+03	-74.9680	-1.210958E+03	-9.317440E+03	4.053241E+03
77	-4.500000E-02	6.336436E+03	4.444343E+03	-1.097960E+04	-42.5376	1.641073E+04	-5.629369E+03	1.102028E+04
	4.500000E-02	6.108058E+03	4.030127E+03	-1.162677E+04	-42.3491	1.678582E+04	-6.567631E+03	1.167672E+04

BQM-34E COMPOSITE FUSELAGE FINE GRID MODEL ———— DECEMBER 18, 1975 NASTRAN 9/16/74

FREE FLIGHT-5G

CALC ONLY

S T R E S S E S   I N   G E N E R A L   T R I A N G U L A R   E L E M E N T S   (C T R I A 2)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM NORMAL-X	NORMAL-Y	SHEAR-XY	PRINCIPAL STRESSES (ZERO SHEAR) ANGLE	MAJOR	MINOR	MAX SHEAR
78	-4.50000E-02	4.346555E+03	1.159600E+02	-1.463267E+03	-15.8713	5.262585E+03	-3.000700E+02	2.781327E+03
	4.50000E-02	4.024736E+03	-2.377132E+02	-1.515670E+03	-15.3325	5.240302E+03	-7.032792E+02	2.971791E+03
79	-4.50000E-02	1.158425E+04	5.216494E+03	-7.680061E+03	-33.7415	1.671426E+04	8.643077E+01	8.313887E+03
	4.50000E-02	9.623649E+03	-3.079049E+02	-7.194563E+03	-27.6929	1.339968E+04	-4.083938E+03	8.741810E+03
80	-4.50000E-02	9.586409E+03	3.769782E+02	-1.487311E+03	-8.9502	9.820649E+03	1.427374E+02	4.839566E+03
	4.50000E-02	1.067307E+04	1.657613E+03	-5.936590E+02	-3.7500	1.071196E+04	1.618715E+03	4.546246E+03
81	-4.50000E-02	1.443194E+04	1.521661E+03	-3.563556E+03	-14.4703	1.535315E+04	6.044950E+02	7.376350E+03
	4.50000E-02	1.745930E+04	7.302268E+03	-4.664679E+03	-21.2839	1.927642E+04	5.485093E+03	6.895590E+03
82	-3.60000E-02	-7.348701E+02	-4.192119E+03	6.178304E+02	9.8337	-6.277775E+02	-4.299211E+03	1.835717E+03
	3.60000E-02	-5.507802E+02	-2.896680E+03	6.717558E+02	14.9000	-3.720396E+02	-3.075421E+03	1.351630E+03
83	-3.60000E-02	-1.071219E+03	-4.285936E+03	-2.252795E+02	-3.9891	-1.055509E+03	-4.301694E+03	1.623093E+03
	3.60000E-02	-4.535397E+02	-3.349403E+03	-1.642611E+02	-2.4687	-4.462215E+02	-3.356405E+03	1.908533E+03
84	-3.60000E-02	-3.103515E+03	-3.714646E+03	-5.095109E+02	-29.5240	-2.814966E+03	-4.003194E+03	5.341140E+02
	3.60000E-02	-3.046014E+03	-4.251133E+03	-3.715965E+02	-15.0310	-2.940646E+03	-4.355501E+03	7.079279E+02
85	-3.60000E-02	-8.705862E+01	-2.665532E+03	2.091965E+03	28.1115	1.030485E+03	-3.003755E+03	2.051673E+03
	3.60000E-02	2.306522E+01	-3.072020E+03	2.052896E+03	26.4949	1.046373E+03	-4.095327E+03	2.057095E+03
86	-4.50000E-02	2.150193E+03	8.050350E+02	-7.637811E+03	-38.9329	1.032037E+04	-4.003042E+03	7.012356E+03
	4.50000E-02	2.026303E+03	-1.697527E+02	-6.855770E+03	-36.8371	1.345801E+04	-5.345342E+03	7.017266E+03
97	-4.50000E-02	5.049748E+03	1.073053E+03	-7.432129E+03	-38.7064	1.100536E+04	-4.224958E+03	7.615159E+03
	4.50000E-02	4.721362E+03	1.649397E+03	-7.372409E+03	-39.1055	1.071393E+04	-4.043360E+03	7.053126E+03
98	-4.50000E-02	4.711339E+03	9.211348E+03	5.771450E+03	-32.4699	7.507568E+03	-3.027010E+03	5.267293E+03
	4.50000E-02	4.186620E+03	-7.748738E+00	4.572961E+03	-32.6810	7.120361E+03	-2.941432E+03	5.030921E+03
99	-4.50000E-02	7.305504E+03	1.957380E+03	-7.266992E+03	-34.8969	1.237401E+04	-3.110928E+03	7.532726E+03
	4.50000E-02	6.242923E+03	-3.336610E+02	-6.744680E+03	-32.0033	1.045800E+04	-5.549443E+03	7.503724E+03
100	-4.50000E-02	6.457297E+03	3.094797E+02	-2.691530E+03	-20.6028	7.469125E+03	7.023483E+02	4.035737E+03
	4.50000E-02	7.232659E+03	1.076241E+02	-1.679886E+03	-15.7323	7.705878E+03	-1.269190E+02	3.216339E+03
101	-4.50000E-02	8.076044E+03	-1.200195E+03	-3.992142E+03	-16.0404	1.498801E+04	2.403555E+03	7.914966E+03
	4.50000E-02	8.162047E+03	-3.094999E+03	-3.941943E+03	-22.0675	1.329063E+04	2.281603E+03	5.050595E+03
102	-3.60000E-02	9.630752E+03	9.516273E+02	5.547871E+02	-93.1942	1.047839E+04	3.699664E+03	2.357016E+03
	3.60000E-02	5.088045E+03	-4.214609E+02	2.457070E+02	-86.9933	4.085511E+02	5.160955E+03	2.346522E+03
103	-3.60000E-02	-2.225203E+03	-7.524255E+01	1.056498E+02	87.1935	-7.006336E+01	-2.230303E+03	1.080160E+03
	3.60000E-02	-2.292843E+03	-3.632203E+03	1.052692E+03	66.2531	9.992008E+01	-2.755971E+03	1.427905E+03

BQM-34 COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5S

CALC ONLY

S T R E S S E S   I N   G E N E R A L   T R I A N G U L A R   E L E M E N T S   (C T R I A 2)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
104	-3.600000E-02	-1.986818E+03	3.510136E+02	-6.515542E+02	-75.4323	5.203380E+02	-2.156142E+03	1.338240E+03
	3.600000E-02	-1.565843E+03	-4.474910E+02	-1.273394E+02	-83.5855	-4.331750E+02	-1.580159E+03	5.734918E+02
105	-3.600000E-02	-2.552747E+03	-3.212276E+03	-1.658655E+03	-39.3777	-1.191393E+03	-4.573629E+03	1.691118E+03
	3.600000E-02	-2.950682E+03	-4.398483E+03	-1.404447E+03	-31.3659	-2.094550E+03	-5.254616E+03	1.580033E+03
116	-4.000000E-02	-1.102163E+03	-1.924850E+03	9.062599E+02	32.7936	-5.182630E+02	-2.508751E+03	9.952438E+02
	4.000000E-02	-1.392400E+03	-1.769993E+03	7.020374E+02	37.4739	-8.542164E+02	-2.308177E+03	7.269504E+02
117	-4.000000E-02	-1.994603E+03	-8.217836E+02	-3.408606E+02	-74.9160	-7.299143E+02	-2.086473E+03	6.782791E+02
	4.000000E-02	-1.181676E+03	1.947792E+03	-1.473652E+03	-68.3585	2.532487E+03	-1.766371E+03	2.149429E+03
118	-4.000000E-02	-1.004410E+03	-3.291550E+02	-2.732512E+02	-70.5079	-2.324347E+02	-1.101131E+03	4.343480E+02
	4.000000E-02	-2.348289E+03	1.349681E+03	-1.091776E+03	-74.7196	1.647955E+03	-2.646563E+03	2.147259E+03
119	-4.000000E-02	-3.433842E+03	-2.289774E+02	-4.908499E+02	-69.6839	-2.108047E+03	-3.615570E+03	7.537615E+02
	4.000000E-02	3.967484E+02	3.837558E+03	-1.811096E+03	-66.7645	4.615125E+03	-3.80818E+02	2.499772E+03
120	-4.000000E-02	-1.976191E+03	4.326733E+02	-1.434142E+03	-65.0122	1.101052E+03	-2.644570E+03	1.872811E+03
	4.000000E-02	-2.069119E+03	3.089884E+02	-3.971567E+02	-80.7651	3.735623E+02	-2.133693E+03	1.253627E+03
121	-4.000000E-02	-6.512333E+02	8.706702E+02	-9.260157E+02	-64.7058	1.308282E+03	-1.088845E+03	1.198563E+03
	4.000000E-02	-2.680405E+03	2.136737E+02	-5.819728E+02	-79.0455	3.263186E+02	-2.793050E+03	1.559685E+03
122	-4.000000E-02	4.999542E+02	9.455878E+02	7.454459E+02	53.3208	1.500805E+03	-5.526298E+01	7.780340E+02
	4.000000E-02	1.021022E+02	-9.092872E+02	1.073828E+02	5.9943	1.133777E+02	-9.205627E+02	5.169702E+02
123	-4.000000E-02	-9.405570E+02	1.102364E+03	-4.957252E+01	-88.6108	1.103566E+03	-9.417592E+02	1.022663E+03
	4.000000E-02	-1.316776E+03	9.508393E+02	1.475047E+01	89.6273	9.509352E+02	-1.316872E+03	1.133904E+03
124	-4.000000E-02	-4.644303E+02	1.250760E+03	-1.263106E+03	-62.0874	1.919896E+03	-1.133565E+03	1.526730E+03
	4.000000E-02	-4.822141E+02	1.074017E+03	-1.234092E+03	-61.1161	1.754821E+03	-1.163019E+03	1.458920E+03
125	-4.000000E-02	-2.744982E-01	-2.634582E+02	1.400496E+03	42.3181	1.274689E+03	-1.538522E+03	1.406655E+03
	4.000000E-02	5.754558E+02	2.177131E+02	1.040071E+03	40.1209	1.451925E+03	-6.587558E+02	1.055340E+03
126	-4.000000E-02	-1.794086E+02	1.930617E+03	5.267300E+02	76.7343	2.054798E+03	-3.035890E+02	1.179193E+03
	4.000000E-02	-6.801890E+01	1.783242E+03	4.976538E+02	75.9959	1.907359E+03	-2.121354E+02	1.059747E+03
127	-4.000000E-02	-1.641051E+02	1.958631E+03	1.156143E+02	86.8917	1.964909E+03	-1.703834E+02	1.067646E+03
	4.000000E-02	-1.290225E+02	1.804943E+03	4.926713E+01	88.5417	1.806198E+03	-1.302766E+02	9.682372E+02
128	-4.000000E-02	1.195142E+02	8.177430E+02	-5.825730E+02	-85.2631	8.225704E+02	1.146869E+02	3.539418E+02
	4.000000E-02	-1.503111E+02	6.845816E+02	9.203538E+02	83.7834	6.946069E+02	-1.603363E+02	4.274716E+02
129	-4.000000E-02	4.273227E+02	1.812892E+02	-6.431564E+02	-58.5637	2.065412E+03	1.748028E+02	9.453046E+02
	4.000000E-02	1.597662E+02	1.561814E+03	-6.637145E+02	-68.2830	1.826165E+02	-1.045863E+03	9.653762E+02

B2M-3xc COMPOSITE FUSELAGE FINE GRID MODEL

FREE FLIGHT-5G

DECEMBER 10, 1975 NASTRAN 9/16/74

CALC ONLY

S T R E S S E S   I N   G E N E R A L   T R I A N G U L A R   E L E M E N T S   (C T R I A 2)

| ELEMENT ID. | FIBRE DISTANCE | STRESSES IN ELEMENT COORD SYSTEM | | | PRINCIPAL STRESSES (ZERO SHEAR) | | | MAX SHEAR |
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
130	-4.00000E-02	3.901279E+02	6.838560E+02	-6.071550E+02	-51.7990	1.161657E+03	-8.767292E+01	6.246549E+02
	4.00000E-02	3.235688E+02	6.282406E+02	-7.563918E+02	-50.6024	1.249494E+03	-2.926350E+02	7.710897E+02
131	-6.00000E-02	3.537753E+02	7.011069E+02	-7.220384E+02	-51.7623	1.270042E+03	-2.151596E+02	7.426008E+02
	6.00000E-02	4.481963E+02	8.633377E+02	-1.074666E+03	-50.4660	1.750295E+03	-4.387614E+02	1.094528E+03
132	-6.00000E-02	2.592466E+02	-1.906545E+02	-5.502368E+02	-37.9037	6.876511E+02	-4.474700E+02	5.675605E+02
	6.00000E-02	3.008903E+02	-1.787677E+02	-8.064697E+02	-36.7193	9.024359E+02	-7.803133E+02	8.413746E+02
133	-6.00000E-02	2.808295E+02	-3.151085E+02	-1.875370E+02	-16.0928	3.349339E+02	-3.692129E+02	3.520734E+02
	6.00000E-02	2.502271E+02	2.915332E+01	-3.249964E+02	-35.6080	4.829701E+02	-2.035897E+02	3.432799E+02
134	-6.00000E-02	3.959775E+02	-2.434521E+02	-5.023588E+02	-28.7631	6.717305E+02	-5.192051E+02	5.954578E+02
	6.00000E-02	-2.401959E+02	-3.909959E+02	-4.548534E+02	-40.2970	1.455065E+02	-7.765982E+02	4.610524E+02
135	-4.50000E-02	3.618037E+03	1.103965E+04	7.715747E+03	57.8427	1.589069E+04	-1.232808E+03	8.561750E+03
	4.50000E-02	3.771640E+03	1.150983E+04	7.920577E+03	58.0174	1.645580E+04	-1.174335E+03	8.815069E+03
136	-4.50000E-02	1.518825E+03	6.748487E+03	1.707166E+03	73.4302	7.256436E+03	1.010876E+03	3.122780E+03
	4.50000E-02	9.827726E+02	5.699267E+03	9.737973E+02	78.7813	5.892413E+03	7.896259E+02	2.551394E+03
137	-4.50000E-02	1.591769E+03	5.807721E+03	6.062223E+03	54.5518	1.014068E+04	-2.741192E+03	6.440437E+03
	4.50000E-02	1.428006E+03	5.431125E+03	5.341565E+03	55.2708	9.133823E+03	-2.274692E+03	5.704257E+03
138	-4.50000E-02	1.449079E+03	4.288361E+03	4.536587E+03	53.6883	7.622245E+03	-1.834805E+03	4.753525E+03
	4.50000E-02	-5.00788E+02	3.137365E+03	3.721530E+03	58.0252	5.460556E+03	-2.824170E+03	4.142363E+03
139	-4.50000E-02	1.543912E+03	3.685232E+03	3.802350E+03	57.4527	6.112016E+03	-2.272392E+03	4.192204E+03
	4.50000E-02	3.618745E+01	3.291761E+03	3.103700E+03	58.8378	5.168635E+03	-1.840687E+03	3.504661E+03
140	-4.50000E-02	2.820529E+03	-2.372196E+03	-3.423893E+03	-26.4133	4.521158E+03	-4.072826E+03	4.296992E+03
	4.50000E-02	3.647066E+03	2.040714E+03	-3.150959E+03	-37.8499	6.095602E+03	-4.078224E+02	3.251712E+03
141	-3.60000E-02	-5.740744E+03	-1.078290E+03	-9.114242E+02	-79.3232	-9.064561E+02	-5.912578E+03	2.503061E+03
	3.60000E-02	-5.131628E+03	1.190547E+03	-2.470804E+02	-87.7653	1.200189E+03	-5.141270E+03	3.170729E+03
142	-3.60000E-02	-3.045895E+03	-9.764813E+03	-5.010912E+03	-28.0805	-3.725106E+02	-1.243820E+04	6.032843E+03
	3.60000E-02	-3.053358E+03	-1.054060E+04	-5.269092E+03	-27.3033	-3.333869E+02	-1.326058E+04	6.463594E+03
143	-2.00000E-02	2.669034E+03	-8.017953E+02	4.648597E+02	.7672	2.669656E+03	-8.024178E+02	1.736037E+03
	2.00000E-02	2.566058E+03	-9.048319E+02	1.270099E+02	2.0965	2.564707E+03	-9.094814E+02	1.737094E+03
144	-2.00000E-02	1.960863E+03	-4.297134E+02	7.366464E+02	15.8226	2.169627E+03	-6.384711E+02	1.404052E+03
	2.00000E-02	1.680951E+03	-4.803177E+02	1.016554E+03	21.6249	2.083945E+03	-8.833119E+02	1.483529E+03
147	-3.60000E-02	-5.027436E+03	-2.032172E+03	3.599181E+02	83.2433	-1.989530E+03	-5.070078E+03	1.540274E+03
	3.60000E-02	-5.361228E+03	-1.055372E+03	3.480795E+02	85.4080	-1.027415E+03	-5.389184E+03	2.180884E+03

B-12

BQM-3 COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

CALC ONLY

DECEMBER 18, 1975   NASTRAN 9/16/76   PAGE   60

S T R E S S E S   I N   G E N E R A L   T R I A N G U L A R   E L E M E N T S   (C T R I A 2)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM NORMAL-X	NORMAL-Y	SHEAR-XY	PRINCIPAL STRESSES (ZERO SHEAR) ANGLE	MAJOR	MINOR	MAX SHEAR
148	-3.600000E-02	-1.478242E+03	-5.335445E+03	-1.151604E+02	-1.7086	-1.474806E+03	-5.338880E+03	1.932037E+03
	3.600000E-02	4.494420E+02	-4.335355E+03	-5.797788E+02	-6.8113	5.186922E+02	-4.404605E+03	2.461648E+03
149	-3.600000E-02	-4.237826E+03	-5.734176E+03	1.098017E+03	27.8650	-3.657315E+03	-6.314687E+03	1.328686E+03
	3.600000E-02	2.877556E+03	-2.146267E+03	1.134565E+03	12.1537	3.121899E+03	-2.390610E+03	2.756254E+03
150	-6.400000E-02	-3.657091E+03	-3.326849E+01	-2.331360E+03	-63.9270	1.107490E+03	-4.797850E+03	2.952670E+03
	6.400000E-02	-9.062362E+02	1.996868E+02	-2.830469E+03	-50.5269	2.530714E+03	-3.237234E+03	2.883974E+03
151	-6.400000E-02	-3.862059E+03	-2.921423E+02	-5.782709E+02	-81.0246	-2.008082E+02	-3.953393E+03	1.876292E+03
	6.400000E-02	-8.943464E+02	-4.046239E+01	-1.126663E+03	-55.3767	7.374256E+02	-1.672254E+03	1.204840E+03
153	-3.600000E-02	-2.855756E+03	-1.461663E+03	7.853692E+02	65.7952	-1.108624E+03	-3.208794E+03	1.050085E+03
	3.600000E-02	3.490066E+03	-3.745913E+02	6.647313E+02	9.4917	3.601207E+03	-4.857307E+02	2.043469E+03
154	-3.600000E-02	-3.778894E+03	-2.143416E+03	8.656292E+02	66.3588	-1.755735E+03	-4.166574E+03	1.205419E+03
	3.600000E-02	-9.813427E+01	-7.665793E+02	8.610594E+02	34.3931	4.912925E+02	-1.356006E+03	9.236493E+02
155	-3.600000E-02	3.775011E+03	-6.091672E+03	-3.291525E+03	-16.8556	4.772268E+03	-7.088929E+03	5.930798E+03
	3.600000E-02	8.501429E+03	7.226167E+03	-4.568006E+03	-41.0268	1.247609E+04	3.251504E+03	4.612294E+03
156	-8.000000E-02	4.466807E+03	7.650374E+03	3.298699E+02	84.1101	7.684404E+03	4.452777E+03	1.615813E+03
	8.000000E-02	-2.022120E+03	-8.609494E+03	-7.524271E+02	-6.4341	-1.937268E+03	-8.694345E+03	3.378538E+03
157	-6.400000E-02	1.135134E+03	7.818009E+02	-8.294827E+02	-38.9883	1.806555E+03	1.107986E+02	8.480876E+02
	6.400000E-02	7.741539E+02	8.328294E+02	-5.769157E+02	-46.4556	1.381153E+03	2.258305E+02	5.776612E+02
158	-4.000000E-03	-1.847050E+04	-6.158817E+03	-1.301043E+03	-84.0331	-6.022830E+03	-1.860649E+04	6.291830E+03
	4.000000E-03	-1.872748E+04	-6.232674E+03	-1.473440E+03	-83.3647	-6.061271E+03	-1.869888E+04	6.418804E+03
159	-4.000000E-03	-1.022588E+04	-3.389810E+03	4.386177E+03	63.9642	-1.247133E+03	-1.236855E+04	5.560710E+03
	4.000000E-03	-1.029955E+04	-3.410609E+03	4.355853E+03	64.1679	-1.301897E+03	-1.240826E+04	5.553181E+03
160	-4.000000E-03	-9.922287E+03	-2.405521E+03	9.988184E+03	55.3102	4.507987E+03	-1.683580E+04	1.067139E+04
	4.000000E-03	-9.950444E+03	-2.417046E+03	9.861012E+03	55.4529	4.372181E+03	-1.673967E+04	1.055593E+04
161	-4.000000E-03	-1.470450E+04	-3.972414E+03	7.081008E+03	63.5776	-4.539149E+02	-1.822300E+04	8.884543E+03
	4.000000E-03	-1.465747E+04	-3.945451E+03	7.096033E+03	63.5226	-4.109873E+02	-1.819134E+04	8.890475E+03
162	-4.000000E-03	-1.504373E+04	-4.650192E+03	7.179975E+03	52.9352	-9.915715E+02	-1.871235E+04	8.860391E+03
	4.000000E-03	-1.474751E+04	-4.558469E+03	7.294512E+03	62.4653	-7.555715E+02	-1.855041E+04	8.897417E+03
163	-4.000000E-03	-1.718338E+04	-4.521252E+03	5.463592E+03	69.6032	-2.489708E+03	-1.921492E+04	8.362606E+03
	4.000000E-03	-1.712158E+04	-4.492964E+03	5.468749E+03	69.5523	-2.453967E+03	-1.916058E+04	8.353306E+03
164	-4.000000E-02	-2.517914E+02	-1.142714E+03	-2.771609E+02	-15.9447	-1.726062E+02	-1.221899E+03	5.246463E+02
	4.000000E-02	-4.599380E+02	-1.359085E+03	-8.622418E+02	-25.3732	-5.101035E+01	-2.278912E+03	1.113501E+03

BQM-34 COMPOSITE FUSELAGE AND WING GRID MODEL
FREE FLIGHT-5G

DECEMBER 20, 1975   NASTRAN 9/16/77

CALC ONLY

STRESSES IN GENERAL TRIANGULAR ELEMENTS

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
165	-4.000000E-02	-1.065271E+03	4.849561E+02	-1.735766E+02	-83.6928	5.041513E+02	-1.085456E+03	7.948037E+02
	4.000000E-02	-1.086074E+03	1.086385E+03	-1.151079E+03	-71.1212	2.280012E+03	-1.479701E+03	1.879556E+03
174	-6.400000E-02	6.130059E+03	1.690852E+03	1.192555E+03	14.1242	6.430144E+03	1.390777E+03	2.519534E+03
	6.400000E-02	4.313469E+03	-1.230047E+03	1.125779E+03	11.0525	4.533370E+03	-1.449948E+03	2.991659E+03
175	-6.400000E-02	4.412272E+02	8.764463E+03	-7.610016E+02	-84.8186	8.833470E+03	3.722202E+02	4.230625E+03
	6.400000E-02	-3.840360E+01	7.226923E+03	-2.911983E+02	-87.7085	7.238576E+03	-5.005630E+01	3.644316E+03
176	-6.400000E-02	1.260158E+03	7.386574E+03	-1.844471E+03	-74.4731	7.899022E+03	7.477099E+02	3.575556E+03
	6.400000E-02	1.290793E+03	8.197650E+03	-1.939990E+03	-75.3436	8.704759E+03	7.836044E+02	3.960537E+03
177	-6.400000E-02	7.350426E+02	1.015724E+04	-5.449677E+02	-86.7807	1.018865E+04	7.036281E+02	4.742513E+03
	6.400000E-02	7.208697E+02	9.843525E+03	-4.658599E+02	-87.0842	9.867253E+03	6.911417E+02	4.585056E+03
178	-6.400000E-02	1.469514E+03	9.449437E+03	-5.437797E+02	-86.1196	9.486322E+03	1.432629E+03	4.026847E+03
	5.400000E-02	1.596751E+03	1.012204E+04	-5.961153E+02	-86.0195	1.016352E+04	1.555271E+03	4.304124E+03
185	-1.900000E-01	-3.230525E+03	5.117259E+03	-1.397279E+03	-80.7456	5.344928E+03	-3.458194E+03	4.401561E+03
	1.900000E-01	-2.996671E+03	5.186377E+03	-1.333281E+03	-80.9755	5.398132E+03	-3.204255E+03	4.303279E+03
186	-1.250000E-01	-1.209599E+03	3.463884E+03	1.363209E+03	74.8251	3.834975E+03	-1.580690E+03	2.707832E+03
	1.250000E-01	1.358339E+03	1.016735E+04	-5.708659E+02	-86.3127	1.020409E+04	1.321601E+03	4.441245E+03
187	-3.150000E-02	-2.620173E+03	1.506106E+04	-1.735561E+04	-58.5101	2.568014E+04	-1.323925E+04	1.945959E+04
	3.150000E-02	5.305700E+03	1.767450E+04	-1.774844E+04	-54.6054	3.028515E+04	-7.304949E+03	1.573205E+04
188	-3.150000E-02	-4.938435E+03	-3.033431E+03	1.223664E+04	47.2255	8.287720E+03	-1.625959E+04	1.227365E+04
	3.150000E-02	-5.333893E+03	-3.492233E+03	1.343290E+04	46.9554	9.048688E+03	-1.787981E+04	1.346425E+04
189	-3.150000E-02	-1.082777E+03	1.413351E+04	-5.926446E+03	-71.0414	1.616636E+04	-3.118627E+03	9.643395E+03
	3.150000E-02	5.779134E+03	1.672563E+04	-6.555794E+03	-63.5899	1.998188E+04	3.522877E+03	8.229503E+03
190	-3.150000E-02	-3.326289E+03	-2.302342E+03	6.912978E+03	47.1178	4.117595E+03	-9.746226E+03	6.931910E+03
	3.150000E-02	-2.688047E+03	-2.324867E+03	7.697512E+03	45.6753	5.193294E+03	-1.020601E+04	7.696611E+03
191	-3.150000E-02	-9.073114E+02	1.045431E+04	-3.393871E+03	-74.5724	1.139089E+04	-1.843900E+03	6.617397E+03
	3.150000E-02	5.269995E+03	1.248853E+04	-4.475408E+03	-64.4425	1.462871E+04	3.129819E+03	5.749443E+03
192	-3.150000E-02	-1.603951E+03	-2.899741E+01	3.565917E+03	51.5703	2.810327E+03	-4.513275E+03	3.661801E+03
	3.150000E-02	-1.536395E+03	-1.794264E+01	3.605713E+03	50.9487	2.908152E+03	-4.461590E+03	3.684871E+03
193	-6.250000E-02	5.022663E+02	3.454240E+03	-9.320757E+01	-88.1933	3.457180E+03	4.993262E+02	1.478927E+03
	6.250000E-02	5.022663E+02	3.454240E+03	-9.320757E+01	-88.1933	3.457180E+03	4.993262E+02	1.478927E+03
194	-4.900000E-02	-1.578265E+04	-7.582016E+03	-1.706337E+03	-83.6014	-5.668488E+02	-1.597400E+04	7.703578E+03
	4.900000E-02	-1.586522E+04	-2.022603E+03	-1.627065E+03	-83.3871	-1.833973E+03	-1.605715E+04	7.111586E+03

BQM-3   COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

CALC ONLY

STRESSES IN GENERAL TRIANGULAR ELEMENTS (CTRIA 2)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
195	-4.900000E-02	-1.048172E+04	-3.329351E+03	9.628746E+03	55.1877	3.365875E+03	-1.717694E+04	1.027141E+04
	4.900000E-02	-9.094426E+03	-2.889430E+03	1.067011E+04	53.1063	5.120079E+03	-1.710393E+04	1.111201E+04
196	-4.900000E-02	-1.014665E+04	-2.034426E+03	6.069727E+03	61.8765	1.209712E+03	-1.339078E+04	7.300247E+03
	4.900000E-02	-8.528066E+03	-1.452750E+03	5.765535E+03	60.7642	1.774793E+03	-1.175561E+04	6.765201E+03
197	-4.900000E-02	-1.926202E+03	-2.864622E+03	7.191075E+02	28.4366	-1.536688E+03	-3.254035E+03	8.587373E+02
	4.900000E-02	-1.950415E+03	-2.507828E+03	3.841777E+02	27.0203	-1.754496E+03	-2.703747E+03	4.746259E+02
198	-4.900000E-02	1.980659E+03	8.993360E+02	3.753560E+03	40.9018	5.232296E+03	-2.352300E+03	3.792298E+03
	4.900000E-02	2.409191E+03	9.899494E+02	3.470732E+03	39.2223	5.242103E+03	-1.842963E+03	3.542533E+03
199	-4.900000E-02	1.637252E+03	-8.905215E+02	2.485074E+03	35.4441	3.403496E+03	-1.658695E+03	2.631095E+03
	4.900000E-02	2.317561E+03	6.497419E+02	2.868800E+03	36.8959	4.471196E+03	-1.503893E+03	2.987544E+03
200	-4.900000E-02	7.323254E+03	-1.464580E+03	-1.031018E+03	-6.6027	7.442595E+03	-1.583922E+03	4.513259E+03
	4.900000E-02	7.551793E+03	-1.505367E+03	-6.553405E+02	-4.1171	7.598965E+03	-1.552539E+03	4.575752E+03
201	-4.900000E-02	7.518726E+03	1.525758E+03	2.149177E+03	17.8247	8.209773E+03	8.347120E+02	3.687530E+03
	4.900000E-02	8.496065E+03	-1.041932E+03	1.727656E+03	9.9569	8.799358E+03	-1.345225E+03	5.072292E+03
202	-4.900000E-02	1.121688E+04	-7.613204E+02	-7.845578E+02	-3.7316	1.126805E+04	-8.124894E+02	6.040272E+03
	4.900000E-02	1.139631E+04	-6.612555E+02	-5.376817E+02	-2.5482	1.142024E+04	-6.851848E+02	6.052712E+03
203	-4.900000E-02	1.240093E+04	3.308164E+03	8.588492E+02	5.3488	1.248134E+04	3.227754E+03	4.626734E+03
	4.900000E-02	1.291475E+04	3.458620E+03	7.906600E+02	4.7468	1.298041E+04	3.392966E+03	4.793720E+03
204	-4.900000E-02	1.444154E+04	-7.479213E+02	-4.514098E+02	-1.7808	1.445495E+04	-7.613248E+02	7.508135E+03
	4.900000E-02	1.484052E+04	3.019056E+02	-3.526602E+02	-1.3887	1.484907E+04	2.933562E+02	7.277857E+03
205	-2.500000E-02	-2.205709E+03	-6.351423E+02	3.721358E+02	77.3222	-5.514291E+02	-2.289422E+03	8.689366E+02
	2.500000E-02	-2.125811E+03	-5.899997E+02	4.235670E+02	75.5597	-4.809287E+02	-2.234882E+03	8.769766E+02
206	-2.500000E-02	-2.721810E+03	1.960929E+03	5.286944E+02	83.6378	2.019878E+03	-2.780759E+03	2.400319E+03
	2.500000E-02	-2.528791E+03	1.354862E+03	5.127432E+02	82.6043	1.421417E+03	-2.595346E+03	2.008381E+03
207	-2.500000E-02	-3.543823E+03	-1.191191E+03	-1.585568E+03	-63.2857	-3.932363E+02	-4.341777E+03	1.974271E+03
	2.500000E-02	-3.590734E+03	-1.201975E+03	-1.711774E+03	-62.4526	-3.090805E+02	-4.463629E+03	2.087274E+03
208	-2.500000E-02	-2.240315E+03	2.169925E+03	-9.074767E+02	-78.8156	2.349352E+03	-2.419743E+03	2.384548E+03
	2.500000E-02	-2.604462E+03	1.930399E+03	-1.333951E+03	-74.7656	2.293685E+03	-2.967746E+03	2.630716E+03
209	-2.500000E-02	-7.230383E+02	-4.579719E+03	-4.505634E+03	-33.4149	2.249563E+03	-7.552320E+03	4.900342E+03
	2.500000E-02	-6.113865E+02	-4.223762E+03	-4.252167E+03	-33.4929	2.202300E+03	-7.037449E+03	4.619875E+03
210	-2.500000E-02	-1.746263E+03	-1.216277E+03	-3.159512E+03	-47.3971	1.689335E+03	-4.651875E+03	3.170605E+03
	2.500000E-02	-5.080604E+02	2.068900E+03	-2.921467E+03	-56.8998	3.973399E+03	-2.412578E+03	3.192988E+03

BQM-34C COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

CALC ONLY

S T R E S S E S   I N   G E N E R A L   T R I A N G U L A R   E L E M E N T S   (C T R I A 2)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
211	-2.000000E-02	-1.238737E+03	-4.280582E+01	-6.277251E+03	-47.7208	5.664896E+03	-6.946439E+03	6.305667E+03
	2.000000E-02	-1.339698E+03	-8.666585E+01	-6.150948E+03	-47.9080	5.469592E+03	-6.895955E+03	6.182774E+03
212	-2.000000E-02	3.049933E+02	8.917941E+02	-4.822001E+03	-46.7424	5.429078E+03	-4.232791E+03	4.830935E+03
	2.000000E-02	-6.869466E+01	-2.123836E+02	-4.691320E+03	-44.5613	4.551331E+03	-4.832410E+03	4.591871E+03
213	-2.000000E-02	1.032428E+02	7.645380E+02	-6.969838E+03	-46.1939	7.449786E+03	-6.562005E+03	6.975896E+03
	2.000000E-02	3.405333E+02	7.877132E+02	-6.959329E+03	-45.9200	7.527072E+03	-6.398766E+03	6.962919E+03
214	-2.000000E-02	2.736639E+03	8.966996E+02	-5.163908E+03	-39.9493	7.061886E+03	-3.428547E+03	5.245216E+03
	2.000000E-02	2.336646E+03	-1.750991E+01	-5.193830E+03	-38.6213	6.489985E+03	-4.170049E+03	5.330417E+03
215	-2.000000E-02	2.250995E+02	2.317085E+03	6.788151E+03	49.3799	8.139360E+03	-5.597175E+03	6.868268E+03
	2.000000E-02	4.493324E+02	2.688630E+03	7.411050E+03	49.2956	9.064131E+03	-5.926169E+03	7.495150E+03
216	-2.000000E-02	-4.549587E+02	4.275905E+03	3.353498E+03	62.5989	6.014278E+03	-2.193332E+03	4.103805E+03
	2.000000E-02	-3.544077E+02	4.252502E+03	3.437574E+03	61.9127	6.087020E+03	-2.188926E+03	4.137973E+03
217	-2.000000E-02	5.464767E+03	1.954245E+03	-4.645112E+03	-34.6426	8.677017E+03	-1.255305E+03	4.966161E+03
	2.000000E-02	5.816995E+03	2.051791E+03	-4.345968E+03	-33.2893	8.670598E+03	-8.018111E+02	4.736204E+03
218	-2.000000E-02	4.697302E+03	-1.073540E+03	-7.224896E+02	-7.0287	4.786381E+03	-1.162619E+03	2.974500E+03
	2.000000E-02	4.743432E+03	-5.074783E+02	-6.163538E+02	-6.6058	4.814809E+03	-5.788559E+02	2.696332E+03
219	-2.000000E-02	3.137029E+03	6.854731E+02	7.735514E+02	16.1274	3.360704E+03	4.617983E+02	1.449453E+03
	2.000000E-02	3.107942E+03	6.863239E+02	1.073111E+03	20.7749	3.515041E+03	2.792252E+02	1.617908E+03
220	-2.000000E-02	6.240895E+03	-7.319116E+03	2.849547E+03	11.3982	6.815371E+03	-7.093592E+03	7.354481E+03
	2.000000E-02	4.930906E+03	-9.900139E+03	3.445664E+03	12.4611	5.692338E+03	-1.066157E+04	8.176954E+03
221	-2.000000E-02	8.337412E+03	-9.440458E+02	-6.185201E+03	-26.5596	1.142928E+04	-4.035915E+03	7.732598E+03
	2.000000E-02	7.908603E+03	-8.988022E+02	-6.286742E+03	-27.4949	1.118056E+04	-4.170757E+03	7.675658E+03
222	-2.000000E-02	2.555161E+03	1.572137E+03	1.071121E+04	43.6863	1.278613E+04	-8.658831E+03	1.072248E+04
	2.000000E-02	3.145053E+03	3.420689E+03	1.111380E+04	45.3552	1.439752E+04	-7.831783E+03	1.111465E+04
223	-2.000000E-02	-5.483819E+03	-4.396894E+03	-3.617270E+03	-49.2721	-1.282489E+03	-8.598224E+03	3.657858E+03
	2.000000E-02	-5.521103E+03	-4.387087E+03	-3.521295E+03	-49.6173	-1.392063E+03	-8.527127E+03	3.567532E+03
224	-2.000000E-02	7.047974E+02	1.452706E+01	6.617335E+02	31.2276	1.059993E+03	-3.866684E+02	7.463307E+02
	2.000000E-02	6.207424E+02	-1.111297E+02	6.989185E+02	31.1823	1.037727E+03	-5.341146E+02	7.883209E+02
225	-2.000000E-02	5.478146E+02	-5.165699E+02	-1.498664E+03	-35.2247	1.605976E+03	-1.574731E+03	1.590353E+03
	2.000000E-02	3.498608E+02	-8.765915E+02	-1.611092E+03	-34.5809	1.460486E+03	-1.987217E+03	1.723851E+03
226	-2.000000E-02	-1.336217E+02	-1.278240E+01	1.772927E+03	45.9759	1.700754E+03	-1.847158E+03	1.773356E+03
	2.000000E-02	-2.841125E+02	-1.758569E+02	1.750741E+03	45.8854	1.521592E+03	-1.981562E+03	1.751577E+03

CALC ONLY

STRESSES IN GENERAL TRIANGULAR ELEMENTS (CTRIA2)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
227	-2.000000E-02	-2.543443E+03	-2.735832E+03	6.331357E+02	48.6805	-1.999236E+03	-3.280039E+03	6.404016E+02
	2.000000E-02	-3.952985E+03	-3.352865E+03	7.445843E+02	55.9745	-2.850153E+03	-4.455696E+03	8.027713E+02
228	-2.000000E-02	-1.846263E+03	1.577250E+03	-5.756026E+02	-80.7070	1.671437E+03	-1.940449E+03	1.805943E+03
	2.000000E-02	-1.243500E+03	2.418678E+03	-7.833772E+02	-78.4189	2.579213E+03	-1.404035E+03	1.991624E+03
229	-2.000000E-02	-2.360213E+03	-4.237258E+02	8.634743E+02	69.1368	-9.463231E+01	-2.689307E+03	1.297337E+03
	2.000000E-02	-2.076325E+03	3.385172E+02	4.417063E+02	79.9531	4.167750E+02	-2.154583E+03	1.285679E+03
230	-2.000000E-02	-1.789477E+03	-6.463204E+02	-1.138962E+03	-58.3247	5.643856E+01	-2.492236E+03	1.274337E+03
	2.000000E-02	-1.931194E+03	-5.104830E+01	-1.472559E+03	-61.2770	7.559242E+02	-2.738166E+03	1.747045E+03
231	-2.000000E-02	-1.686976E+03	-1.319374E+03	6.725835E+02	52.6422	-8.059297E+02	-2.200421E+03	6.972456E+02
	2.000000E-02	-2.573332E+03	-1.868069E+03	5.965102E+02	60.2949	-1.527755E+03	-2.913646E+03	6.929455E+02

BQM-34 COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

CALC ONLY

S T R E S S E S   I N   G E N E R A L   Q U A D R I L A T E R A L   E L E M E N T S   (C - Q U A D 1)

ELEMENT ID.	FIBRE DISTANCE	STRESSES IN ELEMENT COORD SYSTEM			PRINCIPAL STRESSES (ZERO SHEAR)			MAX SHEAR
		NORMAL-X	NORMAL-Y	SHEAR-XY	ANGLE	MAJOR	MINOR	
200	8.100000E-01	-2.198122E+02	-4.053065E+01	-3.505149E+01	-79.3217	-3.392136E+01	-2.264215E+02	9.625006E+01
	-8.100000E-01	7.857500E+01	-2.410527E+01	-6.154355E+00	-3.4178	7.894256E+01	-2.447283E+01	5.170769E+01
201	8.100000E-01	-2.333338E+02	5.017040E+01	-8.638206E+01	-74.3212	7.441685E+01	-2.575802E+02	1.659935E+02
	-8.100000E-01	6.893912E+00	-1.373552E+02	-2.527237E-01	-9.6552	1.119346E+01	-1.416547E+02	7.642410E+01
202	8.100000E-01	-6.670012E+02	4.521845E+01	-2.821937E+01	-87.7346	4.633480E+01	-6.681176E+02	3.572262E+02
	-8.100000E-01	4.771337E+02	-1.139263E+02	2.070463E+01	2.0038	4.778501E+02	-1.146507E+02	2.962544E+02
203	8.100000E-01	-5.844743E+02	-9.077201E+01	-6.736825E+01	-83.6069	-8.322361E+01	-5.920227E+02	3.043335E+02
	-8.100000E-01	4.783151E+02	6.536909E+01	5.307687E+01	7.2083	4.850280E+02	5.865613E+01	2.131860E+02
204	8.100000E-01	-6.192461E+02	5.897531E+01	-2.623775E+01	-88.7573	5.903223E+01	-6.198172E+02	6.050697E+02
	-8.100000E-01	4.635538E+02	-6.619293E+02	3.999028E+01	2.0324	4.649729E+02	-5.633484E+02	5.641507E+02
205	8.100000E-01	-6.350261E+02	3.405915E+02	-8.403654E+01	-85.1093	3.477874E+02	-6.422220E+02	4.950047E+02
	-8.100000E-01	4.625585E+02	-3.627484E+02	1.119133E+02	7.5869	4.774649E+02	-3.776548E+02	4.275599E+02
206	8.100000E-01	-3.204596E+02	1.440956E+03	-1.983489E+01	-89.3549	1.441179E+03	-3.216831E+02	8.809310E+02
	-8.100000E-01	2.219838E+02	-1.639762E+03	6.750688E+01	2.0739	2.244284E+02	-1.642206E+03	9.333174E+02
207	8.100000E-01	-4.121309E+02	9.392796E+02	-6.964457E+01	-87.0577	9.428592E+02	-4.157105E+02	6.792949E+02
	-8.100000E-01	2.070080E+02	-1.105652E+03	2.080608E+02	8.7945	2.391970E+02	-1.137841E+03	6.885188E+02
208	8.100000E-01	-1.024331E+02	2.173435E+03	-7.644398E+01	-88.0784	2.176000E+03	-1.049979E+02	1.140499E+03
	-8.100000E-01	1.165905E+02	-2.070976E+03	8.835519E+01	2.3086	1.201517E+02	-2.074537E+03	1.097344E+03
209	8.100000E-01	-9.074993E+01	2.659737E+03	-5.245558E+02	-79.5609	2.756301E+03	-1.873942E+03	1.471888E+03
	-8.100000E-01	-2.801554E+02	-2.705190E+03	7.729999E+02	16.2591	-5.471330E+01	-2.930632E+03	1.437959E+03

BQM-34 COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

CALC ONLY

S T R E S S E S   I N   B A R   E L E M E N T S   (C B A R)

ELEMENT ID.	SA1 SB1	SA2 SB2	SA3 SB3	SA4 SB4	AXIAL STRESS	SA-MAX SB-MAX	SA-MIN SB-MIN	M.S.-T M.S.-C
1001	0.0 0.0	1.184247E+04 -3.040016E+02	0.0 0.0	0.0 0.0	9.852386E+02	1.282771E+04 9.852386E+02	9.852386E+02 6.812369E+02	4.8E+00
1002	0.0 0.0	6.520962E+02 -1.932698E+03	0.0 0.0	0.0 0.0	-1.552925E+03	-9.008285E+02 -1.552925E+03	-1.552925E+03 -3.485623E+03	1.6E+01
1003	0.0 0.0	-2.899434E+04 -3.982065E+03	-1.315610E+04 -4.785675E+03	1.119989E+04 2.592382E+03	-5.697240E+01	1.114292E+04 2.535409E+03	-2.905131E+04 -8.959037E+03	5.7E+00 1.2E+00
1004	0.0 0.0	6.839779E+02 3.114424E+03	0.0 0.0	0.0 0.0	5.339479E+02	1.217926E+03 3.648372E+03	5.339479E+02 5.339479E+02	2.0E+01
1005	0.0 0.0	1.082872E+04 -1.213195E+04	0.0 0.0	0.0 0.0	8.632524E+02	1.169197E+04 8.632524E+02	8.632524E+02 -1.126870E+04	5.4E+00 4.8E+00
1006	0.0 0.0	-4.522533E+01 1.194381E+03	-6.910765E+02 -1.194699E+03	0.0 0.0	1.200105E+03	1.200105E+03 2.394687E+03	5.090289E+02 5.406696E+00	3.0E+01
1007	0.0 0.0	1.932752E+01 -1.487093E+02	0.0 0.0	0.0 0.0	-1.022198E+03	-1.002870E+03 -1.022198E+03	-1.022198E+03 -1.170907E+03	5.5E+01
1008	0.0 0.0	-8.129405E+03 2.477718E+03	0.0 0.0	0.0 0.0	8.511891E+02	8.511891E+02 3.328907E+03	-7.278216E+03 8.511891E+02	2.2E+01 7.9E+00
1009	0.0 0.0	-2.974249E+04 -1.774169E+03	3.034308E+04 1.809270E+03	0.0 0.0	8.046261E+02	3.122771E+04 2.693896E+03	-2.885786E+04 -8.954291E+02	1.4E+00 1.3E+00
1010	0.0 0.0	-1.125165E+03 5.963497E+02	0.0 0.0	0.0 0.0	-1.443434E+02	-1.443434E+02 4.520063E+02	-1.269508E+03 -1.443434E+02	1.6E+02 5.0E+01
1011	0.0 0.0	-2.448401E+04 -1.222059E+04	0.0 0.0	0.0 0.0	-1.782959E+02	-1.782959E+02 -1.782959E+02	-2.466231E+04 -1.239088E+04	1.6E+01
1012	0.0 0.0	-1.498087E+03 -1.209089E+04	0.0 0.0	0.0 0.0	-4.597637E+02	-4.597637E+02 -4.597637E+02	-1.957851E+03 -1.255066E+04	4.2E+00
1013	0.0 0.0	9.243335E+03 1.245272E+01	-8.465623E+03 -1.887190E+01	0.0 0.0	-9.080194E+02	8.341316E+03 -8.955667E+02	-9.373642E+03 -9.268913E+02	8.0E+00 5.9E+00
1014	0.0 0.0	2.034267E+03 1.321045E+02	-7.474015E+03 2.333199E+03	4.536029E+03 -1.601173E+03	1.234348E+02	4.659464E+03 2.456634E+03	-7.350580E+03 -1.477738E+03	1.5E+01 7.8E+00
1015	0.0 0.0	-3.711629E+03 1.247583E+04	0.0 0.0	0.0 0.0	3.003910E+02	3.003910E+02 1.277622E+04	-3.411237E+03 3.003910E+02	4.9E+00 1.8E+01
1016	0.0 0.0	-1.010640E+04 -4.847007E+01	1.045123E+04 -3.322174E+02	0.0 0.0	1.337740E+03	1.178897E+04 1.337740E+03	-8.768656E+03 1.005522E+03	5.4E+00 6.4E+00

BQM-34C COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

DECEMBER 18, 1975 NASTRAN 9/16/74

CALC ONLY

S T R E S S E S   I N   B A R   E L E M E N T S   (C B A R)

ELEMENT ID.	SA1 SB1	SA2 SB2	SA3 SB3	SA4 SB4	AXIAL STRESS	SA-MAX SB-MAX	SA-MIN SB-MIN	M.S.-T M.S.-C
1017	0.0 0.0	-3.32286E+04 -9.93036E+03	3.398535E+04 1.036503E+04	0.0 0.0	1.206730E+02	3.410702E+04 1.048570E+04	-3.310796E+04 -9.809689E+03	1.2E+00 9.6E-01
1018	0.0 0.0	-1.099505E+02 -5.701676E+04	-7.333153E+01 5.741797E+04	0.0 0.0	-1.789832E+03	-1.789832E+03 5.562814E+04	-1.899782E+03 -5.880660E+04	3.5E-01 1.1E-01
1019	0.0 0.0	3.210854E+02 -7.473029E+02	3.367440E+02 9.405735E+02	0.0 0.0	-7.940415E+02	-4.572975E+02 1.465320E+02	-7.940415E+02 -1.541344E+03	5.1E+02 4.1E+01
1020	0.0 0.0	1.172574E+03 -1.734806E+03	-1.492660E+03 3.476908E+03	0.0 0.0	-7.936954E+02	3.788790E+02 2.683213E+03	-2.286355E+03 -2.528501E+03	2.7E+01 2.5E+01
1021	0.0 0.0	-6.385935E+02 1.149254E+02	0.0 0.0	0.0 0.0	6.352805E+02	6.352805E+02 7.502139E+02	-3.304977E+00 6.352085E+02	9.9E+01 2.0E+04
1022	0.0 0.0	0.0 0.0	0.0 0.0	0.0 0.0	1.779500E+03	1.779500E+03 1.779500E+03	1.779500E+03 1.779500E+03	3.3E+01
1023	0.0 0.0	0.0 0.0	0.0 0.0	0.0 0.0	-3.184089E+03	-3.184089E+03 -3.184089E+03	-3.184089E+03 -3.184083E+03	1.1E+01
1024	0.0 0.0	0.0 0.0	0.0 0.0	0.0 0.0	-1.483545E+03	-1.483545E+03 -1.483545E+03	-1.483545E+03 -1.483545E+03	2.5E+01
1025	0.0 0.0	0.0 0.0	0.0 0.0	0.0 0.0	-3.332267E+03	-3.332267E+03 -3.332267E+03	-3.332267E+03 -3.332267E+03	1.0E+01
1026	0.0 0.0	0.0 0.0	0.0 0.0	0.0 0.0	-2.102261E+03	-2.102261E+03 -2.102261E+03	-2.102261E+03 -2.102261E+03	1.7E+01
1027	0.0 0.0	0.0 0.0	0.0 0.0	0.0 0.0	-4.446876E+03	-4.446876E+03 -4.446876E+03	-4.446876E+03 -4.446876E+03	7.5E+00
1028	0.0 0.0	0.0 0.0	0.0 0.0	0.0 0.0	8.723300E+03	8.723300E+03 8.723300E+03	8.723300E+03 8.723300E+03	2.9E+00
1029	0.0 0.0	0.0 0.0	0.0 0.0	0.0 0.0	1.687033E+04	1.687033E+04 1.687033E+04	1.687033E+04 1.687033E+04	1.0E+00
1030	0.0 0.0	0.0 0.0	0.0 0.0	0.0 0.0	2.815443E+03	2.815443E+03 2.815443E+03	2.815443E+03 2.815443E+03	1.1E+01
1031	0.0 0.0	-6.546667E+03 2.096034E+03	3.524448E+03 -7.075117E+03	0.0 0.0	3.031574E+03	6.556023E+03 5.127604E+03	-3.513093E+03 -4.043543E+03	1.1E+01 1.5E+01
1032	0.0 0.0	-7.905314E+03 9.413502E+02	8.715120E+03 -2.258748E+03	0.0 0.0	-1.521839E+03	7.193281E+03 -5.804886E+02	-9.427153E+03 -3.780586E+03	9.7E+00 5.8E+00

BQM-3 COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-55

CALC ONLY

STRESSES IN BAR ELEMENTS

ELEMENT ID.	SA1 / SB1	SA2 / SB2	SA3 / SB3	SA4 / SB4	AXIAL STRESS	(C BAR) SA-MAX / SB-MAX	SA-MIN / SB-MIN	M.S.-T / M.S.-C
1033	0.0 / 0.0	-2.115696E+03 / 1.145492E+03	5.074175E+03 / -4.636205E+03	0.0 / 0.0	5.446698E+02	5.618845E+03 / 1.690162E+03	-1.571026E+03 / -4.891615E+03	1.3E+01 / 1.5E+01
1034	0.0 / 0.0	-1.485626E+03 / -4.060747E+03	2.458219E+03 / 3.897322E+03	9.311530E+02 / 1.694625E+03	2.667677E+03	5.125896E+03 / 6.564999E+03	1.182051E+03 / -1.393070E+03	1.1E+01 / 4.5E+01
1035	0.0 / 0.0	-9.909220E+02 / -1.829194E+02	-1.539192E+03 / 1.206025E+03	2.987462E+03 / -9.386814E+02	-3.491066E+03	-5.036034E+02 / -2.285040E+03	-5.030257E+03 / -4.429747E+03	1.2E+01
1036	0.0 / 0.0	2.278299E+02 / -1.994926E+03	-1.908489E+03 / -1.292666E+03	0.0 / 0.0	-1.052482E+03	-8.246526E+02 / -1.052482E+03	-2.960972E+03 / -3.047410E+03	2.0E+01
1037	0.0 / 0.0	3.126321E+03 / 2.332562E+03	-4.493676E+01 / -3.126801E+03	0.0 / 0.0	1.390599E+03	4.516920E+03 / 3.723160E+03	1.345662E+03 / -1.735420E+03	1.6E+01 / 3.6E+01
1038	0.0 / 0.0	2.224168E+02 / 1.196230E+04	-2.515387E+03 / -3.086517E+03	0.0 / 0.0	3.597820E+03	3.620237E+03 / 1.536012E+04	8.824337E+02 / 3.113037E+02	4.0E+00
1039	0.0 / 0.0	-9.837960E+01 / 1.191649E+03	2.704251E+02 / 7.166017E+02	0.0 / 0.0	-3.972228E+02	-1.267578E+03 / 7.944263E+02	-4.956024E+02 / -3.972228E+02	9.6E+01 / 1.3E+02
1041	0.0 / 0.0	1.555653E+04 / -1.407717E+02	-4.800976E+03 / 4.102364E+02	0.0 / 0.0	1.090777E+03	1.664731E+04 / 1.501013E+03	-3.710200E+03 / 9.500049E+02	3.6E+00 / 1.6E+01
1042	3.702699E+04 / -1.700051E+04	-3.702699E+04 / 1.700051E+04	0.0 / 0.0	0.0 / 0.0	-1.045008E+03	3.598198E+04 / 1.595550E+04	-3.807199E+04 / -1.804551E+04	1.1E+00 / 6.5E-01
1043	5.539852E+03 / -6.617391E+03	-5.539852E+03 / 6.617391E+03	0.0 / 0.0	0.0 / 0.0	3.952960E+03	9.492812E+03 / 1.057035E+04	-1.586892E+03 / -2.664431E+03	6.0E+00 / 2.3E+01
1045	1.469270E+04 / -6.682585E+03	-1.469270E+04 / 6.682585E+03	0.0 / 0.0	0.0 / 0.0	-1.423981E+03	1.326872E+04 / 5.258604E+03	-1.611668E+04 / -8.106565E+03	4.6E+00 / 2.9E+00
1046	0.0 / 0.0	-2.206096E+01 / 1.495857E+03	-1.353416E+02 / -4.759867E+03	0.0 / 0.0	1.132696E+03	1.132696E+03 / 2.628553E+03	9.973546E+02 / 6.567895E+02	2.8E+01
1048	1.109364E+04 / -6.779331E+03	-1.109364E+04 / 6.779331E+03	0.0 / 0.0	0.0 / 0.0	-7.511946E+02	1.034245E+04 / 6.028137E+03	-1.184484E+04 / -7.530526E+03	6.2E+00 / 4.3E+00
1049	-1.667271E+03 / 4.332509E+03	1.667271E+03 / -4.332509E+03	0.0 / 0.0	0.0 / 0.0	-6.030807E+02	8.641900E+02 / 3.529428E+03	-2.470351E+03 / -5.135589E+03	2.0E+01 / 1.1E+01
1050	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	3.177089E+03	3.177089E+03 / 3.177089E+03	3.177089E+03 / 3.177089E+03	9.7E+00
1051	0.0 / 0.0	-3.898966E+02 / -5.963127E+03	5.647023E+01 / 1.312413E+03	0.0 / 0.0	1.444876E+02	2.009578E+02 / 1.456901E+03	-2.454091E+02 / -5.818639E+03	5.0E+01 / 1.0E+01

BQM-??? COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

DECEMBER 18, 1975   NASTRAN 9/16/74

CALC ONLY

S T R E S S E S   I N   B A R   E L E M E N T S   (C B A R)

ELEMENT ID.	SA1 SB1	SA2 SB2	SA3 SB3	SA4 SB4	AXIAL STRESS	SA-MAX SB-MAX	SA-MIN SB-MIN	M.S.-T M.S.-C
1052	0.0 0.0	-3.015926E+02 -1.61194E+03	5.383697E+01 2.773354E+03	1.265174E+02 -1.809399E+03	-1.055915E+03	-9.293975E+02 1.717439E+03	-1.357507E+03 -2.865314E+03	4.3E+01 2.2E+01
1053	0.0 0.0	-1.048870E+03 -5.287154E+02	1.819269E+03 3.557662E+01	0.0 0.0	-2.145029E+03	-3.257599E+02 -2.109452E+03	-3.193899E+03 -2.673744E+03	1.9E+01
1054	0.0 0.0	8.853433E+02 -4.746825E+02	1.059482E+02 9.337422E+01	-1.588923E+03 1.904891E+02	-3.445218E+02	7.149602E+02 -1.540327E+02	-1.933445E+03 -8.192042E+02	1.0E+02 3.3E+01
1055	0.0 0.0	1.273418E+03 -3.749742E+03	-5.457506E+02 2.235282E+03	0.0 0.0	1.293547E+03	2.566965E+03 3.528828E+03	7.477959E+02 -2.456196E+03	2.0E+01 2.5E+01
1056	0.0 0.0	4.420006E+02 -1.909231E+02	4.458882E+02 7.692070E+02	-1.465616E+03 -1.094708E+03	5.711855E+02	1.017074E+03 1.340392E+03	-9.144304E+02 -5.235222E+02	5.5E+01 7.0E+01
1057	0.0 0.0	4.716131E+02 -3.104135E+01	-5.150583E+02 9.480037E+02	0.0 0.0	-1.467445E+03	-9.958321E+02 -5.186415E+02	-1.982503E+03 -4.571580E+03	1.3E+01
1058	0.0 0.0	-8.099422E+02 3.775117E+02	-4.331376E+03 -1.006521E+02	4.850423E+03 -1.412744E+02	-4.887271E+02	4.361696E+03 -1.112154E+02	-4.820103E+03 -6.300015E+02	1.6E+01 1.2E+01
1059	0.0 0.0	3.714040E+01 1.831230E+03	-2.410309E+03 2.172413E+03	0.0 0.0	2.950386E+02	3.321790E+02 2.467451E+03	-2.115270E+03 2.950386E+02	2.9E+01 3.0E+01
1060	0.0 0.0	4.998009E+02 -8.556299E+02	-6.623520E+02 6.176234E+02	0.0 0.0	9.082456E+02	1.408047E+03 1.525869E+03	2.458936E+02 5.261577E+01	4.8E+01
1061	0.0 0.0	1.536676E+02 1.524571E+02	-1.065726E+03 -6.326452E+02	0.0 0.0	-8.569104E+02	-7.032429E+02 -7.044533E+02	-1.922637E+03 -1.489556E+03	3.3E+01
1062	0.0 0.0	6.983024E+01 2.401231E+03	-3.806366E+02 -4.924733E+02	0.0 0.0	-7.465006E+02	-6.766703E+02 1.654731E+03	-1.127137E+03 -1.238974E+03	4.4E+01 5.1E+01
1063	0.0 0.0	1.182905E+03 -8.534337E+02	-2.598982E+03 -1.018195E+03	2.253857E+03 1.267193E+03	1.275977E+03	3.529834E+03 2.543170E+03	-1.323005E+03 2.577820E+02	2.0E+01 4.8E+01
1064	0.0 0.0	7.244055E+01 -4.788260E+02	1.903349E+02 1.135160E+03	-3.724938E+02 -1.143320E+03	1.736213E+03	1.926548E+03 2.871373E+03	1.363719E+03 5.878935E+02	2.5E+01
1065	0.0 0.0	1.006021E+03 1.020706E+03	-1.401148E+03 -2.571163E+03	1.107631E+03 2.273361E+03	7.302623E+02	1.837893E+03 3.003623E+03	-6.708855E+02 -1.840900E+03	2.4E+01 3.4E+01
1066	0.0 0.0	-2.664749E+03 -2.66957E+03	6.979174E+02 5.616799E+02	0.0 0.0	-2.632820E+02	4.346355E+02 2.983979E+02	-1.928031E+03 -2.932861E+03	1.7E+02 2.1E+01
1067	0.0 0.0	-7.031101E+02 1.170031E+02	1.237567E+03 -2.536994E+02	-1.038545E+03 2.448704E+02	1.644914E+03	2.882482E+03 1.809785E+03	6.063697E+02 1.391215E+03	2.5E+01

BQM-3 COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-5G

DECEMBER 18, 1975 NASTRAN 9/16/74 PAGE 70

CALC ONLY

S T R E S S E S   I N   B A R   E L E M E N T S

ELEMENT ID.	SA1 / SB1	SA2 / SB2	SA3 / SB3	SA4 / SB4	AXIAL STRESS	(C BAR) SA-MAX / SB-MAX	SA-MIN / SB-MIN	M.S.-T / M.S.-C
1068	0.0 / 0.0	-8.954345E+01 / 6.964503E+02	8.777239E+01 / 7.636696E+02	-3.526523E+01 / -1.172059E+03	7.053620E+02	8.731344E+02 / 1.549032E+03	6.958185E+02 / -3.866972E+02	4.7E+01 / 1.7E+02
1069	0.0 / 0.0	4.525977E+02 / -8.861499E+02	1.303166E+03 / -1.019799E+03	0.0 / 0.0	1.428524E+02	1.446018E+03 / 1.428524E+02	1.428524E+02 / -8.769461E+02	5.1E+01 / 7.3E+01
1070	0.0 / 0.0	-4.323784E+02 / 3.979423E+02	1.219394E+02 / -6.541976E+02	3.254993E+02 / 5.180412E+02	4.329083E+02	7.584076E+02 / 9.509495E+02	5.299255E-01 / -2.212893E+02	7.8E+01 / 2.9E+02
1071	0.0 / 0.0	-5.038287E+02 / 1.728042E+02	-5.614628E+02 / 1.667354E+02	8.569016E+02 / -2.680656E+02	1.339399E+02	9.908415E+02 / 3.067441E+02	-4.275229E+02 / -1.341257E+02	7.5E+01 / 1.5E+02
1072	0.0 / 0.0	1.336373E+02 / 4.780258E+02	1.123068E+03 / -1.198426E+03	0.0 / 0.0	3.127109E+02	1.435779E+03 / 7.907367E+02	3.127109E+02 / -8.857147E+02	5.1E+01 / 7.2E+01
1073	0.0 / 0.0	-5.406718E+02 / 7.123509E+02	-8.064023E+02 / -1.653373E+02	1.669930E+03 / -4.975907E+02	-3.554767E+02	1.314451E+03 / 3.568723E+02	-1.161801E+03 / -8.530693E+02	5.6E+01 / 5.5E+01
1074	0.0 / 0.0	-5.225133E+02 / -2.559669E+02	4.591637E+02 / -1.299786E+03	-1.487070E+02 / 1.451871E+03	8.213312E+01	5.412969E+02 / 1.534004E+03	-4.403801E+02 / -1.217652E+03	4.8E+01 / 5.2E+01
1075	0.0 / 0.0	-2.145605E+03 / -6.656756E+03	1.505951E+02 / 4.673293E+02	0.0 / 0.0	1.625583E+02	3.331533E+02 / 6.498876E+02	-1.963047E+03 / -6.474198E+03	1.1E+02 / 9.0E+00
1076	0.0 / 0.0	2.357626E+02 / -4.042547E+02	-1.107713E+03 / 2.568827E+03	0.0 / 0.0	-1.354121E+03	-1.118359E+03 / 1.214706E+03	-2.461834E+03 / -5.396668E+03	6.1E+01 / 1.1E+01
1077	0.0 / 0.0	4.420049E+03 / -3.761894E+02	-2.397507E+03 / 2.040513E+02	-2.397507E+03 / 2.040513E+02	-5.323710E+02	3.087678E+03 / -3.283197E+02	-2.929878E+03 / -9.085605E+02	1.9E+01 / 2.1E+01
1078	0.0 / 0.0	3.923650E+03 / -1.205514E+04	-2.128252E+03 / 6.544329E+03	-2.128252E+03 / 6.544329E+03	-3.169878E+03	7.537715E+02 / 3.374451E+03	-5.298130E+03 / -1.523501E+04	2.2E+01 / 3.2E+00
1079	0.0 / 0.0	-1.072118E+04 / 2.400555E+03	5.815345E+03 / -1.302100E+03	5.815345E+03 / -1.302100E+03	-2.724801E+03	3.090544E+03 / -3.242459E+02	-1.344598E+04 / -4.026901E+03	2.4E+01 / 3.8E+00
1080	0.0 / 0.0	2.356009E+03 / 1.645063E+03	-1.277938E+03 / -8.923092E+02	-1.277938E+03 / -8.923092E+02	-1.148726E+03	1.207281E+03 / 4.963347E+02	-2.426666E+03 / -2.041038E+03	6.3E+01 / 2.5E+01
1081	0.0 / 0.0	2.831125E+03 / 3.710752E+02	-1.536734E+03 / -2.012773E+02	-1.536734E+03 / -2.012773E+02	-1.081825E+03	1.751300E+03 / -7.107494E+02	-2.618558E+03 / -1.283102E+03	4.3E+01 / 2.3E+01
1082	-4.006527E+03 / -3.758396E+03	4.006627E+03 / 8.758396E+03	0.0 / 0.0	0.0 / 0.0	1.592467E+04	1.993130E+04 / 2.468307E+04	1.191804E+04 / 7.166273E+03	2.0E+00 /
1083	-1.160162E+04 / -3.738261E+03	1.160162E+04 / 3.738261E+03	0.0 / 0.0	0.0 / 0.0	1.448967E+04	2.609129E+04 / 1.822793E+04	2.888048E+03 / 1.075141E+04	1.8E+00 /

BQM-34C COMPOSITE FUSELAGE FINE GRID MODEL — DECEMBER 18, 1975 — NASTRAN 9/16/74 — PAGE 71

FREE FLIGHT-5G

CALC ONLY

STRESSES IN BAR ELEMENTS

ELEMENT ID.	SA1 / SB1	SA2 / SB2	SA3 / SB3	SA4 / SB4	AXIAL STRESS	(C B A R) SA-MAX / SB-MAX	SA-MIN / SB-MIN	M.S.-T / M.S.-C
1084	-2.251609E+04 / 1.848072E+04	2.251609E+04 / -1.848072E+04	0.0 / 0.0	0.0 / 0.0	1.075157E+04	3.326766E+04 / 2.923230E+04	-1.176451E+04 / -7.729150E+03	1.2E+00 / 4.4E+00
1085	3.302405E+03 / 3.862452E+03	-3.302405E+03 / -3.062452E+03	0.0 / 0.0	0.0 / 0.0	3.654865E+03	6.957270E+03 / 7.517317E+03	3.524598E+02 / -2.075875E+02	8.8E+00 / 3.0E+02
1086	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	1.325099E+03	1.325099E+03 / 1.325099E+03	1.325099E+03 / 1.325099E+03	2.5E+01
1087	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	-3.103808E+03	-3.103808E+03 / -3.103808E+03	-3.103808E+03 / -3.103808E+03	6.4E+00
1088	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	-1.250942E+03	-1.250942E+03 / -1.250942E+03	-1.250942E+03 / -1.250942E+03	1.7E+01
1090	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	-4.720228E+03	-4.720228E+03 / -4.720228E+03	-4.720228E+03 / -4.720228E+03	3.9E+00
1091	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	2.588185E+03	2.588185E+03 / 2.588185E+03	2.588185E+03 / 2.588185E+03	1.2E+01
1093	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	0.0 / 0.0	7.246874E+03	7.246874E+03 / 7.246874E+03	7.246874E+03 / 7.246874E+03	3.7E+00
1094	1.748692E+04 / -8.281071E+03	-1.748692E+04 / 8.281071E+03	0.0 / 0.0	0.0 / 0.0	6.179306E+03	2.366623E+04 / 1.446038E+04	-1.130761E+04 / -2.101766E+03	2.1E+00 / 4.6E+00
1095	-3.847319E+02 / 1.205088E+02	3.847319E+02 / -1.205088E+02	0.0 / 0.0	0.0 / 0.0	1.212379E+03	1.597111E+03 / 1.332888E+03	8.276475E+02 / 1.091871E+03	4.5E+01
1096	-9.290508E+00 / 4.655164E+01	9.290508E+00 / -4.655164E+01	-9.155863E+00 / 4.587698E+01	9.155863E+00 / -4.587698E+01	-8.457401E-01	8.444768E+00 / 4.570590E+01	-1.013625E+01 / -4.739738E+01	
1097	-6.345449E-01 / -2.053939E+02	6.345449E-01 / 2.053939E+02	-6.345449E-01 / -2.053939E+02	6.345449E-01 / 2.053933E+02	-1.576940E+02	-1.570594E+02 / 4.769995E+01	-1.583285E+02 / -3.630879E+02	
1099	-4.526506E+02 / -5.782234E+02	4.526506E+02 / 5.782234E+02	-4.692273E+02 / -6.002930E+02	4.692273E+02 / 6.002930E+02	-1.204002E+02	3.495271E+02 / 4.798928E+02	-5.903275E+02 / -7.206932E+02	
1101	-6.199089E+02 / -3.982298E+02	6.199089E+02 / 3.982298E+02	-6.199089E+02 / -3.982298E+02	6.199089E+02 / 3.982298E+02	-1.027625E+02	5.171464E+02 / 2.960674E+02	-7.226713E+02 / -5.015923E+02	
1103	-4.085269E+02 / -2.866632E+02	4.085269E+02 / 2.866632E+02	-3.993808E+02 / -2.822006E+02	3.993808E+02 / 2.822006E+02	-1.553023E+02	2.532246E+02 / 1.336609E+02	-5.638292E+02 / -4.439655E+02	
1104	5.836581E+02 / 4.453471E+02	-5.836581E+02 / -4.453471E+02	5.836581E+02 / 4.453471E+02	-5.836581E+02 / -4.453471E+02	2.187634E+01	6.055444E+02 / 4.672235E+02	-5.617818E+02 / -4.234708E+02	

BQM-3 COMPOSITE FUSELAGE FINE GRID MODEL
FREE FLIGHT-55

CALC ONLY

S T R E S S E S   I N   B A R   E L E M E N T S   (C B A R)

ELEMENT ID.	SA1 / SB1	SA2 / SB2	SA3 / SB3	SA4 / SB4	AXIAL STRESS	SA-MAX / SB-MAX	SA-MIN / SB-MIN	M.S.-T / M.S.-C
1105	5.509165E+03	-5.509165E+03	0.0	0.0	-2.174784E+03	3.334381E+03	-7.683949E+03	2.1E+01
	7.958946E+02	-7.958946E+02	0.0	0.0		-1.377889E+03	-2.971679E+03	7.2E+00
1106	-9.461033E+03	9.461033E+03	0.0	0.0	-4.118057E+02	9.049227E+03	-9.872839E+03	2.7E+00
	2.047019E+04	-2.047019E+04	0.0	0.0		2.005839E+04	-2.088200E+04	2.0E+00
1107	5.848264E+03	-5.848264E+03	0.0	0.0	-7.020160E+02	5.146248E+03	-6.550280E+03	7.6E+00
	9.352561E+03	-3.352561E+03	0.0	0.0		8.650545E+03	-1.005458E+04	5.3E+00
1108	-1.734078E+04	1.734078E+04	0.0	0.0	8.628755E+02	1.820366E+04	-1.647791E+04	3.1E+00
	6.334868E+03	-6.334868E+03	0.0	0.0		7.197743E+03	-5.471992E+03	2.8E+00
1109	0.0	-1.443644E+02	-5.579537E+02	0.0	2.203174E+02	2.203174E+02	-3.376363E+02	2.9E+02
	0.0	-7.124799E+02	3.679174E+01	0.0		2.571091E+02	-4.921625E+02	1.3E+02
1110	-1.518029E+01	1.518029E+01	-1.496343E+01	1.496343E+01	8.322030E-01	1.601250E+01	-1.434808E+01	
	3.565416E+00	-3.566416E+00	3.515467E+00	-3.515467E+00		4.398625E+00	-2.734207E+00	
1114	3.152177E+02	-3.152177E+02	3.105822E+02	-3.105822E+02	3.478616E+01	3.500039E+02	-2.804316E+02	
	2.807361E+02	-2.807361E+02	2.766076E+02	-2.766076E+02		3.155223E+02	-2.459499E+02	
1115	2.118973E+02	1.971567E+02	0.0	0.0	8.427078E+03	1.039864E+04	8.427078E+03	4.6E+00
	5.023938E+03	4.889064E+03	0.0	0.0		1.331614E+04	3.403140E+03	
1115	6.576910E+03	-6.320510E+03	0.0	0.0	2.026291E+03	8.603200E+03	-4.294219E+03	7.6E+00
	2.507980E+03	3.639794E+01	0.0	0.0		4.534271E+03	2.026291E+03	1.4E+01
1117	-1.123573E+03	1.055777E+03	0.0	0.0	6.787093E+02	1.734486E+03	-4.448633E+02	4.2E+01
	-2.233369E+03	3.395189E+02	0.0	0.0		1.018228E+03	4.553724E+02	1.4E+02
1118	3.236243E+03	-1.097199E+03	0.0	0.0	-1.777416E+02	3.058501E+03	-1.274940E+03	2.3E+01
	-9.048020E+02	8.714585E+02	0.0	0.0		6.937169E+02	-1.082544E+03	4.8E+01
1119	-3.224718E+03	2.283124E+03	0.0	0.0	-2.284210E+03	7.891402E+01	-5.428928E+03	4.2E+01
	3.930256E+03	-3.720235E+03	0.0	0.0		1.726047E+03	-5.924445E+03	9.6E+01
1120	-9.574585E+03	9.503353E+03	0.0	0.0	-1.745269E+03	7.758084E+03	-1.131935E+04	8.5E+00
	-2.769458E+03	1.915566E+03	0.0	0.0		1.702963E+02	-4.533727E+03	4.6E+00
1121	3.354432E+03	-2.468528E+03	-4.006251E+03	0.0	-1.171417E+03	2.183015E+03	-5.177669E+03	3.2E+00
	-1.194316E+04	3.279839E+03	1.960323E+04	0.0		1.843181E+04	-1.311457E+04	4.3E+00
1122	-2.179312E+03	5.006266E+03	-6.948521E+02	0.0	-7.912187E+03	-2.905921E+03	-1.009150E+04	5.8E+00
	2.199038E+02	1.495702E+03	-1.869075E+03	0.0		-6.416486E+03	-9.781263E+03	
1123	-3.000774E+03	2.524793E+03	5.479381E+03	0.0	3.373394E+03	8.852776E+03	3.726205E+02	5.9E+00
	-1.291592E+03	7.855563E+03	-5.149493E+03	0.0		1.122896E+04	-1.776099E+03	3.8E+01

BQM-34E COMPOSITE FUSELAGE FINE GRID MODEL   DECEMBER 18, 1975 NASTRAN 9/16/74   PAGE 73
FREE FLIGHT-SS

CALC ONLY

STRESSES IN BAR ELEMENTS

ELEMENT ID.	SA1 / SB1	SA2 / SB2	SA3 / SB3	SA4 / SB4	AXIAL STRESS	(C BAR) SA-MAX / SB-MAX	SA-MIN / SB-MIN	M.S.-T / M.S.-C
1124	6.200995E+03 / -2.654982E+03	-3.470228E+03 / 3.310650E+03	-8.480411E+03 / 1.655850E+03	0.0 / 0.0	1.074032E+04	1.694922E+04 / 1.405097E+04	2.259914E+03 / 8.085342E+03	3.6E+00
1125	0.0 / 0.0	3.228296E+02 / 3.545181E+02	-3.615843E+03 / 1.459625E+03	3.408960E+03 / -1.686816E+03	1.410820E+02	3.550042E+03 / 1.600707E+03	-3.474761E+03 / -1.545734E+03	2.0E+01 / 1.8E+01
1126	0.0 / 0.0	-7.170323E+03 / 5.886998E+02	6.975212E+03 / -5.726808E+02	0.0 / 0.0	-1.916465E+02	6.783566E+03 / 3.970534E+02	-7.361969E+03 / -7.643273E+02	1.0E+01 / 8.4E+00
1127	0.0 / 0.0	-6.010374E+00 / 1.331648E+03	5.846826E+00 / -1.295412E+03	0.0 / 0.0	-3.972541E+02	-3.914072E+02 / 9.343935E+02	-4.032644E+02 / -1.692666E+03	8.2E+01 / 4.0E+01
1128	0.0 / 0.0	4.965274E+02 / 3.407670E+03	-4.830164E+02 / -8.178889E+00		-1.398763E+03	-9.022354E+02 / -1.390355E+03	-1.881779E+03 / -1.406942E+03	3.6E+01
1129	0.0 /	-8.230787E+02 / -8.891856E+02	8.006820E+02 / 8.649901E+02	0.0 / 0.0	-2.252942E+03	-1.452260E+03 / -1.387952E+03	-3.076021E+03 / -3.142128E+03	2.1E+01
1130	0.0 / 0.0	-1.260445E+03 / 1.275435E+03	1.226147E+03 / -1.240729E+03	0.0 / 0.0	-3.507879E+03	-2.281732E+03 / -3.380336E+03	-4.768324E+03 / -3.631952E+03	1.3E+01
1136	-7.019751E+01 / -8.809030E+01	7.019751E+01 / 8.809030E+01	-7.019751E+01 / -8.809030E+01	7.019751E+01 / 8.809030E+01	-5.519335E+01	1.500417E+01 / 3.289695E+01	-1.253999E+02 / -1.432836E+02	
1139	-1.459710E+03 / 3.262303E+04	-1.465353E+03 / 4.113786E+04	4.534462E+03 / -4.664369E+04	0.0 / 0.0	-1.536675E+04	-1.083229E+04 / 1.725628E+04	-1.683647E+04 / -6.201044E+04	3.3E+00 / 1.6E-02
1140	-1.772879E+03 / 4.098513E+03	2.645319E+04 / 9.370297E+02	-1.825071E+04 / -2.908120E+03	9.975360E+03 / -6.069603E+03	3.832040E+03	3.028523E+04 / 7.930553E+03	-1.441867E+04 / -2.237563E+03	1.4E+00 / 3.4E+00
1141	3.673381E+03 / -1.097598E+03	5.521086E+02 / -6.337194E+02	-2.397477E+03 / 1.051403E+03	-5.518749E+03 / 1.505282E+03	-1.051804E+03	2.621577E+03 / 4.534773E+02	-6.570553E+03 / -2.139403E+03	2.7E+01 / 8.6E+00
1142	-1.055112E+03 / 1.675925E+03	-5.707782E+02 / 5.927243E+02	9.880292E+02 / -1.341377E+03	1.472363E+03 / -2.424578E+03	-3.939356E+03	-2.466993E+03 / -2.263431E+03	-4.994468E+03 / -6.363934E+03	8.9E+00
1143	1.658321E+03 / -4.088009E+02	8.203151E+02 / -1.527268E+03	-1.502688E+03 / 1.331608E+03	-2.351414E+03 / 2.133208E+02	-4.442465E+03	-2.773644E+03 / -3.110858E+03	-6.793679E+03 / -5.969733E+03	8.3E+00
1144	3.953317E+02 / 8.035576E+03	1.437323E+03 / 7.249167E+03	-1.259021E+03 / -9.631612E+03	-2.173297E+02 / -1.041602E+04	-5.054543E+03	-3.617225E+03 / 2.979028E+03	-6.313569E+03 / -1.547057E+04	2.4E+01 / 3.1E+00
1145	0.0 / 0.0	6.982476E+02 / 1.905994E+03	-3.787410E+02 / -1.033842E+03	-3.787410E+02 / -1.033842E+03	-1.257320E+03	-5.590722E+02 / 6.486737E+02	-1.636061E+03 / -2.291162E+03	1.2E+02 / 2.7E+01
1146	3.565452E+03 / -3.788218E+03	5.322128E+03 / -3.669339E+03	-5.322128E+03 / 3.669339E+03	0.0 / 0.0	-1.267855E+03	4.054274E+03 / 2.401484E+04	-6.589983E+03 / -5.056073E+03	1.7E+01 / 8.6E+00

BQM-3.. COMPOSITE FUSELAGE FINE GRID MODEL   DECEMBER 18, 1975   NASTRAN   9/16/74   PAGE   74

FREE FLIGHT-5G

CALC ONLY

ELEMENT ID.	SA1 SB1	S T R E S S E S I N B A R E L E M E N T S SA2 SB2	SA3 SB3	SA4 SB4	AXIAL STRESS	(C B A R) SA-MAX SB-MAX	SA-MIN SB-MIN	M.S.-T M.S.-C
1147	6.548716E+02 -1.999036E+03	-1.387828E+03 3.007974E+03	1.018588E+03 -1.995494E+03	-1.205970E+03 3.009745E+03	3.047912E+02	1.323379E+03 3.314536E+03	-1.083037E+03 -1.694245E+03	2.1E+01 3.6E+01
1148	1.347475E+03 1.017066E+03	-2.144023E+03 -1.981319E+03	1.203828E+03 1.227283E+03	-2.279721E+03 -1.851859E+03	9.894505E+02	2.336926E+03 2.216733E+03	-1.190271E+03 -9.918684E+02	3.1E+01 5.2E+01
1149	1.199391E+03 7.428280E+02	-1.306851E+03 -1.146963E+03	5.432753E+02 6.329348E+02	-1.598153E+03 -1.181714E+03	1.736124E+03	2.936015E+03 2.478952E+03	1.379706E+02 5.544102E+02	2.4E+01
1152	-1.040051E+04 2.597869E+04	9.480443E+03 2.515029E+04	4.600341E+02 -2.556449E+04	0.0 0.0	8.469083E+02	1.032735E+04 2.682560E+04	-9.553603E+03 -2.471758E+04	1.8E+00 9.2E-02
1153	2.596054E+04 7.923792E+03	2.508904E+04 8.222859E+03	-2.552469E+04 -8.073325E+03	0.0 0.0	-1.119167E+03	2.484117E+04 7.103692E+03	-2.664306E+04 -9.192492E+03	2.0E+00 1.3E-02
1154	7.524401E+03 -1.180325E+04	7.844892E+03 -1.228727E+04	-7.684646E+03 1.204826E+04	0.0 0.0	-5.101382E+03	2.743510E+03 6.946879E+03	-1.276603E+04 -1.738865E+04	9.8E+00 5.5E-01
1155	-1.175675E+04 -5.388430E+03	-1.216113E+04 -4.564890E+03	1.195894E+04 4.976660E+03	0.0 0.0	-6.611523E+03	5.347420E+03 -1.634862E+03	-1.877266E+04 -1.199995E+04	1.3E+01 4.4E-01
1156	5.479566E+03 -1.397818E+04	4.616650E+03 -1.441522E+04	-5.048108E+03 1.419670E+04	0.0 0.0	-4.831776E+03	6.477893E+02 9.364926E+03	-9.879884E+03 -1.924700E+04	7.0E+00 4.0E-01

DETAIL DIMENSION	A	B	C
a	$1\frac{1}{8}$	$1\frac{1}{8}$	$2\frac{5}{8}$
b	$2\frac{1}{8}$	$2\frac{1}{8}$	$2\frac{5}{8}$
c	$2\frac{7}{16}$	$2\frac{7}{16}$	$2\frac{15}{16}$
d	$3\frac{1}{8}$	$3\frac{1}{8}$	$3\frac{5}{8}$
e	$4\frac{1}{2}$	8	$8\frac{1}{2}$

DETAIL F

KEY DETAIL

G-0° GRAPHITE EPOXY
W- 45° WOVEN GLASS

PLY #

.006 REF

.010 REF
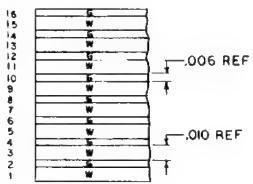
DETAIL F

LAYUP SEQUENCE

SEE
ATTACHMENT
(5)

GLASS SOFTENING STRIPS
$\frac{1}{2}$" WIDTH (TYP)

$7\frac{3}{4}$

7

.050

DETAIL A
SEE
ATTACHMENT
(2)

$39\frac{3}{8}$

DETAIL B
SEE
ATTACHMENT
(7)

$15\frac{3}{4}$

$12.5 \pm .03$

$3\frac{7}{16}$

$3\frac{1}{2}$

DETAIL
A

$7\frac{7}{8}$

$6\frac{1}{2}$

SECTION A-A
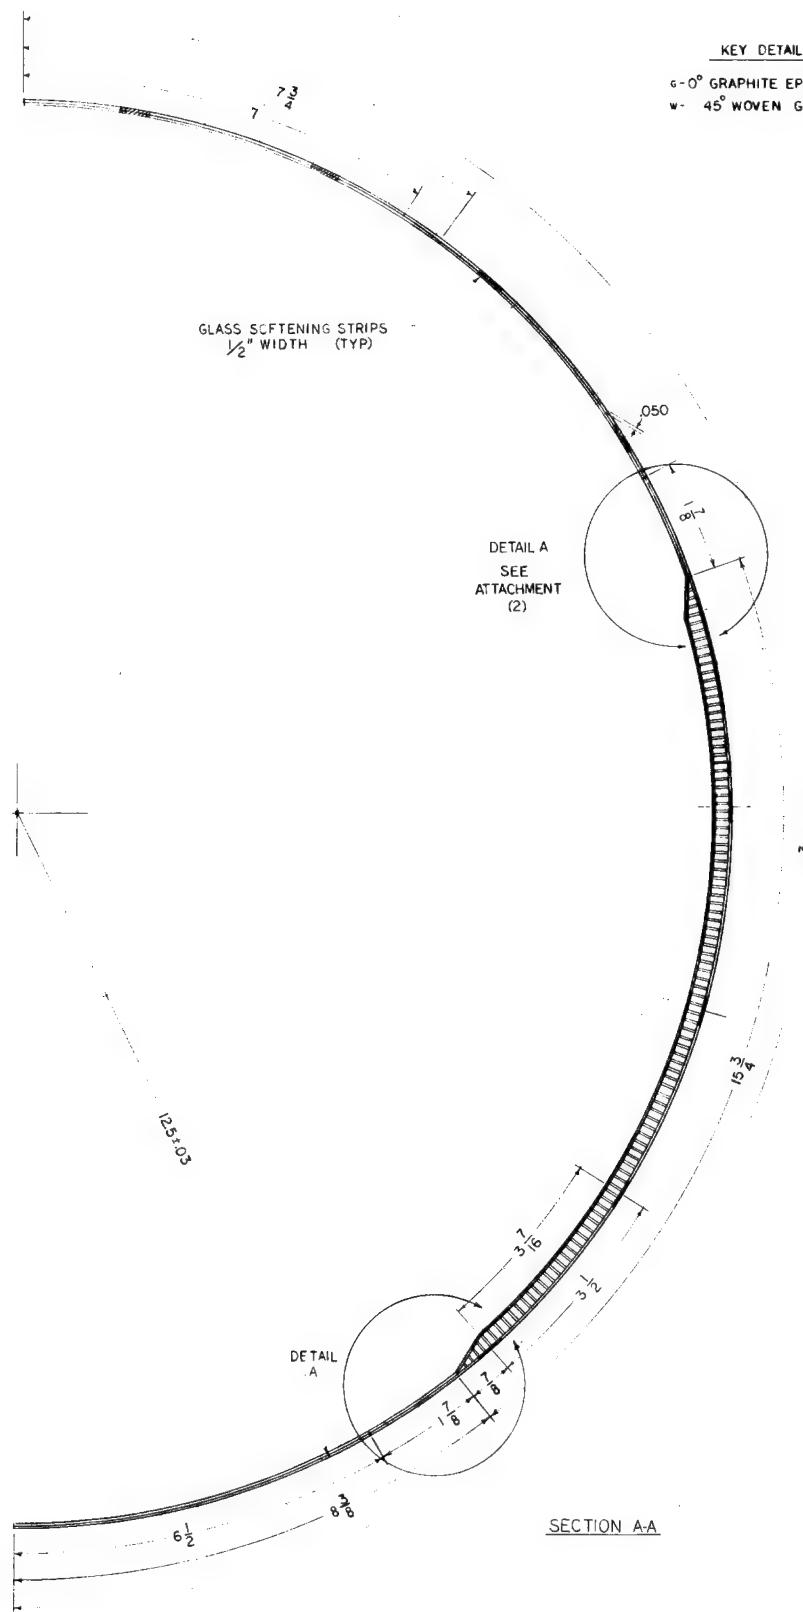
$\frac{15}{16}$

'AIL	A	B	C
$1\frac{1}{8}$	$1\frac{1}{8}$	$2\frac{3}{8}$
$2\frac{1}{8}$	$2\frac{1}{8}$	$2\frac{5}{8}$
$2\frac{7}{16}$	$2\frac{7}{16}$	$2\frac{15}{16}$
$3\frac{1}{8}$	$3\frac{1}{8}$	$3\frac{5}{8}$
$4\frac{1}{2}$	8	$8\frac{1}{2}$

DETAIL F

.006 REF

.010 REF

DETAIL F

LAYUP SEQUENCE

128 (REF)

DETAIL F

— CORE FILL TYP. OF ALL CLOSEOUT SECTIONS

DETAILS A & B & C
4X
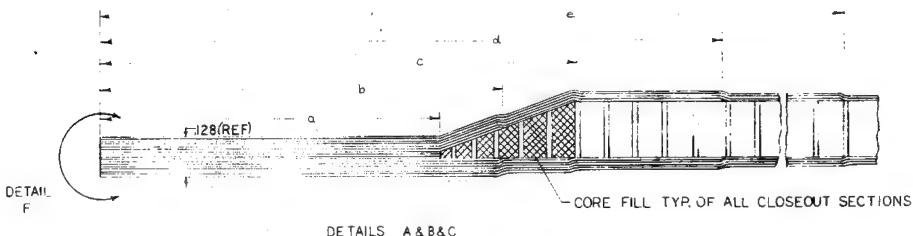
NOTES

1. MATERIALS
   GRAPHITE - HERCULE
   GLASS - CORDOPREG
   ADHESIVE - METABON
2. MB.329 SHALL BE US
3. SOFTENING STRIPS
   GLASS REPLACES G
   SOFTENING STRIP F
4. CURE TEMPERATURE
5. CORE FILL-
6. TOLERANCES $\pm\frac{1}{32}$ OR

DETAIL B
SEE
ATTACHMENT
(7)

.026 (REF)

$\frac{1}{4}$ CORE

.016 (REF)

-45   +45

0°

GLASS SOFTENING STRIP, WIDTH = $\frac{1}{2}$ TYP.

$\frac{1}{8}$ - 5060 .0007

RIBBON

3 R TRUE TYP

$\frac{15}{16}$

NAVAL AIR DEVEL
WARMINSTER,

RIGHT SKIN PAN

	CODE IDENT NO.	MARK DWG N
	80206	667 A
SCALE FULL		

UNLESS OTHERWISE SPECIFIED
DIMENSIONS ARE IN INCHES
TOLERANCES ARE:
FRACTIONS ± ... angles ± ½°
2 PLACE DECIMALS ±
3 PLACE DECIMALS ±

DO NOT SCALE THIS DRAWING

MATERIAL:

| DRAWN | R. RICHEY | |
| CHECKED | | |

APPROVED

APPROVED
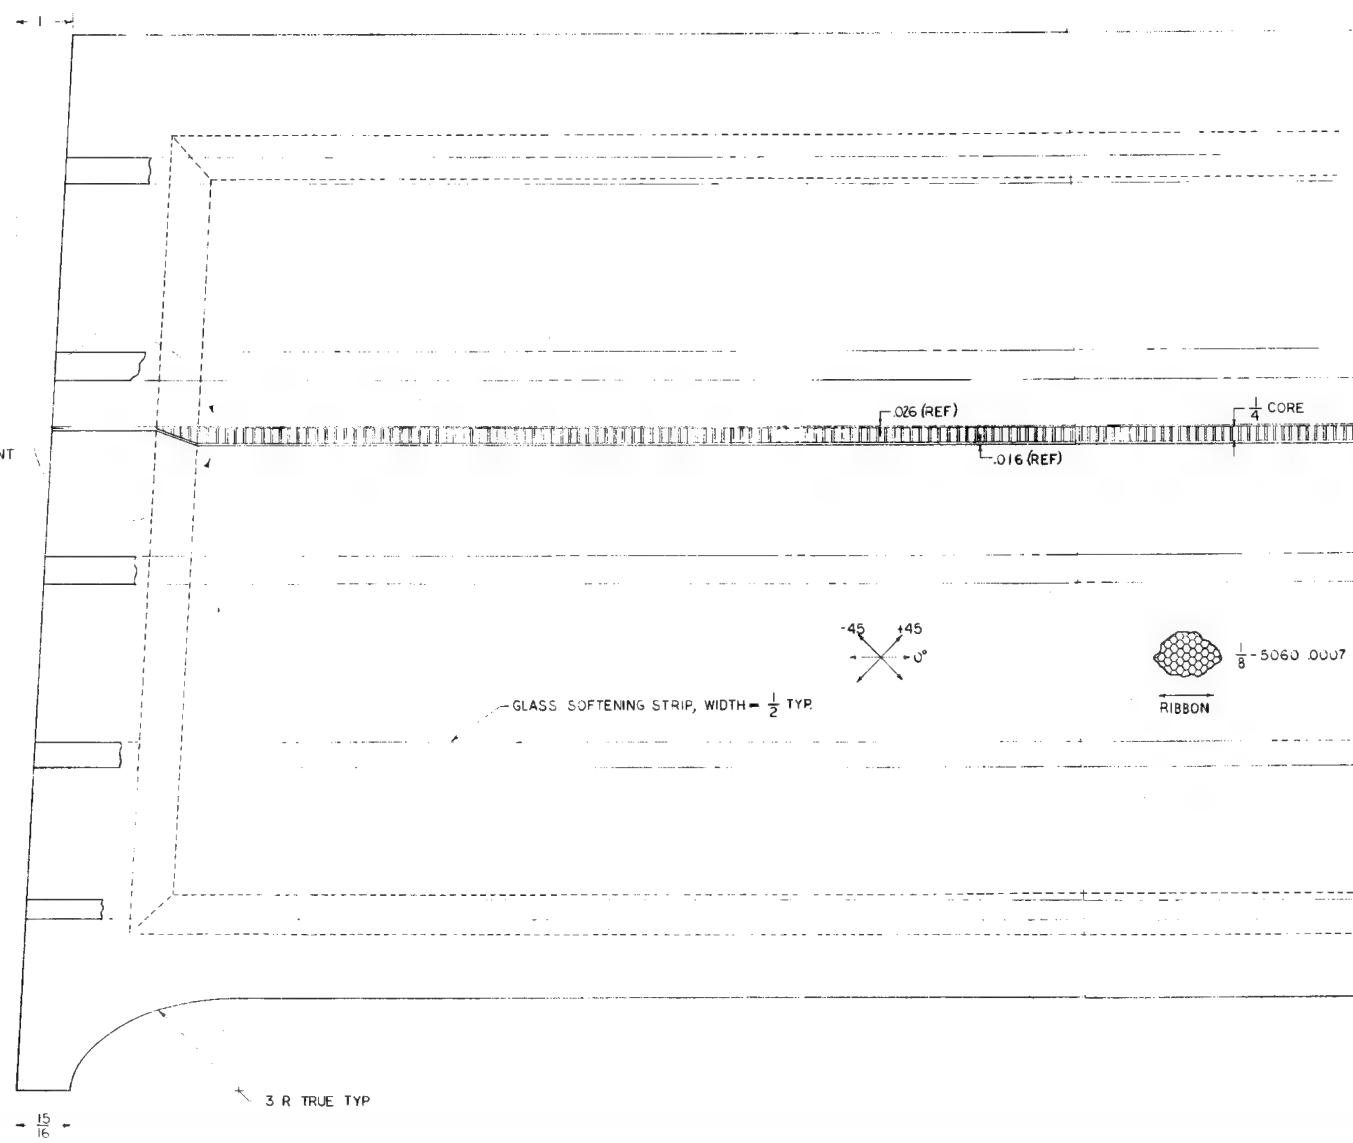
NOTES

1. MATERIALS
   GRAPHITE - HERCULES 3501 AS
   GLASS - CORLOPREG E293
   ADHESIVE - METABOND 329
2. MB 329 SHALL BE USED TO BOND CORE TO FACES
3. SOFTENING STRIPS
   GLASS REPLACES GRAPHITE IN THESE AREAS
   SOFTENING STRIP RUNS ENTIRE LENGTH OF PLIES 2,4,14,16
4. CURE TEMPERATURE - 350°
5. CORE FILL -
6. TOLERANCES = .xx OR AS NOTED
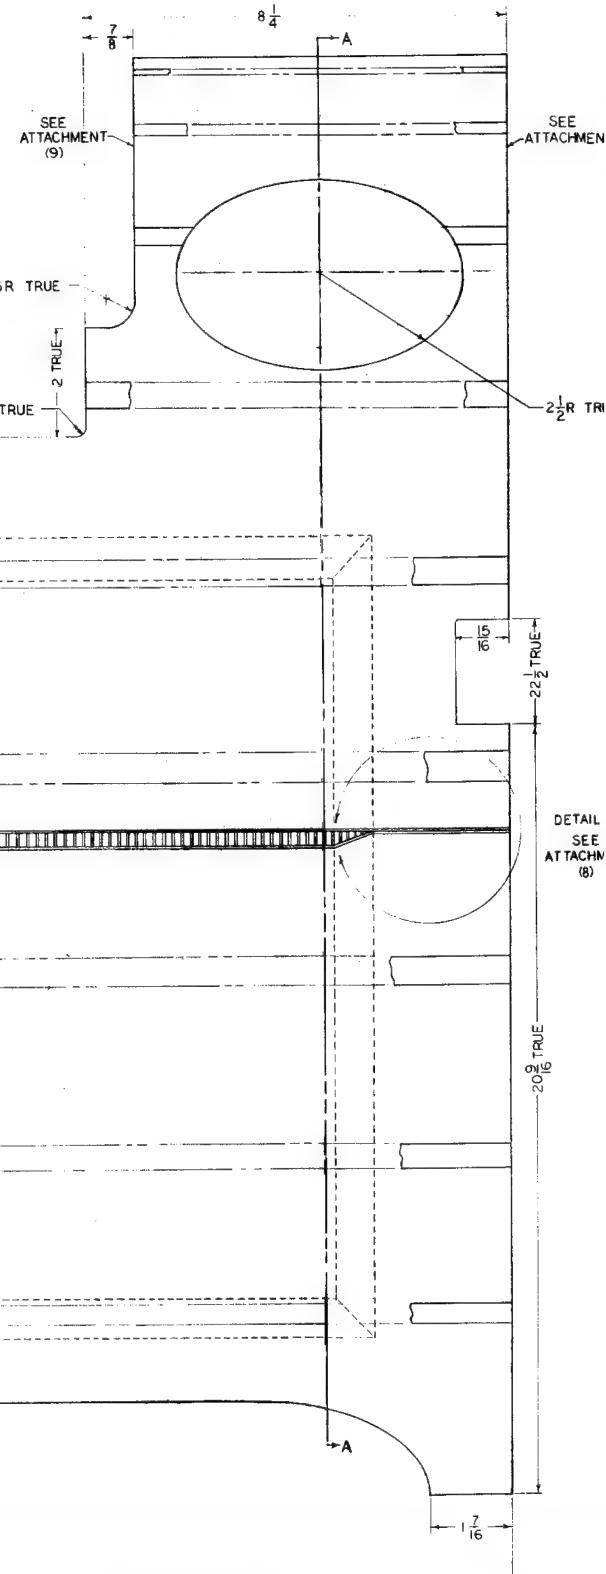
$8\frac{1}{4}$

$\frac{7}{8}$

A

SEE ATTACHMENT (9)

SEE ATTACHMEN

.5R TRUE

2 TRUE

.16R TRUE

$2\frac{1}{2}$R TR

$\frac{15}{16}$

$22\frac{1}{2}$ TRUE

DETAIL
SEE
ATTACHM
(8)

.026 (REF)

$\frac{1}{4}$ CORE

.016 (REF)

$20\frac{9}{16}$ TRUE

+45

0°

$\frac{1}{8}$ - 5060 .0007 CORE 3.1 pcf

RIBBON

A

$1\frac{7}{16}$

$42\frac{1}{4}$

	CONTRACT NO		NAVAL AIR DEVELOPMENT CENTER
UNLESS OTHERWISE SPECIFIED DIMENSIONS ARE IN INCHES. TOLERANCES ARE: FRACTIONS ± 1/64 ANGLES ± ½° 2 PLACE DECIMALS ±.01 3 PLACE DECIMALS ±.005			WARMINSTER, PA. 18974
			RIGHT SKIN PANEL
DO NOT SCALE THIS DRAWING	DRAWN R. RICHEY		
MATERIAL:	CHECKED		
	APPROVED		CODE IDENT NO. 80206	BASIC PART NO. 667A107
	APPROVED		SCALE FULL	WT.	SHEET 1 OF 4

ES 3501 AS
G E293
OND 329
SEL TO BOND CORE TO FACES
S
GRAPHITE IN THESE AREAS
RUNS ENTIRE LENGTH OF PLIES 2,4,14,16
E · 350°

OR AS NOTED

8 1/4

7/8 ←→ ←A

SEE ATTACHMENT (9)

SEE ATTACHMENT (10)

.5R TRUE —

.16R TRUE —

2 TRUE

2½R TRUE, CUT TO A DEPTH OF .050"

15/16

22½ TRUE

DETAIL C
SEE ATTACHMENT (8)

CORE 3.1 pcf

20 9/16 TRUE

←A

1 7/16

42 1/4

DETAIL C
SEE
ATTACHMENT
(2)

GLASS SOFTENING STRIPS
½" WIDTH (TYP.)

4 REF

2 1/8

1 7/8

7/8 REF

1

15 3/4

28 1/8

3 7/16 TYP

3 1/2 TYP

7/8

1 7/8

DETAIL C

12.5 R ±.03

6 1/2

3/8

SEC. A—A

8 7/8

2 3/8

15/16 TRUE

DETAIL B

20 9/16 TRUE

3 R. TRUE

1 7/16

DETAIL D

P

N

M

L

K

.128 (REF.)

CORE FILL

DETAIL A & B & C
4X

$8\frac{3}{8}$

A

.16 R. TRUE

$2\frac{3}{8}$

$1\frac{15}{16}$ TRUE

RIBBON DIRECTION

−45° +45°

0°

$28\frac{1}{8}$

DETAIL B

.026 (REF.)

−.016 (REF.)

.5060 −.0007 CORE 3.1 pcf

$20\frac{9}{16}$ TRUE

A

3 R. TRUE (TYP)

$1\frac{7}{16}$

$42\frac{1}{4}$

P

N

M

L

K

.128 (REF.)

CORE FILL TYP. ALL 20° CLOSEOUT SECTIONS

DETAIL A & B & C
4X

DIRECTION

−45° +45°
0°

.026 (REF.)

.016 (REF.)

DETAIL

S
ATT

42 1/4

1 7/8

15/16

UNLESS OTHERWISE SPECIFIED
DIMENSIONS ARE IN INCHES
TOLERANCES ARE:
FRACTIONS ±1/64   ANGLES ± 2°
2 PLACE DECIMALS ±.01
3 PLACE DECIMALS ±.005

DO NOT SCALE THIS DRAWING

MATERIAL:

·ONS

DETAIL D

PLY NO.

KEY

G — GRAPHITE EPOXY 0°

W — WOVEN GLASS ±45°

.006 REF

.010 REF

DETAIL DIMENSION	A	B	C
K	$1\frac{7}{8}$	$2\frac{3}{8}$	$1\frac{7}{8}$
L	$2\frac{1}{8}$	$2\frac{5}{8}$	$2\frac{1}{8}$
M	$2\frac{7}{16}$	$2\frac{15}{16}$	$2\frac{7}{16}$
N	$3\frac{1}{8}$	$3\frac{5}{8}$	$3\frac{1}{8}$
P	8	$8\frac{1}{2}$	$4\frac{1}{2}$

$1\frac{7}{8}$

DETAIL A

SEE
ATTACHMENT
(7)

$\frac{15}{16}$

P SONG

LEFT SKIN PANEL

80206 667A107

SCALE FULL   SHEET 2 OF 4

DETAIL A

SEE
ATTACHMENT (1)

GR/EP INSERT

GLASS SOFTENING STRIP

125±.03

$3\frac{7}{16}$ TYP

$3\frac{1}{2}$ TYP

SEC AA

SEC BB

SEC CC

DETAIL DIMENSION	A	B
a	$1\frac{1}{4}$	$1\frac{1}{4}$
b	$1\frac{1}{2}$	$1\frac{1}{2}$
c	$1\frac{13}{16}$	$1\frac{13}{16}$
d	$2\frac{1}{2}$	$2\frac{1}{2}$
e	3	6

KEY
G-GRAPHITE EPOXY
W-WOVEN GLASS

PLY NO.

.006 REF

.010 REF

DETAIL C
LAYUP SEQUENCE

CORE FILL

DETAIL C

2.0°

a

b

c

d

e

DETAIL A+B
4X

SEC AA

$\frac{1}{2}$ TYP

P INSERT

IP

$3\frac{7}{16}$ TYP

$3\frac{1}{2}$ TYP

$\frac{3}{8}$

13

SEC BB

$3\frac{10}{16}$

$\frac{7}{32}$

$8\frac{1}{2}$

SEC CC

$\frac{3}{8}$

$\frac{3}{8}$

$19\frac{1}{4}$

$12\frac{15}{16}$

A

$9\frac{5}{8}$

DETAIL B

.026 REF

.016 REF

$\frac{1}{4}$

GR/EP INSERTS

D

.191 DIA HOLE TYP
.196

$\frac{1}{8}$ 5056 .0007 31 pcf
TYP ALL CORE
SECTIONS

RIBBON

BOND CORE TO INSERT
WITH AF 3002 (TYP.)

3R TRUE TYP

A

$7\frac{3}{8}$ REF

$7\frac{3}{8}$ REF

GR/EP INSERT

$\frac{3}{8}$

$\frac{3}{8}$

SEC DD
SEE ATTACHMENT (13)

SEC EE

$\frac{3}{8}$

$\frac{3}{8}$

SEC FF

$\frac{15}{16}$

$7\frac{7}{16}$

$\frac{15}{16}$

SEC GG

$\frac{3}{8}$

$\frac{3}{8}$

ALL DIMENSIONS ABOVE ARE REFERENCE DIMENSIONS

CORE FILL

20°

c

d

e

_ETAIL A+B
4X

19 1/4

12 15/16

A

B

C

9 5/8

SEE ATTACHMENT 12

SEE ATTACHMENT 11

1 3/8

-45   +45

0°

13

.026 REF.

.016 REF.   1/4

D

D

E

E

F

F

G

G

07 31 pcf
CORE
5

RIBBON

.191
.196 DIA HOLE TYP

BOND WITH AF 3002 (TYP.)

A

B

C

7 3/8 REF

7 3/8 REF

8 1/8 REF

8 1/4 REF

39 3/4

5/16

7/16

7/16

5/16

3/8

3/8

SEC F F

SEC G G

N$ ABOVE ARE REFERENCE DIMENSIONS

UNLESS OTHERWISE SPECIFIED
DIMENSIONS ARE IN INCHES.
TOLERANCES ON:
FRACTIONS = 1/32   ANGLES = 2°
2 PLACE DECIMALS =
2 PLACE DECIMALS = -.3

DO NOT SCALE THIS DRAWING

MATERIAL:

CONTRACT NO.

DRAWN

CHECKED

APPROVED

APPROVED

SEE ATTACHMENT 12

SEE ATTACHMENT 11

$1\frac{3}{8}$

-45   +45

0°

13

C

E
E

F
F

G
G

BOND WITH AF 3002 (TYP.)

C

$8\frac{1}{8}$ REF

$8\frac{1}{4}$ REF

$8\frac{5}{8}$ REF

$39\frac{3}{4}$

MENT HOLES TO BE
LED FROM EXISTING

D

C

B

A

DETAIL A

GLASS SOFTENING STRIPS
$\frac{1}{2}$ WIDTH (TYP)

NOTE – GLASS STRIPS
CONTAINED WITHIN
GR/EP PLIES 2,4,
14 + 16

$3\frac{1}{2}$

$11\frac{1}{2}$

$3\frac{1}{2}$

$2\frac{1}{4}$

12.5 R
±.03

.128
REF

DETAIL A

GLASS SOFTENING STRIPS
$\frac{1}{2}$ WIDTH (TYP) ─┐

GLASS STRIPS
CONTAINED WITHIN
GR/EP PLIES 2,4,
14 + 16

$3\frac{1}{2}$

$11\frac{1}{2}$

$3\frac{1}{2}$

$2\frac{1}{4}$

.128
REF

RIBBON DIRECTION

$-45°$ $\pm45°$
$0°$

$7\frac{3}{8}$

REVISIONS				
ZONE	LTR	DESCRIPTION	DATE	APPROVED

D

PLY NO.

16	G
15	W
14	G
13	W
12	G
11	W
10	G
9	W
8	G
7	W
6	G
5	W
4	G
3	W
2	G
1	W

.006 REF

.010 REF
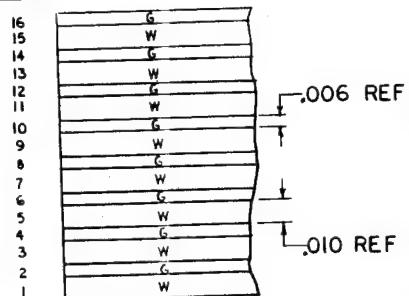
DETAIL A

KEY

   G—GRAPHITE EPOXY 0°

   W—WOVEN FIBER GLASS
     EPOXY ± 45°

C

RIBBON DIRECTION

−45° ±45°
0°

$7\frac{3}{8}$

A

CONTRACT NO.

DRAWN   Rt. Riley
CHECKED   JE. Hira

APPROVED

APPROVED

NAVAL AIR DEVELOPMENT CENTER
WARMINSTER, PA. 18974

ACCESS DOOR - BQM 34E
CENTER FUSELAGE SECTION-
HYBRID COMPOSITE DESIGN

SIZE	CODE IDENT NO.	NADC DWG NO.	REV
D	80206	667A107	

SCALE FULL   WT   SHEET 4 OF 4

PLATE NO. 18250

ACCESS DOOR

ATTACHMENT 6

MI3601-2

LEFT SKIN PANEL

GR/EP INSERT

TYP.
KEEL
ATTACHMENT

ATTACHMENT 13

FUEL TANK ACCESS DOOR

ATTACHMENT 5

ATTACHMENT 4

FUEL CAP MOUNT

UPPER

ATTACHMENT 3

ATTACHMENT 9

ATTACHMENT 2

NOTES

- MS 21140-06 RIVET
- CENTER LINES MAR
- ALL ATTACHMENTS H
  FROM EXISTING PAR

RIGHT SKIN PANEL

BULKHEAD

XF
274.590

ATTACHMENT 7

NAS 1473A3

ATTACHMENT 1

FUEL TANK ACCESS DOOR

ATTACHMENT 11
(DRAIN MOUNT)

ATTACHMENT 12
(VALVE, DRAIN)

UNLESS OTHERWISE SPECIFIED DIMENSIONS ARE IN INCHES TOLERANCES ARE: FRACTIONS ±1/32 ANGLES ±2° 1 PLACE DECIMALS ± 2 PLACE DECIMALS ±.03	CONTRACT NO.		
DO NOT SCALE THIS DRAWING	DRAWN	RICHEY	29MA
MATERIAL	CHECKED		5/
	APPROVED		
	APPROVED		

EL CAP MOUNT

ATTACHMENT 3

ATTACHMENT 2

UPPER SECTION, RIGHT SKIN PANEL

XF
233,500
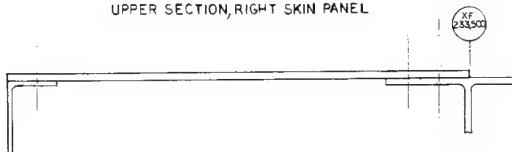
ATTACHMENT 9

ATTACHMENT 10

NOTES

-MS 21140-06   RIVETS-TYP. ATTACHMENT FASTENER
-CENTER LINES MARK RIVET LOCATIONS
-ALL ATTACHMENTS HOLES ARE LOCATED
 FROM EXISTING PARTS .

RIGHT SKIN PANEL

BULKHEAD

BULKHEAD

RE
274.500

XF
233,500

ATTACHMENT 7

ATTACHMENT 8

CONTRACT NO.

DRAWN   RICHEY   29 AY 75
CHECKED

APPROVED

APPROVED

NAVAL AIR DEVELOPMENT CENTER
WARMINSTER, PA 18974

ATTACHMENTS

SIZE	CODE IDENT NO.	NADC DWG. NO.		REV
	80206	667A109		

SCALE FULL   WT.   SHEET   OF

DETAIL A

PLY NO
16
15
14
13
12
11
10
9
8
7
6
5
4
3
2
1

.006(REF)

.010(REF)

KEY
G-GRAPHITE 0°
W-WOVEN GLASS ±45°

DETAIL B
LAYUP SEQUENCE

8
(PLIES 4,13,14)

3 1/8
(PLY 5)

2 7/16 (PLIES 6,12)

2 1/8 (PLIES 7,11)

1 7/8
(PLIES 8,9,10)

.128(REF)

20°

DETAIL B

16 PLIES
(8 GRAPHITE, 8 GLASS)

DETAIL A
4X

RIBBON DIRECTION

0°
±45°

0.016(REF)

0.026(REF)

1.0

HONEYCOMB SPLICE PLATE

EPOXY FILLER

C

C
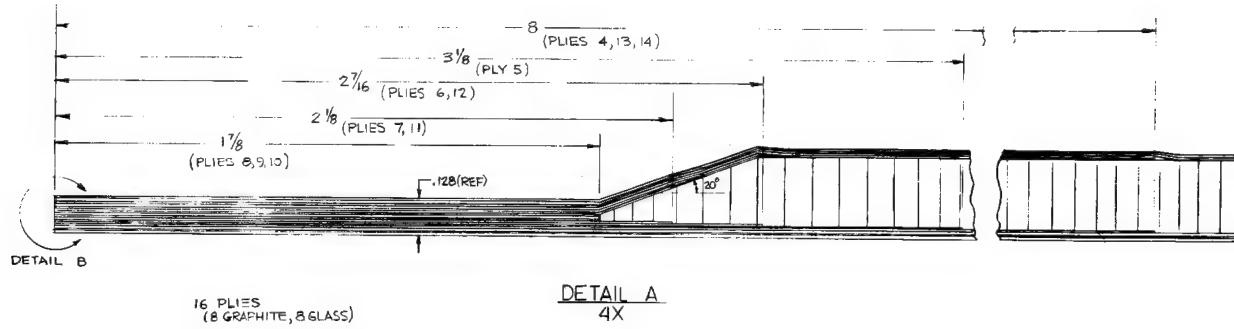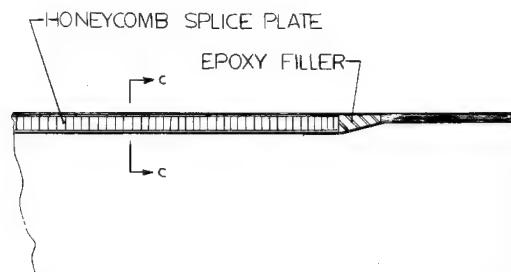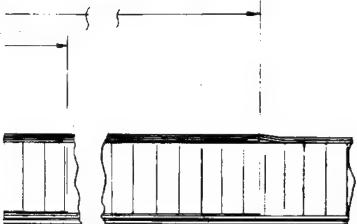
SECTION B-B   SPLICE DETAIL

A

B

B

RIBBON   DIRECTION

0°

±45°

12.5

A

0.032(REF)

0.016(REF)

0.026(REF)

0.25 (CORE)

0.032(REF)

SAME AS DETAIL A

HONEYCOMB SPLICE PLATE

EPOXY FILLER

SECTION B-B SPLICE DETAIL

GLASS(±45°)
GRAPHITE(0°)
GLASS(±45°)
GLASS(0°)

DETAIL C
4X

SPLICE

1⅛

1⅛   1¾

3
(TYP)   2 15/16 (TYP)

12.5 R ± .03
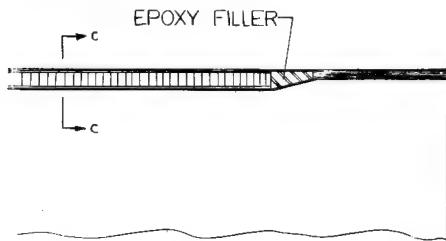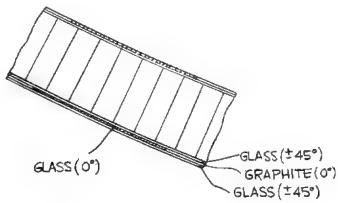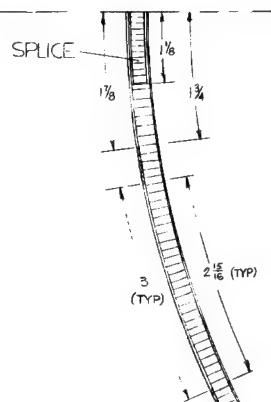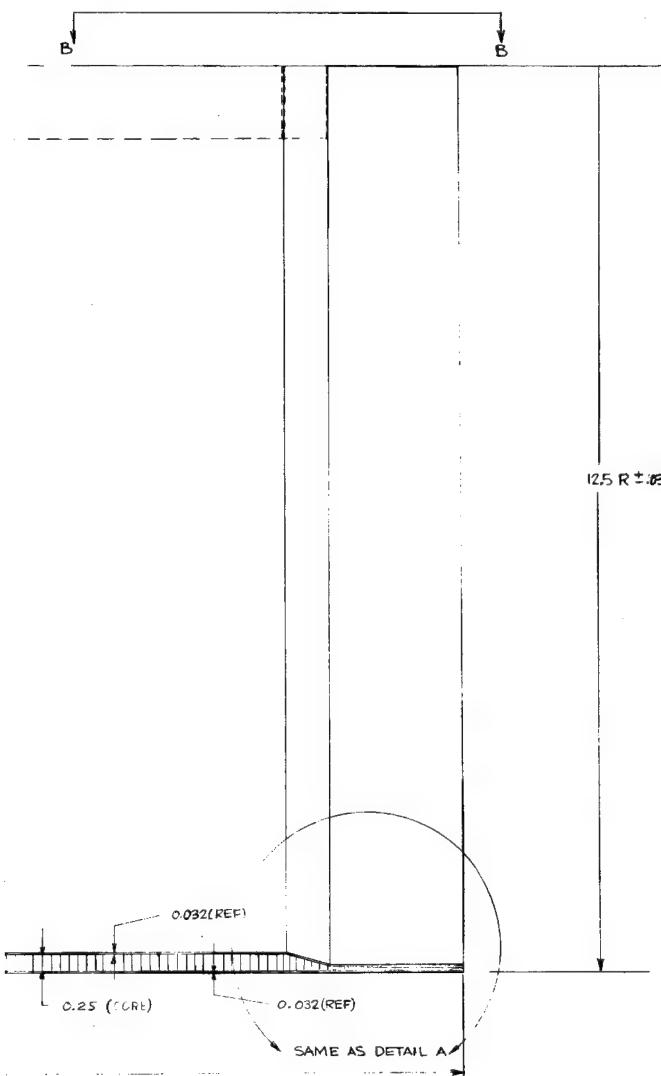
CYLINDER IS SYMMETRIC
ABOUT BOTH AXES

GLASS SOFTENING
STRIPS
(TYP)

½(TYP)

0.032(REF)

0.25 (CORE)   0.032(REF)

SECTION A-A

DETAIL C

SAME AS DETAIL A

DETAIL C
4X

GLASS (0°)
GLASS (±45°)
GRAPHITE (0°)
GLASS (±45°)

CORFIL
5 PLY FACES (3 GLASS, 2 GRAPHITE)
.15 ±.010

SECTION C-C
2X
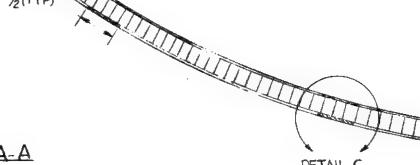
NOTES:

1. MATERIALS
   GRAPHITE-HERCULES
   GLASS-CORDOPREG
   ADHESIVE-HYSOL EA

2. RELEASE AGENT TO
   AREA-FREECOTE OR

3. EA951 SHALL BE US

4. SOFTENING STRIPS
   GLASS REPLACES G
   SOFTENING STRIP

5. SPLICE SHALL BE B
   EA·951.

6. CURE TEMPERATURE

7. EPOXY FILLER-AF 30

8. TOLERANCES ± 1/32 OR

3/4
1

2 15/16 (TYP)

CYLINDER IS SYMMETRIC
ABOUT BOTH AXES

NING

1/2 (TYP)

SECTION A-A

DETAIL C
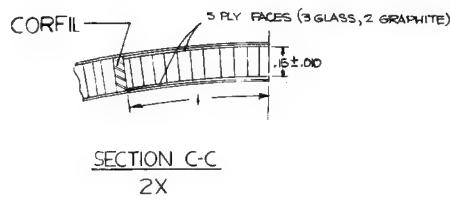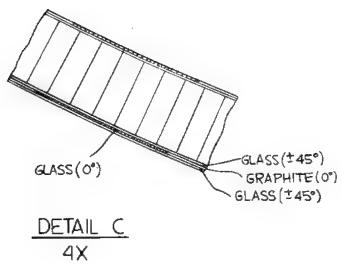
BQM-34E CYLINDER TEST SPECIMEN

SCALE-FULL   8-27-74
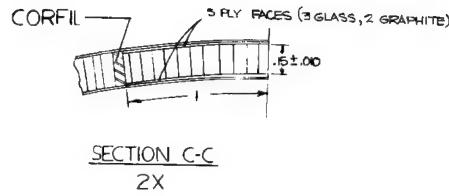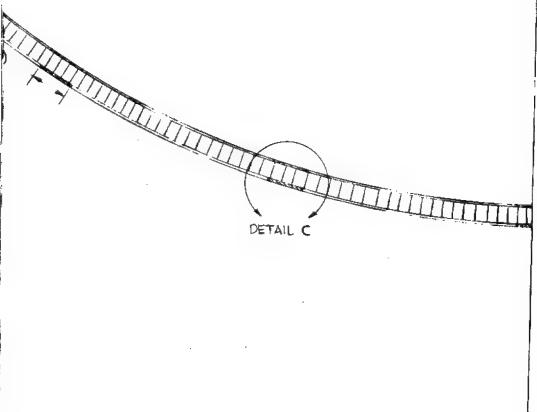
MA
FA
CO

C

GLASS (±45°)
GRAPHITE (0°)
GLASS (±45°)

CORFIL
5 PLY FACES (3 GLASS, 2 GRAPHITE)

.15±.010

SECTION C-C
2X

NOTES:
1. MATERIALS
   GRAPHITE-HERCULES 3501 AS
   GLASS-CORDOPREG E293
   ADHESIVE-HYSOL EA951
2. RELEASE AGENT TO BE USED WITH STEEL INSE
   AREA - FREECOTE OR #1711.
3. EA951 SHALL BE USED TO BOND CORE TO FACE
4. SOFTENING STRIPS
   GLASS REPLACES GRAPHITE IN THESE AREAS
   SOFTENING STRIP RUNS ENTIRE LENGTH OF F
5. SPLICE SHALL BE BONDED AT 350° WITH
   EA-951.
6. CURE TEMPERATURE - 350°.
7. EPOXY FILLER-AF 3002.
8. TOLERANCES ± 1/32 OR AS NOTED.

CYLINDER IS SYMMETRIC
ABOUT BOTH AXES

DETAIL C

BQM-34E CYLINDER TEST SPECIMEN		MATERIAL: FACING-GRAPHITE/GLASS HYBR CORE-AL-1/8-5056-.0007-3.1 (HEX
SCALE - FULL	8-27-74	

5 PLY FACES (3 GLASS, 2 GRAPHITE)

.15 ±.010

ECTION C-C
2X

NOTES:
1. MATERIALS
   GRAPHITE - HERCULES 3501 AS
   GLASS - CORDOPREG E293
   ADHESIVE - HYSOL EA951
2. RELEASE AGENT TO BE USED WITH STEEL INSERT IN SPLICE
   AREA - FREECOTE OR #1711.
3. EA951 SHALL BE USED TO BOND CORE TO FACES.
4. SOFTENING STRIPS
   GLASS REPLACES GRAPHITE IN THESE AREAS.
   SOFTENING STRIP RUNS ENTIRE LENGTH OF PLIES 2,4,14,16.
5. SPLICE SHALL BE BONDED AT 350° WITH
   EA-951.
6. CURE TEMPERATURE -350°.
7. EPOXY FILLER-AF 3002.
8. TOLERANCES ± 1/32 OR AS NOTED.

BQM-34E CYLINDER TEST SPECIMEN		MATERIAL: FACING-GRAPHITE/GLASS HYBRID CORE-AL-1/8-5056-.0007-3.1 (HEXCEL)
SCALE-FULL	8-27-74	

DISTRIBUTION LIST

Government Activities

No. of
Copies

NAVAIRSYSCOM, AIR-954 (2 for retention), 2 for AIR-530,
   1 for AIR-320B, AIR-52032D, AIR-5302, AIR-53021, AIR-530215).   9
AFFDL, WPAFB, OH 45433
   (Attn: FB/Mr. P. A. Parmley)   2
   (Attn: FBC/Mr. C. Wallace)   1
   (Attn: FBC/Mr. E. E. Zink)   1
AFML, WPAFB, OH 45433
   (Attn: LAM (Technical Library)).   1
   (Attn: LT-1/Mr. W. R. Johnston).   1
   (Attn: LTF/Mr. T. Cordell)   1
   (Attn: FBSC/Mr. L. Kelly).   1
   (Attn: MAC/Mr. G. P. Peterson)   1
   (Attn: MXA/Mr. F. J. Fechek)   1
   (Attn: MBC/Mr. T. G. Reinhard, Jr.).   1
AFOSR, Washington, D.C. 20333
   (Attn: Mr. J. Pomerantz)   1
DDC.   12
FAA, Airframes Branch, FS-120, Washington, D.C. 20553
   (Attn: Mr. J. Dougherty)   1
NASA (ADM), Washington, D.C. 20546
   (Attn: Secretary).   1
NASA, George C. Marshall Space Flight Center, Huntsville,
   AL 35812
   (Attn: S&E-ASTN-ES/Mr. E. E. Engler)   1
   (Attn: S&E-ASTN-M/Mr. R. Schwinghamer)   1
   (Attn: S&E-ASTM-MNM/Dr. J. M. Stuckey)   1
NASA, Langley Research Center, Hampton, VA 23365
   (Attn: Mr. J. P. Peterson, Mr. R. Pride, and Dr. M. Card). .   3
NASA, Lewis Research Center, Cleveland, OH 44153
   (Attn: Technical Library, and M. Hershberg).   2
NAVPGSCHL, Monterey, CA 95940
   (Attn: Prof. R. Ball, Prof. M. H. Bank).   2
NAVSEASYSCOM, Washington, D.C. 20362
   (Attn: Code 035, Mr. C. Pohler).   1
NAVSEC, Hyattsville, MD 20782
   (Attn: Code 6101E03, Mr. W. Graner).   1
NAVSHIPRANDCEN, Bethesda, MD 20034
   (Attn: Code 173.2, Mr. W. P. Cauch).   1
NAVSHIPRANDCEN, Annapolis, MD 21402
   (Attn: Code 2870, Mr. H. Edelstein).   1
NOL, White Oak, MD 20910
   (Attn: Mr. F. R. Barnet)   1
NRL, Washington, D.C. 20375
   (Attn: Dr. I. Wolock).   1
ONR, Washington, D.C. 20362
   (Attn: Dr. N. Perrone)   1

Non-Government Agencies (Cont.)

Hercules Powder Company, Inc., Cumberland, MD 21501
   (Attn: Mr. D. Hug) 1
H. I. Thompson Fiber Glass Company, Gardena, CA 90249
   (Attn: Mr. N. Myers) 1
ITT Research Institute, Chicago, IL 60616
   (Attn: Mr. K. Hofar) 1
J. P. Stevens & Co., Inc., N.Y., NY 10036
   (Attn: Mr. H. I. Shulock). 1
Kaman Aircraft Corporation, Bloomfield, CT 06002
   (Attn: Tech. Library). 1
Lehigh University, Bethlehem, PA 18015
   (Attn: Dr. G. C. Sih). 1
Lockheed-California Company, Burbank, CA 91520
   (Attn: Mr. E. K. Walker, R. L. Vaughn) 2
Lockheed-Georgia Company, Marietta, GA
   (Attn: Advanced Composites Information Center, Dept. 72-14,
       Zone 42). 1
LTV Aerospace Corporation, Dallas, TX 75222
   (Attn: Mr. O. E. Dhonau/2-53442, C. R. Foreman). 2
Martin Company, Baltimore, MD 21203
   (Attn: Mr. J. E. Pawken) 1
Materials Sciences Corp., Blue Bell, PA 19422 1
McDonnell Douglas Corporation, St. Louis, MO 63166
   (Attn: Mr. R. C. Goran, O. B. McBee, C. Stenberg). 3
McDonnell Douglas Corporation, Long Beach, CA 90801
   (Attn: H. C. Schjulderup, G. Lehman) 2
Minnesota Mining and Manufacturing Company, St. Paul, MN 55104
   (Attn: Mr. W. Davis) 1
Northrop Aircraft Corp., Norair Div., Hawthorne, CA 90250
   (Attn: Mr. R. D. Hayes, J. V. Noyes, R. C. Isemann). 3
Rockwell International, Columbus, OH 43216
   (Attn: Mr. O. G. Acker, K. Clayton). 2
Rockwell International, Los Angeles, CA 90053
   (Attn: Dr. L. Lackman) 1
Rockwell International, Tulsa, OK 74151
   (Attn: Mr. E. Sanders, Mr. J. H. Powell) 2
Owens Corning Fiberglass, Granville, OH 43023
   (Attn: Mr. D. Mettes). 1
Rohr Corporation, Riverside, CA 92503
   (Attn: Dr. F. Riel and Mr. R. Elkin) 2
Ryan Aeronautical Company, San Diego, CA 92112
   (Attn: Mr. R. Long). 1
Sikorsky Aircraft, Stratford, CT 06497
   (Attn: Mr. J. Ray) 1
University of Oklahoma, Norman, OK 93069
   (Attn: Dr. G. M. Nordby) 1
Union Carbide Corporation, Cleveland, OH 44101
   (Attn: Dr. H. F. Volk) 1

Government Activities (Cont.)

PLASTEC, Picatinny Arsenal, Dover, NJ 07801
    (Attn: Librarian, Bldg. 176, SARPA-FR-M-D and Mr. H. Pebly). . 2
Scientific & Technical Information Facility, College Park, MD
    (Attn: NASA Representative). 1
USAAVMATLAB, Fort Eustis, VA 23603
    (Attn: Mr. R. Beresford) 1
USAMATRESAG, Watertown, MA
    (Attn: Dr. E. Lenoe) 1
USARESOFC, Durham, NC 27701 1

Non-Government Agencies

Avco Aero Structures Division, Nashville, TN 37202
    (Attn: Mr. W. Ottenville). 1
Battelle Columbus Laboratories, Metals and Ceramics Information
    Center, 505 King Avenue, OH 43201. 1
Bell Aerospace Company, Buffalo, NY 14240
    (Attn: Zone I-85, Mr. F. M. Anthony) 1
Bell Helicopter Company, Fort Worth, TX 76100
    (Attn: Mr. Charles Harvey) 1
Bendix Products Aerospace Division, South Bend, IN 46619
    (Attn: Mr. R. V. Cervelli) 1
Boeing Aerospace Company, P.O. Box 3999, Seattle, WA 98124
    (Attn: Code 206, Mr. R. E. Horton) 1
Boeing Company, Renton, Washington 98055
    (Attn: Dr. R. June). 1
Boeing Company, Vertol Division, Phila., PA 19142
    (Attn: Mr. R. L. Pinckney, Mr. D. Hoffstedt) 2
Boeing Company, Wichita, KS 67210
    (Attn: Mr. V. Reneau/MS 16-39) 1
Cabot Corporation, Billerica Research Center, Billerica, MA
    01821 1
Drexel University, Phila., PA 19104
    (Attn: Dr. P. C. Chou) 1
E.I. DuPont Company, Wilmington, DE 19898
    (Attn: Dr. Carl Zweben) Bldg. 262/Room 316 1
Fairchild Industries, Hagerstown, MD 21740
    (Attn: Mr. D. Ruck). 1
Georgia Institute of Technology, Atlanta, GA
    (Attn: Prof. W. H. Horton) 1
General Dynamics/Convair, San Diego, CA 92138
    (Attn: Mr. D. R. Dunbar, W. G. Scheck) 2
General Dynamics, Fort Worth, TX 76101
    (Attn: Mr. P. D. Shockey, Dept. 23, Mail Zone P-46). . . . 1
General Electric Company, Phila., PA 19101
    (Attn: Mr. L. McCreight) 1
Great Lakes Carbon Corp., N.Y., NY 10017
    (Attn: Mr. W. R. Benn, Mgr., Markey Development) 1
Grumman Aerospace Corporation, Bethpage, L.I., NY 11714
    (Attn: Mr. R. Hadcock, Mr. S. Dastin). 2